
Microstructure of cast irons —

Part 1:

Graphite classification by visual analysis

Microstructure des fontes —

Partie 1: Classification du graphite par analyse visuelle

STANDARDSISO.COM : Click to view the full PDF of ISO 945-1:2008



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 945-1:2008



COPYRIGHT PROTECTED DOCUMENT

© ISO 2008

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword.....	iv
Introduction	v
1 Scope	1
2 General.....	1
2.1 Designation system for classifying graphite in cast irons.....	1
2.2 Visual classification of graphite.....	9
3 Sampling and preparation of samples.....	10
3.1 Samples taken from a casting	10
3.2 Sample preparation	10
4 Procedure for graphite classification	10
4.1 Procedure for visual classification of graphite	10
4.2 Evaluation of the analysis results.....	10
5 Reference images	11
5.1 General.....	11
5.2 Reference images for graphite form.....	11
5.3 Reference images for the distribution of graphite (form I).....	11
5.4 Reference images for graphite size	11
6 Designation of graphite by form, distribution and size	11
6.1 Designation system.....	11
6.2 Designation of intermediate graphite sizes	12
6.3 Designation of mixed graphite forms, distributions and sizes.....	12
6.4 Nodule count.....	13
7 Report	13
Annex A (informative) Typical graphite forms in cast-iron materials (Examples of photomicrographs)....	15
Annex B (informative) Distribution of flake (lamellar) graphite (form I) (Examples of photomicrographs).....	16
Annex C (informative) Common terminology and main occurrences concerning graphite in cast irons	17
Bibliography	19

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 945-1 was prepared by Technical Committee ISO/TC 25, *Cast irons and pig irons*.

Together with ISO 945-2, this first edition of ISO 945-1 cancels and replaces ISO 945:1975, which has been technically revised to take into account the expanding range of cast-iron alloys available. In addition, photomicrographs have been included together with schematic images to aid classification.

ISO 945 consists of the following parts, under the general title *Microstructure of cast irons*:

— *Part 1: Graphite classification by visual analysis*

Graphite classification by image analysis will be the subject of a future Part 2.

Introduction

Microstructure designation is a useful feature that provides a means of classifying the graphite form, distribution and size in cast irons.

Graphite classification by visual analysis is a well-established method which is well recognized within the foundry industry as a means of quickly determining the overall graphite microstructure of a cast-iron casting.

STANDARDSISO.COM : Click to view the full PDF of ISO 945-1:2008

[STANDARDSISO.COM](https://standardsiso.com) : Click to view the full PDF of ISO 945-1:2008

Microstructure of cast irons —

Part 1: Graphite classification by visual analysis

1 Scope

This part of ISO 945 specifies a method of classifying the microstructure of graphite in cast irons by comparative visual analysis.

The purpose of this part of ISO 945 is to provide information about the method of graphite classification. It is not intended to give information on the suitability of cast-iron types and grades for any particular application.

The particular material grade is specified by results from tensile tests or hardness testing and, in the case of austenitic cast irons, by their chemical composition. The interpretation of graphite form and size does not allow a statistically valid statement on the fulfilment of the requirements specified in the relevant material standard. The structure of the metallic matrix (e.g. ferrite, pearlite) has a significant effect on the material properties. Such an interpretation is not the purpose of this part of ISO 945.

2 General

2.1 Designation system for classifying graphite in cast irons

When cast-iron materials are examined under a microscope in accordance with this part of ISO 945, the graphite shall be classified by

- a) its form, designated by Roman numerals I to VI (see Figure 1 and Annex A);
- b) its distribution, designated by capital letters A to E (see Figure 2 and Annex B); the graphite distribution designation is only specified for grey cast iron (form I);
- c) its size, designated by Arabic numerals 1 to 8 (see Figures 3, 4 and 5 and Table 1).

NOTE Figures 1 to 5 show only the outlines and not the structure of the graphite.

FORM

Magnification $\times 100$

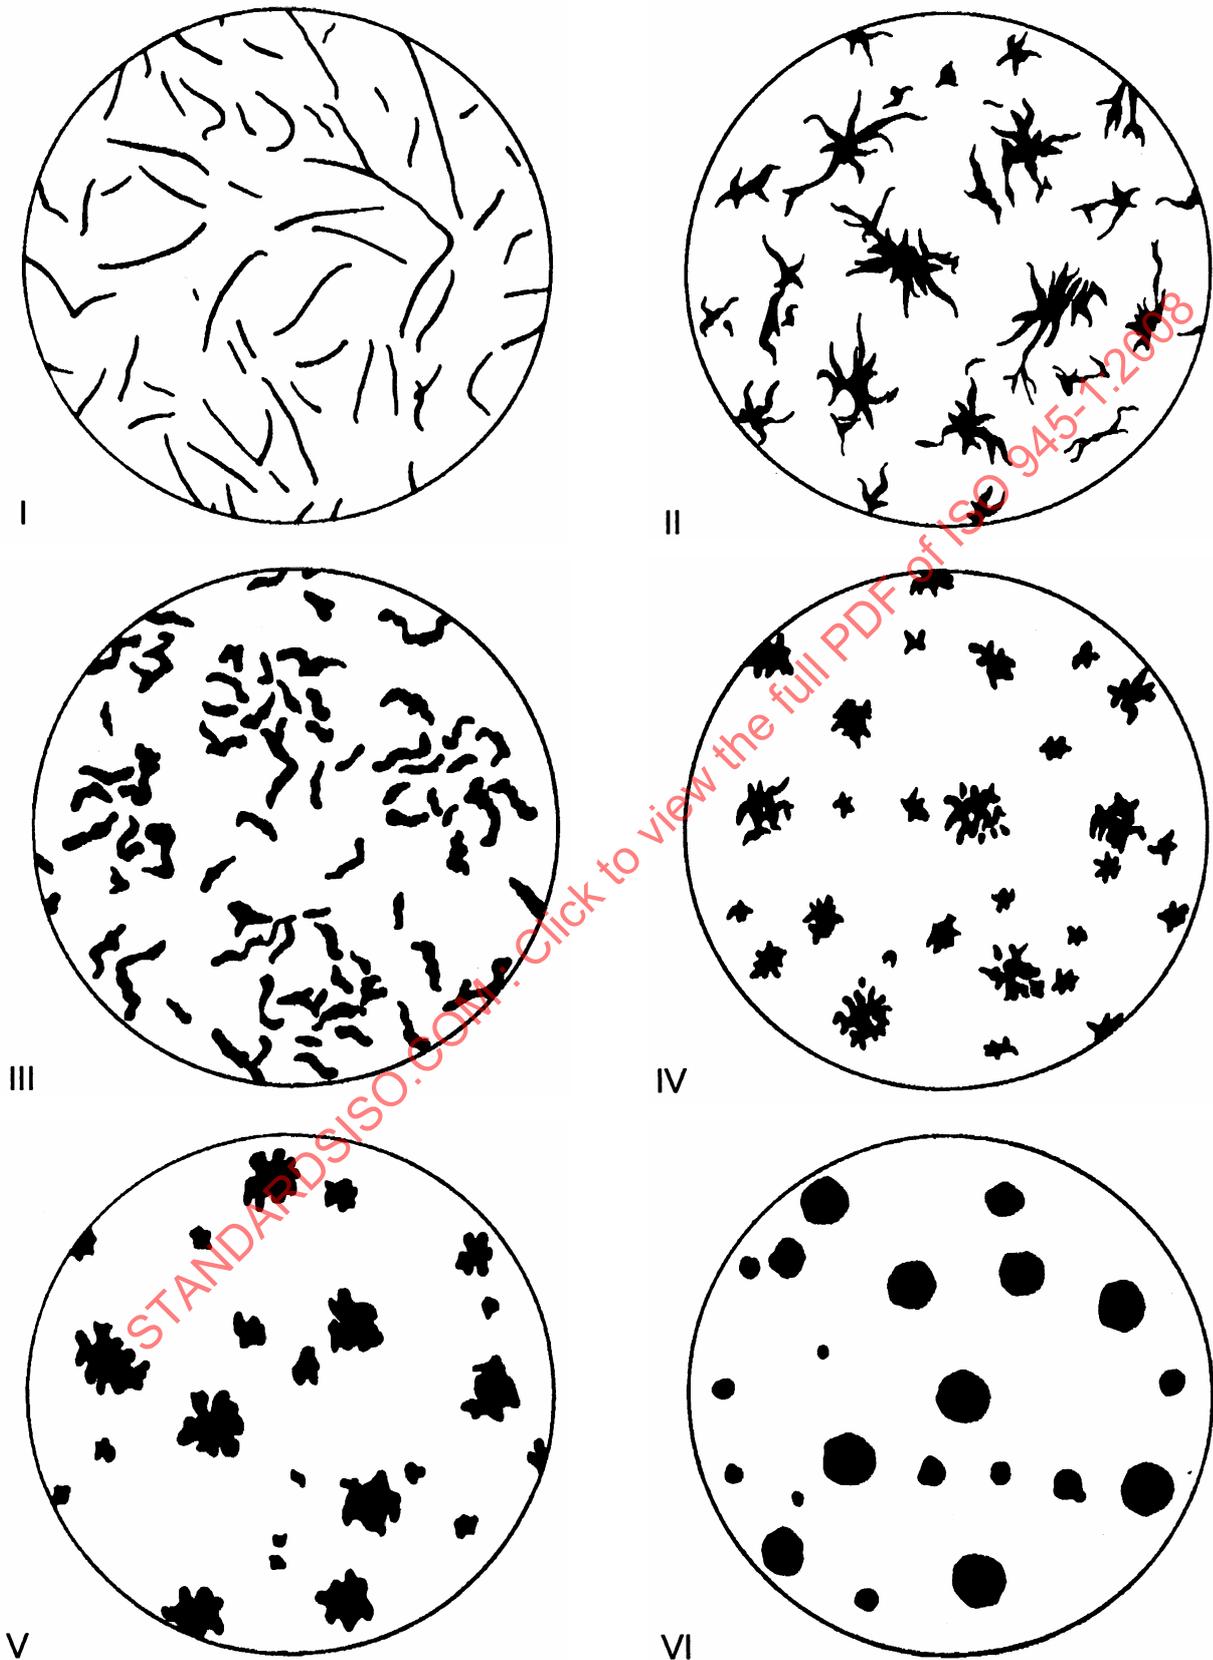


Figure 1 — Principal graphite forms in cast-iron materials — Reference images

DISTRIBUTION

Magnification $\times 100$


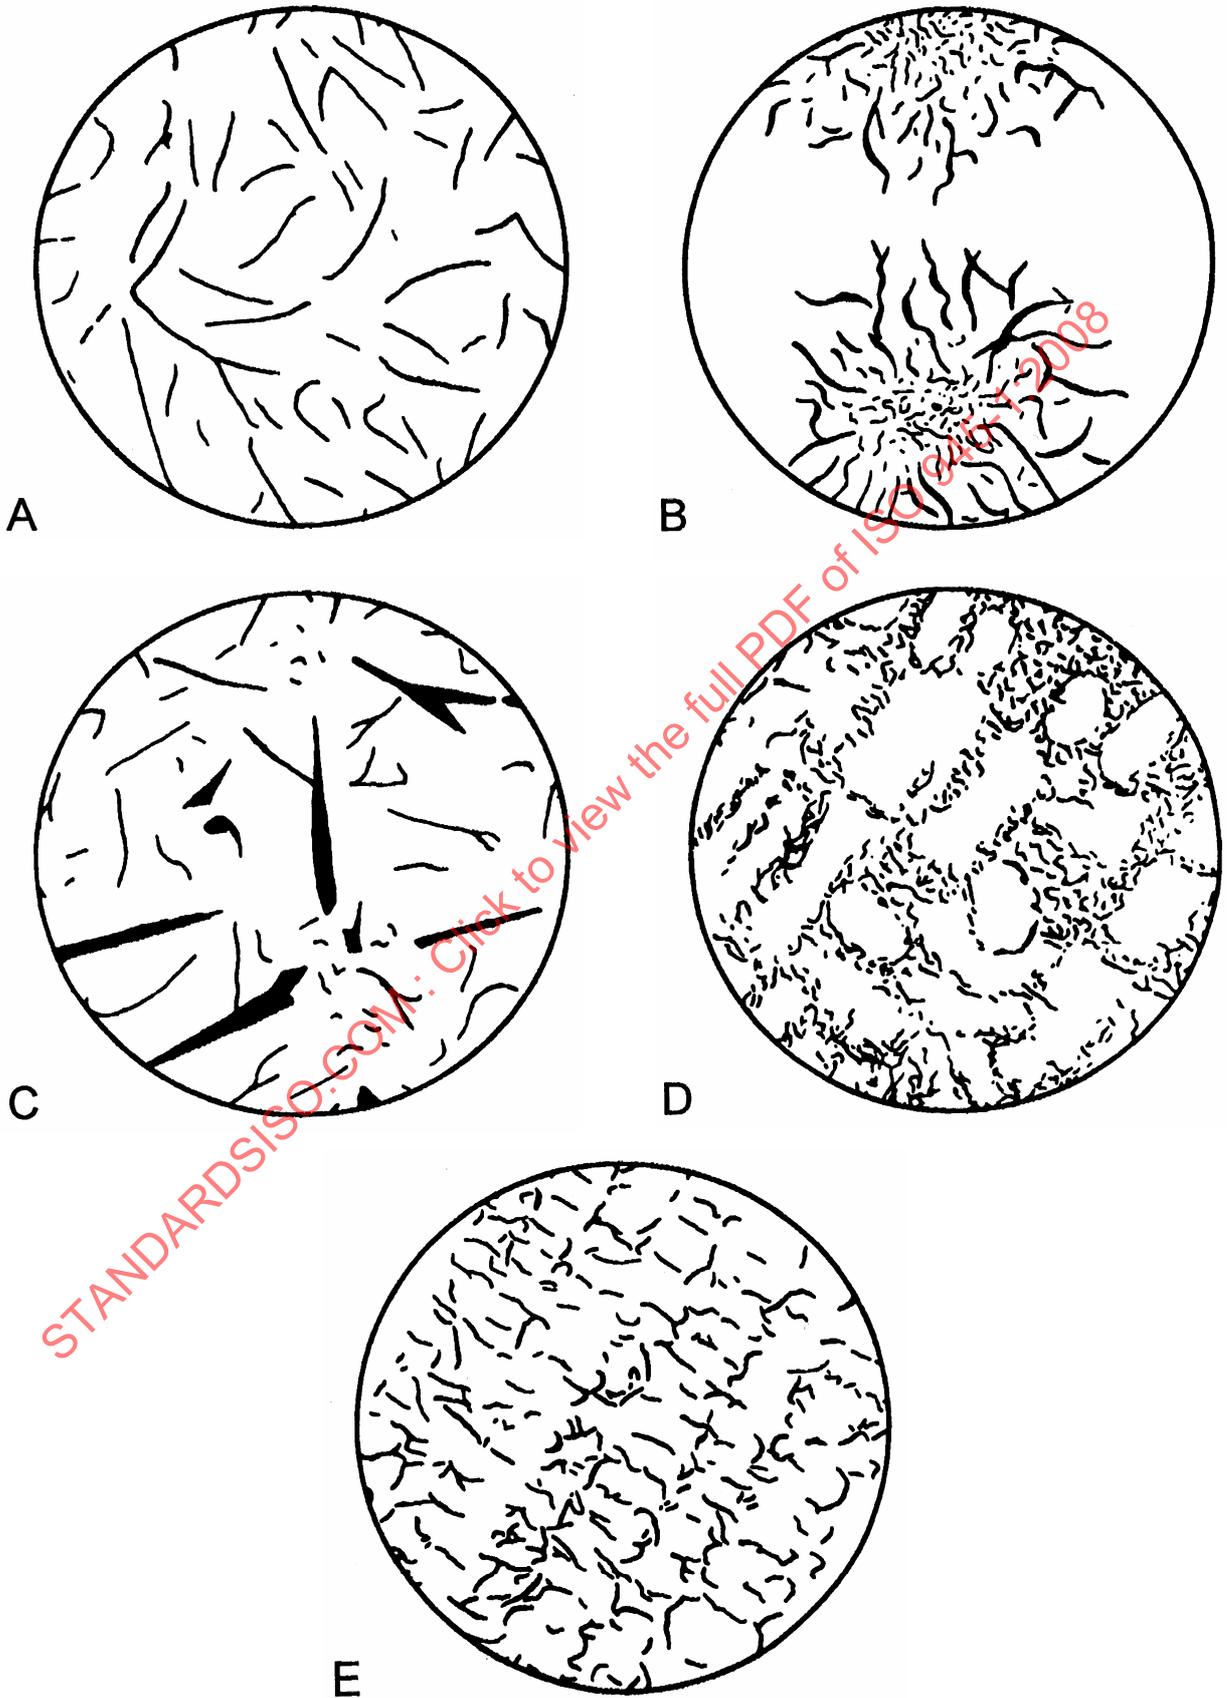


Figure 2 — Reference images for graphite distribution (form I)

SIZE

Magnification $\times 100$

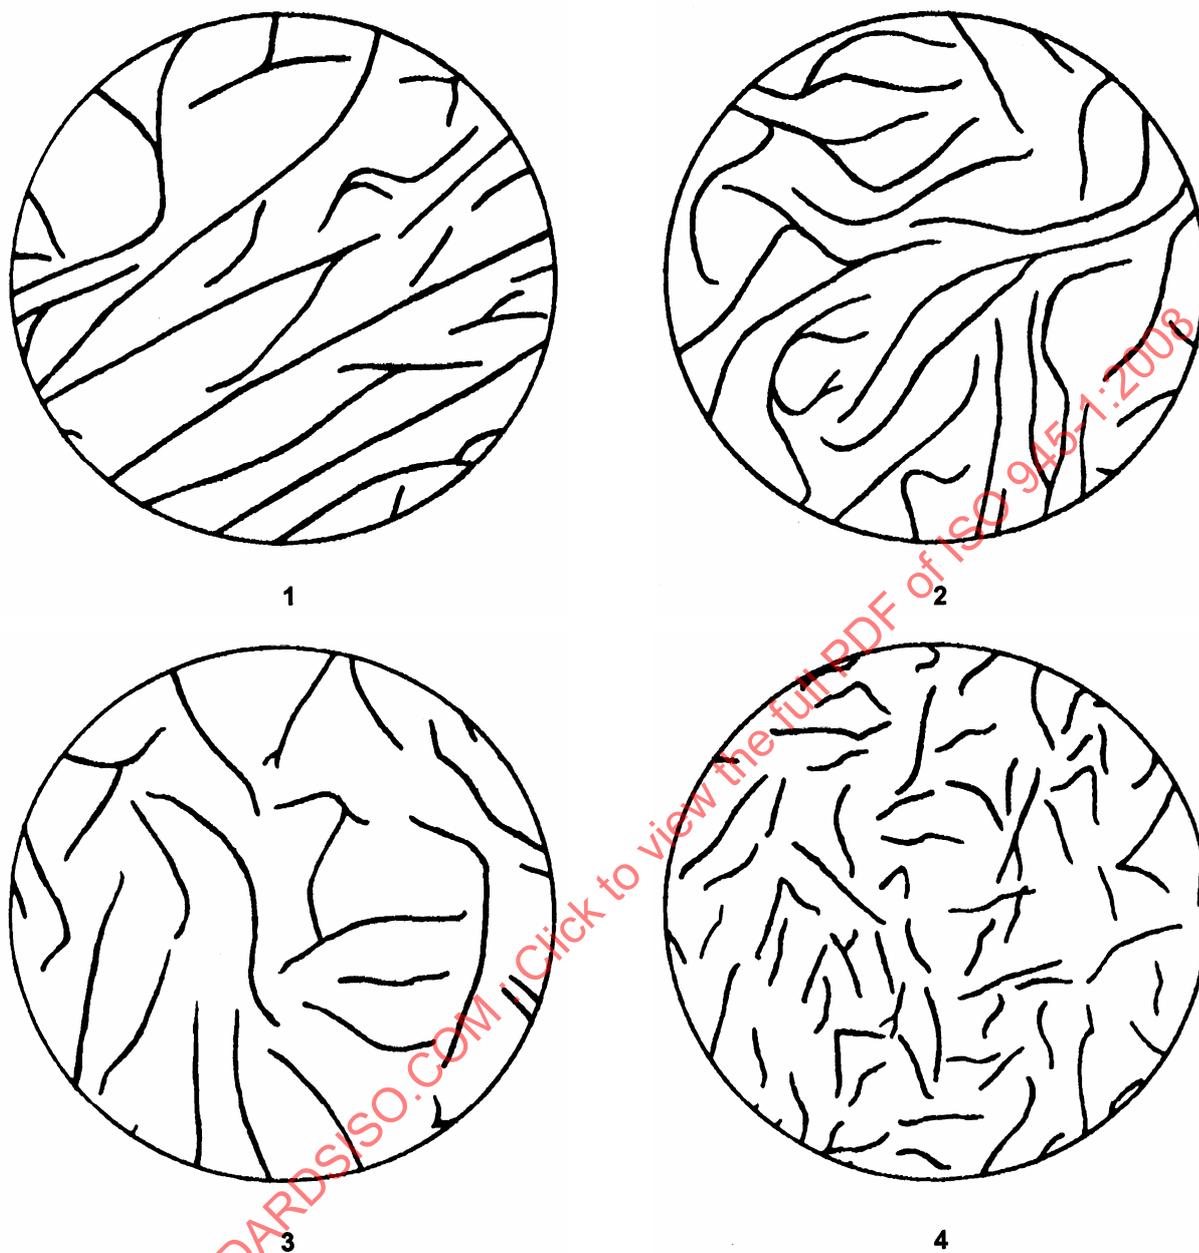


a) Sizes 1 to 4


Figure 3 — Reference images for graphite size (form I)

SIZE


Magnification $\times 100$

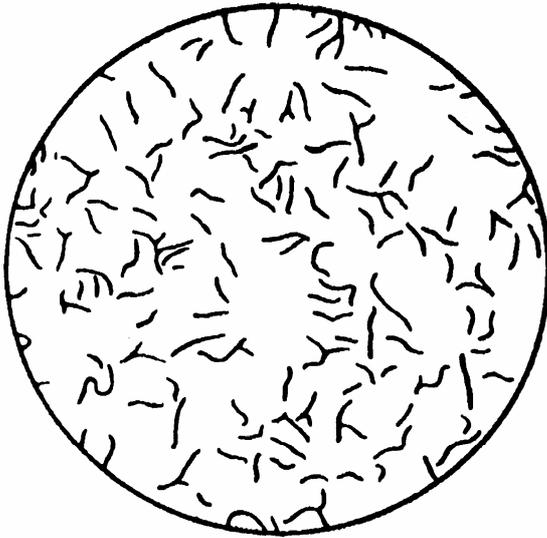


5

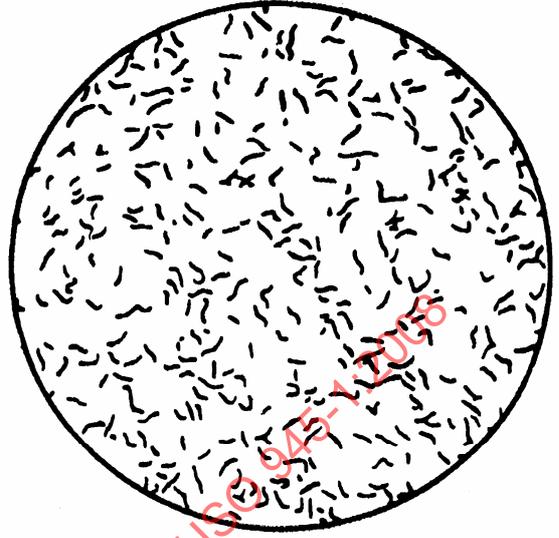

6

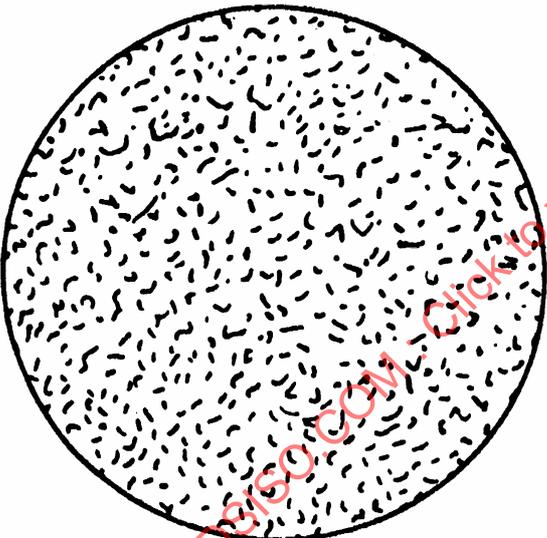

7

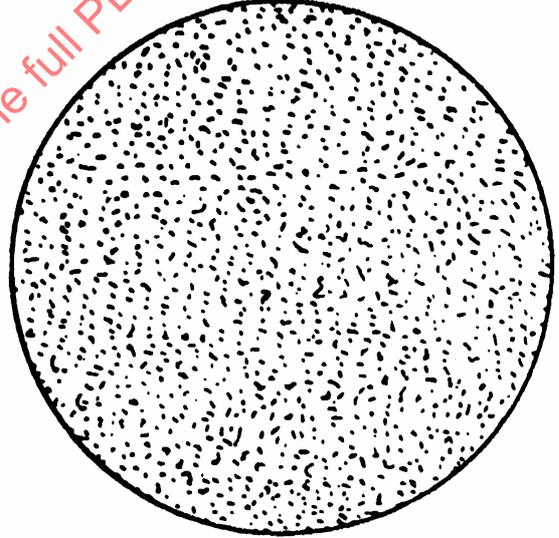


8

b) Sizes 5 to 8

Figure 3 — Reference images for graphite size (form I)

SIZE

Magnification $\times 100$

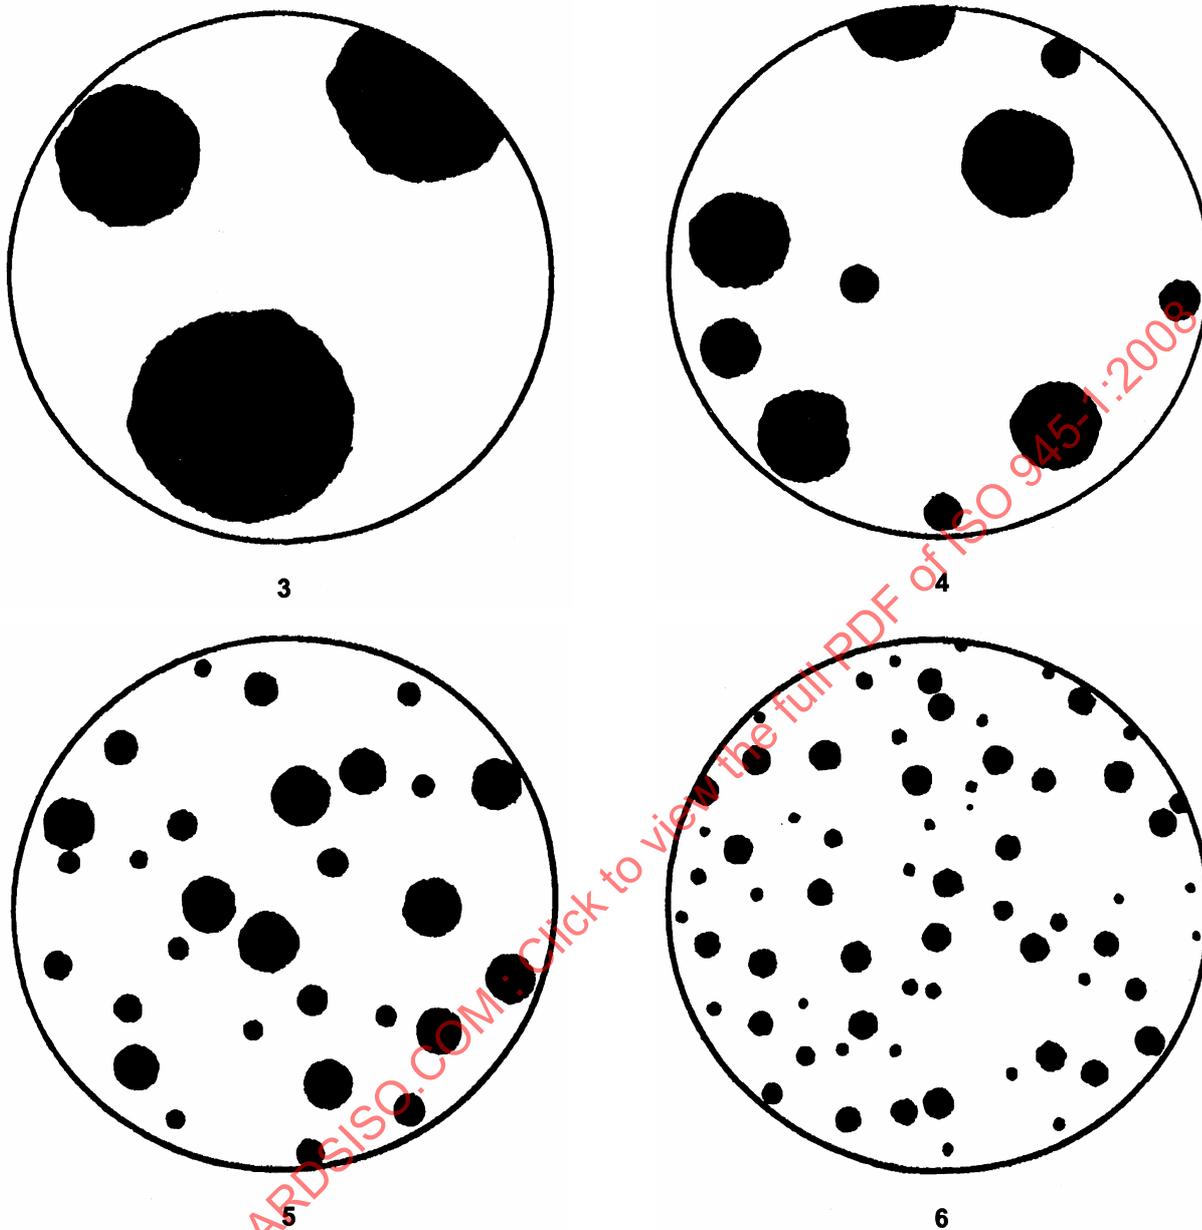


a) Sizes 3 to 6

Figure 4 — Reference images for graphite size (forms IV to VI)

SIZE

Magnification $\times 100$

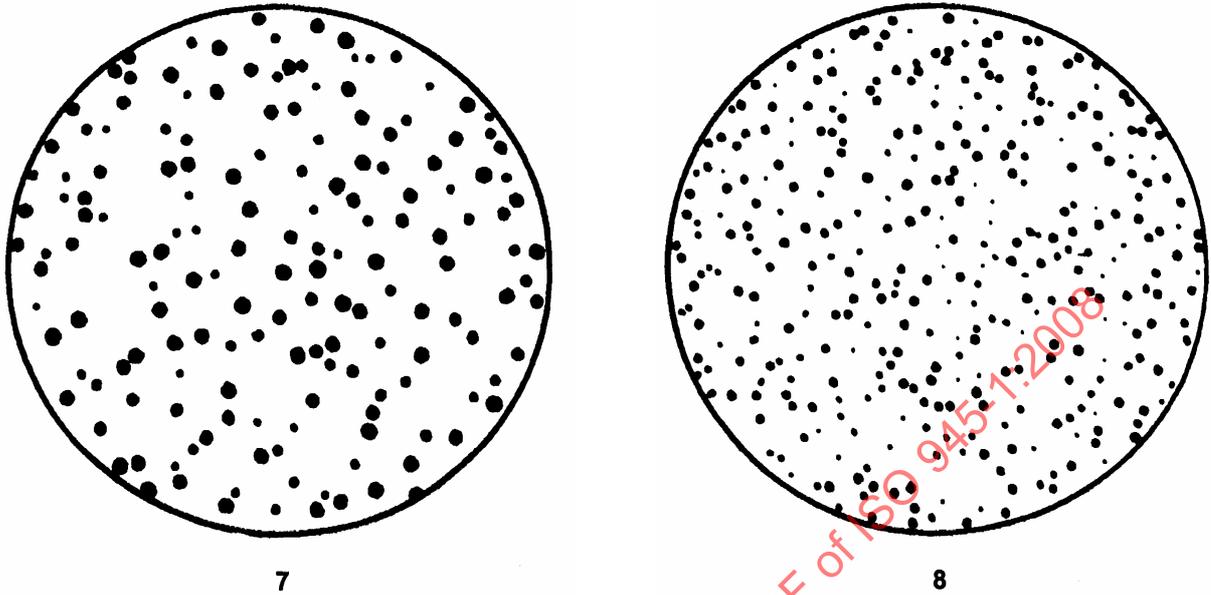


b) Sizes 7 and 8

Figure 4 — Reference images for graphite size (forms IV to VI)

SIZE


Magnification $\times 100$

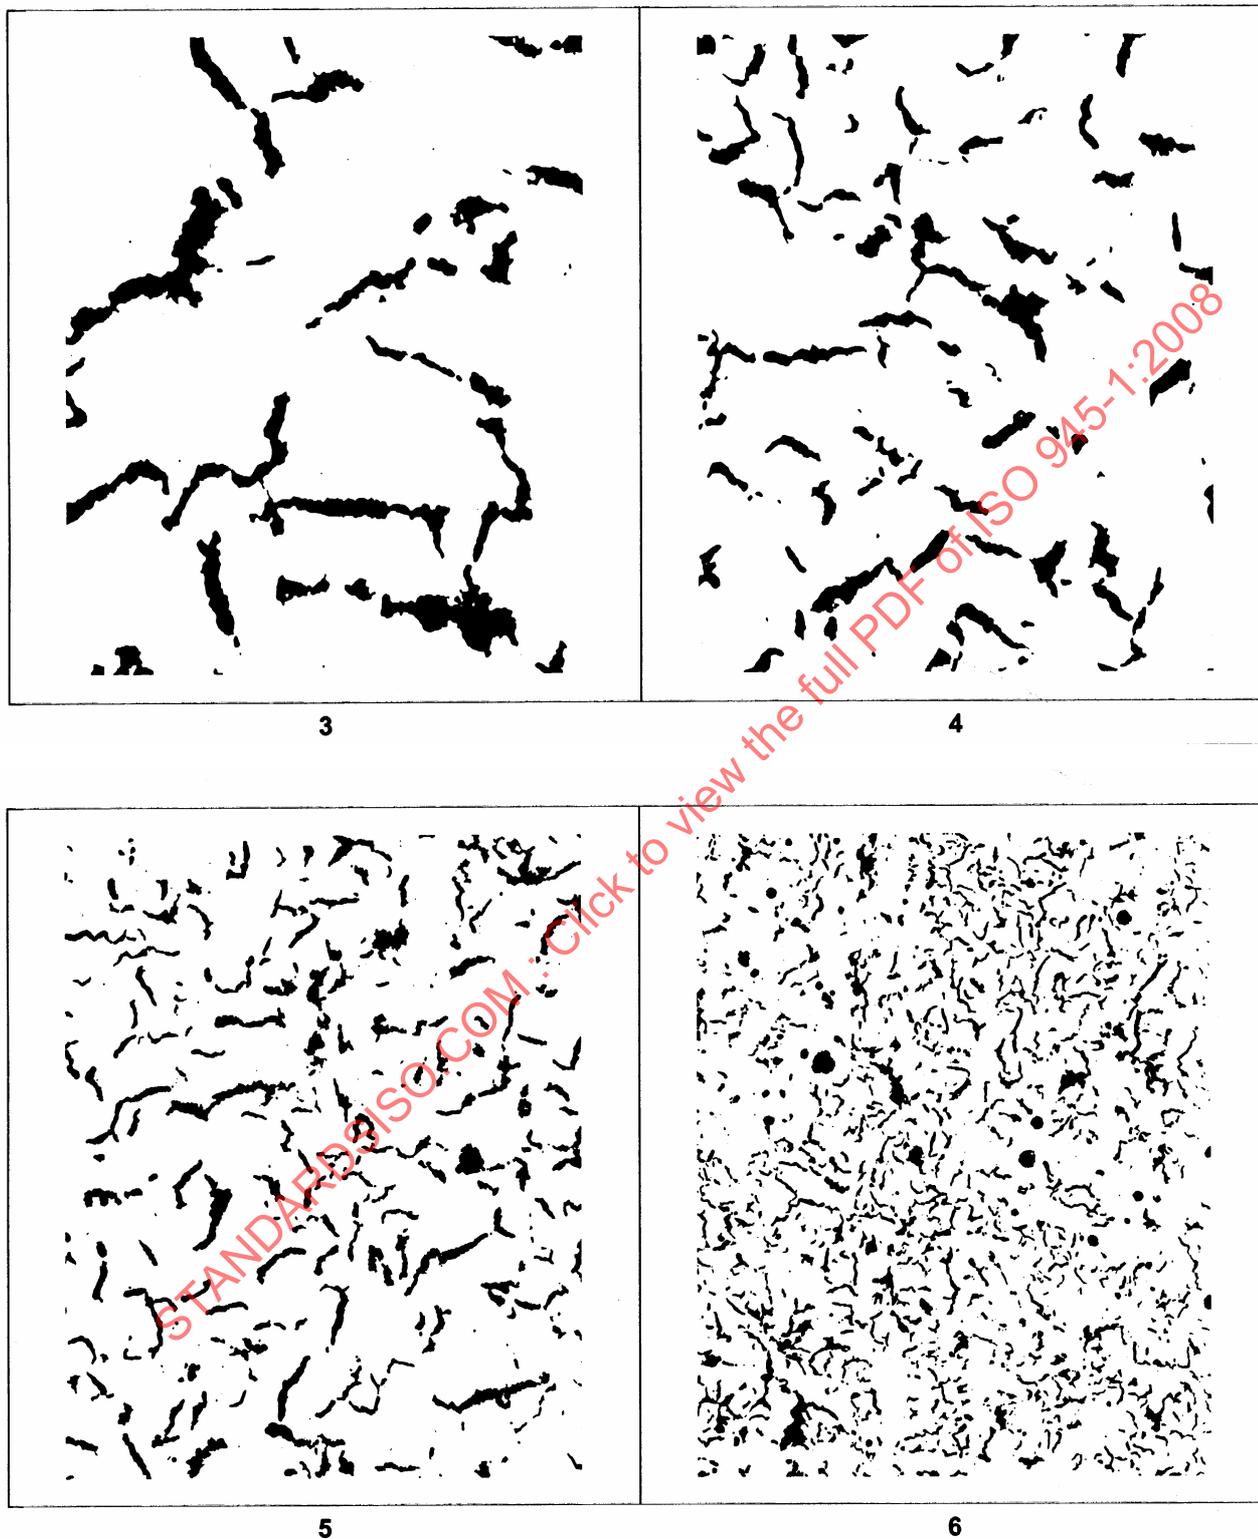

a) Sizes 3 to 6

Figure 5 — Reference images for graphite size (form III)

SIZE

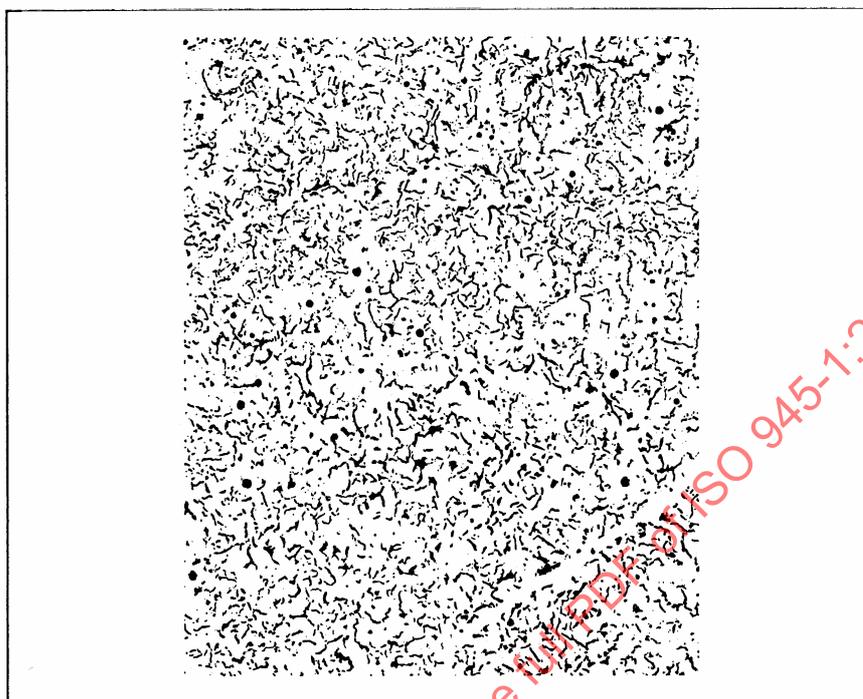Magnification $\times 100$ 

7

b) Size 7

Figure 5 — Reference image for graphite size (form III)

2.2 Visual classification of graphite

The reference images given in Figures 1, 2, 3, 4 and 5 provide a basis for classifying graphite forms, distribution and size. The characteristic features of the graphite which occur are designated by letters and numerals. For this purpose, microstructures of graphite are arranged in a series of reference images consisting of schematic microstructures and photomicrographs of cast-iron microstructures. Therefore, among the images representing the size of the graphite, those for graphite form III (vermicular) in Figure 5 correspond to actual structures with the matrix removed. Those for graphite form I in Figure 3 and for graphite forms IV to VI in Figure 4 are fully schematic.

The form, distribution and size of the graphite observed are determined by comparison with the reference images and the allocation of the same classification as that of the images that resemble them most closely. This method permits quick identification of the graphite form.

NOTE The comparison of actual microstructures with schematic images or photomicrographs depends on the subjective impression of the metallographer.

3 Sampling and preparation of samples

3.1 Samples taken from a casting

When taking samples from a casting, it is essential that attention be paid to the location, to the wall thickness, to the distance from the surface and to the presence of chills. The location of the sample in the casting shall be recorded in a report.

If more than one casting is examined, the samples shall be taken from the same location in each casting for the purpose of comparability.

The location of the metallographic specimen shall be agreed between the manufacturer and the purchaser, as stated in the relevant material standard.

3.2 Sample preparation

The area of the polished surface shall be sufficient to give a true representation of the graphite structure. Attention shall be paid to the careful grinding and polishing of the samples, so that the graphite particles appear in their original form, size and distribution. Inappropriate grinding and polishing can cause an unacceptable alteration of the microstructure. If necessary, the method of polishing may be agreed between the manufacturer and the purchaser.

The examination of the graphite under the microscope is usually carried out on the unetched polished section.

4 Procedure for graphite classification

4.1 Procedure for visual classification of graphite

The polished samples shall be scanned under a microscope in such a manner that a representative area is examined. To examine the graphite form and distribution, a $\times 100$ magnification should preferably be chosen. If necessary, the magnification may be adapted in relation with the wall thickness so that the form and distribution of graphite can be determined by using the reference images given in Figures 1 and 2 (see also Annexes A, B and C). Adjust the microscope magnification to match as closely as possible the corresponding images in Figures 1 and 2 before classifying the graphite form and its distribution, if appropriate. The graphite size shall only be determined by reference to Figures 3, 4 and 5 and Table 1, preferably at $\times 100$ magnification. Other magnifications are permitted (see Table 1, Notes 1 and 2, as well as 5.4).

Examination under the microscope shall be carried out by direct observation in the microscope or by projection on the ground glass of the microscope or on a visual display screen. The field of view should preferably have approximately the same size as the reference images. The measurement of the graphite particles can be facilitated by the use of suitably calibrated eye-pieces.

Form and distribution of graphite shall be determined by using the reference images, given in Figures 1 and 2 (see also Annexes A, B and C). Adjust the microscope magnification to match as closely as possible the corresponding images in Figures 1 and 2 before classifying the graphite form and its distribution, if appropriate.

If the microstructure is visualized on a visual display screen, the combined magnification of both microscope and screen (depending on its size) shall be taken into account.

4.2 Evaluation of the analysis results

The evaluation of the analysis results shall be carried out by an operator trained in this metallographic technique.

5 Reference images

5.1 General

A series of reference images (see Figures 1 to 5) showing schematic microstructures and photomicrographs is provided for the classification of the form, distribution and size of the graphite in cast iron.

In addition to reference images, the photomicrographs show actual graphite microstructures (see Annexes A and B).

5.2 Reference images for graphite form

The reference images for the graphite form (see Figure 1) show six characteristic forms which are designated by the Roman numerals I to VI (see also Annex A). These represent the principal types of graphite observed in cast-iron materials. Annex C gives the common terminology and the occurrence of these types of graphite.

The graphite forms are specified in the relevant material standards. Percentages of these graphite forms may also be specified by these standards, e.g. in the case of compacted (vermicular) graphite cast irons.

NOTE ASTM A 247 designates graphite forms in the reverse order compared to this part of ISO 945. It is therefore necessary to specify the test method used to classify the graphite form.

5.3 Reference images for the distribution of graphite (form I)

The reference images for the graphite distribution (see Figure 2) show characteristic graphite distributions designated by the letters A to E.

In addition to reference images, the photomicrographs show actual graphite microstructures (see Annex B).

A variant of distribution C, designated C', has been included in Annex B. This distribution corresponds to thin-walled castings.

5.4 Reference images for graphite size

Figures 3, 4 and 5 shall be used to determine the graphite size. By agreement between the manufacturer and the purchaser, Table 1 may be used in addition. For $\times 100$ magnification, sizes are indicated ranging from a maximum size of the particle of $> 100 \mu\text{m}$ (size 1) down to $< 1,5 \mu\text{m}$ (size 8). The size ranges covered by the size reference numbers 3 to 7 inclusive are based on an average particle size which is half that in the larger size range. When using Table 1, alternative magnifications may be used (see Table 1, Notes 1 and 2).

If necessary, different size ranges may be agreed upon.

NOTE Sizes 1 and 2 have no practical application for graphite forms III to VI. Therefore, they have not been included in Figures 4 and 5.

6 Designation of graphite by form, distribution and size

6.1 Designation system

To characterize the graphite observed, indications are generally necessary on the form, distribution and size of the graphite particles. For this purpose, the following symbols shall be used at different positions of the designation:

- the Roman numerals given in Figure 1 are used for the graphite form at position 1;
- for form I, the capital letters given in Figure 2 are used for the distribution at position 2;
- the Arabic numerals given in Figures 3, 4, and 5 and Table 1 are used for the graphite size at position 3.

EXAMPLE 1 For a grey cast iron with flake (lamellar) shaped graphite particles of form I, distribution A, and size 4, the following designation is used to describe that structure:

I A 4

EXAMPLE 2 For a cast iron with spheroidal graphite particles of form VI and size 4, the following designation is used to describe that structure:

VI 4

Table 1 — Dimensions of graphite particle forms I to VI

Dimensions in millimetres

Size range reference number	Indication of the particle size observed at $\times 100$ magnification	Actual dimension
1	≥ 100	≥ 1
2	50 to < 100	0,5 to < 1
3	25 to < 50	0,25 to $< 0,5$
4	12 to < 25	0,12 to $< 0,25$
5	6 to < 12	0,06 to $< 0,12$
6	3 to < 6	0,03 to $< 0,06$
7	1,5 to < 3	0,015 to $< 0,03$
8	$< 1,5$	$< 0,015$

NOTE 1 When determining size ranges 1 and 2, a lower magnification ($\times 25$ or $\times 50$) may be used.
 NOTE 2 When determining size ranges 6 to 8, a higher magnification ($\times 200$ or $\times 500$) may be used.
 NOTE 3 For determining size ranges, the largest visible graphite particle size is used.

6.2 Designation of intermediate graphite sizes

If the graphite observed covers two sizes, reference to both is possible:

EXAMPLE 1 3/4

In addition, the predominant size may be emphasized by underlining:

EXAMPLE 2 3/4

This method can be extended to cover microstructures where more than two sizes are present.

6.3 Designation of mixed graphite forms, distributions and sizes

More complex microstructures containing different types of graphite can be defined by estimating the percentage proportions of the different types of graphite.

EXAMPLE 1 For a cast iron with a graphite area comprising 60 % flake (lamellar) shaped graphite particles of form I, distribution A and size 4 and 40 % flake (lamellar) shaped graphite particles of form I, distribution D and size 7, the following designation is used to describe the structure:

60 % I A 4 + 40 % I D 7

EXAMPLE 2 For a cast iron with a graphite area comprising 85 % spheroidal graphite particles of form VI and size 4 and 15 % vermicular graphite particles of form III and covering sizes 3 and 4, the following designation is used to describe the structure:

85 % VI 4 + 15 % III 3/4

6.4 Nodule count

The graphite nodule count n_F is determined by using the planimetric method (see Reference [2]). Nodules are particles normally classified as form VI or V (or even form IV).

$$n_F = \frac{N}{A} \times F^2 \quad (1)$$

where

n_F is the number of particles per unit surface area of the sample;

N is the number of nodules counted;

A is the magnified area;

F is the linear magnification factor.

EXAMPLE At a magnification of $\times 100$, a circle measuring 79,8 mm in diameter ($= 5\,000\text{ mm}^2$) is superimposed over a micrograph. At the preferred magnification of $\times 100$, the circular area should preferably contain at least 50 graphite particles in order to minimize the counting error associated with a circular test pattern. Two counts are made:

n_1 is the number of graphite particles completely within the test circle;

n_2 is the number of graphite particles intersected by the test circle.

The total number of graphite particles in this circle of $5\,000\text{ mm}^2$ is

$$n_{100} = n_1 + \frac{n_2}{2} \quad (2)$$

In this case, to express the nodule count as nodules/ mm^2 , the result given by Equation (2) has to be multiplied by 2, since

$$\frac{F^2}{A} = \frac{100^2}{5\,000} \quad (3)$$

This operation is repeated on other fields.

The larger the number of fields measured, the more representative is the result.

7 Report

If a report is required, it shall contain the following information:

- identification of the sample or casting;
- the sampling location(s);
- the number of samples taken and the number of areas evaluated;
- the form, distribution and size of the graphite;
- the magnification used;
- a reference to this part of ISO 945;
- the date of the report;

ISO 945-1:2008(E)

- the name of the organization;
- the name of the person authorized to sign the report.

If required, the report shall also contain the following information:

- the nodule count;
- the designation of the material;
- the metallographic preparation procedure used;
- the size of the cast-on sample or separately cast sample and/or the wall thickness of the respective sample;
- the size of the graphite;
- details of the presence of any other graphite form not covered by this part of ISO 945.

One or more photomicrographs may also be included in the report.

STANDARDSISO.COM : Click to view the full PDF of ISO 945-1:2008