
**Approval testing of welders — Fusion
welding —**

**Part 4:
Nickel and nickel alloys**

*Épreuve de qualification des soudeurs — Soudage par fusion —
Partie 4: Nickel et ses alliages*



Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the Technical Committees are circulated to member bodies for voting. Publication as an International Standard requires approval by at least 75 % of member bodies casting a vote.

International Standard ISO 9606-4 was prepared by the European Committee for Standardization (CEN) in collaboration with ISO Technical Committee TC 44, *Welding and allied processes*, Subcommittee SC 11, *Approval requirements for welding and allied processes personnel*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Throughout the text of this standard, read "...this European Standard..." to mean "...this International Standard...".

ISO 9606 consists of the following parts, under the general title *Approval testing of welders — Fusion welding*:

- Part 1: Steels
- Part 2: Aluminium and aluminium alloys
- Part 3: Copper and copper alloys
- Part 4: Nickel and nickel alloys
- Part 5: Titanium and titanium alloys
- Part 6: Magnesium and magnesium alloys

© ISO 1999

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case postale 56 • CH-1211 Genève 20 • Switzerland
Internet iso@iso.ch

Printed in Switzerland

Annexes A and ZA of this part of ISO 9606 are for information only.

For the purposes of this part of ISO 9606, the CEN annex regarding fulfilment of European Council Directives has been removed.

STANDARDSISO.COM : Click to view the full PDF of ISO 9606-4:1999

Contents

	Page
1 Scope.....	1
2 Normative references	1
3 Definitions	2
4 Symbols and abbreviations	2
5 Essential variables for approval testing	3
6 Range of approval for the welder	5
7 Examination and testing.....	8
8 Acceptance requirements for test pieces.....	15
9 Re-tests.....	15
10 Period of validity	15
11 Certificate.....	16
12 Designation.....	16
Annex A Job knowledge	18
Annex ZA Bibliography	20

Introduction

This standard covers the principles to be observed in the approval testing of welder performance for the fusion welding of nickel and nickel alloys.

The term "nickel" stands for nickel and weldable nickel alloys.

The ability of the welder to follow verbal or written instructions and testing of his skill are therefore important factors in ensuring the quality of the welded product.

Testing of skill to this standard depends on welding methods in which uniform rules and test conditions are complied with, and standard test pieces are used.

The test weld can be used to approve a welding procedure and a welder provided that all the relevant requirements, e.g. test piece dimensions, are satisfied (see relevant part of EN 288-2).

1 Scope

This standard specifies essential requirements, ranges of approval, test conditions, acceptance requirements and certification for the approval testing of welder performance for the welding of nickel.

This standard applies to the approval testing of welders for the fusion welding of nickel.

This standard is intended to provide the basis for the mutual recognition by examining bodies for approval relating to welders' competence in the various fields of application. Tests will be carried out in accordance with this standard unless more severe tests are specified by the relevant application standard when these are applied.

During the approval test the welder should be required to show adequate practical experience and job knowledge (test non mandatory) of the welding processes, materials and safety requirements for which he is to be approved; information on these aspects is given in Annex A.

This standard is applicable when the welder's approval testing is required by the purchaser, by inspection authorities or by other organizations.

The welding processes referred to in this standard include those fusion welding processes which are designated as manual or partly mechanized welding. It does not cover fully mechanized and automatic processes (see 5.2).

This standard covers approval testing of welders for work on semi-finished and finished products made from wrought, forged or cast material types listed in 5.4.

The certificate of approval testing is issued under the sole responsibility of the examiner or examining body.

2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN 287-1 : 1992	Approval testing of welders – Fusion welding – Part 1: Steels
EN 288-2 : 1992	Specification and approval of welding procedures for metallic materials – Part 2: Welding procedure specification for arc welding
EN 571-1	Non destructive testing - Penetrant testing – Part 1: General principles
EN 910	Destructive test on welds in metallic materials – Bend tests
EN 970	Non-destructive examination of fusion welds – Visual examination

EN 1289	Non-destructive examination of welds – Penetrant testing of welds – Acceptance levels
EN 1320	Destructive tests on welds in metallic materials – Fracture test
EN 1321	Destructive tests on welds in metallic materials – Macroscopic and microscopic examination of welds
EN 1435	Non-destructive examination of welds – Radiographic examination of welded joints
EN 24063 : 1992	Welding, brazing, soldering and braze welding of metals – Nomenclature of processes and reference numbers for symbolic representation on drawings (ISO 4063 : 1990)
EN 25817 : 1992	Arc-welded joints in steel – Guidance on quality levels for imperfections (ISO 5817 : 1992)
EN 26520 : 1991	Classification of imperfections in metallic fusion welds, with explanations (ISO 6520 : 1982)
EN ISO 6947 : 1997	Welds – Working positions – Definitions of angles of slope and rotation (ISO 6947 : 1993)
CR 12187	Welding – Guidelines for a grouping system of materials for welding purposes
ISO 857 : 1990	Welding, brazing and soldering processes – Vocabulary

3 Definitions

For the purposes of this standard the definitions given in EN 287-1 apply.

4 Symbols and abbreviations

4.1 General

Where the full wording is not used, the following symbols and abbreviations shall be used when completing the test certificate (see Annex B of EN 287-1 : 1992).

4.2 Test piece

a	nominal throat thickness ;
BW	butt weld ;
D	outside diameter of pipe ;
FW	fillet weld ;
P	plate ;
t	plate or pipe wall thickness ;
T	pipe ;
z	leg length of fillet weld.

4.3 Consumables

nm	no filler metal ;
wm	with filler metal.

4.4 Miscellaneous

4.4 Miscellaneous

bs	welding from both sides ;
gg	back gouging or back grinding of welds ;
mb	welding with backing material ;

nb	welding without backing ;
ng	no back gouging or no back grinding ;
ss	single-side welding.

5 Essential variables for approval testing

The criteria specified in this clause shall be examined in order to identify the ability of the welder in these areas. Each criterion is considered to be a significant factor in the approval testing.

The welder's approval test shall be carried out on test pieces and is independent of the type of construction.

5.2 Welding processes

Welding processes are defined in ISO 857 and reference numbers of welding processes for symbolic representation are listed in EN 24063.

This standard covers the following welding processes:

111	metal-arc welding with covered electrode;
131	metal-arc inert gas welding (MIG welding);
135	metal-arc active gas welding (MAG welding);
136	flux-cored wire metal-arc welding with active gas shield;
141	tungsten inert gas arc welding (TIG welding);
15	plasma arc welding;

other fusion welding processes by agreement.

5.3 Joint types (butt and fillet welds)

Test pieces shall be produced for butt weld (BW) and fillet weld (FW) in plates (P) or pipes¹⁾ (T) for approval tests in accordance with 7.2.

5.4 Material groups

5.4.1 General

In order to minimize unnecessary multiplication of technically identical tests, nickel with similar metallurgical and welding characteristics are grouped for the purpose of a welder's approval (see 5.4.2).

In general, a welder's approval test shall involve depositing weld metal having a chemical composition compatible with any of the nickel in the parent metal group(s).

5.4.2 Nickel groups of parent metal

5.4.2.1 General

Nickel casting alloys are included in the following groups but the filler metal shall be compatible with the filler metal used for the wrought materials in the same group.

Material groups according to CR 12187

5.4.2.2 Group W 41: Pure nickel

5.4.2.3 Group W 42: Nickel-copper alloys Ni ≥ 45 %, Cu > 10 %

¹⁾ The word "pipe", alone or in combination, is used to mean "pipe", "tube" or "hollow section".

5.4.2.4 Group W 43: Nickel-chromium alloys (Ni/Fe/Cr/Mo) Ni \geq 40 %

5.4.2.5 Group W 44: Nickel-molybdenum alloys (Ni/Mo) Ni \geq 45 %, Mo \leq 30 %

5.4.2.6 Group W 45: Nickel-iron-chromium alloys (Ni/Fe/Cr) Ni \geq 45 %

5.4.2.7 Group W 46: Nickel-chromium-cobalt alloys (Ni/Cr/Co) Ni \geq 45 %, Co \geq 10 %

5.4.2.8 Group W 47: Nickel-iron-chromium-copper alloys (Ni/Fe/Cr/Cu) Ni \geq 45 %

5.5 Consumables

It is assumed that in most approval tests the filler metal will be similar to the parent metal. When a welder's test according to a relevant pWPS or WPS has been carried out using a filler metal and shielding gas suitable for that material group, this test will confer approval on the welder to use any other similar consumables (filler metal or shielding gas) for the same material group.

5.6 Dimensions

The approval test should be based on the thickness of the material (i.e. plate thickness or wall thickness of pipe) and pipe diameters which the welder will use in production. A test is listed for each of the three ranges of plate thickness and pipe wall thickness or pipe diameter as specified in tables 1 and 2.

It is not intended that thicknesses or diameters should be measured precisely but rather the general philosophy behind the values given in tables 1 and 2 should be applied.

Table 1: Test piece (plate or pipe) and range of approval

Test piece thickness t mm	Range of approval
$t < 3$	t to $2t$
$3 < t \leq 12$	3 mm to $2t$
$t > 12$	≥ 5 mm

Table 2: Test piece diameter and range of approval

Test piece diameter D mm	Range approval
$D \leq 25$	D to $2D$
$D > 25$	$\geq 0,5 D$ (25 mm min.)

5.7 Number of test pieces

Plate: One test piece per position.

Pipe: A minimum weld length of 150 mm is required, but not more than three test pieces.

5.8 Welding positions

The welding positions shall be taken from EN ISO 6947.

The test pieces shall be welded in accordance with the nominal angles of the positions according to EN ISO 6947.

6 Range of approval for the welder

6.1 General

As a general rule, the test piece approves the welder not only for the conditions used in the test, but also for all joints which are considered easier to weld. The range of approval for each type of test is given in the relevant sub-clauses and tables. In these tables the range of approval is indicated in the same horizontal line.

6.2 Welding process

Each test normally approves one process. A change of process requires a new approval test. However, it is possible for a welder to be approved for more than one welding process by a single test or by two separate approval tests to be used to cover a multi-process joint. For example in a case where approval is required for a single-side butt joint with the root to be welded by TIG (141) without backing and to be filled by metal-arc welding with covered electrode (111), the welder may be approved by either of the following routes:

- a) a successful completion of an approval test simulating the multi-process joint, i. e. the root run welded by TIG (141) without backing, subsequent runs or layers welded by metal-arc welding with covered electrode (111) within the limits of the range of approval for each welding process;
- b) successful completion of separate relevant approval tests (within the limits of each range of approval) one for TIG (141) without backing for the root run and a separate test for the fill by metal-arc welding with covered electrode (111) with backing or welded from both sides with or without back gouging or grinding.

6.3 Joint types

Depending on the test piece, the range of welds for which the welder is approved is shown in table 3; the following criteria are applicable:

- a) approval for butt welds in pipes, diameter > 25 mm, includes butt welds in plates;
- b) approval for butt welds in plates in all relevant positions covers butt welds on pipes having an outside diameter ≥ 500 mm, except when item c) also applies;
- c) approval on test butt joints in plates welded in the flat (PA) or horizontal (PC) position shall include approval for butt joints in pipes of outside diameter ≥ 150 mm welded in similar positions according to table 4;
- d) butt welds approve fillet welds. In cases where the majority of production work is fillet welding, the welder shall be approved also by an appropriate fillet welding test;
- e) approval for butt welds in pipes without backing includes approval for branch connections within the same range of approval as in tables 3 and 4. For a branch weld the range of approval is based on the diameter of the branch;
- f) in cases where the majority of production work is predominantly branch welding or involves a complex branch connection, the welder should receive special training. In some cases a welder approval test on a branch connection can be necessary.

Table 3: Range of approval for tests on butt joints (Detail of weld type)

Details of weld type				Range of approval					
				Butt welds in plate				Butt welds in pipe	
				welded from one side ss		welded from both sides bs		welded from one side ss	
				with backing mb	no backing nb	with gouging gg	no gouging ng	with backing mb	no backing nb
Butt weld in plate	welded from one side ss	with backing	mb	*	-	x	-	1)	-
		no backing	nb	x	*	x	x	1)	1)
	welded from both sides bs	with gouging	gg	x	-	*	-	1)	-
		no gouging	ng	x	-	x	*	1)	-
Butt weld in pipe	welded from one side ss	with backing	mb	x	-	x	-	*	-
		no backing	nb	x	x	x	x	x	*

1) See 6.3 b) and 6.3 c)

* indicates the weld for which the welder is approved in the approval test
 x indicates those welds for which the welder is also approved
 - indicates those welds for which the welder is not approved

6.4 Material groups

A test carried out in group W 41 covers all other groups, but not vice versa. A test carried out in any of the groups W 42 to W 47 covers all groups of W 42 to W 47.

Groups W 41 to W 47 also cover the group W 11 according to EN 287-1, but not vice versa.

Approval of dissimilar metal joints: When using filler metal from groups W 41 to W 47, all combinations of steel/steel and steel/nickel alloy are covered.

6.5 Consumables

A change in the type of electrode may require a change in the welder's technique, therefore a new test may be necessary.

A change of shielding gas is permitted (see 5.5). However, a change from active to inert shielding gas or from inert to active shielding gas requires a new approval test for the welder.

6.6 Dimensions

The range of approval according to plate thickness or wall thickness of pipe and/or pipe diameter is shown in tables 1 and 2.

6.7 Welding positions

The range of approval for each welding position is given in table 4. The welding positions and codes refer to EN ISO 6947.

Table 4: Range of approval according to welding position

Welding position of approval test piece		Range of approval																							
		Plates								Pipes															
		Butt welds				Fillet welds				Butt welds				Fillet welds											
		Pipe-axis and -angle				rotating 1)				fixed				rotating 1)				fixed							
		rotating		0°		45°		90°		45°		90°		45°		90°									
		PA	PC	PG	PF	PE	PA	PB	PG	PF	PD	PA	PC	PG	PF	PD	PA	PC	PG	PF	PD				
Plates	Butt welds	PA	*	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-			
		PC	x	*	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
		PG	-	-	*	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
		PF	x	-	-	*	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
		PE	x	x	-	x	*	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
	Fillet welds	PA	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
		PB	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
		PG	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
		PF	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
		PD	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
Pipes	Butt welds	rotating 0°	PA	x	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
		fixed	90°	PG	-	-	x	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	
			45°	PF	x	-	-	x	x	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	
			Axis of the pipe and angle	45°	PC	x	x	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
				rotating 45°	H	x	x	-	x	x	x	-	-	-	-	-	-	-	-	-	-	-	-	-	-
	Fillet welds	rotating 1)	J	-	-	x	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
		fixed	0°	PA	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	
			45°	PB	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	
			90°	PG	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	
			PD	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	

STANDARD ISO.COM: Click to view the full PDF of ISO 9606-4:1999

1) PB for pipes can be welded in two versions
 (1) pipe: rotating; axis: horizontal; weld: horizontal vertical
 (2) pipe: fixed; axis: vertical; weld: horizontal vertical

2) This is an approved position and is covered by the other related tests.

* indicates the welding position for which the welder is approved in the approval test
 x indicates those welding positions for which the welder is also approved
 - indicates those welding positions for which the welder is not approved

7 Examination and testing

7.1 Supervision

The welding and testing of test pieces shall be witnessed by an examiner or examining body acceptable to the contracting parties.

The test pieces shall be marked with the identification of the examiner and the welder before welding starts.

The examiner or examining body can stop the test if the welding conditions are not correct or if it appears that the welder does not have the technical competence to achieve the requirements of this standard, e. g. where there are excessive and/or systematic repairs.


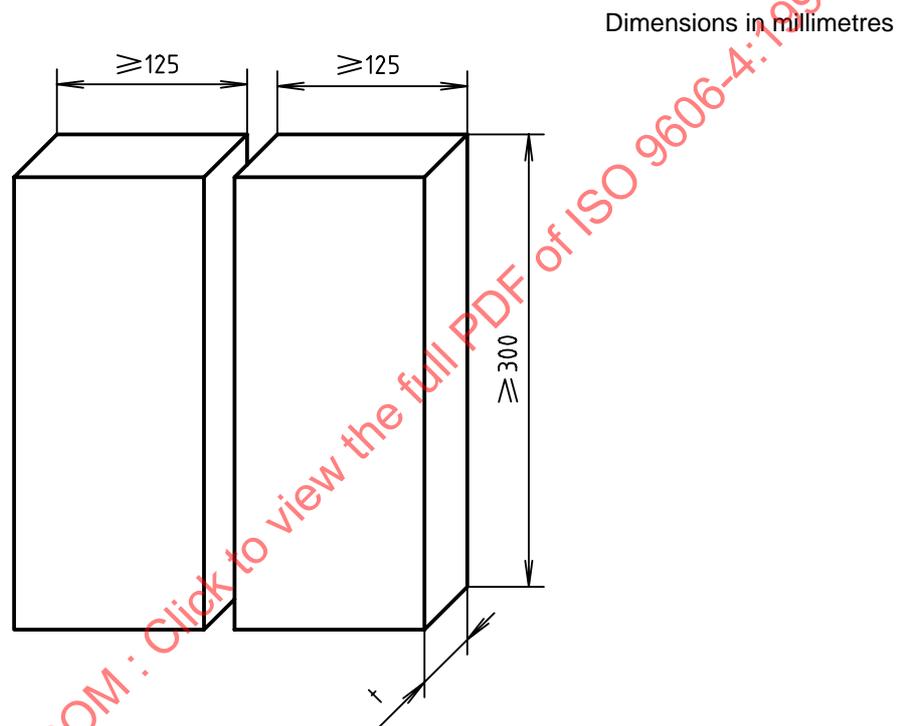


Figure 1: Dimensions of test piece for a butt weld in plate

7.2 Shapes and dimensions of test pieces

The shape and dimension of test pieces (see 5.6) required are shown in figures 1 to 4.

Dimensions in millimetres

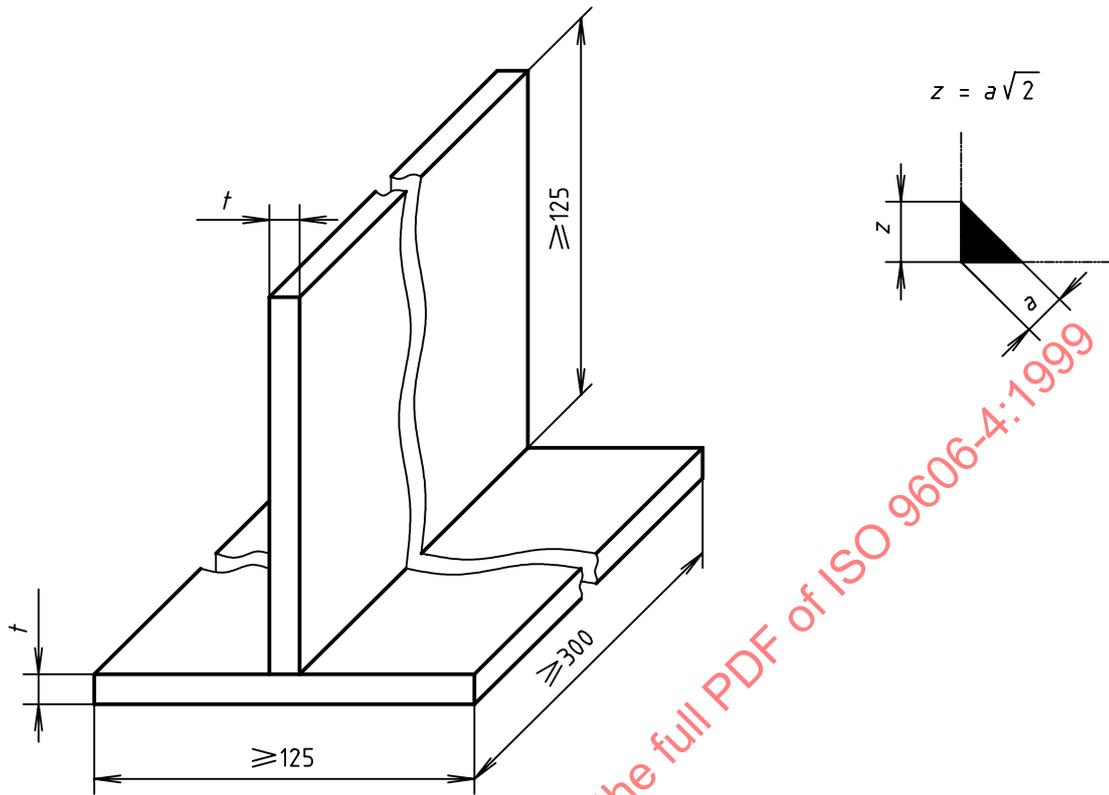

For $t \geq 6$ mm, $a \leq 0,5 t$
 For $t < 6$ mm, $0,5 t \leq a \leq t$
 ($z \approx 0,7 t$)

Figure 2: Dimensions of test piece for fillet weld(s) on plate

Dimensions in millimetres

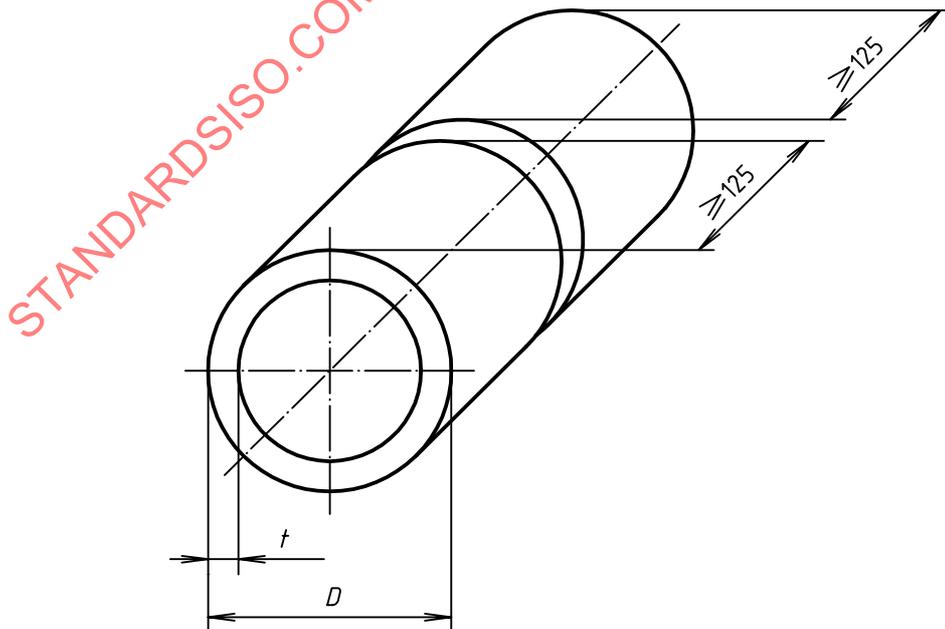


Figure 3: Dimensions of test piece for a butt weld in pipe

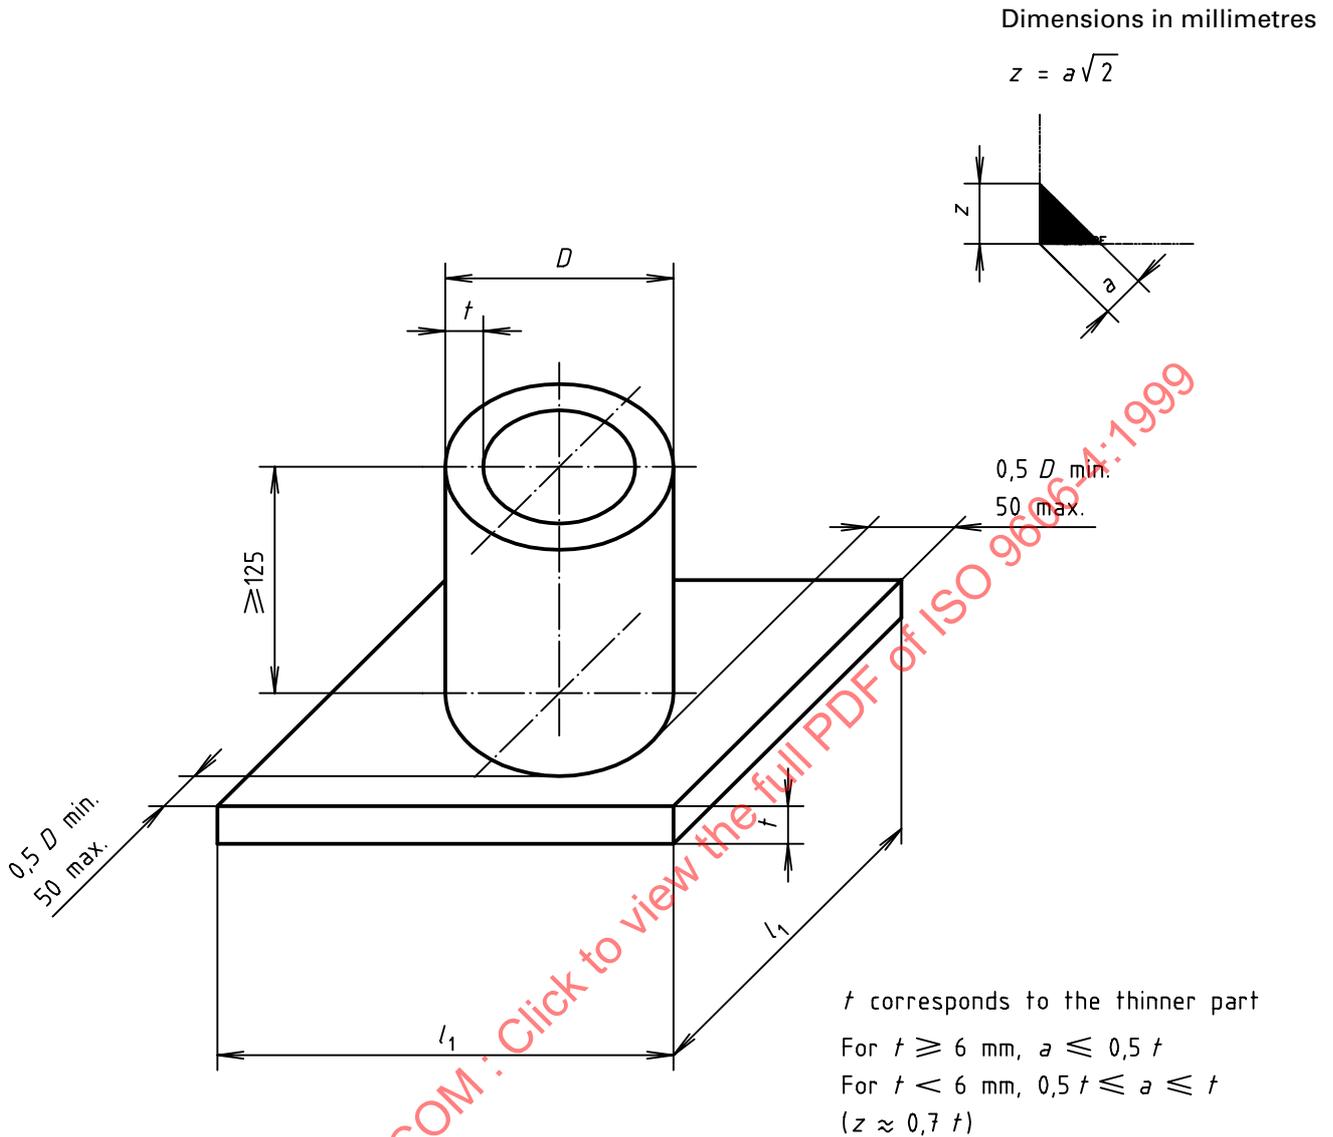


Figure 4: Dimensions of test piece for a fillet weld on pipe

7.3 Welding conditions

The approval test for the welder shall correspond to the conditions used in production and follow a pWPS or WPS prepared in accordance with EN 288-2.

The following conditions shall apply:

- a) the welding time for the test piece shall correspond to the working time under usual production conditions;
- b) the test piece shall have at least one stop and one re-start in the root run and in the top capping run and be identified in the inspection length to be examined;
- c) any pre-heat or controlled heat input required in the pWPS or WPS is mandatory for the welder's test piece;
- d) any post-weld heat treatment required in the pWPS or WPS can be omitted unless bend tests are required;
- e) identification of the test piece;
- f) the welder shall be allowed to remove minor imperfections, except on the surface layer, by grinding or any other method used in production. The approval of the examiner or test body shall be obtained.

7.4 Test methods

Each completed weld shall be examined visually according to EN 970 in the as-welded condition. When required, visual examination can be supplemented by penetrant (see EN 571-1) or other test methods (see table 5).

If accepted by visual examination, additional radiographic tests (see EN 1435), fracture tests (see EN 1320) and/or macroscopic tests (see EN 1321) are required (see table 5).

The macroscopic specimen shall be prepared and etched on one side to clearly reveal the weld (see EN 1321).

When radiography is used, bend tests (see EN 910) shall always be applied to butt welds made by MIG/MAG (131, 135) processes.

Prior to mechanical testing, backing strips, where used, shall be removed. The test piece can be sectioned by mechanical means discarding the first and last 25 mm of the test piece at the end of the plates (figures 5 and 6).

Table 5: Test methods

Test method	Butt weld plate	Butt weld pipe	Filet weld
Visual	mandatory	mandatory	mandatory
Radiography	mandatory ¹⁾⁵⁾	mandatory ¹⁾⁵⁾	not mandatory
Bend	mandatory ²⁾	mandatory ²⁾	not mandatory
Fracture	mandatory ¹⁾	mandatory ¹⁾	mandatory ³⁾⁴⁾
Macroscopic test (without polishing)	not mandatory	not mandatory	not mandatory ⁴⁾
Magnetic particle/penetrant	not mandatory	not mandatory	not mandatory

1) Radiography or fracture test shall be used, but not both test methods.

2) When radiography is used, bend tests are mandatory for the processes 131 and 135.

3) The fracture test should be supported by magnetic particle/penetrant testing when required by the examiner or examining body.

4) The fracture test may be replaced by a macroscopic examination of at least 4 sections, one of which will be taken from the stop/start location.

5) The radiographic test may be replaced by an ultrasonic test for thickness ≥ 8 mm on ferritic steels only.

7.5 Test piece and specimens

7.5.1 General

In 7.5.2 to 7.5.5 details of the type, dimensions and preparation of test pieces and test specimens are given. In addition, the requirements for mechanical tests are indicated.

7.5.2 Butt welds in plate

When radiographic testing is used, the inspection length of the weld (see figure 5 a) in the test piece shall be radiographed in the as-welded condition in accordance with EN 1435 using class B technique.

When fracture testing is used, it shall be carried out in accordance with EN 1320. One root fracture test specimen and one face fracture test specimen shall be tested. The inspection length of the test specimen shall be ≈ 50 mm. The specimen preparation, types of notch profiles and methods of fracture shall be in accordance with EN 1320.

When transverse bend testing is used, one root bend test specimen and one face bend test specimen shall be tested in accordance with EN 910. The diameter of the former or the inner roller shall be $4t$ and the bending angle 180° unless the low ductility of the parent metal or filler metal imposes other limitations.

For plate thickness ≥ 12 mm, the transverse bend tests can be substituted by two side bend tests in accordance with EN 910.

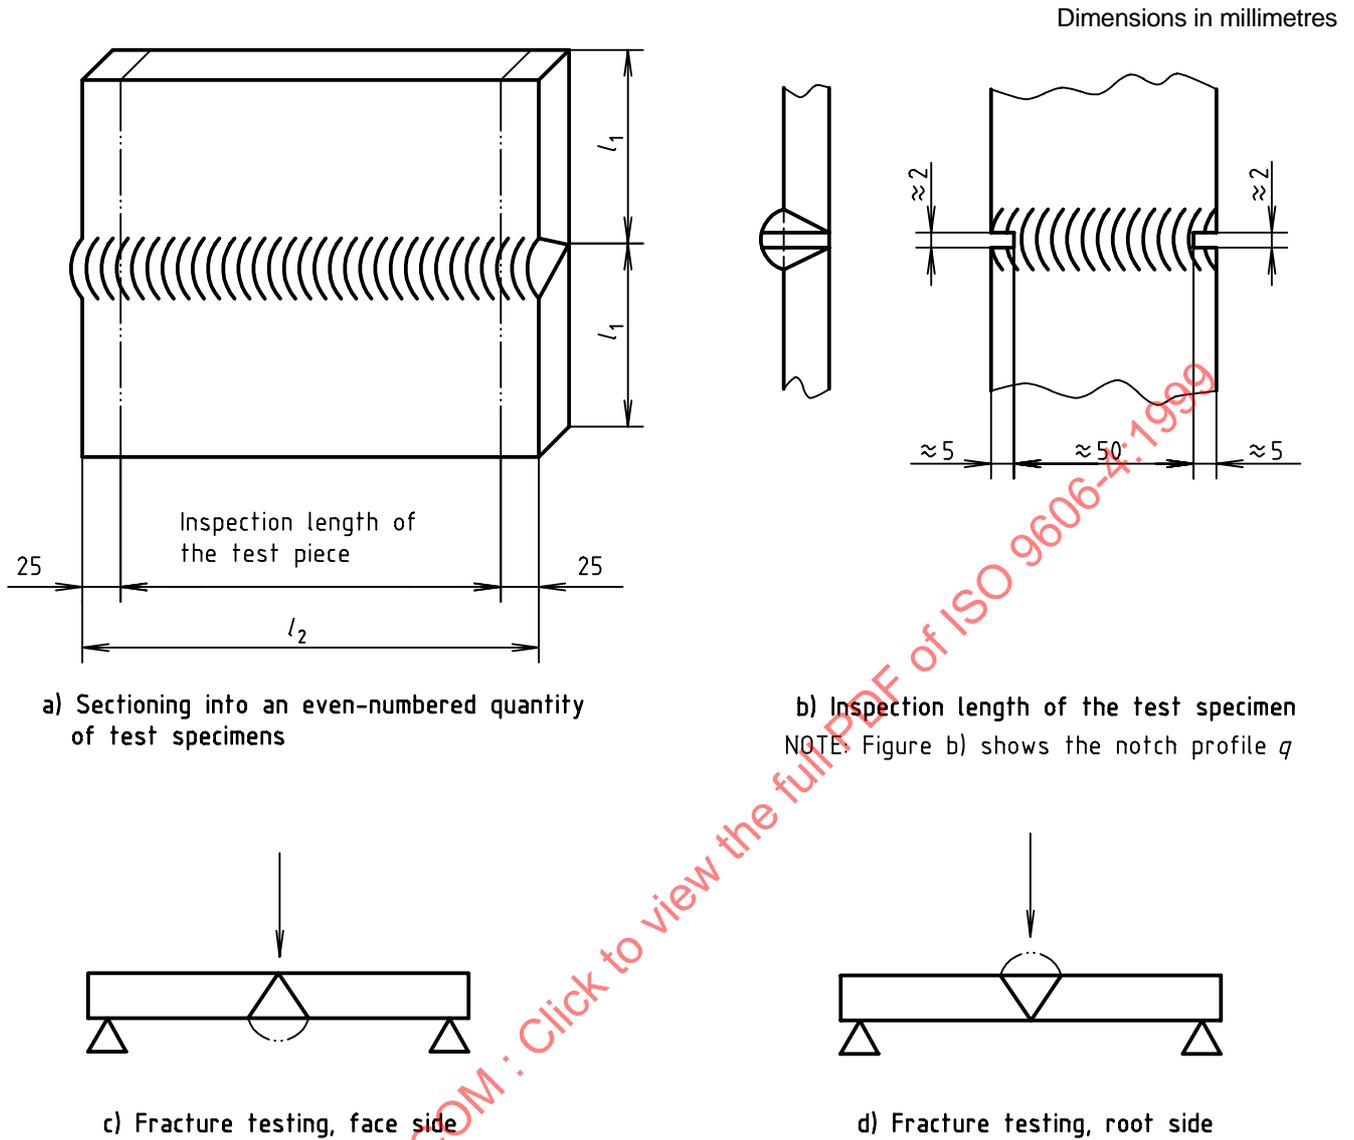


Figure 5: Preparation and fracture testing of test specimens for a butt weld in plate

7.5.3 Fillet weld on plate

For fracture tests according to EN 1320 the test piece can be cut, if necessary, into several test specimens (see figure 6a). Each test specimen shall be positioned for breaking as shown in figure 6b, and examined after fracture.

When macroscopic examination is used, at least four test specimens shall be taken equally spaced in the inspection length. Macroscopic tests shall be carried out in accordance with EN 1321.

Dimensions in millimetres

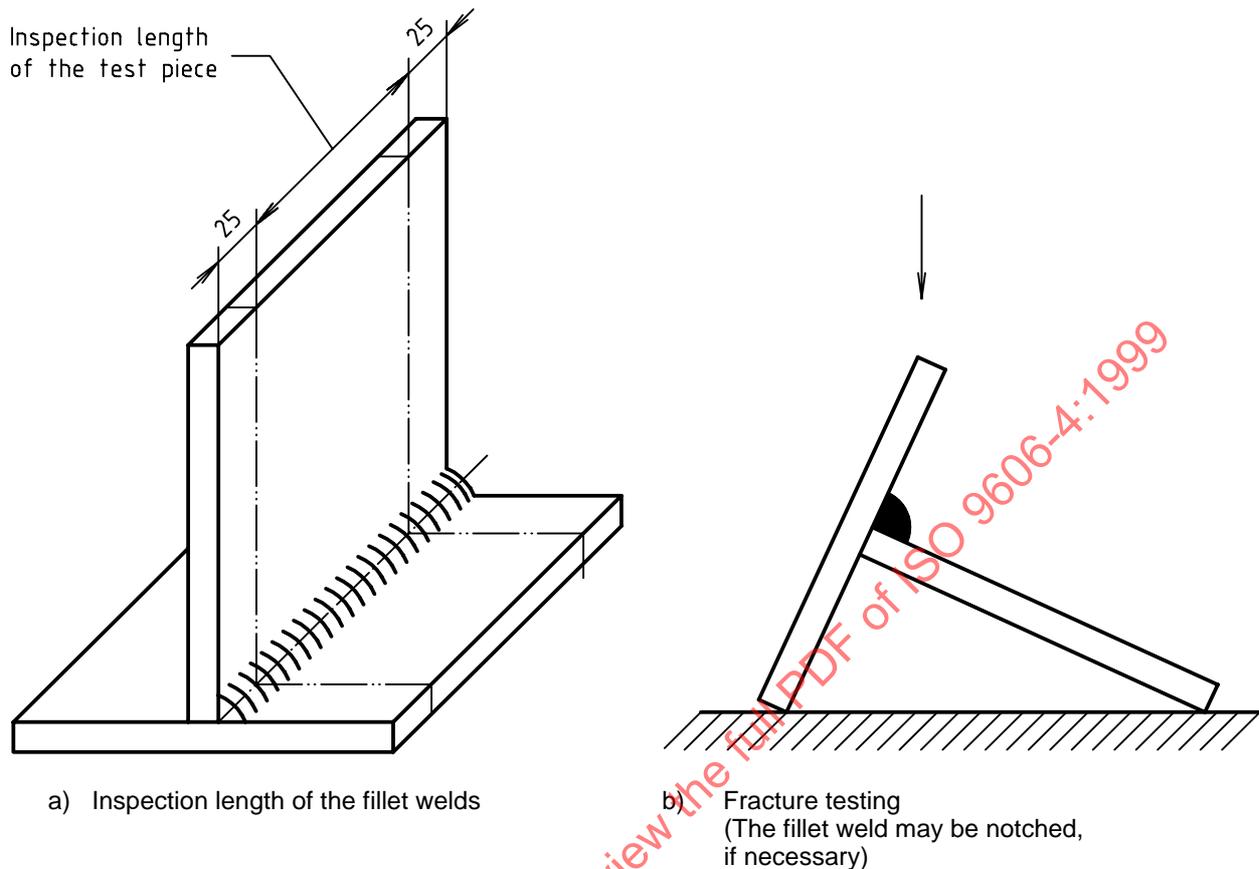


Figure 6: Preparation and fracture testing of test specimens for a fillet weld on plate

7.5.4 Butt weld in pipe

A minimum weld length of 150 mm is required for testing of pipes. If the circumference is less than 150 mm, additional weld test pieces will be required.

When radiographic testing is used, the inspection length of the weld (see figure 7 a and 7 b) in the test piece shall be radiographed in the as-welded condition in accordance with EN 1435 using class B technique.


When fracture testing is used, it shall be carried out in accordance with EN 1320. The inspection length of the fracture test specimen shall be ≈ 40 mm. Test specimen preparation, types of notch profiles and methods of fracture shall be in accordance with EN 1320.

When transverse bend testing is used, it shall be carried out in accordance with EN 910. The diameter of the former or the inner roller shall be $4t$, and the bending angle shall be 180° unless the low ductility of the parent metal or filler metal imposes other limitations.

The number of fracture or transverse bend test specimens depends on the welding position. For welding position PA or PC, one root and one face bend test specimen shall be tested (see figure 7 a). For all other welding positions, two root and two face bend test specimens shall be tested (see figure 7 b).

For wall thickness ≥ 12 mm, the transverse bend tests can be substituted by side bend tests in accordance with EN 910.


Dimensions in millimetres

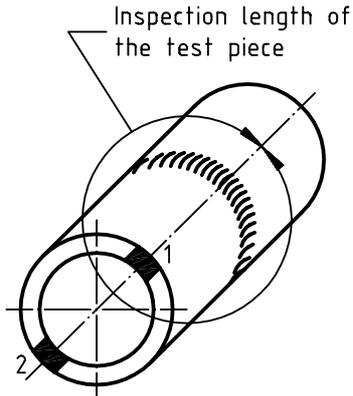

Position 1:
For one root fracture or one root transverse bend or one side bend test specimen

Position 2:
For one face fracture or one root face transverse bend or one side bend test specimen


a) Sectioning into at least two test specimens

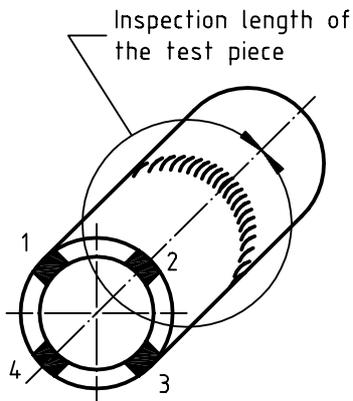

Position 1 + 3:
Each position one root fracture or one root transverse bend or one side bend test specimen


Position 2 + 4:
Each position one face fracture or one face transverse bend or one side bend test specimen

b) Sectioning into at least four test specimens

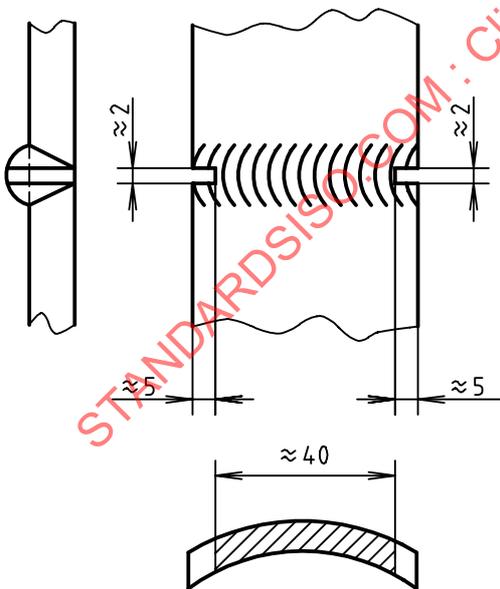


c) Inspection length of the test specimen

NOTE Figure c) shows the notch profile *q*

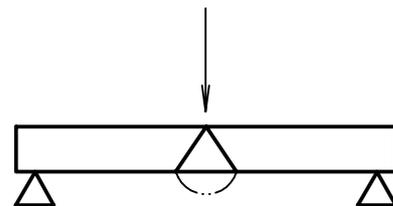

d) Fracture testing, face side

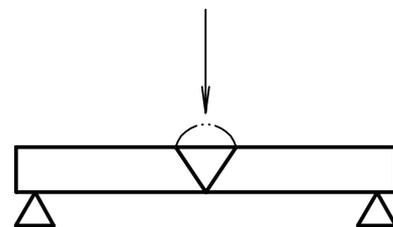

e) Fracture testing, root side

Figure 7: Preparation and fracture testing of test specimens for a butt weld in pipe

7.5.5 Fillet weld on pipe

For fracture tests the test piece shall be cut into four or more test specimens and fractured (figure 8).

When macroscopic examination in accordance with EN 1321 is used, at least four test specimens shall be taken equally spaced around the pipe.

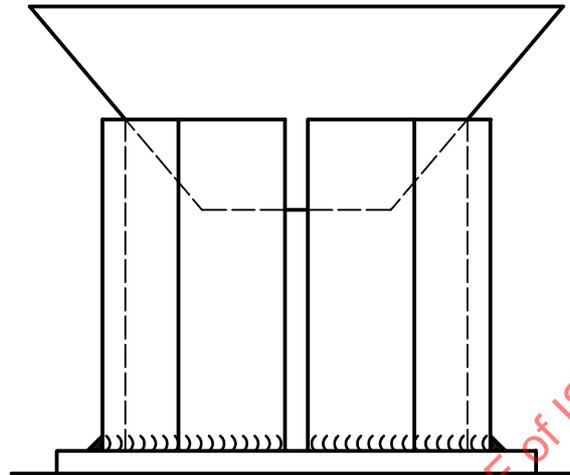


Figure 8: Preparation and fracture testing of test specimens for a fillet weld on pipe

8 Acceptance requirements for test pieces

Test pieces shall be evaluated according to the acceptance requirements specified for relevant types of imperfections. A full explanation of these imperfections is given in EN 26520. The acceptance requirements for imperfections found by test methods according to this standard shall, unless otherwise specified, be assessed following EN 25817. A welder is approved if the imperfections in the test piece are within the specified limits of level B in EN 25817, except for imperfection types as follows: excess weld metal, excessive convexity, excessive throat thickness and excessive penetration, for which level C in EN 25817 applies.

If the imperfections in the welder's test piece exceed the permitted maximum specified, then the welder shall not be approved.

Reference should also be made to the corresponding acceptance criteria for non-destructive examination. Specified procedures shall be used for all destructive and non-destructive examinations.

9 Re-tests

If any test piece fails to comply with the requirements of this standard, the welder shall produce a new test piece.

If it is established that failure is attributed to the welder's lack of skill, the welder shall be regarded as incapable of complying with the requirements of this standard without further training before re-testing.

If it is established that failure is due to metallurgical or other extraneous causes and cannot be directly attributed to the welder's lack of skill, an additional test is required in order to assess the quality and integrity of the new test material and/or new test conditions.

10 Period of validity

10.1 Initial approval

The validity of the welder's approval begins from the date the required tests are satisfactorily completed. This date can be different to the date of issue marked on the certificate.

A welders approval is valid for a period of two years provided that the relevant certificate is confirmed at six months intervals by the welding coordinator or the employer, and that all the following conditions are fulfilled:

- a) The welder shall be engaged with reasonable continuity on welding work within the current range of approval. An interruption for a period no longer than six months is permitted;
- b) There is no specific reason to question the welder's skill and knowledge.

If any of these conditions are not fulfilled, the approval shall be revoked.

10.2 Prolongation

The validity of the approval on the certificate may be prolonged for further periods of two years, within the original range of approval, provided each of the following conditions according to 10.1 are fulfilled:

- a) the production welds made by the welder are of the required quality;
- b) records of tests, e.g. either half yearly documentation about radiographic testing or test reports about fracture test shall be maintained on file with the welder's approval certificate.

The examiner or examining body shall verify compliance with the above conditions and sign the prolongation of the welder's approval test certificate.

11 Certificate

It shall be verified that the welder has successfully passed the performance approval test. All relevant test conditions shall be recorded on the certificate. If the welder fails any of the prescribed tests, no certificate is issued.

The certificate shall be issued under the sole responsibility of the examiner or test body and shall contain all the information detailed in Annex B of EN 287-1 : 1992. The format of this Annex B of EN 287-1 : 1992 is recommended to be used as the welder's approval test certificate. If any other form of welder's approval test certificate is used, it shall contain the information required in Annex B of EN 287-1 : 1992.

The manufacturer's pWPS or WPS as shown in Annex A of EN 288-2 : 1992 shall give information about materials, welding positions, welding processes, range of approval etc., in accordance with this standard.

The welder's approval test certificate shall be issued at least in one of the official CEN languages (English, French, German).

The practical test and the examination of job knowledge (see Annex A) shall be designated by "Accepted" or "Not tested".

Each change of the essential variables for the approval testing beyond the permitted ranges requires a new test and a new approval certificate.12 Designation

12 Designation

The designation of a welder approval shall comprise the following items in the order given (the system is arranged so that it can be used for computerization):

- a) the number of this standard;
- b) the essential variables:
 - 1) welding processes: see 5.2 and EN 24063;
 - 2) semi-finished product: plate (P), pipe (T), see 5.3;
 - 3) joint type: butt weld (BW), fillet weld (FW), see 5.3;
 - 4) material group: see 5.4;
 - 5) consumables: see 5.5;
 - 6) dimension of test piece: thickness (t) and pipe diameter (D), see 5.6;
 - 7) welding positions: see 5.8 and EN ISO 6947;
 - 8) details of the joint type: see 6.3 and table 3, for abbreviations see 4.4.