

# INTERNATIONAL STANDARD

**ISO**  
**9649**

First edition  
1990-02-01

---

---

## **Metallic materials — Wire — Reverse torsion test**

*Matériaux métalliques — Fils — Essai de torsion alternée*



Reference number  
ISO 9649:1990(E)

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council. They are approved in accordance with ISO procedures requiring at least 75 % approval by the member bodies voting.

International Standard ISO 9649 was prepared by Technical Committee ISO/TC 164, *Mechanical testing of metals*.

STANDARDSISO.COM : Click to view the full PDF of ISO 9649:1990

© ISO 1990

All rights reserved. No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization  
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

# Metallic materials — Wire — Reverse torsion test

## 1 Scope

This International Standard specifies a method for determining the ability of metallic wire of diameter 0,3 mm to 10,0 mm inclusive to undergo plastic deformation during reverse torsion. This test is used for detecting surface and internal defects in wires.

## 2 Normative reference

The following standard contains provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the edition indicated was valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent edition of the standard indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 7800:1984, *Metallic materials — Wire — Simple torsion test*.

## 3 Symbols and designations

The symbols used in the reverse torsion testing of wires are shown in figure 1 and defined in table 1.

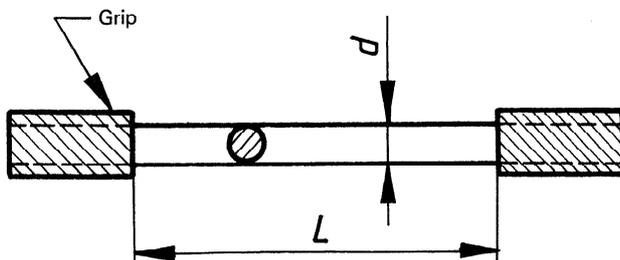


Figure 1

Table 1

Symbol	Designation	Unit
$d$	Diameter of a round wire	mm
$L$	Free length between grips	mm
$N_t$	Number of turns in one direction	—

## 4 Principle

A test piece of wire is twisted a specified number of times through 360° about its own axis in one direction and the same number of times through 360° in the opposite direction.

## 5 Testing machine

**5.1** The grips shall be of sufficient hardness to provide rigidity and/or resistance to abrasion. The grips shall be arranged in the testing machine in such a way that, during testing, they remain on the same axis and do not apply any bending force to the test piece.

**5.2** The machine shall be constructed so that a change of length between grips, caused by the test piece during the test, is not prevented.

**5.3** One of the grips shall be capable of being rotated about the axis of the test piece while the other shall not be subject to any angular deflection, except for such deflection as may be necessary to measure the torque.

**5.4** The distance between grips shall be adjustable to accommodate test pieces of different lengths.

**5.5** The machine shall be constructed so that an appropriate tensile stress (see 7.2) can be applied to the test piece.