



**International  
Standard**

**ISO/ASTM 52909**

**Additive manufacturing of  
metals — Finished part properties  
— Orientation and location  
dependence of mechanical  
properties for metal parts**

*Fabrication additive de métaux — Propriétés des pièces finies  
— Dépendance de l'orientation et de l'emplacement sur les  
propriétés mécaniques pour les pièces métalliques*

**Second edition  
2024-02**

STANDARDSISO.COM : Click to view the full PDF of ISO/ASTM 52909:2024

STANDARDSISO.COM : Click to view the full PDF of ISO/ASTM 52909:2024



**COPYRIGHT PROTECTED DOCUMENT**

© ISO/ASTM International 2024

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester. In the United States, such requests should be sent to ASTM International.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11

Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

ASTM International  
100 Barr Harbor Drive, PO Box C700  
West Conshohocken, PA 19428-2959, USA  
Phone: +610 832 9634  
Fax: +610 832 9635  
Email: [khooper@astm.org](mailto:khooper@astm.org)  
Website: [www.astm.org](http://www.astm.org)

**Contents**

Page

<b>Foreword</b> .....	<b>iv</b>
<b>Introduction</b> .....	<b>v</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>2</b>
3.1 Definition.....	2
3.2 Abbreviations.....	2
3.3 Acronyms.....	2
<b>4 Summary of document</b> .....	<b>3</b>
<b>5 Significance and use</b> .....	<b>3</b>
<b>6 Procedure</b> .....	<b>4</b>
<b>7 Report</b> .....	<b>4</b>
7.1 General.....	4
7.2 Additional requirements.....	4
<b>Annex A (informative) Example raster (scan) strategies for reporting</b> .....	<b>5</b>
<b>Bibliography</b> .....	<b>12</b>

STANDARDSISO.COM : Click to view the full PDF of ISO/ASTM 52909:2024

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at [www.iso.org/patents](http://www.iso.org/patents). ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

The document was prepared by Technical Committee ISO/TC 261, *Additive manufacturing*, in cooperation with ASTM Committee F42, *Additive Manufacturing Technologies*, on the basis of a partnership agreement between ISO and ASTM International with the aim to create a common set of ISO/ASTM standards on Additive Manufacturing, and in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 438, *Additive manufacturing*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

This second edition cancels and replaces the first edition (ISO/ASTM 52909:2022), of which it constitutes a minor revision.

The main changes are as follows:

- The third element of the title of the standard has been changed to "Orientation and location dependence of mechanical properties for metal parts";
- The title for [Figure A.6 b](#)) has been corrected;
- Reference [\[12\]](#) in bibliography has been corrected.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

## Introduction

AM produced metallic parts are being intensively developed and used more widely today with an expected faster growth in near future. This document aims to support customers' needs to address specifics of the AM deposited parts – location and orientation dependent local properties and their variations over the part or deposition chamber.

This document provides a list of accurate terminologies and existing standards dedicated to mechanical testing of metallic materials, guidance on designation of coordinate systems and their application to AM specimens/parts designation, and recommendations on possibilities for local properties measurement.

STANDARDSISO.COM : Click to view the full PDF of ISO/ASTM 52909:2024

[STANDARDSISO.COM](https://standardsiso.com) : Click to view the full PDF of ISO/ASTM 52909:2024

# Additive manufacturing of metals — Finished part properties — Orientation and location dependence of mechanical properties for metal parts

## 1 Scope

This document covers supplementary guidelines for evaluation of mechanical properties including static/quasi-static and dynamic testing of metals made by additive manufacturing (AM) to provide guidance toward reporting when results from testing of as-built specimen or specimen cut out from AM parts made by this technique or both.

This document is provided to leverage already existing standards. Guidelines are provided for mechanical properties measurements and reporting for additively manufactured metallic specimen as well as those cut out from AM parts.

This document does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health and environmental practices and determine the applicability of regulatory limitations prior to use.

This document expands upon the nomenclature of ISO/ASTM 52900 and principles of ISO 17295 and extends them specifically to metal additive manufacturing. The application of this document is primarily intended to provide guidance on orientation designations in cases where meaningful orientation/direction for AM cannot be obtained from available test methods.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1099, *Metallic materials — Fatigue testing — Axial force-controlled method*

ISO 4506, *Hardmetals — Compression test*

ISO 6892-1, *Metallic materials — Tensile testing — Part 1: Method of test at room temperature*

ISO 12106, *Metallic materials — Fatigue testing — Axial-strain-controlled method*

ISO 12108, *Metallic materials — Fatigue testing — Fatigue crack growth method*

ISO 12135, *Metallic materials — Unified method of test for the determination of quasistatic fracture toughness*

ISO 17295, *Additive manufacturing — General principles — Part positioning, coordinates and orientations*

ISO/ASTM 52900, *Additive manufacturing — General principles — Fundamentals and vocabulary*

ASTM E8/E8M, *Standard test methods for tension testing of metallic materials*

ASTM E9, *Standard test methods of compression testing of metallic materials at room temperature*

ASTM E399, *Standard test method for linear-elastic plane-strain fracture toughness  $K_{Ic}$  of metallic materials*

ASTM E466, *Standard practice for conducting force-controlled constant amplitude axial fatigue tests of metallic materials*

# ISO/ASTM 52909:2024(en)

ASTM E561, *Standard test method for k-r curve determination*

ASTM E606/E606M, *Standard test method for strain-controlled fatigue testing*

ASTM E647, *Standard test method for measurement of fatigue crack growth rates*

ASTM E1820, *Standard test method for measurement of fracture toughness*

ASTM E1921, *Test Method for Determination of Reference Temperature,  $T_0$ , for Ferritic Steels in the Transition Range*

ASTM E2472, *Standard Test Method For Determination Of Resistance To Stable Crack Extension Under Low-Constraint Conditions*

ASTM E2899, *Standard test method for measurement of initiation toughness in surface cracks under tension and bending*

ASTM F2971, *Practice for Reporting Data for Test Specimens Prepared by Additive Manufacturing*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 17295 and ISO/ASTM 52900 and apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

### 3.1 Definition

#### 3.1.1 part location

location of the part/sample/specimen within the build volume

Note 1 to entry: The part location is normally specified by the  $x$ ,  $y$ ,  $z$  coordinates for the position of the geometric centre of the part's bounding box with respect to the build volume origin.

### 3.2 Abbreviations

The abbreviations used in [Figure A.4](#), are listed in [Table 1](#).

**Table 1 — Abbreviations**

Abbreviation	Signification	Comment
S	Start	Any base of the specimen or part that provides a surface upon which deposition starts (see <a href="#">Annex A</a> ).
E	End	Any area of a specimen or part that provides a surface upon which the specimen or part deposition ends (see <a href="#">Annex A</a> ).
M	Middle	Mid-plane of a specimen or part between start and end (see <a href="#">Annex A</a> ).
B	Both	Crack growth captures both start and end of build (see <a href="#">Annex A</a> ).
RD	Scan direction	This may or may not be the same throughout the build (see <a href="#">Annex A</a> ).

### 3.3 Acronyms

The acronyms used in this document for illustrating crack growth directions with respect to the build direction are listed in [Table 2](#) and illustrated in [Figure A.4](#).

Table 2 — Acronyms

Acronym	Signification
XY, YX, XZ, ZX, YZ, ZY	The first letter represents the direction normal to the crack plane and the second letter represents the expected direction of crack extension.
XYB	Indicates that crack growth captures both the start and end of the build in XY direction.
XZE	Indicates that the crack growth occurs from the end to the start of build in the XZ direction.
XZS	Indicates that the crack growth occurs from the start to the end of build in the XZ direction.
YXB	Indicates that crack growth captures both the start and end of the build in YX direction.
YZE	Indicates that the crack growth occurs from the end to the start of build in the YZ direction.
YZS	Indicates that the crack growth occurs from the start to the end of build in the YZ direction.
ZXM (or ZX1/2)	Indicates that crack growth occurs at the middle plane in ZX direction.
ZYM	Indicates that crack growth occurs at the middle plane in ZY direction.

In situations in which a test specimen is created from other locations with respect to the start of the build (for example  $\frac{1}{4}$ ,  $\frac{3}{4}$ , etc. distance from the start of the build) in the ZX direction, the notation used should indicate this location. For example, ZX1/4 indicates that testing was conducted in the ZX direction at a location one quarter of the way from the start of the build.

In situations where a test specimen (i.e. either a standard size or miniaturized specimen) is cut out from a portion of a built part (e.g. from an actual part) this should be noted. The terminology provided above should still be used to indicate the location of the cut-out sample with respect to the original part geometry.

## 4 Summary of document

**4.1** The purpose of this document is to provide guidelines for test methods referenced in [Clause 2](#) and also use some of the terminologies defined in ISO/ASTM 52900 with metal additive manufacturing test specimens. Test specimens may be built directly to net-shape, or near net-shape, or cut out from a part.

**4.2** Standard geometries can be used based on the reference standards indicated in [Clause 2](#), however, direct testing of a part is a highly recommended practice for metal AM (See [A.6](#)).

**4.3** In order to investigate and document orientation and location-specific mechanical properties, cut small-scale specimen from the relevant locations of the parts should be achieved. This document describes some principles to apply for the testing of various properties.

## 5 Significance and use

**5.1** Although evaluation of mechanical properties of many additively manufactured materials can be conducted using the guidelines developed for conventional materials within existing testing standards, the coordinate systems and nomenclature specific to conventional materials testing (for example in ASTM E399, ASTM E647, ISO 12108 and ISO 12135) are not sufficient to be applicable across the full spectrum of specimens/parts produced by metal AM without causing confusion. This document is based on the nomenclature and principles of ISO 17295 and extends them specifically to metal AM. The application of this document is primarily intended to provide guidance on orientation designations in cases in which meaningful orientation/direction for AM cannot be obtained from available test methods.

**5.2** It shall be understood that the interpretations and guidelines in this document do not alter the validity requirements of test methods nor can this document be used to change the designation of “invalid” data (that is according to test methods) to a “valid” condition. This document is primarily concerned with cases in which it is not possible or practical to obtain meaningful data based on orientation/direction designations that are currently covered in standards developed for conventionally processed materials.

## 6 Procedure

The test procedure, analysis of test record, and calculations shall be made in accordance with [Table 3](#).

**Table 3 — Standards to be applied according to test method**

Test method	Referenced standards
tensile	ASTM E8/E8M, ISO 6892-1
compression	ASTM E9, ISO 4506
force controlled fatigue	ASTM E466, ISO 1099
strain-controlled fatigue	ASTM E606/606M, ISO 12106
linear elastic fracture toughness	ASTM E399
$K_R$ curve determination	ASTM E561
non-linear fracture toughness	ASTM E1820, ASTM E1921, ASTM E2472, ASTM E2899, ISO 12135
fatigue crack growth	ASTM E647, ISO 12108

## 7 Report

### 7.1 General

The report shall include all the information required by test methods along with the location and orientation of the part or specimen, following the guidance provided in this document.

### 7.2 Additional requirements


Since the scan strategy can have a significant effect on the mechanical properties of the parts, it is highly recommended that a specification of the scan strategy is included in the test report for metallic materials. There are a number of different strategies that can be used to manufacture a part. Some of the common scan strategies are included in [A.1](#). However, different types of scan strategies can be used depending on the type of AM machine used. Besides the scanning strategy, other process parameters that can have significant influence on the mechanical properties in the parts include, but are not limited to: preheating of the base plate, scanning speed, spot size, scan path overlaps and others. Because of variation in scan strategies typically used in AM, it is not possible to relate the orientation nomenclatures to the scan strategy directly. Conventional directions typically used for deformation processing have been used presently to define the axes and terminologies. Processing/post-processing parameters shall be reported in accordance with ASTM F2971.

**Annex A**  
(informative)

**Example raster (scan) strategies for reporting**

**A.1 Example of strategies for reporting**

All units are expressed in SI system. [Figure A.1](#) gives example of strategies for reporting.

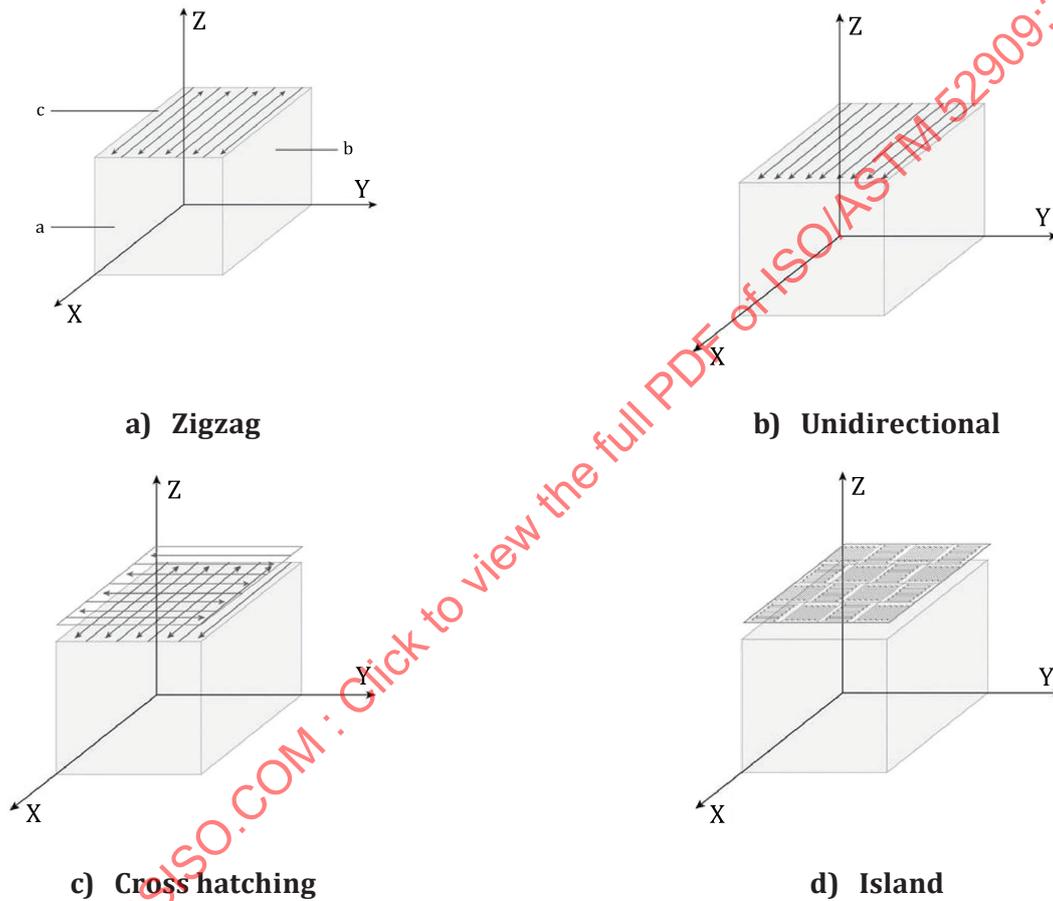

**Key**


- X scanning direction
- Y Y axis
- Z build direction
- a Front.
- b Side.
- c Top.

**Figure A.1 — Example raster (scan) strategies for reporting**

## A.2 Rectangular specimens orientations designation for tensile, low- and high-cycle fatigue testing

The orientation of the specimen in the build chamber shall be identified by orthogonal orientation notation as specified in ISO 17295. This nomenclature can be used for tests on rectangular specimens in which there is no starter crack/notch requirement. These test methods are not limited to ASTM E8/E8M and ISO 6892-1 (tensile), ASTM E9 and ISO 4506 (compression), ASTM E466 and ISO 1099 (force-controlled fatigue), and ASTM E606/606M and ISO 12106 (strain-controlled fatigue). For test methods that require a starter crack/notch, see [A.4](#).

[Figure A.2](#) illustrates possible orientation designation for tensile, low and high-cycle fatigue testing for rectangular specimens.

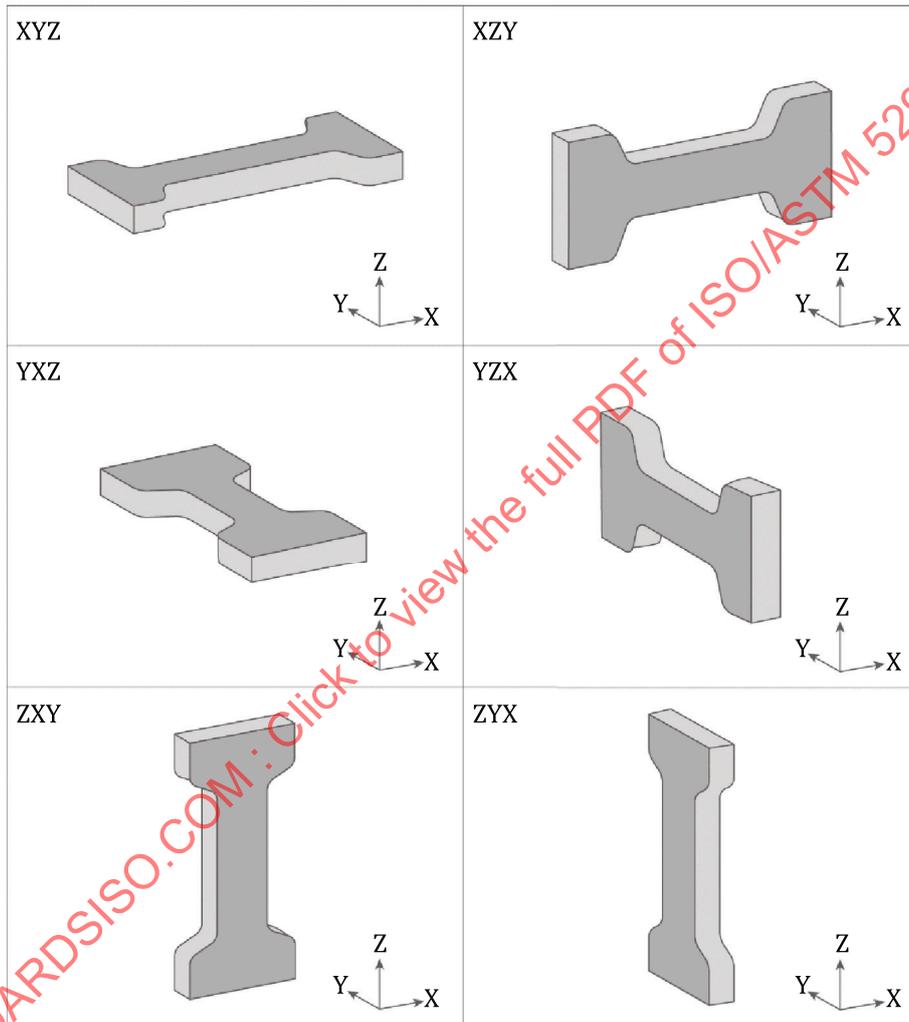



**Figure A.2 — Specimen orientations illustrating example orientation designation for tensile, low and high-cycle fatigue testing for rectangular specimens**

**NOTE** Orientations shown in [Figure A.2](#) are based on ISO 17295. For example, for the XYZ specimen, the longest dimension is parallel to the X axis, the second longest dimension is parallel to the Y axis and the shortest dimension is parallel to the Z axis. The Z axis is always the build direction.



## A.3 Round specimen orientations for tensile, low-, and high-cycle fatigue testing

[Figure A.3](#) illustrates possible orientation designation for tensile, low and high-cycle fatigue testing for round specimens<sup>[1][2][3]</sup>.


X

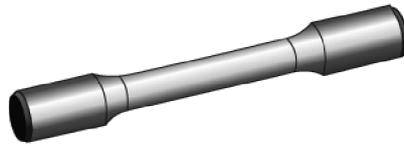

Y

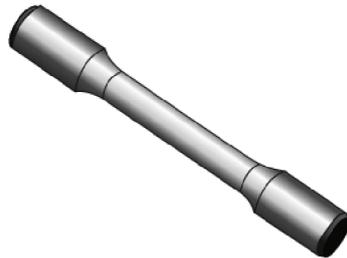

Z




**Figure A.3 — Specimen orientations illustrating possible orientation designation for tensile, low- and high-cycle fatigue testing for round specimens**

The orientation of the specimen in the build chamber shall be identified by abbreviated orthogonal orientation notation, as specified in ISO 17295, where the orientation of the specimen can unambiguously be described by listing only the axis to which the longest dimension runs parallel. These nomenclatures can be used for tests conducted on circular specimen in which there is no starter crack/notch requirement. These test methods are not limited to ASTM E8/E8M and ISO 6892-1 (tensile), ASTM E9 and ISO 4506 (compression) ASTM E466 and ISO 1099 (force-controlled fatigue), and ASTM E606/606M and ISO 12106 (strain-controlled fatigue). For test methods that require a starter crack/notch, see [A.4](#).

NOTE Orientations shown in [Figure A.3](#) are based upon principles of ISO 17295. For example, an X specimen designation indicates that the longest dimension is parallel to the X axis and the other two axes have symmetry. The Z axis is always in the build direction.

## A.4 Specimen orientations illustrating crack growth directions with respect to the build direction for fracture toughness and fatigue crack growth testing

Figure A.4 illustrates specimen orientations and crack growth directions with respect to the build direction for fracture toughness and fatigue crack growth testing<sup>[1][2][3][4]</sup>.

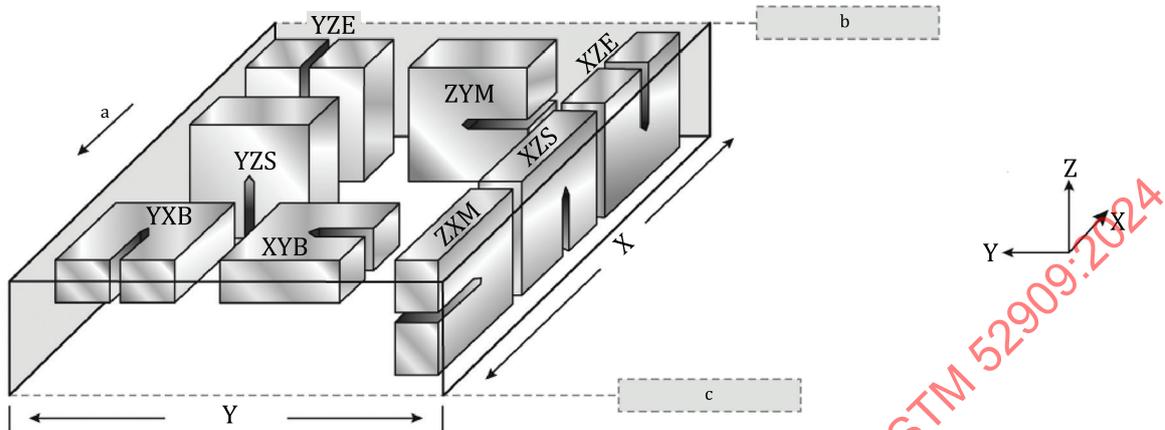

### Key

- X X axis
- Y Y axis
- Z build direction
- E end
- M middle
- S start
- B both
- a RD, final raster direction.
- b End of the build.
- c Start of the build.

**Figure A.4 — Specimen orientations illustrating crack growth directions with respect to the build direction for fracture toughness and fatigue crack growth testing**

These nomenclatures can only be used for test methods that require a starter crack/notch in the test specimens (e.g. bend, compact tension, etc.). These test methods are not limited to ASTM E399/E1820 and ISO 12135 (fracture toughness), ASTM E647 and ISO 12108 (fatigue crack growth).

The raster strategy/direction should be reported along with the test report, although there is no direct linkage between the nomenclatures here with raster strategies.

## A.5 Examples of specimen extraction from standard geometries as well as parts to measure location- and orientation-dependent mechanical properties directly

### A.5.1 General


Figure A.5 gives examples of specimen extraction from standard geometries as well as parts to directly measure location and orientation dependent mechanical properties<sup>[5][6][7][8]</sup>.

In the case of specimens cut out from complex geometries, a computer-aided design (CAD) figure of the part and a set of coordinate axes should be constructed based on the ISO 17295 coordinate systems to record precisely the location and orientation of all the specimens to be extracted. Examples have been provided here as a guidance. For the purpose of this guidance, the build direction is always considered as being parallel to the Z-axis.

## A.5.2 Cut-out sample

The angle of the cut-out sample with respect to the build direction should also be reported.

Excised specimen may also be used to document location- and orientation-specific microstructure or defect structure. Various metallographic and non-destructive testing (NDT) techniques may be used on the parts as well as the cut-out specimen following the same nomenclature outlined presently.

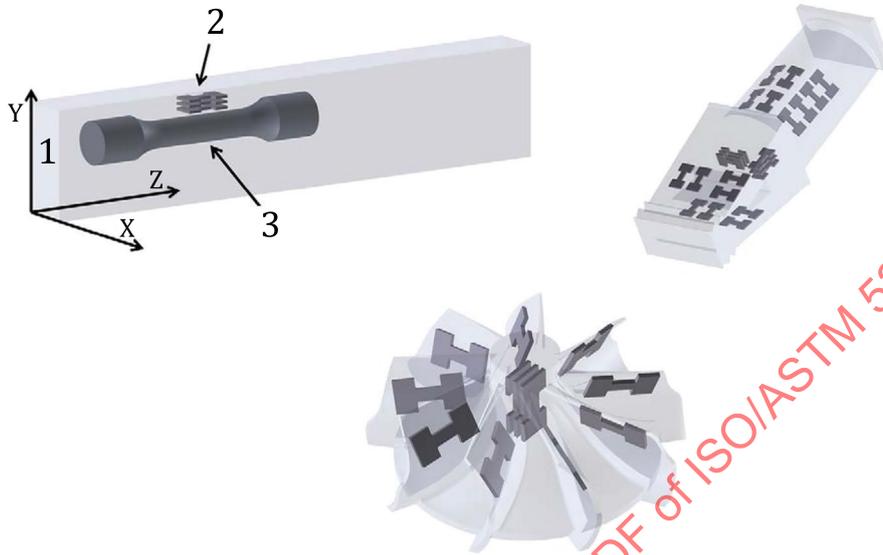

### Key

- 1 base
- 2 cut-out samples
- 3 standard geometries

**Figure A.5 — Examples of specimen extraction from standard geometries and parts to directly measure location- and orientation-dependent mechanical properties**

## A.6 Mini-specimens testing approach

### A.6.1 General

In the case of additively manufactured parts, it is often difficult to assess the mechanical properties with the use of standard-sized specimens due to the limited amount of material available. Miniaturized specimens shall be used in cases in which local property measurements are desired in smaller parts with complex shapes. This is important as separate deposition of the “reference” standard-sized specimens can yield misleading and different results from those obtained directly from the AM part because of AM process specifics. This requires preparation of specimens of similar size to the part critical dimensions, with similar deposition orientation, for subsequent material properties assessment.

AM-produced parts can exhibit anisotropy and variable properties along the build height in addition to varying properties with different wall thickness<sup>[9][10][11][12]</sup>. Characterization of as-built surfaces in addition to, or instead of, conditioned surfaces (e.g. polished, burnished, etc.) should also be considered depending on intended application. In order to provide representative material properties, the samples should be subjected to post-processing that is identical or equivalent to that of the intended final product, before any testing of the material properties is performed.

Even if all of the recommendations above are followed, the use of miniaturized specimens shall be highlighted when test results are reported to clearly indicate that non-standard specimens were used.

NOTE This document does not provide recommendations for miniaturized tension testing, resulting in a wide range of sample geometries currently being used. Recent success was reported using the flat sample geometries shown in Figure A.6, where elongation results most consistent with round specimens were obtained using a thickness width ratio  $\geq 0,5$  [13][14].

If elongation is not a critical property measurement, or the space is very limited, specimens with shorter gauge lengths (see Figure A.6 b) have been used to yield reliable strength properties. From a practical point of view, the minimum recommended gauge length is 3 mm.

The thickness of the specimens should be of about 10 times the grain size to represent “bulk” material behaviour [13]. Based on recent experience summarized in References [13], [14] and [15], a minimum thickness of 0,5 mm is recommended for machined specimens (see Figure A.6). Based on recent experience for near net shape specimens [9][16], Figure A.7 provides recommended minimum specimen dimensions, although using specimens with larger volume is highly recommended if possible, given the constraints of the build volume. In all cases, the testing and evaluation procedures should comply with ASTM E8/E8M. Strain measurement shall be conducted with measuring systems of appropriate accuracy (video extensometer, laser extensometers, digital image correlation systems, or mechanical extensometer).

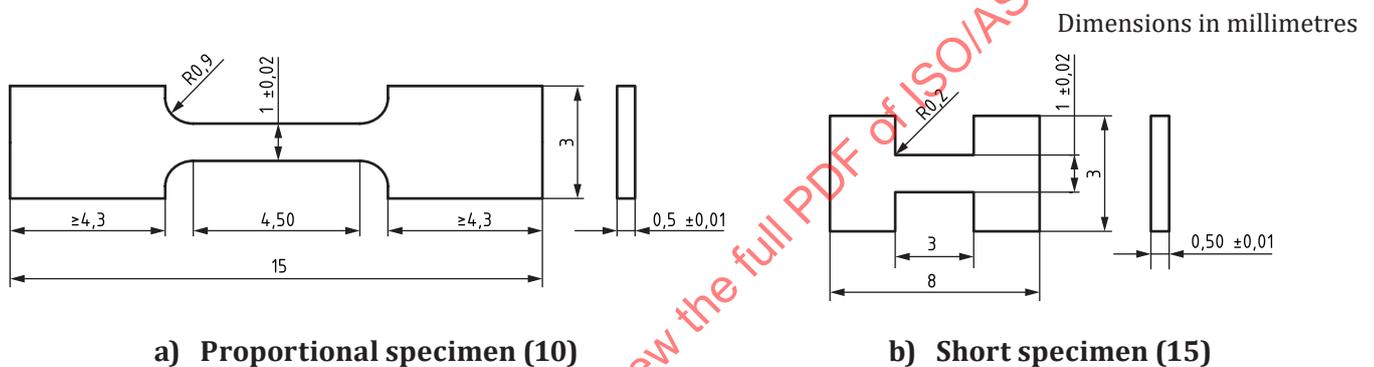


Figure A.6 — Example flat mini tensile specimen geometry

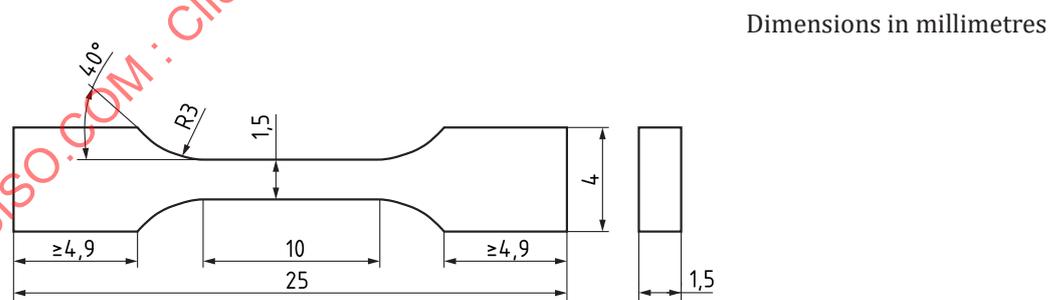


Figure A.7 — Example of as-built shape specimen geometry (9)

Miniaturized tensile specimens can also be used for quality control of the AM process, as small specimens (see e.g. Figure A.7) can be built at different locations within each batch. Their small size would not reduce the available “commercial” build space within the chamber and not significantly increase build costs.

## A.6.2 Fracture toughness tests

In the case of fracture toughness tests, small-sized specimen geometries based on Charpy-sized specimens in ISO 26843 or ASTM E2248 are recommended. In case of smaller available material volumes, ASTM E1921 implements 0,16 T-CT specimens of dimensions 10 mm × 10 mm × 4 mm [17][18]. Fatigue pre-cracked mini-Charpy specimens have also been used for fracture toughness assessments in appropriate cases [19].