

---

---

**Welding consumables — Hardfacing  
classification — Microstructures**

*Produits consommables pour le soudage — Classification des  
rechargements durs — Microstructures*

STANDARDSISO.COM : Click to view the full PDF of ISO/TR 13393:2009



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO/TR 13393:2009



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2009

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

Foreword.....	v
Introduction .....	vi
<b>1 Scope .....</b>	<b>1</b>
<b>2 Proposed classification/designation system.....</b>	<b>1</b>
<b>3 Summary of the designators for iron-base microstructures .....</b>	<b>1</b>
<b>4 Identification of iron-base alloy microstructural groups in a carbon/alloying elements diagram .....</b>	<b>2</b>
<b>5 Description of the iron-base alloys belonging to the different microstructure groups .....</b>	<b>4</b>
5.1 General.....	4
5.2 Fe-FS Group (ferrite with second phase) .....	5
5.3 Fe-M1 Group (low-alloy martensite).....	7
5.4 Fe-M2 Group (tool-steel martensite) .....	8
5.5 Fe-M3 Group (stainless-steel martensite) .....	10
5.6 Fe-M4 Group (maraging steel).....	11
5.7 Fe-MA Group (martensite and austenite) .....	12
5.8 Fe-MK Group (martensite with alloy carbides) .....	13
5.9 Fe-MEK Group (martensite with eutectic) .....	15
5.10 Fe-A Group (nominally austenitic stainless steel) .....	17
5.11 Fe-AF Group (ferritic-austenitic stainless steel) .....	18
5.12 Fe-AM Group (austenitic manganese steel).....	19
5.13 Fe-AMC Group (austenitic chromium-manganese steel) .....	20
5.14 Fe-AK Group (austenitic manganese steel containing alloy carbides).....	21
5.15 Fe-PAE Group (primary austenite with eutectic).....	22
5.16 Fe-NE Group (near eutectic).....	23
5.17 Fe-PKE Group (primary carbides with eutectic).....	24
5.18 Fe-KKA Group (primary carbides, alloy carbides and eutectic) .....	25
<b>6 Summary of the designators for non-ferrous hardfacing deposit types .....</b>	<b>26</b>
<b>7 Description of the alloys belonging to the different non-ferrous microstructure groups and microstructural illustrations.....</b>	<b>27</b>
7.1 Co-CS Group (cobalt solid-solution alloy) .....	27
7.2 Co-PC Group (primary cobalt solid-solution alloy with cobalt alloy/carbide eutectic) .....	28
7.3 Co-NE Group (near-eutectic mix of carbides and cobalt solid-solution alloy).....	30
7.4 Co-PKE Group (primary carbides with eutectic) .....	32
7.5 Co-LP Group (cobalt solid-solution alloy with Laves phase particles).....	33
7.6 Ni-NS Group (nickel alloy solid solution) .....	34
7.7 Ni-B Group (nickel borides) .....	35
7.8 Ni-CB Group (chromium borides in nickel alloy/boride eutectic).....	36
7.9 Ni-LP Group (nickel-base alloy solid solution with Laves-phase particles).....	37
7.10 Cu-BS Group (solid-solution bronzes) .....	38
7.11 Cu-BT Group (two-phase bronzes) .....	39
7.12 W-Fe Group (tungsten carbide in an iron matrix).....	41
7.13 W-Ni Group (tungsten carbide in a nickel-base alloy matrix) .....	42
<b>Annex A (informative) Types of wear and factors governing the severity of wear phenomena .....</b>	<b>43</b>
<b>Annex B (informative) General considerations on basic factors governing wear resistance.....</b>	<b>44</b>
<b>Annex C (informative) Abrasive-wear-resistance test methods .....</b>	<b>45</b>
<b>Annex D (informative) Practical guidance .....</b>	<b>48</b>

<b>Annex E (informative) Cross-references to national standards .....</b>	<b>51</b>
<b>Bibliography .....</b>	<b>53</b>

STANDARDSISO.COM : Click to view the full PDF of ISO/TR 13393:2009

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

In exceptional circumstances, when a technical committee has collected data of a different kind from that which is normally published as an International Standard ("state of the art", for example), it may decide by a simple majority vote of its participating members to publish a Technical Report. A Technical Report is entirely informative in nature and does not have to be reviewed until the data it provides are considered to be no longer valid or useful.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO/TR 13393 was prepared by the *International Institute of Welding*, Commission II, *Arc Welding and Filler Metals*, which has been approved as an international standardizing body in the field of welding in accordance with Council Resolution 42/1999.

Requests for official interpretations of any aspect of this International Standard should be directed to the ISO Central Secretariat, who will forward them to the IIW Secretariat for an official response.

## Introduction

Hardfacing is the deposition of a given type of alloy onto a substrate, in view of protecting this substrate against various types of degradation known under the name of wear. The science that deals with wear and wear mechanisms is called "tribology."

In this sense, this Technical Report does not cover the surfacing processes and alloys that are commonly known under the name of "cladding technologies", which more specifically address the protection of substrates against corrosion.

Hardfacing can be carried out by means of a large variety of alloys.

The selection of the optimum alloy to resist a given combination of wear factors is not necessarily an easy task. This task can, however, be facilitated by giving consideration to those attributes of alloys that are dominant in determining their behaviour and their properties.

In this sense, the microstructure of the alloys, which itself is determined by a composition and a thermo-mechanical history, certainly can be accepted as an attribute of major importance and significance.

It is the purpose of this Technical Report to propose a classification system of hardfacing alloys based on compositions and microstructures.

Since most of these alloys exist under the form of consumables that can be used with a variety of welding processes, no specific reference is made to these processes in the rest of this Technical Report.

STANDARDSISO.COM : Click to view the full PDF of ISO/TR 13393:2009

# Welding consumables — Hardfacing classification — Microstructures

**IMPORTANT** — The electronic file of this document contains colours which are considered to be useful for the correct understanding of the document. Users should therefore consider printing this document using a colour printer.

## 1 Scope

This Technical Report proposes a system for classifying hardfacing microstructures deposited by fusion welding processes.

## 2 Proposed classification/designation system

The designation system indicates the type of consumable (electrode; tubular cored electrode, wire or rod; solid wire or rod; or powder), the use of the consumable for hardfacing, the alloy base (iron, nickel, copper, cobalt, or tungsten carbide), and the microstructure type. Designations of microstructure types for the various alloy bases are given in Clauses 3 and 6. Definitions and examples of the microstructure types are given in Clauses 5 and 7. The designation scheme for a hardfacing deposit is given below:

<b>E</b>	<b>H</b>	<b>XX</b>	<b>XXX</b>
Electrode	Hardfacing type	Alloy base	Microstructure
<b>T</b> = tubular-cored electrode		<b>Fe</b> = iron base	
<b>S</b> = solid wire or rod		<b>Ni</b> = nickel base	
<b>P</b> = powder		<b>Cu</b> = copper base	
		<b>Co</b> = cobalt base	
		<b>W</b> = tungsten carbide base	

## 3 Summary of the designators for iron-base microstructures

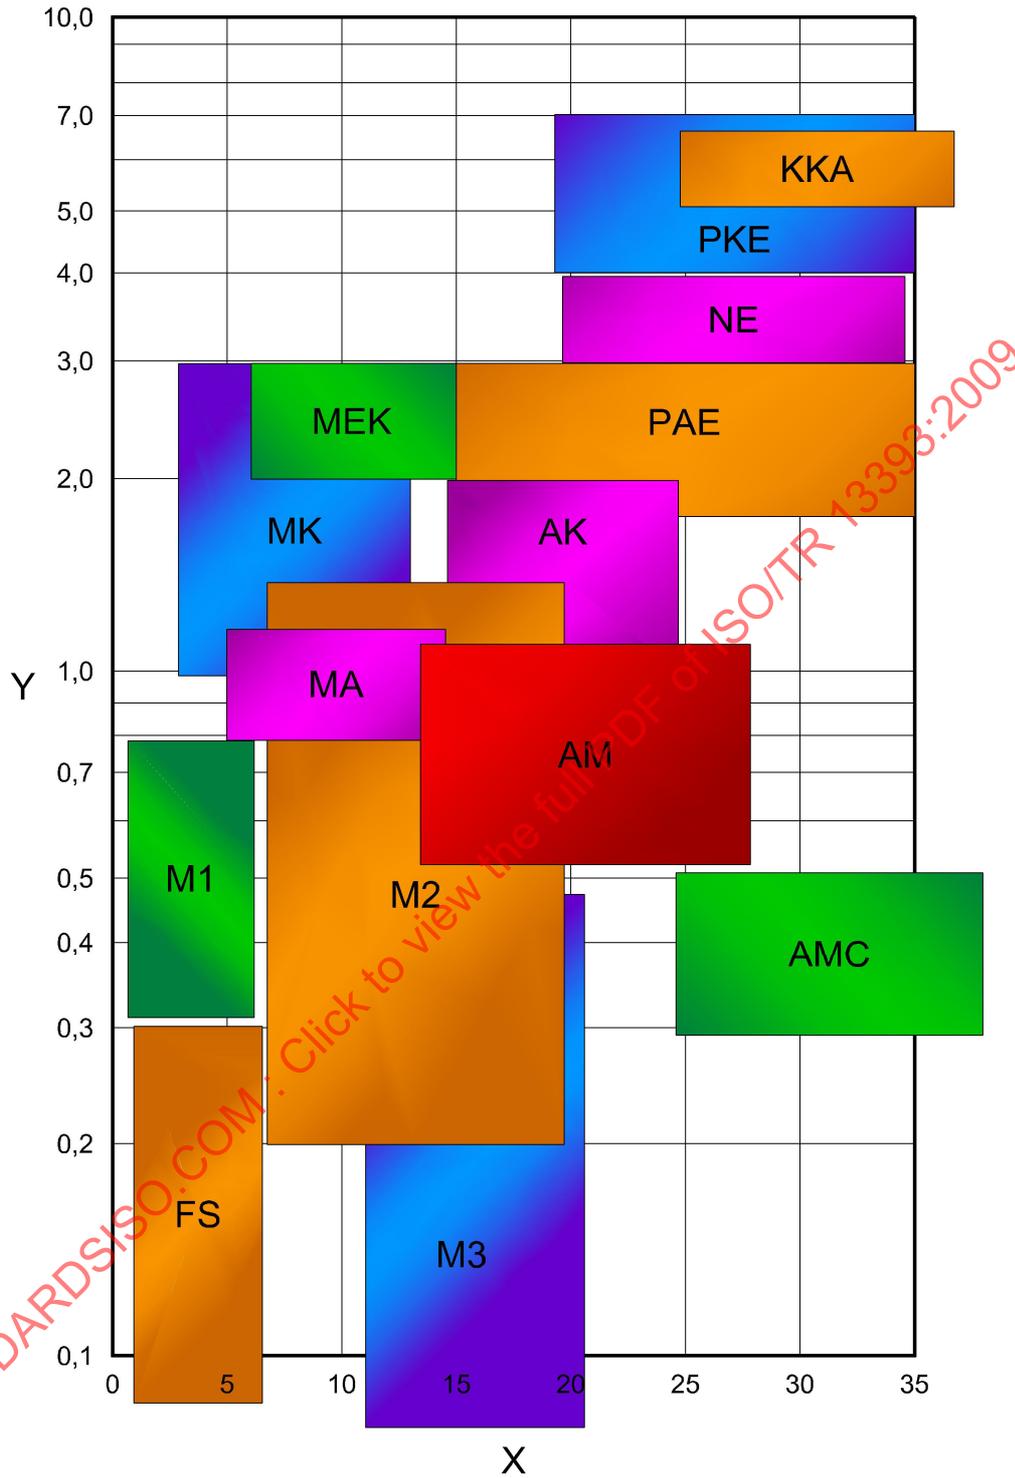
Most of the currently known Fe-based hardfacing alloys fall into one of about 17 typical microstructural categories. These types of microstructure are listed in Table 1, which also gives the proposed corresponding designators for covered electrodes. For convenience, only the E (electrode) form is shown, but it is understood that T (tubular-cored electrode), S (solid wire or rod), or P (powder) may be substituted for E.

Table 1 — Iron-base hardfacing deposit microstructure types

Hardfacing deposit designation	Microstructure type
E-H-Fe-FS	Mostly ferritic steel with second phase
E-H-Fe-M1	Low-alloy martensitic steel
E-H-Fe-M2	Tool steel martensite with secondary hardening
E-H-Fe-M3	Stainless steel martensite
E-H-Fe-M4	Maraging steel martensite
E-H-Fe-MA	Approximately equal amounts of martensite and austenite
E-H-Fe-MK	Martensite with alloy carbides
E-H-Fe-MEK	Martensite with austenite-carbide eutectic
E-H-Fe-A	Austenitic stainless steel with little or no ferrite
E-H-Fe-AF	Austenitic stainless steel with more than 30 FN
E-H-Fe-AM	Austenitic manganese steel with low or no chromium
E-H-Fe-AMC	Austenitic manganese steel with chromium nearly equal to manganese
E-H-Fe-AK	Austenitic manganese steel containing alloy carbides
E-H-Fe-PAE	Primary austenite with austenite-carbide eutectic
E-H-Fe-NE	Near-eutectic austenite-carbide iron
E-H-Fe-PKE	Primary chromium carbides with austenite-carbide eutectic
E-H-Fe-KKA	Primary chromium carbides with alloy carbides and austenite-carbide eutectic

#### 4 Identification of iron-base alloy microstructural groups in a carbon/alloying elements diagram

A convenient and systematic way to correlate composition and microstructures of hardfacing alloys consists in using a diagram such as that given in Figure 1. On the ordinate, the mass fraction of carbon is plotted as a percentage using a logarithmic scale. On the abscissa, the total amount of alloying elements, also plotted as a percentage, is represented. Alloying elements include Cr, Mn, Si, Mo, Ni, Nb, V, W and Ti. These are the most commonly encountered alloy elements in Fe-based hardfacing alloys. In this diagram, based on compositional ranges and corresponding microstructures that are known for most of the alloys currently being used in practice, the domains which correspond to the types of microstructure listed in Table 1 have been delineated. It should be noted that these delineations are to be taken as guidelines, not absolutes. Transitions from one type to another type of microstructure are often progressive, and therefore, at least with alloys that are characterized by borderline compositions, a certain degree of overlap is to be expected in practice. Note that composition ranges for microstructure types A, AF and M4 are not included in Figure 1 because their mass fraction of carbon is below 0,1 %.



**Key**

X alloy, percent  
 Y carbon, percent

**Figure 1 — Map of composition ranges for hardfacing microstructures**

## 5 Description of the iron-base alloys belonging to the different microstructure groups

### 5.1 General

For each group, the following pages contain some general information as to the following topics:

- typical chemical composition ranges;
- as-welded microstructure;
- typical as-welded hardness range;
- typical response to post-weld heat treatment;
- impact resistance (as a qualitative judgment);
- metal-to-metal wear resistance (as a qualitative judgment);
- resistance against abrasive wear;
- corrosion resistance;
- high-temperature resistance;
- machineability;
- typical applications;
- typical microstructure illustrations.

STANDARDSISO.COM : Click to view the full PDF of ISO/TR 13393:2009

## 5.2 Fe-FS Group (ferrite with second phase)

See Table 2.

**Table 2 — Fe-FS Group**

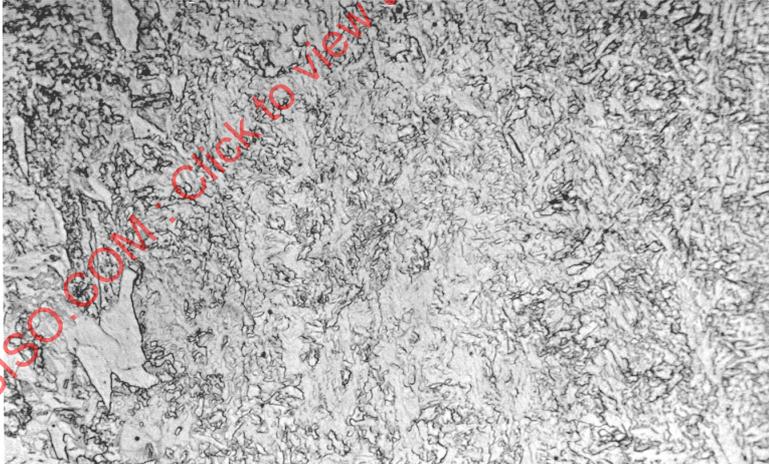
<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— Up to 0,3 % C</li> <li>— Up to 6 % alloying elements</li> </ul>
<p><b>Microstructure:</b> Predominantly ferrite with small amounts of pearlite, bainite, martensite</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness (as deposited): Generally expressed in HB, ranging from 200 HB to 400 HB, function of mass fraction of C</li> <li>— Machineable in the as-welded condition, PWHT improves machineability</li> <li>— Excellent impact resistance</li> <li>— Good metal-to-metal wear resistance</li> <li>— Low to moderate abrasion resistance (function of hardness)</li> <li>— Hardness drops if heat treated</li> <li>— Deposits rust</li> <li>— Typical example: 0,25 % C, 3 % Cr</li> </ul>
<p><b>Applications:</b> Build-up to return worn parts to original size, metal-to-metal wear as in pulleys, idlers, gears</p>

<p>Deposit made with preheating at 200 °C, cooled slowly, resulting in a hardness of 20 R<sub>C</sub>.  Microstructure is primarily ferrite with a little second phase.  Photomicrograph provided by The Lincoln Electric Company, USA.</p> <p style="text-align: center;"><b>Microstructure of Type FS Deposit, ×650, 2 % Nital (alcoholic nitric acid) etch</b></p>
<p>(continued)</p>

Table 2 (continued)



Deposit made without preheating, and allowed to cool rapidly, resulting in a hardness of 35 R<sub>C</sub>.

Microstructure is heavily bainitic.

Photomicrograph provided by The Lincoln Electric Company, USA.

**Microstructure of Type FS Deposit (same electrode as above), ×650, Nital etch**

STANDARDSISO.COM : Click to view the full PDF of ISO/TR 13393:2009

### 5.3 Fe-M1 Group (low-alloy martensite)

See Table 3.

**Table 3 — Fe-M1 Group**

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 0,3 % to 0,8 % C</li> <li>— Up to 6 % alloying elements</li> </ul>
<p><b>Microstructure:</b> Predominantly martensitic</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: 450 HB to 600 HB, 45 R<sub>C</sub> to 60 R<sub>C</sub>, function of mass fraction of C</li> <li>— Generally not machineable as-welded, grinding only. PWHT can soften enough to make deposit easily machineable</li> <li>— Good impact resistance</li> <li>— Excellent metal-to-metal wear resistance</li> <li>— Improved abrasion resistance compared with FS group, function of hardness</li> <li>— Hardness drops if heat treated</li> <li>— Deposits rust</li> <li>— Typical example: 0,5 % C, 5 % Cr, 0,5 % Mo</li> </ul>
<p><b>Applications:</b> Metal-to-metal wear, as in transfer rolls or guides</p>

<p>Microstructure is predominantly blocky martensite, with white retained austenite around the former grain boundaries. Photomicrograph provided by The Lincoln Electric Company, USA.</p> <p style="text-align: center;"><b>Microstructure of Type M1 Deposit, ×650, 2 % Nital</b></p>

**5.4 Fe-M2 Group (tool-steel martensite)**

See Table 4.

**Table 4 — Fe-M2 Group**

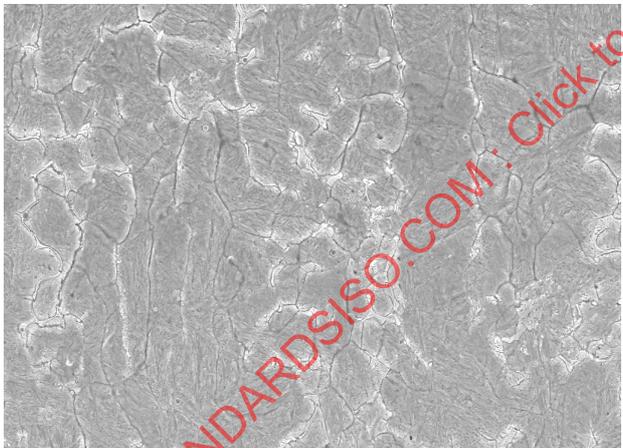
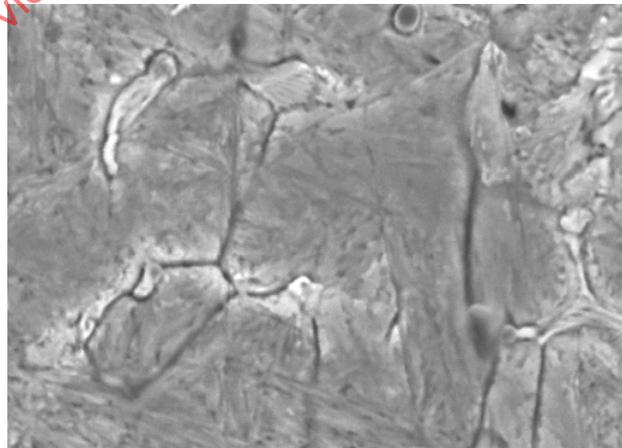
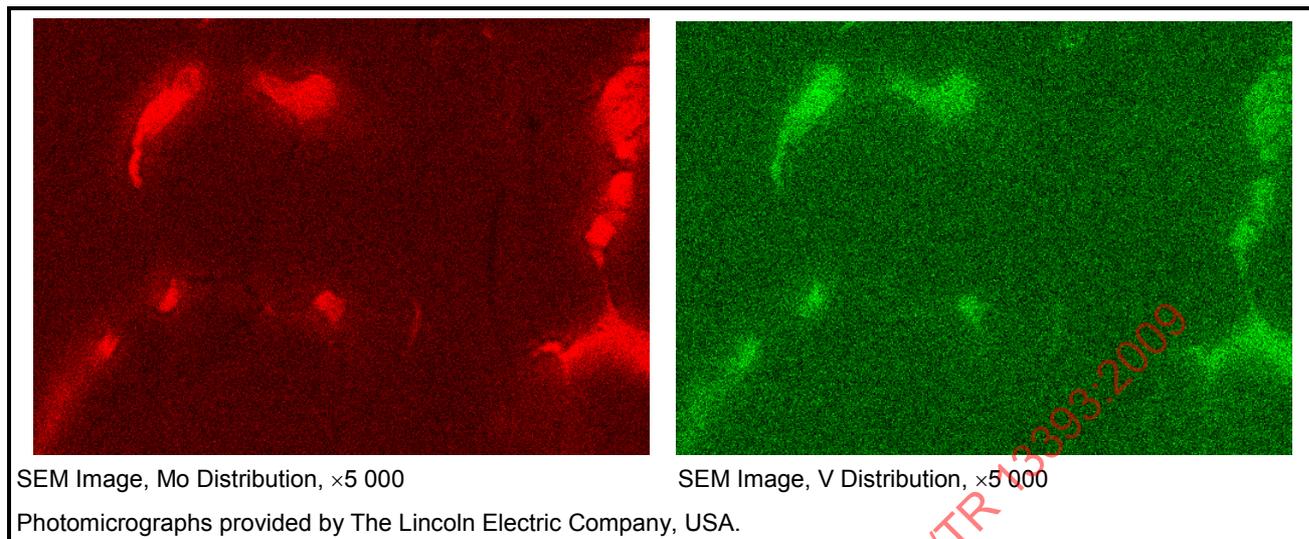
<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 0,2 % to 1,5 % C</li> <li>— 7 % to 20 % alloying elements, essentially Mo, W, Cr, V</li> </ul>
<p><b>Microstructure:</b> High-alloyed martensite with complex alloy carbides</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: Ranging from 45 R<sub>C</sub> to 60 R<sub>C</sub> (as deposited)</li> <li>— Generally not machineable as-welded, grinding only. PWHT can soften enough to make deposit easily machineable</li> <li>— Fair impact resistance, decreases with increasing mass fraction of carbon</li> <li>— Good abrasion resistance</li> <li>— Maintain or even increase the hardness after heat treatment at temperatures up to 550 °C or higher</li> <li>— Maintain the hardness at high service temperature</li> <li>— Good thermal shock and thermal cycling resistance</li> <li>— Deposits rust</li> <li>— Typical example: 0,7 % C, 3,75 % Cr, 6,0 % Mo, 1,8 % W, 1,1 % V</li> </ul>
<p><b>Applications:</b> Tool steels for hot/cold shears and dies, hot metal-to-metal wear, work rolls in the metals-processing industries</p>
<div style="display: flex; justify-content: space-around;"> <div style="text-align: center;">  <p>SEM Image, x1 000</p> </div> <div style="text-align: center;">  <p>SEM Image, x5 000</p> </div> </div> <p>Photomicrographs provided by The Lincoln Electric Company, USA.</p>
<p>(continued)</p>

Table 4 (continued)

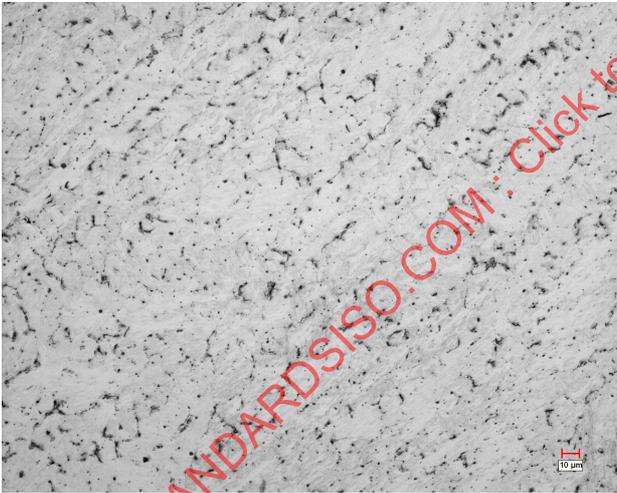
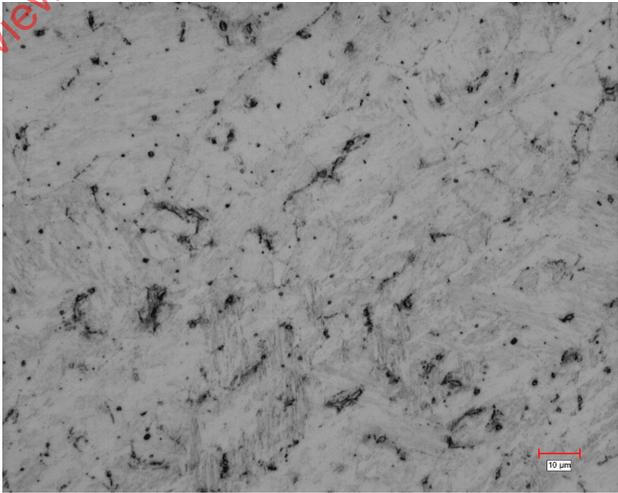


STANDARDSISO.COM : Click to view the full PDF of ISO/TR 13393:2009

**5.5 Fe-M3 Group (stainless-steel martensite)**

See Table 5.

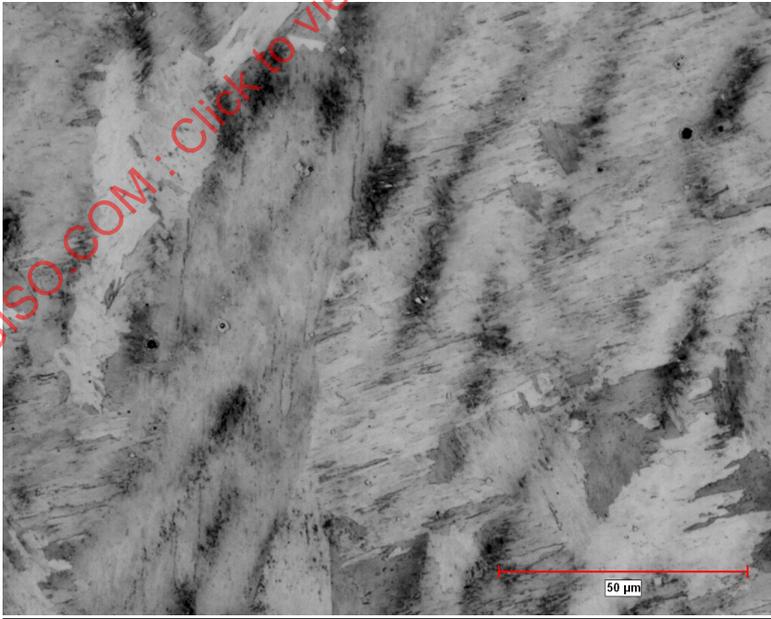
**Table 5 — Fe-M3 Group**

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 0,05 % to 0,6 % C</li> <li>— 10 % to 20 % alloying elements, mainly chromium</li> </ul>
<p><b>Microstructure:</b> Essentially martensitic</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: ranging from 30 R<sub>C</sub> to 55 R<sub>C</sub> (as deposited), function of mass fraction of C</li> <li>— Lower carbon deposits are machineable as-welded. Deposits above about 40 R<sub>C</sub> usually require PWHT to soften for machining</li> <li>— Fair to good impact resistance</li> <li>— Good corrosion/oxidation resistance, function of the mass fraction of Cr</li> <li>— Good metal-to-metal wear resistance</li> <li>— Low to fair abrasion resistance</li> <li>— Hardness drops if heat treated above about 480 °C</li> <li>— Deposits do not rust</li> <li>— Typical example: 0,17 % C, 1,3 % Mn, 13,6 % Cr, 4,2 % Ni, 0,6 % Mo, 0,6 % Nb, 0,2 % V</li> </ul>
<p><b>Applications:</b> Continuous caster rolls in steel mills</p>
<div style="display: flex; justify-content: space-around;"> <div style="text-align: center;">  <p>×200</p> </div> <div style="text-align: center;">  <p>×500</p> </div> </div> <p>The microstructure is predominantly tempered martensite, with about 1,3 % ferrite (dark etching phase). Photomicrographs provided by The Lincoln Electric Company, USA.</p> <p style="text-align: center;"><b>Microstructure of Type M3 Deposit, Kalling's etch, as-welded condition</b></p>

## 5.6 Fe-M4 Group (maraging steel)

See Table 6.

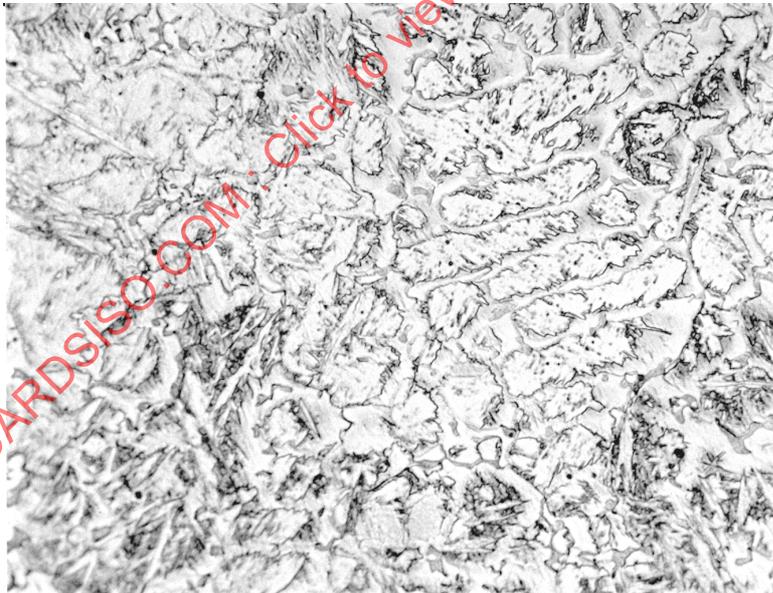
Table 6 — Fe-M4 Group

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 0,02 % C</li> <li>— 17 % Ni, 4 % Mo, 9 % Co, 0,5 % Ti + V</li> </ul>
<p><b>Microstructure:</b></p> <ul style="list-style-type: none"> <li>— low-carbon martensite as-deposited</li> <li>— martensite with age-hardening precipitates and traces of austenite after PWHT of 450 °C to 480 °C</li> </ul>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: 30 R<sub>C</sub> to 40 R<sub>C</sub> as deposited</li> <li>— 50 R<sub>C</sub> to 55 R<sub>C</sub> after PWHT</li> <li>— PWHT at 450 °C to 480 °C is essential to developing full hardness</li> <li>— Readily machineable in the as-deposited condition, much more difficult to machine after PWHT</li> <li>— High impact resistance</li> <li>— Low corrosion resistance</li> <li>— High resistance to thermal shock, but service temperatures limited to 400 °C as higher temperatures over-age the material</li> </ul>
<p><b>Applications:</b> Mill rolls, cutting and stamping dies, die-casting molds for aluminium alloys</p>

<p>Photomicrograph provided by The Lincoln Electric Company USA from a sample provided by Metrode Products Ltd., United Kingdom.</p> <p style="text-align: center;"><b>Microstructure of Type M4 Deposit, ×500, Kallings etch</b></p>

**5.7 Fe-MA Group (martensite and austenite)**

See Table 7

**Table 7 — Fe-MA Group**

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 0,8 % to 1,5 % C</li> <li>— 5 % to 15 % alloying elements, mainly Mn, Cr, Si</li> </ul>
<p><b>Microstructure:</b> Martensite and austenite in nearly equal amounts</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: 45 R<sub>C</sub> to 60 R<sub>C</sub>, work hardens to a limited extent in service</li> <li>— Generally not machineable as-welded, PWHT tends to reform fresh martensite and does not improve machineability</li> <li>— Good impact resistance</li> <li>— Fairly good metal-to-metal wear resistance</li> <li>— Fairly good abrasion resistance, especially to soft materials such as limestone</li> <li>— Moderate corrosion resistance</li> <li>— Tendency to check crack in multiple layers</li> <li>— Deposits rust</li> <li>— Typical example: 1 % C, 9 % Cr, 3 % Si alloy</li> </ul>
<p><b>Applications:</b> Agricultural implements in soft soils</p>

<p>Martensite appears as islands that were dendrite cores. Austenite appears as the continuous matrix around the martensite islands.</p> <p>Photomicrograph provided by The Lincoln Electric Company, USA.</p> <p style="text-align: center;"><b>Microstructure of Type MA Deposit, ×670, Vilella's etch</b></p>

## 5.8 Fe-MK Group (martensite with alloy carbides)

See Table 8.

Table 8 — Fe-MK Group

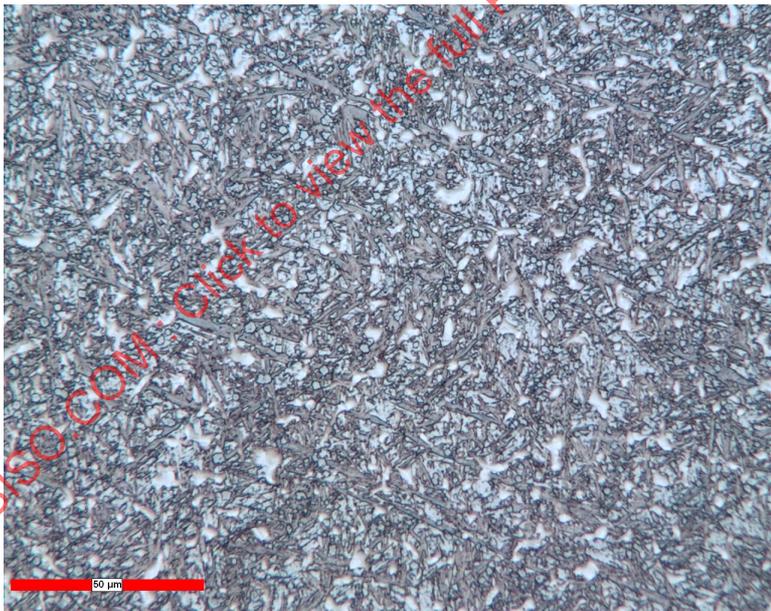
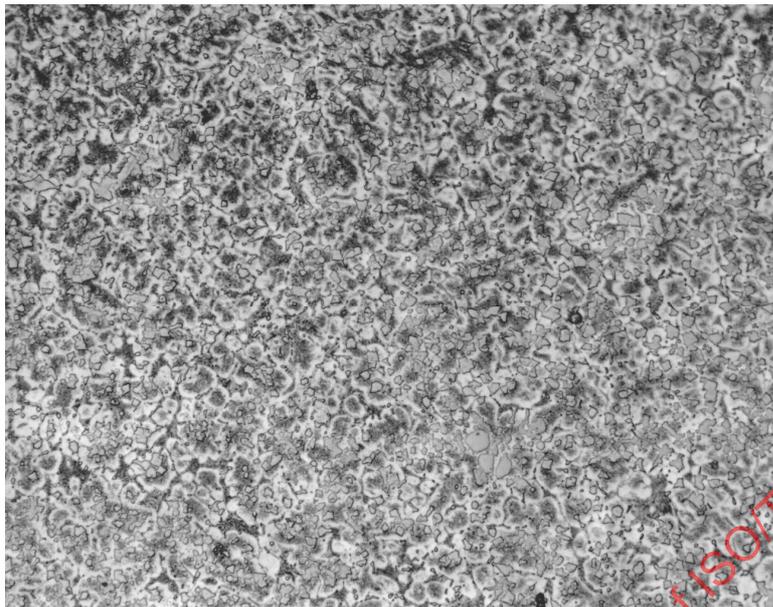
<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 1 % to 3 % C</li> <li>— Up to 13 % alloying elements, essentially Cr, Mo, W and a carbide former such as Ti, V, Nb</li> </ul>
<p><b>Microstructure:</b> Medium-alloyed martensite with precipitated carbides</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: 50 R<sub>C</sub> to 55 R<sub>C</sub></li> <li>— Not machineable as-welded, nor after PWHT; grinding only</li> <li>— Good impact resistance combined with good abrasion resistance, function of amount and type of carbides</li> <li>— Heat treatment softens matrix, but not carbides</li> <li>— Deposits rust</li> <li>— Typical example: Top – 2 % C, 8 % Cr, 1,5 % Mo, 6 % Ti; Bottom – 3 % C, 6 % Cr, 5 % V, 5 % Ti</li> </ul>
<p><b>Applications:</b> Metal-to-metal wear with abrasion, high stress (crushing) abrasion</p>

<p>Photomicrograph provided by The Stoodly Company (a division of Thermadyne Industries).</p> <p><b>Microstructure of Type Fe-MK consisting of TiC carbides in a matrix that is predominately martensite</b></p> <p style="text-align: right;"><i>(continued)</i></p>

Table 8 (continued)



Photomicrograph provided by ESAB AB, Sweden.

**Microstructure of Type Fe-MK consisting of TiC/VC carbides in a matrix that is predominately martensite**

STANDARDSISO.COM : Click to view the full PDF of ISO/TR 13393:2009

## 5.9 Fe-MEK Group (martensite with eutectic)

See Table 9.

Table 9 — Fe-MEK Group

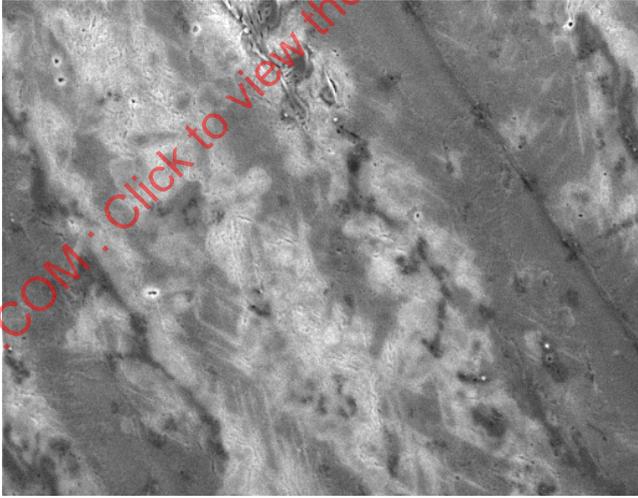
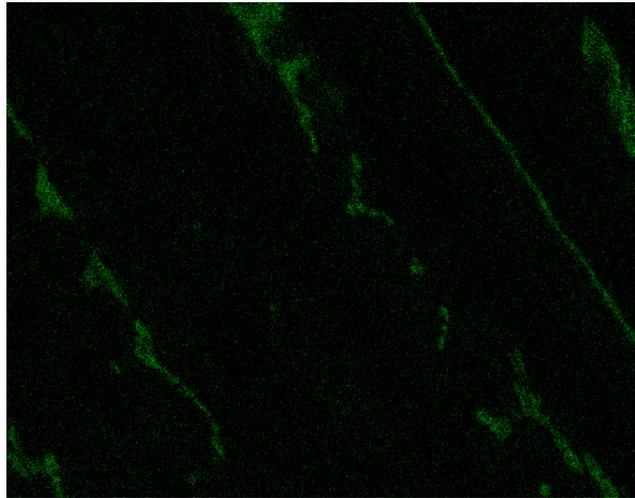
<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 2 % to 3 % C</li> <li>— 6 % to 15 % alloying elements, predominantly Cr and Mn</li> </ul>
<p><b>Microstructure:</b> Martensite with austenite-carbide eutectic</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: 45 R<sub>C</sub> to 60 R<sub>C</sub> (as deposited)</li> <li>— Not machineable as-welded, nor after PWHT; grinding only</li> <li>— Good metal-to-metal wear resistance</li> <li>— Fair impact resistance</li> <li>— Moderate abrasion resistance, increases with increasing mass fraction of carbon</li> <li>— Tendency to check crack in multiple layers</li> <li>— Deposits rust</li> <li>— Typical example: 2,2 % C, 7 % Cr</li> </ul>
<p><b>Applications:</b> Cover layer on hammer-mill hammers, metal transfer guides</p>

<p>SEM photomicrograph, ×1 000  Photomicrograph provided by The Lincoln Electric Company, USA.</p> <p><b>Microstructure of Type Fe-MEK consisting of martensite, retained austenite and eutectic carbides</b></p> <p style="text-align: right;"><i>(continued)</i></p>

Table 9 (continued)



Cr distribution

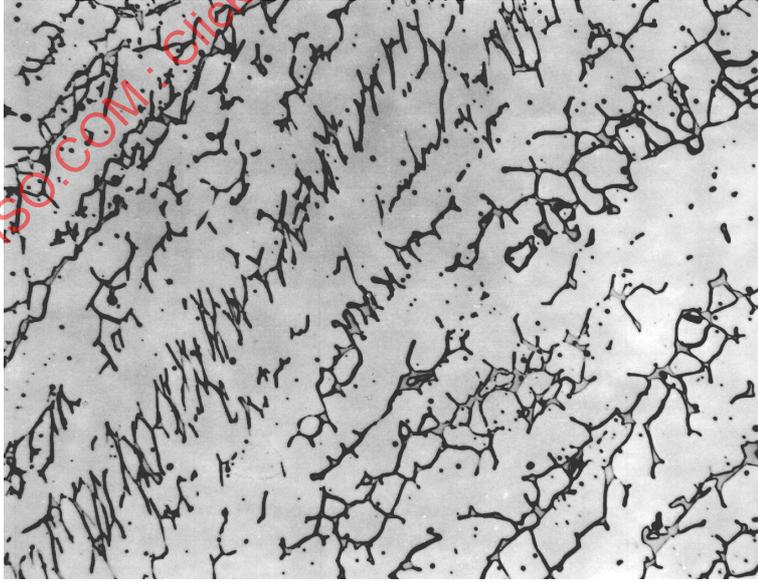
Photomicrograph provided by The Lincoln Electric Company, USA.

STANDARDSISO.COM : Click to view the full PDF of ISO/TR 13393:2009

## 5.10 Fe-A Group (nominally austenitic stainless steel)

See Table 10.

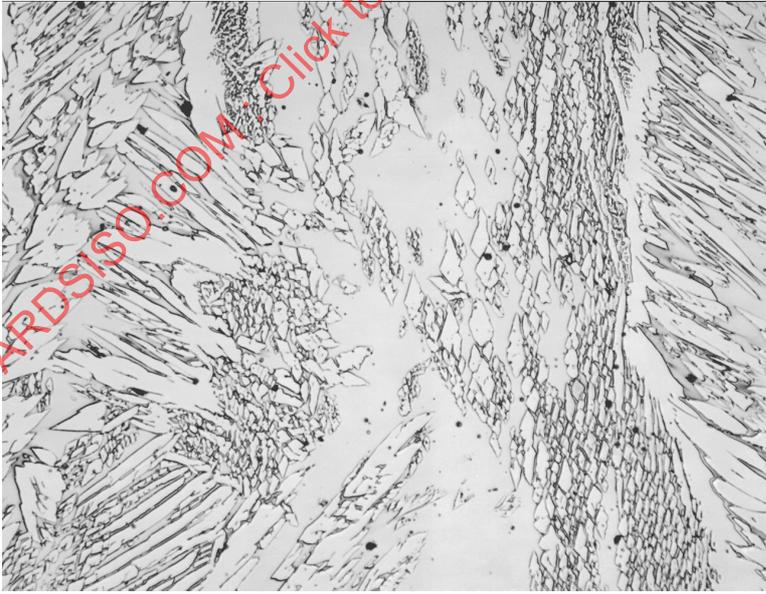
**Table 10 — Fe-A Group**

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 0,02 % to 0,15 % C</li> <li>— Up to 40 % alloying elements, essentially Cr, Ni, sometimes Mo</li> </ul>
<p><b>Microstructure:</b> Austenite with ferrite below 30 FN</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: typically 180 HB to 250 HB, not relevant</li> <li>— Readily machineable with sharp tooling and rigid machinery</li> <li>— High ductility and impact resistance</li> <li>— Excellent corrosion resistance</li> <li>— Fair to good metal-to-metal wear resistance, some tendency to gall under high pressure</li> <li>— Poor abrasion resistance</li> <li>— Work hardenable</li> <li>— Due to ferrite-to-sigma phase transformation, the higher ferrite grades become somewhat embrittled when subjected to heat treatment</li> <li>— Deposits do not rust</li> <li>— Typical examples: 307 (0,1 % C, 4 % Mn, 20 % Cr, 10 % Ni, 1 % Mo), 309 (0,04 % C, 24 % Cr, 13 % Ni), 309 Mo (0,04 % C, 23 % Cr, 13 % Ni, 2,5 % Mo), 310 (0,15 % C, 25 % Cr, 21 % Ni) stainless-steel types</li> </ul>
<p><b>Applications:</b> Buffer layers, joining austenitic manganese plates</p>
<div style="text-align: center;">  </div> <p>The ferrite is the darker, lacy phase. The austenite is the lighter phase. Some deposits (e.g. 307 or 310) may contain little or no ferrite.</p> <p>Photomicrograph provided by The Lincoln Electric Company, USA.</p> <p style="text-align: center;"><b>Microstructure of Type A Deposit, ×500, Kalling's etch</b></p>

**5.11 Fe-AF Group (ferritic-austenitic stainless steel)**

See Table 11.

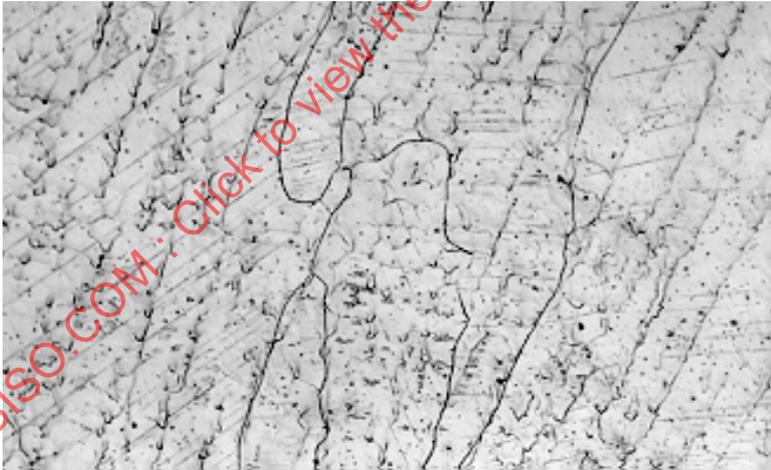
**Table 11 — Fe-AF Group**

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 0,05 % to 0,15 % C</li> <li>— Up to 40 % alloying elements, essentially Cr, Ni</li> </ul>
<p><b>Microstructure:</b> Austenite with ferrite above 30 FN</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: typically 200 HB to 280 HB, not relevant</li> <li>— Readily machineable</li> <li>— High ductility and impact resistance</li> <li>— Excellent corrosion resistance</li> <li>— Fair to good metal-to-metal wear resistance, some tendency to gall under high pressure</li> <li>— Poor abrasion resistance</li> <li>— Work hardenable</li> <li>— Due to ferrite-to-sigma phase transformation, the high-ferrite grades become embrittled when subjected to heat treatment</li> <li>— Deposits do not rust</li> <li>— Typical examples: 312 types of stainless steels, 29 % Cr, 9 % Ni</li> </ul>
<p><b>Applications:</b> Buffer layers, joining austenitic manganese plates, temporary repairs of tool steel and other martensitic pieces</p>

<p>Lighter austenite plates grow from ferrite grain boundaries, and blocky austenite plates appear within ferrite regions. Photomicrograph provided by The Lincoln Electric Company, USA.</p> <p style="text-align: center;"><b>Microstructure of Type AF Deposit, x500, Murakami's etch</b></p>

## 5.12 Fe-AM Group (austenitic manganese steel)

See Table 12.

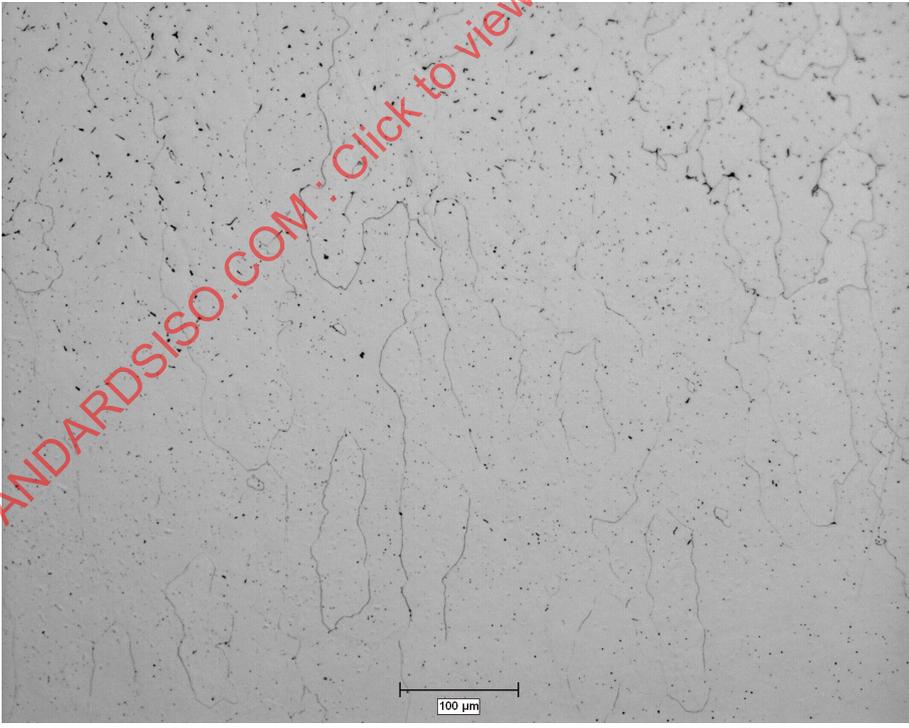
Table 12 — Fe-AM Group

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 0,5 % to 1,2 % C</li> <li>— Up to 30 % alloying elements, essentially C, Mn, sometimes up to 8 % Cr, Ni, Mo additions</li> </ul>
<p><b>Microstructure:</b> Austenite (with small amounts of intergranular carbides)</p>
<p><b>Main characteristics</b></p> <ul style="list-style-type: none"> <li>— Hardness: about 300 HB (as deposited), work hardenable up to 550 HB</li> <li>— Machineable only with sharp rigid tooling, with difficulty</li> <li>— Extreme impact resistance</li> <li>— Excellent metal-to-metal wear resistance</li> <li>— Good abrasion resistance, but only in the work-hardened condition</li> <li>— Slow cooling during welding or post-weld heat treatments results in very significant embrittlement of these alloys</li> <li>— Deposits rust</li> <li>— Typical example: 1 % C, 14 % Mn</li> </ul>
<p><b>Applications:</b> Rock crushers, hammer-mill hammers, rail frogs</p>

<p>Microstructure is almost all austenite, with only a few scattered carbides and inclusions. Photomicrograph provided by The Lincoln Electric Company, USA.</p> <p style="text-align: center;"><b>Microstructure of Type AM Deposit, ×260, 5 % Nital + 15 % HCl etch</b></p>

**5.13 Fe-AMC Group (austenitic chromium-manganese steel)**

See Table 13.

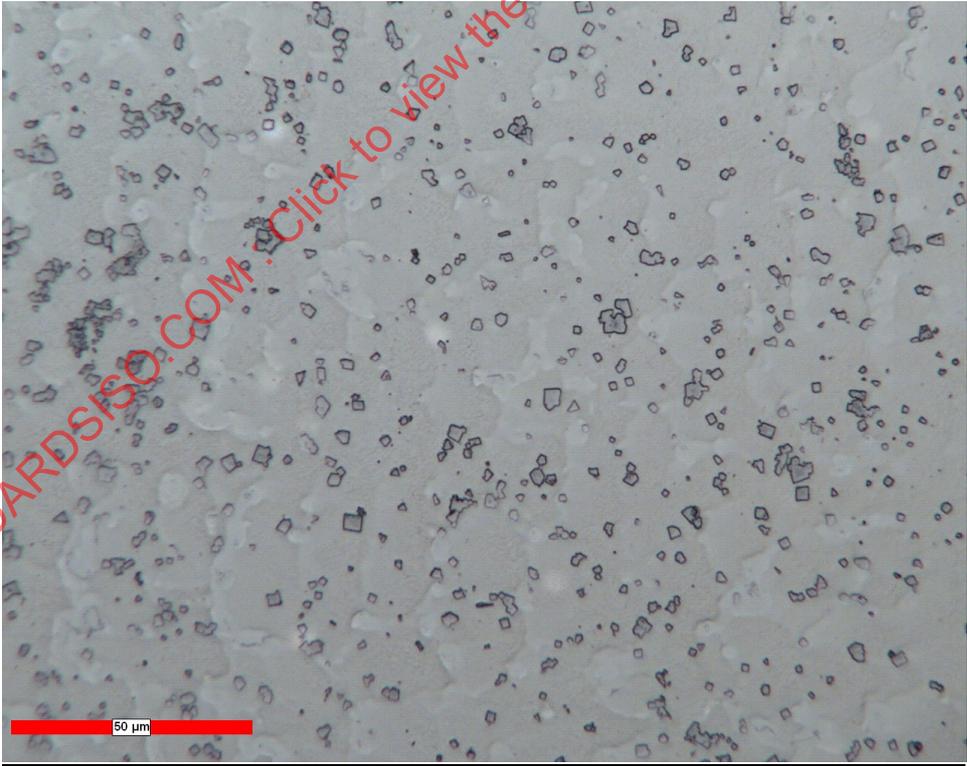
**Table 13 — Fe-AMC Group**

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 0,3 % to 0,5 % C</li> <li>— 25 % to 40 % alloying elements, essentially Cr and Mn in nearly equal amounts</li> </ul>
<p><b>Microstructure:</b> Austenite</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: about 300 HB (as deposited), work hardenable up to 550 HB</li> <li>— Machineable only with sharp and rigid tooling, with difficulty</li> <li>— Extreme impact resistance</li> <li>— Excellent metal-to-metal wear resistance</li> <li>— Very good abrasion resistance, but only in the work-hardened condition</li> <li>— Slow cooling during welding or post-weld heat treatments results in some embrittlement of these alloys, but is much less susceptible to thermal embrittlement than the AM Group</li> <li>— Deposits do not rust</li> <li>— Typical example: 0,4 % C, 15 % Mn, 15 % Cr</li> </ul>
<p><b>Applications:</b> Joining austenitic manganese-base metals, buffer and build-up layers, rock crushers, hammer-mill hammers, rail frogs</p>

<p>Microstructure is almost all austenite, with only a few scattered carbides and inclusions.  Photomicrograph provided by The Lincoln Electric Company, USA.</p> <p style="text-align: center;"><b>Microstructure of Type AMC Deposit, ×100, 20 % aqua regia etch</b></p>

### 5.14 Fe-AK Group (austenitic manganese steel containing alloy carbides)

See Table 14.

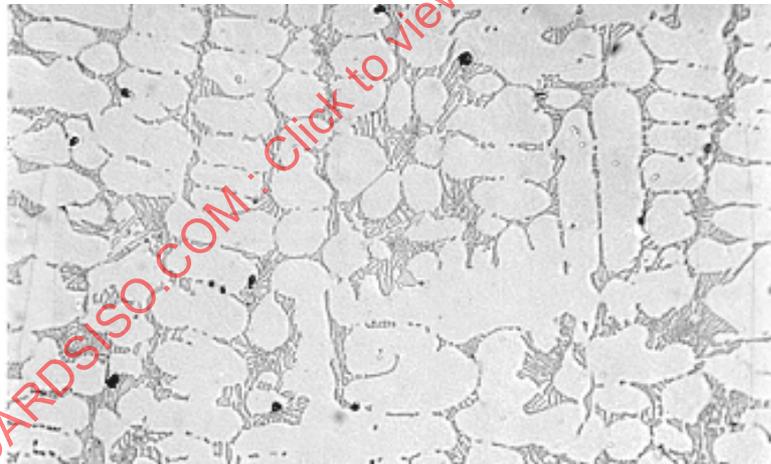
Table 14 — Fe-AK Group

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 1 % to 2 % C</li> <li>— 15 % to 25 % alloy, mainly manganese with Ti or Nb as a strong carbide former</li> </ul>
<p><b>Microstructure:</b> Austenite with dispersed alloy carbides</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: 30 R<sub>C</sub> to 40 R<sub>C</sub> (as deposited), work hardens rapidly</li> <li>— Not machineable as welded, nor after PWHT</li> <li>— Excellent impact resistance</li> <li>— Very good abrasion resistance</li> <li>— Good metal-to-metal wear resistance</li> <li>— Slow cooling during welding or post-weld heat treatments results in very significant embrittlement of these alloys</li> <li>— Deposits rust</li> <li>— Typical example: 2 % C, 15 % Mn, 3,5 % Cr, 3,5 % Ti</li> </ul>
<p><b>Applications:</b> Severe impact with abrasion-hammer-mill hammers, rock crushers</p>
 <p>50 μm</p>
<p>×500, Nital etch</p>
<p>Photomicrograph provided by The Stoodly Company (a division of Thermadyne Industries).</p>

5.15 Fe-PAE Group (primary austenite with eutectic)

See Table 15.

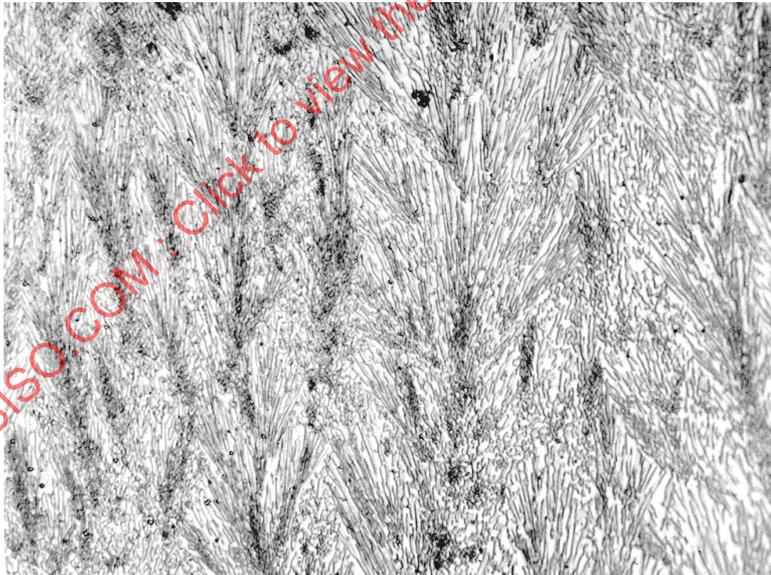
Table 15 — Fe-PAE Group

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 2 % to 3 % C</li> <li>— 15 % to 35 % alloy elements, mainly Cr but often some Mo</li> </ul>
<p><b>Microstructure:</b> Primary austenite with austenite-carbide eutectic, carbides are mainly of the <math>M_{23}C_6</math> type</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: 40 <math>R_C</math> to 55 <math>R_C</math> (as deposited), some work hardening in softer alloys with a lower C content</li> <li>— Not machineable, grinding only</li> <li>— Fair impact resistance, decreases with increasing mass fraction of carbon</li> <li>— Good abrasion resistance, increases with increasing mass fraction of carbon</li> <li>— Not softened by PWHT</li> <li>— Alloys with a lower C and higher Cr content have some corrosion resistance due to significant amounts of Cr remaining in solid solution after all carbides are formed, others rust</li> <li>— Multi-layer deposits in stringer beads tend to check crack at intervals of 25 mm to 50 mm</li> <li>— Deposits rust</li> <li>— Typical example: 2,5 % C, 30 % Cr</li> </ul>
<p><b>Applications:</b> Abrasion with significant impact-cap layers on hammer-mill hammers, bucket teeth.</p>

<p>Large light shapes are primary austenite. The mottled structure consists of eutectic mix of <math>M_{23}C_6</math> carbides (darker) with austenite (lighter).</p> <p>Photomicrograph provided by The Lincoln Electric Company, USA.</p> <p style="text-align: center;"><b>Microstructure of Type PAE Deposit, x650, 5 % Nital etch</b></p>

## 5.16 Fe-NE Group (near eutectic)

See Table 16.

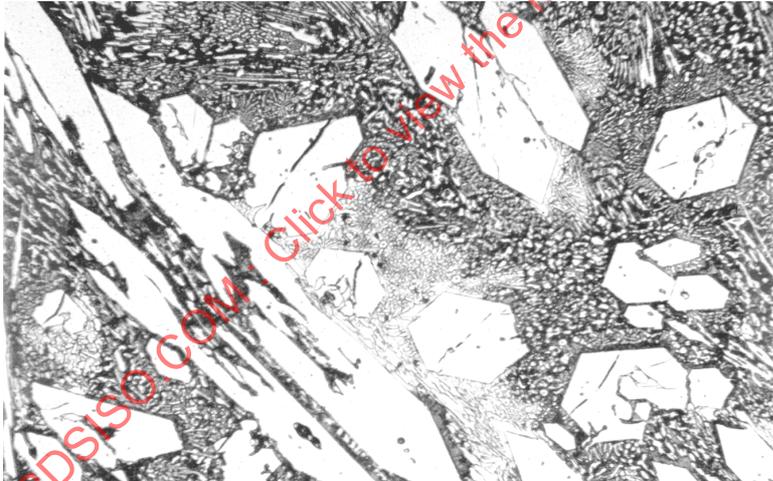
Table 16 — Fe-NE Group

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 3 % to 4 % C</li> <li>— 20 % to 35 % alloy, mainly Cr but often with some Mo</li> </ul>
<p><b>Microstructure:</b> Near-eutectic mix of austenite and carbides (mainly <math>M_{23}C_6</math> type); alloys with a lower C content may have a small amount of primary austenite, while alloys with a higher C content may have a small amount of primary carbides, but properties are dominated by the eutectic</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: 53 <math>R_C</math> to 58 <math>R_C</math> (as deposited), alloys do not work harden and do not soften appreciably by PWHT</li> <li>— Not machineable as-welded, nor after PWHT; grinding only</li> <li>— Fair impact resistance</li> <li>— Good abrasion resistance</li> <li>— Multi-layer deposits in stringer beads tend to check crack at intervals of 20 mm to 30 mm</li> <li>— Deposits rust</li> <li>— Typical example: 3,5 % C, 25 % Cr</li> </ul>
<p><b>Applications:</b> Abrasion with moderate impact: bucket lips and teeth, earth-moving blades</p>

<p>Lamellar structure consists of a eutectic mix of dark <math>M_{23}C_6</math> carbides in lighter austenite. Photomicrograph provided by The Lincoln Electric Company, USA</p> <p style="text-align: center;"><b>Microstructure of Type NE Deposit, <math>\times 670</math>, Vilella's etch</b></p>

5.17 Fe-PKE Group (primary carbides with eutectic)

See Table 17.

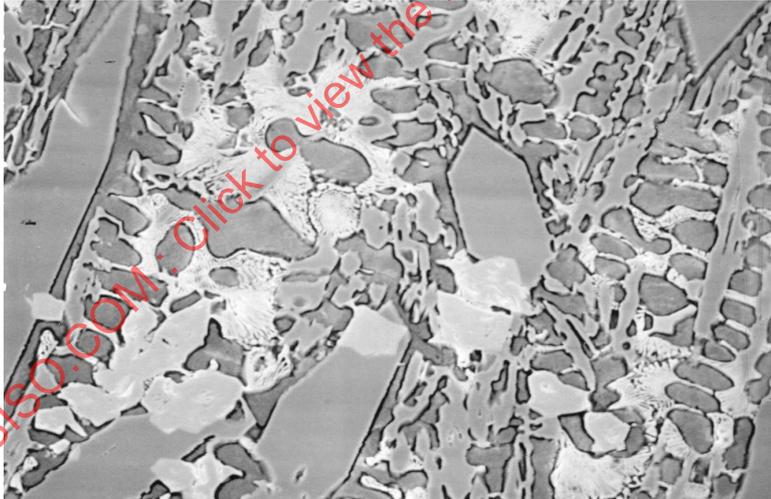
Table 17 — Fe-PKE Group

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— More than 4 % C</li> <li>— 20 % to 35 % alloy, mainly Cr</li> </ul>
<p><b>Microstructure:</b> Primary carbides (<math>Cr_7C_3</math> type, appearing as large hexagonal rods) in a matrix of eutectic austenite-carbide (mainly <math>M_{23}C_6</math> type)</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: 58 <math>R_C</math> to 65 <math>R_C</math>, does not work harden, does not soften in PWHT</li> <li>— Not machineable, grinding only</li> <li>— Low impact resistance</li> <li>— Excellent abrasion resistance</li> <li>— Multi-layer deposits in stringer beads tend to check crack at intervals of 10 mm to 20 mm</li> <li>— Deposits rust</li> <li>— Typical example: 4,5 % C, 25 % Cr</li> </ul>
<p><b>Applications:</b> Severe abrasion: coal crusher rolls, ore chutes</p>

<p>Large white shapes are <math>M_7C_3</math> carbides; mottled dark structure consists of austenite plus <math>M_{23}C_6</math> carbide eutectic. At a higher magnification, the austenite-carbide eutectic will appear exactly as it does in the Type PAE and NE deposits.</p> <p>Photomicrograph provided by The Lincoln Electric Company, USA.</p> <p style="text-align: center;"><b>Microstructure of Type PKE Deposit, x260, Vilella's etch</b></p>

### 5.18 Fe-KKA Group (primary carbides, alloy carbides and eutectic)

See Table 18.

Table 18 — Fe-KKA Group

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— More than 5 % C</li> <li>— 25 % to 40 % alloy, mainly Cr but also at least 5 % of a strong carbide former (Ti, Nb, V)</li> </ul>
<p><b>Microstructure:</b> Large primary carbides (<math>Cr_7C_3</math> type) and dispersed harder (but smaller) alloy carbides (TiC, NbC, VC type) in a eutectic austenite/carbide (<math>M_{23}C_6</math> type) matrix</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness: 58 <math>R_C</math> to 70 <math>R_C</math> (as deposited), not softened by PWHT, does not work harden</li> <li>— Not machineable, grinding only</li> <li>— Excellent abrasion resistance (both low stress and high stress), abrasion resistance retained up to 650 °C</li> <li>— Low impact resistance</li> <li>— Multi-layer deposits in stringer beads tend to check crack at intervals of 5 mm to 15 mm</li> <li>— Deposits rust</li> <li>— Typical example: 5,5 % C, 20 % Cr, 6 % Mo, 6 % Nb</li> </ul>
<p><b>Applications:</b> Severe abrasion, often at high temperatures, cement clinker crushers</p>
<div style="text-align: center;">  </div> <p>Darker angular particles are <math>Cr_7C_3</math> primary carbides (the same as in Type PKE deposit); lighter particles are complex Mo-Nb carbides (mostly formed from eutectic); spaces between carbides consist of austenite (formed from eutectic).</p> <p>Photomicrograph provided by The Lincoln Electric Company, USA.</p> <p style="text-align: center;"><b>Microstructure of Type KKA Deposit, <math>\times 1\ 040</math>, Vilella's etch, SEM image</b></p>

## 6 Summary of the designators for non-ferrous hardfacing deposit types

Most of the currently known non-ferrous hardfacing alloys fall into one of thirteen microstructural categories. These types of microstructures are listed in Table 19, which also gives the proposed designations. For convenience, only the E (electrode) form is shown, but it is understood that T (tubular-cored electrode), S (solid wire or rod) or P (powder) may be substituted for E.

**Table 19 — Non-ferrous-base hardfacing deposit types**

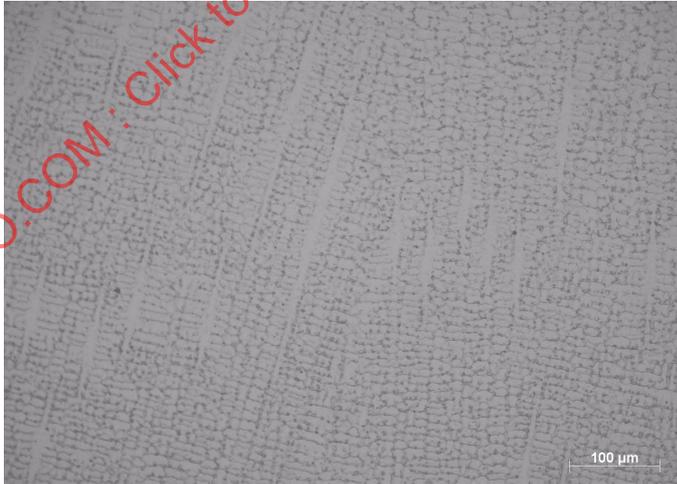
Hardfacing deposit designation	Microstructure type
E-H-Co-CS	Cobalt solid-solution alloy
E-H-Co-PC	Primary cobalt solid-solution alloy with cobalt alloy/carbide eutectic
E-H-Co-NE	Near-eutectic mix of carbides and cobalt solid-solution alloy
E-H-Co-PKE	Primary carbides with cobalt alloy/carbide eutectic
E-H-Co-LP	Cobalt solid-solution alloy with Laves-phase intermetallic compounds
E-H-Ni-NS	Nickel solid-solution alloy
E-H-Ni-B	Primary nickel alloy solid solution with nickel alloy/boride eutectic
E-H-Ni-CB	Primary nickel alloy solid solution with nickel alloy/chrome boride eutectic
E-H-Ni-LP	Nickel solid-solution alloy with Laves-phase intermetallic compounds
E-H-Cu-BS	Solid-solution bronzes
E-H-Cu-BT	Two-phase bronzes
E-H-W-Fe	Approximately 40 % to 60 % (by mass) tungsten carbide in an alloy steel matrix
E-H-W-Ni	Approximately 40 % to 60 % (by mass) tungsten carbide in a nickel alloy matrix

## 7 Description of the alloys belonging to the different non-ferrous microstructure groups and microstructural illustrations

### 7.1 Co-CS Group (cobalt solid-solution alloy)

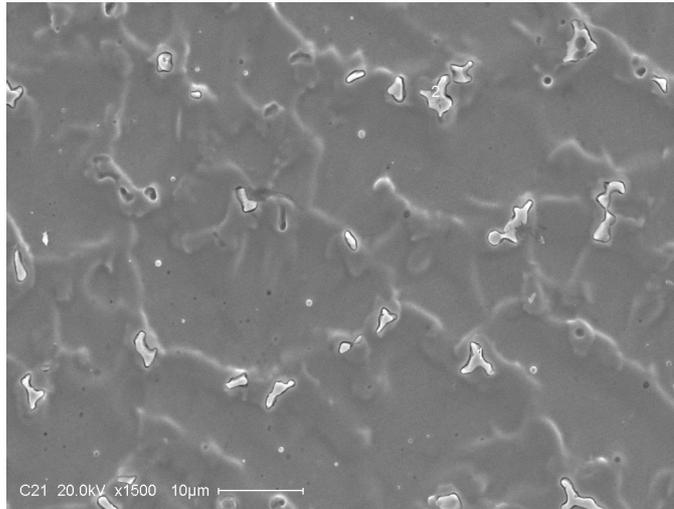
See Table 20.

Table 20 — Co-CS Group

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 0,15 % to 0,40 % C</li> <li>— Approximately 26 % Cr, 3 % Ni, 5 % Mo, balance Co</li> </ul>
<p><b>Microstructure:</b> Predominately cobalt alloy solid solution with scattered carbides</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness (as deposited): 20 R<sub>C</sub> to 30 R<sub>C</sub></li> <li>— Seldom heat treated, little hardness change occurs in heat treatment</li> <li>— Machineable in the as-welded condition, but with difficulty, due to rapid work-hardening</li> <li>— Excellent impact resistance</li> <li>— Exceptional metal-to-metal wear resistance, especially to galling</li> <li>— Exceptional cavitation erosion resistance</li> <li>— High corrosion resistance</li> <li>— High resistance to thermal shock, oxidizing and reducing atmospheres. Strength and ductility retained up to 850 °C</li> </ul>
<p><b>Applications:</b> Valve faces and valve seats in aqueous corrosive environments and in hot gas environments</p>

<p>5 % HCl electrolytic etch Optical, ×200 Photomicrograph provided by The Lincoln Electric Company, USA.</p>

(continued)

Table 20 (continued)



The particles in the cell boundaries are identified as carbides rich in Cr and Mo.

SEM, ×1 500

Photomicrograph provided by The Lincoln Electric Company, USA.

7.2 Co-PC Group (primary cobalt solid-solution alloy with cobalt alloy/carbide eutectic)

See Table 21.

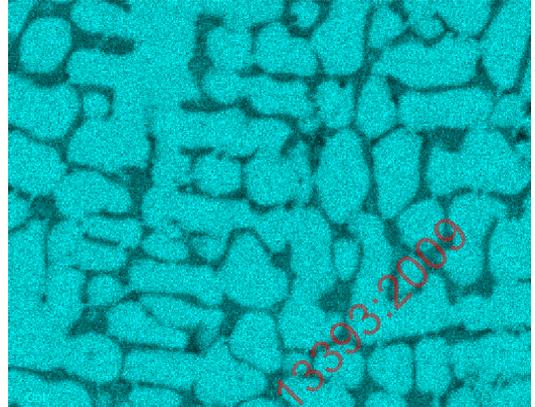
Table 21 — Co-PC Group

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 0,7 % to 1,7 % C</li> <li>— Approximately 28 % Cr, 4 % W, 1 % Ni, 2 % Fe, balance Co</li> </ul>
<p><b>Microstructure:</b> Primary cobalt solid solution with eutectic carbides</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness (as deposited): 40 R<sub>C</sub> to 45 R<sub>C</sub></li> <li>— Seldom heat treated, little hardness change occurs in heat treatment</li> <li>— Very difficult to machine using carbide tools; grinding is preferred</li> <li>— Good impact resistance and abrasion resistance</li> <li>— Good metal-to-metal wear resistance</li> <li>— High corrosion resistance</li> <li>— High resistance to thermal shock, oxidizing and reducing atmospheres</li> </ul>
<p><b>Applications:</b> Valve seats and valve faces in internal combustion engines and other hot-fluid streams containing particulates</p>
<p>The optical image below cannot resolve the eutectic, but the scanning electron microscope (SEM) back-scattered electron image can. Note that cobalt is shown by the SEM to be concentrated in the dendrite cores, while chromium and tungsten are shown to be concentrated in the inter-dendritic eutectic regions.</p>
<p>(continued)</p>

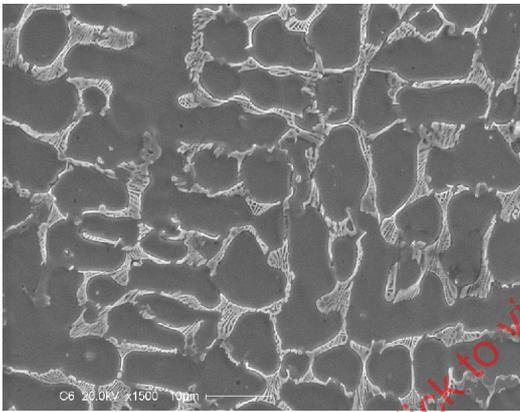
Table 21 (continued)



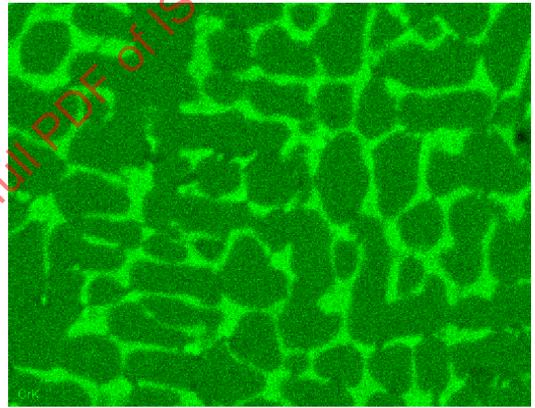
Optical image ×200



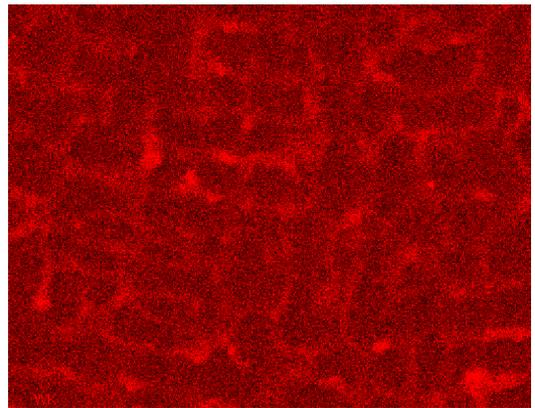
Co map



Back-scattered electron image, ×1 500



Cr map



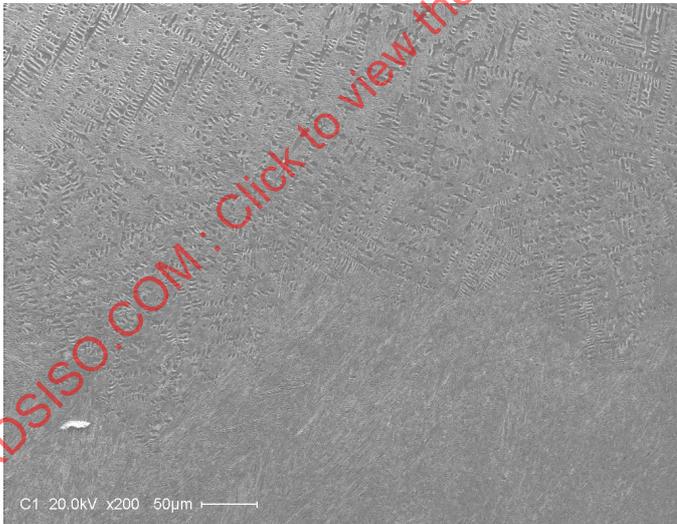
W map

Photomicrographs provided by The Lincoln Electric Company.

**7.3 Co-NE Group (near-eutectic mix of carbides and cobalt solid-solution alloy)**

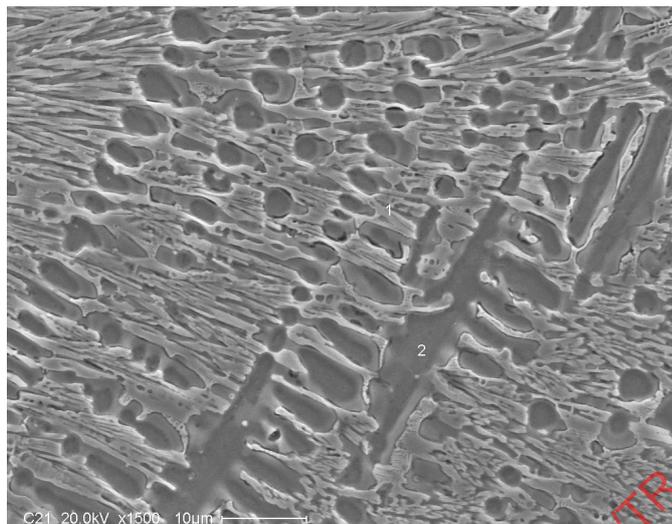
See Table 22.

**Table 22 — Co-NE Group**

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 1,8 % to 2,2 % C</li> <li>— Approximately 28 % Cr, 12 % W, 1 % Ni, 2 % Fe, balance Co</li> </ul>
<p><b>Microstructure:</b> Near-eutectic mix of carbides and cobalt alloy solid solution, only traces of primary cobalt or primary carbides</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness (as deposited): 45 R<sub>C</sub> to 50 R<sub>C</sub></li> <li>— Difficult to deposit without cracking, even with preheating at 300 °C to 400 °C. Seldom post-weld heat treated, little hardness change occurs in heat treatment</li> <li>— Not machineable, grinding only</li> <li>— Moderate impact resistance</li> <li>— High abrasion resistance</li> <li>— Moderate corrosion resistance</li> <li>— Retains abrasion resistance at high temperatures</li> </ul>
<p><b>Applications:</b> High-temperature mixers, sliding components in furnaces</p>

<p>5 % HCl electrolytic etch                  Optical, ×200                  Photomicrograph provided by The Lincoln Electric Company, USA.</p>

(continued)

Table 22 (continued)



SEM,  $\times 1\ 500$

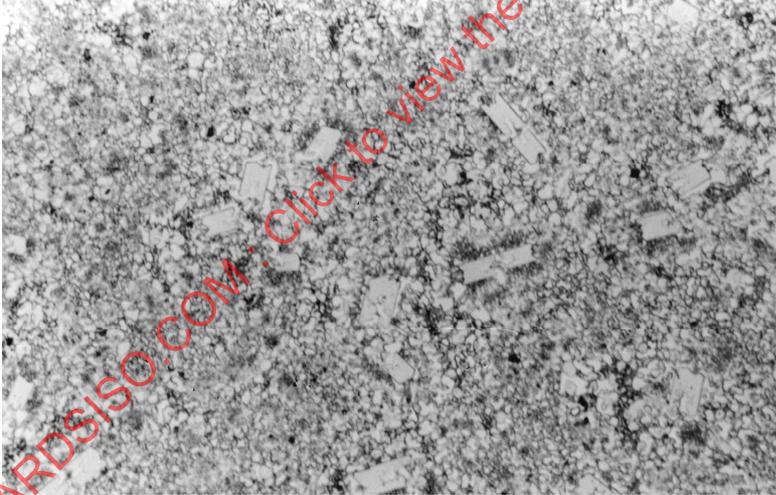
Scattered primary cobalt solid-solution dendrites (2) appear among the extensive cobalt plus carbide eutectic (1).

Photomicrograph provided by The Lincoln Electric Company, USA.

7.4 Co-PKE Group (primary carbides with eutectic)

See Table 23.

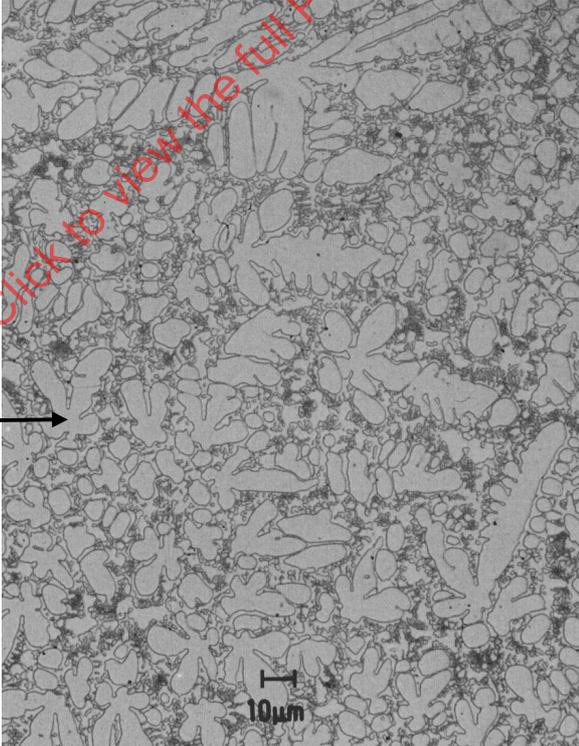
Table 23 — Co-PKE Group

<p><b>Typical composition:</b></p> <ul style="list-style-type: none"> <li>— 2,5 % C</li> <li>— 30 % Cr, 12 % W, 4 % Fe</li> </ul>
<p><b>Microstructure:</b> Primary <math>M_7C_3</math> type carbides in a matrix of eutectic carbides and solid-solution cobalt alloy</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness (as deposited): 50 R<sub>C</sub> to 55 R<sub>C</sub></li> <li>— Very difficult to deposit without cracking, even with very high preheating. Seldom heat treated, little hardness change occurs in heat treatment</li> <li>— Not machineable, grinding only</li> <li>— Low impact resistance</li> <li>— Exceptional abrasion resistance at high temperatures (1 000 °C and upwards)</li> <li>— Moderate corrosion resistance</li> <li>— Good resistance to oxidizing environments</li> </ul>
<p><b>Applications:</b> High-temperature abrasion resistance, such as catalyst slide trays, furnace chains</p>

<p>Optical, ×400 Photomicrograph provided by Tokuden Co., Ltd., Japan.</p>

## 7.5 Co-LP Group (cobalt solid-solution alloy with Laves phase particles)

See Table 24.

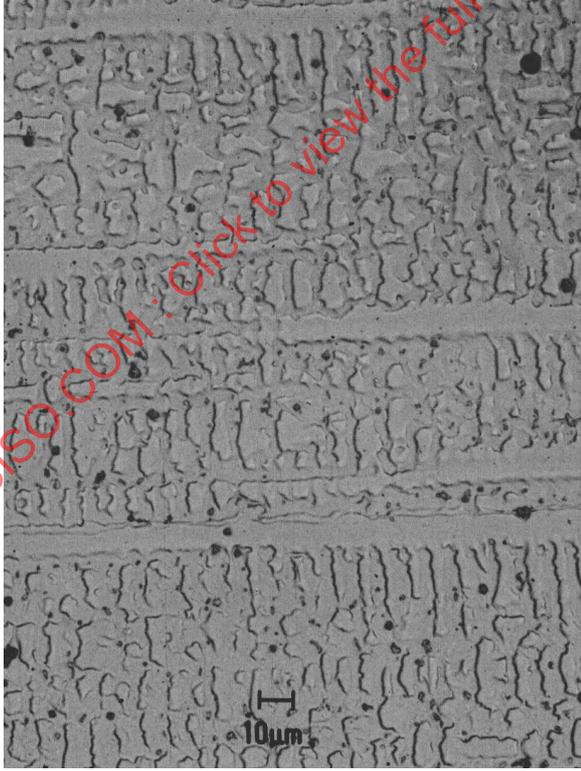
**Table 24 — Co-LP Group**

<b>Typical composition:</b> 0,08 % C max., 25 % to 35 % Mo, 8 % to 18 % Cr, 2 % to 4 % Si, balance Co
<b>Microstructure:</b> Cobalt alloy solid solution containing Laves-phase particles (Mo-Cr-Si intermetallic compounds)
<b>Main characteristics:</b> <ul style="list-style-type: none"> <li>— Hardness (as deposited): 40 R<sub>C</sub> to 45 R<sub>C</sub></li> <li>— Heat treatment can be used to precipitate additional Laves phase, increase the hardness to over 50 R<sub>C</sub></li> <li>— Machineable with carbide tools</li> <li>— Good impact resistance</li> <li>— Exceptional metal-to-metal wear resistance</li> <li>— Moderate abrasion resistance</li> <li>— Moderate corrosion resistance</li> <li>— Typical example: 0,02 % C, 3,6 % Si, 0,3 % Ni, 17 % Cr, 30 % Mo, 0,7 % Fe, balance Co</li> </ul>
<b>Applications:</b> Unlubricated bearing surfaces, valve seats and valve faces

<p>Photomicrograph provided by Nippon Welding Rod Co., Ltd, Japan.</p> <p style="text-align: center;"><b>Microstructure of Type Co-LP, ×400</b></p>

7.6 Ni-NS Group (nickel alloy solid solution)

See Table 25.

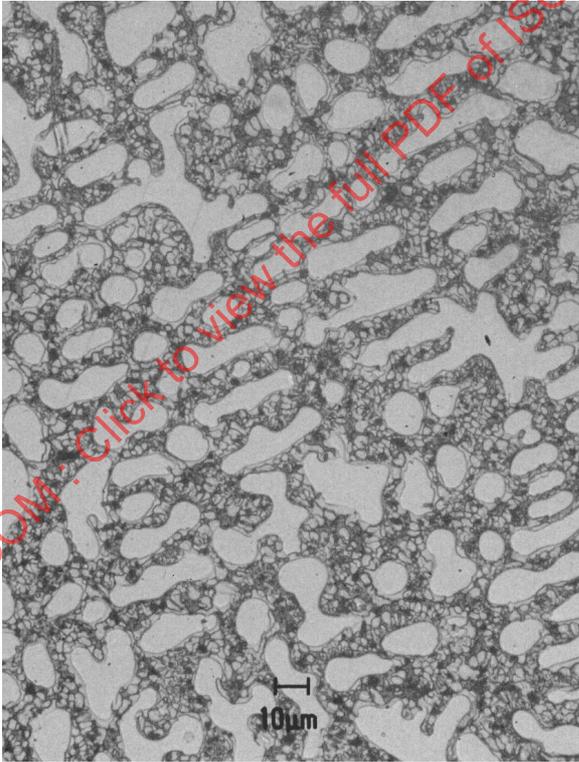
Table 25 — Ni-NS Group

<p><b>Typical composition:</b> 0,1 % C, 17 % Cr, 17 % Mo, 4,5 % W, 5,5 % Fe, balance Ni</p>
<p><b>Microstructure:</b> Primarily nickel-base alloy solid solution; some intermetallic compound precipitation is possible after prolonged high-temperature exposure</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness (as deposited): 90 R<sub>B</sub></li> <li>— Seldom heat treated, may soften in heat treatment</li> <li>— Machineable in the as-welded condition</li> <li>— Excellent impact resistance</li> <li>— Limited metal-to-metal wear resistance</li> <li>— Low abrasion resistance</li> <li>— High corrosion resistance</li> <li>— High resistance to thermal shock</li> </ul>
<p><b>Applications:</b> Forging dies, hot extrusion dies</p>

<p>Photomicrograph provided by Nippon Welding Rod Co., Ltd., Japan.</p> <p style="text-align: center;"><b>Microstructure of Type Ni-NS</b></p>

## 7.7 Ni-B Group (nickel borides)

See Table 26.

**Table 26 — Ni-B Group**

<p><b>Typical composition:</b> 0,2 % to 0,5 % C, 1,5 % to 1,8 % B, 1 % to 8 % Cr, 2 % to 4 % Si, up to 2 % Fe, balance Ni</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness (as deposited): 20 R<sub>C</sub> to 40 R<sub>C</sub></li> <li>— Seldom heat treated, little hardness change with heat treatment</li> <li>— Machineable with carbide tools (difficult), grinding preferred</li> <li>— Moderate impact resistance</li> <li>— Good abrasion resistance</li> <li>— Moderate corrosion resistance</li> </ul>
<p><b>Applications:</b> Self-fluxing, low-melting hardfacing alloy for abrasion resistance, often applied in thin single layers</p>
<div style="text-align: center;">  </div> <p>Composition of example: 0,25 % C, 3,5 % Si, 7,5 % Cr, 2,5 % Fe, 1,6 % B, balance Ni.  Primary nickel alloy solid-solution dendrites surrounded by nickel/chromium/boride eutectic.  Photomicrograph provided by Nippon Welding Rod Co., Ltd., Japan.</p> <p style="text-align: center;"><b>Microstructure of Type Ni-B</b></p>

7.8 Ni-CB Group (chromium borides in nickel alloy/boride eutectic)

See Table 27.

Table 27 — Ni-CB Group

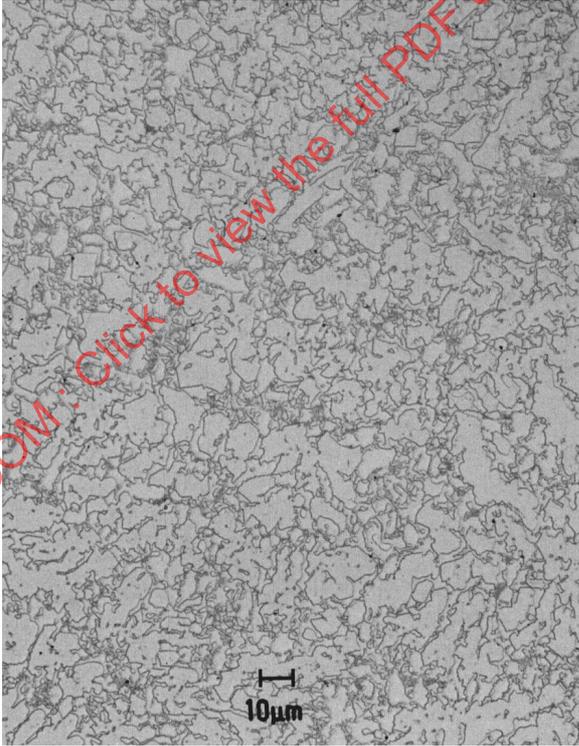
<b>Typical composition:</b> 0,5 % C, 2,5 % to 3,5 % B, 11 % to 15 % Cr, 3,5 % Fe, 4 % Si, balance Ni
<b>Microstructure:</b> Primary chromium borides in nickel alloy/boride eutectic
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness (as deposited): 50 R<sub>C</sub> to 60 R<sub>C</sub></li> <li>— Seldom heat treated, little hardness change in heat treatment</li> <li>— Not machineable, grinding only</li> <li>— Moderate impact resistance</li> <li>— Exceptional abrasion resistance</li> <li>— Moderate corrosion resistance</li> </ul>
<b>Applications:</b> Severe abrasion resistance in aqueous media

<p>Hexagonal chromium boride rods in a nickel-chromium-boron eutectic matrix.                  Composition: 0,7 % C, 4,3 % Si, 15,0 % Cr, 2,7 % Fe, 3,0 % B, balance Ni.                  Photomicrograph provided by Tukoden Co., Ltd., Japan.</p> <p style="text-align: center;"><b>Microstructure of Type Ni-CB, ×400</b></p>

## 7.9 Ni-LP Group (nickel-base alloy solid solution with Laves-phase particles)

See Table 28.

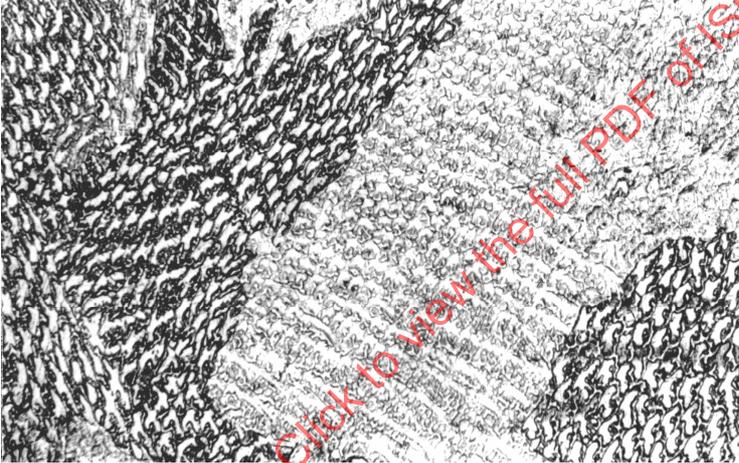
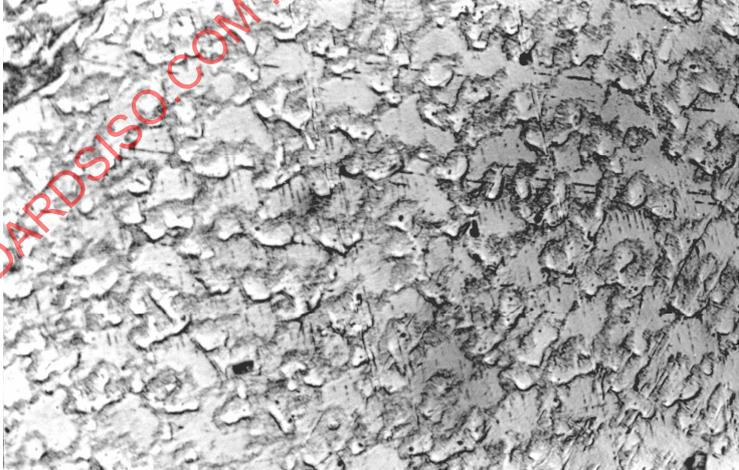
**Table 28 — Ni-LP Group**

<b>Typical composition:</b> 0,05 % C, 32 % Mo, 16 % Cr, 3,5 % Si, balance Ni
<b>Microstructure:</b> Nickel alloy solid solution with massive Laves-phase particles
<b>Main characteristics:</b> <ul style="list-style-type: none"> <li>— Hardness (as deposited): 40 R<sub>C</sub> to 50 R<sub>C</sub>, can harden a few more R<sub>C</sub> points during heat treatment if additional Laves-phase precipitates</li> <li>— Very difficult to machine, grinding preferred</li> <li>— Moderate impact resistance</li> <li>— Exceptional metal-to-metal wear resistance, especially to galling, in unlubricated conditions</li> <li>— Good corrosion resistance</li> <li>— Retains wear resistance over a wide temperature range</li> </ul>
<b>Applications:</b> Valves, piston rings, wear pads and seals

Photomicrograph provided by Nippon Welding Rod Co., Ltd., Japan.
<b>Microstructure of Type Ni-LP</b>

7.10 Cu-BS Group (solid-solution bronzes)

See Table 29.

Table 29 — Cu-BS Group

<b>Typical composition:</b> Up to 4 % Si or up to 2 % Sn, balance mainly copper, may contain some phosphorus
<b>Microstructure:</b> Copper-rich solid-solution alloy hardened by solute elements
<b>Main characteristics:</b> <ul style="list-style-type: none"> <li>— Hardness (as deposited): 80 R<sub>B</sub> to 90 R<sub>B</sub></li> <li>— Seldom heat treated, little effect</li> <li>— Readily machineable</li> <li>— High impact resistance</li> <li>— Very good corrosion resistance in fresh water and seawater</li> </ul>
<b>Applications:</b> Bearings, pump and valve parts, corrosion-resistant overlays
 <p style="text-align: right;">×100</p>  <p style="text-align: right;">×400</p>
<p>Composition: 3,48 % Si, 0,88 % Mn, balance Cu.</p> <p>Photomicrographs provided by Tokuden Co., Ltd., Japan.</p> <p style="text-align: center;"><b>Microstructure of Type Cu-BS</b></p>

### 7.11 Cu-BT Group (two-phase bronzes)

See Table 30.

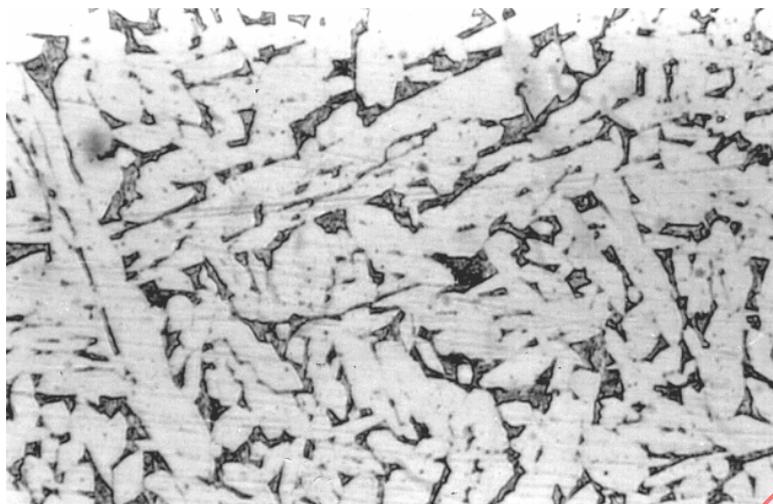
**Table 30 — Cu-BT Group**

<b>Typical composition:</b> 7 % to 15 % Al or 4 % to 9 % Sn, up to 5 % Fe, may contain Mn and/or Ni, balance Cu
<b>Microstructure:</b> Cu-bearing intermetallic compounds in a copper alloy solid-solution matrix
<b>Main characteristics:</b> <ul style="list-style-type: none"> <li>— Hardness: depends upon Al and Sn content; low alloy, about 140 Brinell; high alloy, about 300 Brinell</li> <li>— Seldom heat treated</li> <li>— Machineable</li> <li>— Low alloys have high impact resistance; high alloys have low impact resistance</li> <li>— Very good metal-to-metal wear resistance</li> <li>— Low Al alloys have good corrosion resistance in media such as seawater; high-Al alloys are not recommended for corrosion-resistant applications.</li> <li>— Service is generally limited to temperatures below about 200 °C</li> </ul>
<b>Applications:</b> Bearing surfaces, gears, cams, corrosion-resistant overlays for some alloys

<p>Copper alloy solid solution plus copper alloy eutectic.  Composition: 9,84 % Al, 0,92 % Fe, balance copper.  Photomicrograph provided by Tokuden Co., Ltd., Japan.</p> <p style="text-align: center;"><b>Microstructure of Type Cu-BT, ×100</b></p>

(continued)

Table 30 (continued)



×400

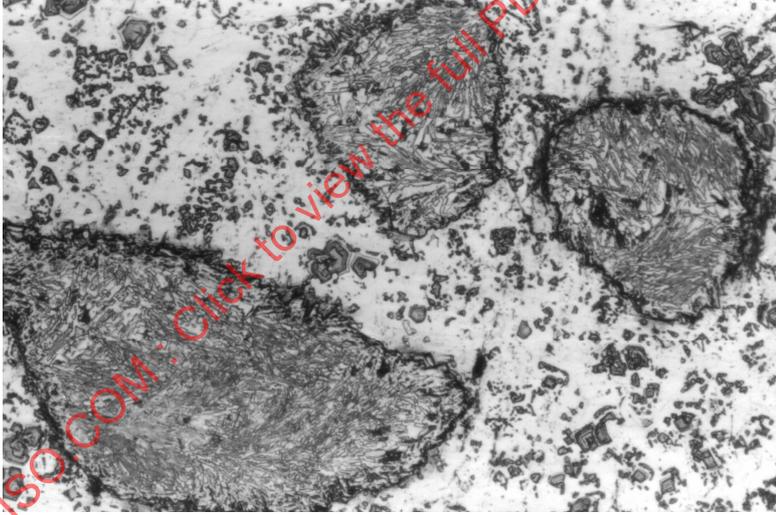
Photomicrograph provided by Tokuden Co., Ltd., Japan.

STANDARDSISO.COM : Click to view the full PDF of ISO/TR 13393:2009

## 7.12 W-Fe Group (tungsten carbide in an iron matrix)

See Table 31.

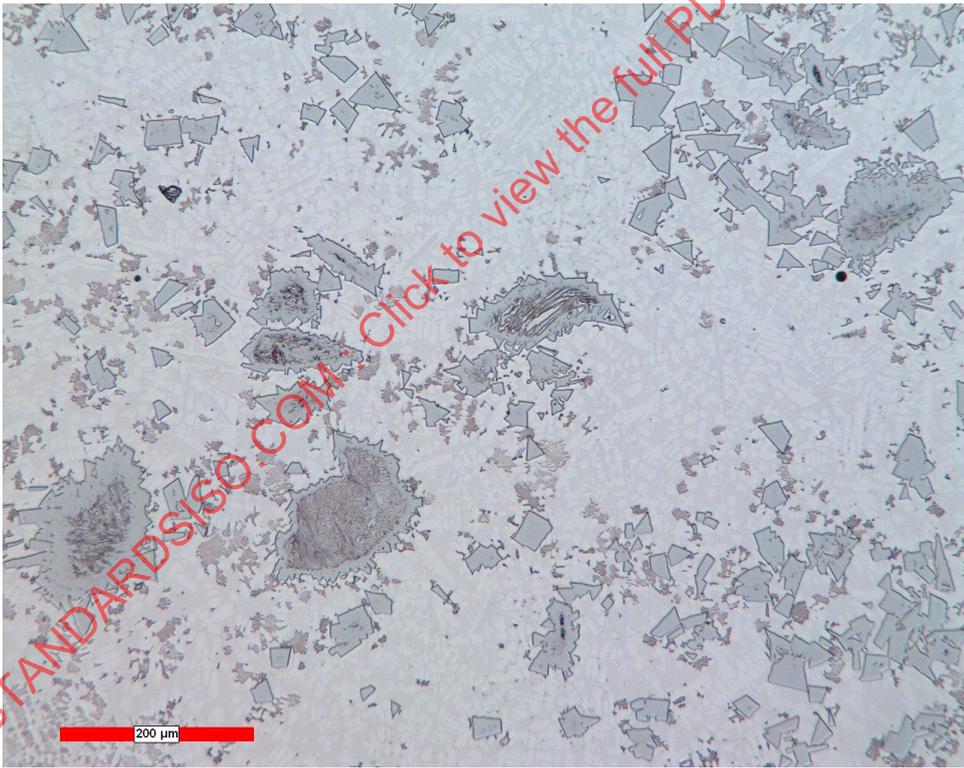
**Table 31 — W-Fe Group**

<p><b>Typical composition:</b> 40 % to 60 % WC and/or <math>W_2C</math>, balance Fe</p>
<p><b>Microstructure:</b> Chunks of unmelted tungsten carbide in a steel matrix</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness (as deposited): matrix – 30 <math>R_C</math> to 60 <math>R_C</math></li> <li>— Particles: about 2 400 HV20</li> <li>— Heat treatment serves no useful purpose</li> <li>— Not machineable, grinding only</li> <li>— Low impact resistance</li> <li>— Exceptional abrasion resistance where particles are concentrated. There is a tendency for the particles to sink to the bottom of a weld deposit, so that the top portion of the deposit will wear much more rapidly than the bottom.</li> <li>— Low corrosion resistance</li> </ul>
<p><b>Applications:</b> Rock drill bits, tool joints, augers, excavator teeth, agricultural implements</p>

<p>Unfused chunks of tungsten carbide embedded in an iron-base matrix. Photomicrograph provided by Nippon Engineering Industry Service, Japan.</p> <p style="text-align: center;"><b>Microstructure of Type W-Fe Deposit</b></p>

7.13 W-Ni Group (tungsten carbide in a nickel-base alloy matrix)

See Table 32.

Table 32 — W-Ni Group

<p><b>Typical composition:</b> 40 % to 60 % WC and/or W<sub>2</sub>C, balance nickel-base alloy</p>
<p><b>Microstructure:</b> Chunks of unmelted tungsten carbide in a nickel-base alloy matrix</p>
<p><b>Main characteristics:</b></p> <ul style="list-style-type: none"> <li>— Hardness (as deposited): matrix – 30 R<sub>C</sub> to 60 R<sub>C</sub></li> <li>— Particles: about 2 400 HV20</li> <li>— Heat treatment serves no useful purpose</li> <li>— Not machineable, grinding only</li> <li>— Low impact resistance</li> <li>— Exceptional abrasion resistance where particles are concentrated. There is a tendency for the particles to sink to the bottom of a weld deposit, so that the top portion of the deposit will wear much more rapidly than the bottom.</li> <li>— Moderate corrosion resistance</li> </ul>
<p><b>Applications:</b> Dredges, rock drill bits, tool joints, augers, excavator teeth, agricultural implements</p>
<div style="text-align: center;">  <p>200 μm</p> <p>×150</p> </div> <p>Microstructure of Ni-W group: approximate composition: 2,5 % C, 0,7 % Si, 45 % W, 1,0 % B, balance Ni. The small angular particles are WC and the larger particles are W<sub>2</sub>C. The matrix is a Ni-Cr-B-Si eutectic. Photomicrograph provided by The Stoody Company (a division of Thermadyne Industries).</p>