

TC 17

TECHNICAL REPORT

ISO/TR 9769

Second edition
1990-02-15

Steel and iron — Review of available methods of analysis

Aciers et fontes — Vue d'ensemble des méthodes d'analyse disponibles

STANDARDSISO.COM : Click to view the full PDF of ISO/TR 9769:1990



Reference number
ISO/TR 9769 : 1990 (E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The main task of ISO technical committees is to prepare International Standards. In exceptional circumstances a technical committee may propose the publication of a technical report of one of the following types:

- type 1, when the necessary support within the technical committee cannot be obtained for the publication of an International Standard, despite repeated efforts;
- type 2, when the subject is still under technical development requiring wider exposure;
- type 3, when a technical committee has collected data of a different kind from that which is normally published as an International Standard ("state of the art", for example).

Technical reports are accepted for publication directly by ISO Council. Technical reports of types 1 and 2 are subject to review within three years of publication, to decide whether they can be transformed into International Standards. Technical reports of type 3 do not necessarily have to be reviewed until the data they provide are considered to be no longer valid or useful.

ISO/TR 9769, which is a technical report of type 3, was prepared by Technical Committee ISO/TC 17, *Steel*.

This second edition cancels and replaces the first edition (ISO/TR 9769 : 1988), of which it constitutes a minor revision.

Annexes A and B of this Technical Report are for information only.

© ISO 1990

All rights reserved. No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Steel and iron — Review of available methods of analysis

1 Scope and field of application

This Technical Report aims to facilitate reference to the available international standard method(s) for the determination of required element(s) in steel and iron.

In this Technical Report, field of application, method of determination (principle) and precision (see informative annex A.) of each standard are stated.

STANDARDSISO.COM: Click to view the full PDF of ISO/TR 9769:1990

2 List of International Standards

2.1 Al Aluminium

Reference	Ed	Pages	Title
ISO 9658:1990		11	Steel - Determination of aluminium content - Flame atomic absorption spectrometric method

2.2 As Arsenic

to be prepared

2.3 B Boron

under preparation

2.4 Bi Bismuth

to be prepared

2.5 C Carbon

ISO 437:1982		4	Steel and cast iron - Determination of total carbon content - Combustion gravimetric method
ISO/TR 4830-1 :1978		6	Steel - Determination of low carbon contents - Part I: Manometric (low-pressure) method after combustion
ISO/TR 4830-2 :1978		10	Steel - Determination of low carbon contents - Part II: Titrimetric method after combustion
ISO/TR 4830-3 :1978		8	Steel - Determination of low carbon contents - Part III: Conductimetric measurement after combustion
ISO/TR 4830-4 :1978		8	Steel - Determination of low carbon contents - Part IV: Coulometric method after combustion
ISO 9556:1989		8	Steel and iron - Determination of total carbon content - Infrared absorption method after combustion in an induction furnace

2.6 Ca Calcium

under preparation

2.7 Ce Cerium

to be prepared

2.8 Co Cobalt

to be prepared

2.9 Cr Chromium

Reference	Ed	Pages	Title
ISO 4936:1984		3	Steel and cast iron - Determination of chromium content - Diphenylcarbazide spectrophotometric method
ISO 4937:1986		8	Steel and iron - Determination of chromium content - Potentiometric or visual titration method

2.10 Cu Copper

ISO 4943:1985		6	Steel and cast iron - Determination of copper content - Flame atomic absorption spectrometric method
ISO 4946:1984 (Corrected and reprinted:1986)		6	Steel and cast iron - Determination of copper content - 2,2'-Diquinolyl spectrophotometric method

2.11 Mg Magnesium

to be prepared

2.12 Mn Manganese

ISO 629:1982		4	Steel and cast iron - Determination of manganese content - Spectrophotometric method
--------------	--	---	--

2.13 Mo Molybdenum

ISO 4941:1978		4	Steels and cast irons - Determination of molybdenum content - Photometric method
---------------	--	---	--

2.14 N Nitrogen

Reference	Ed	Pages	Title
ISO 4945:1977		6	Steel - Determination of nitrogen content - Spectrophotometric method

2.15 Nb Niobium

ISO 9441:1988		6	Steel - Determination of niobium content - PAR spectrophotometric method
---------------	--	---	--

2.16 Ni Nickel

ISO 4938:1988		8	Steel and iron - Determination of nickel content - Gravimetric or titrimetric method
ISO 4939:1984 (Corrected and reprinted:1986)		6	Steel and cast iron - Determination of nickel content - Dimethylglyoxime spectrophotometric method
ISO 4940:1985		7	Steel and cast iron - Determination of nickel content - Flame atomic absorption spectrometric method

2.17 O Oxygen

to be prepared

2.18 P Phosphorus

ISO 2732:1984	2	3	Steel and cast iron - Determination of phosphorus content - Phosphovanadomolybdate spectrophotometric method
---------------	---	---	--

2.19 Pb Lead

to be prepared

2.20 S Sulfur

Reference	Ed	Pages	Title
ISO 671:1982		5	Steel and cast iron - Determination of sulphur content - Combustion titrimetric method
ISO 4934:1980		5	Steel and cast iron - Determination of sulphur content - Gravimetric method
ISO 4935:1989		7	Steel and iron - Determination of sulfur content - Infrared absorption method after combustion in an induction furnace

2.21 Sb Antimony

under preparation

2.22 Si Silicon

ISO 439:1982		3	Steel and cast iron - Determination of total silicon - Gravimetric method
ISO 4829-1:1986		7	Steel and cast iron - Determination of total silicon content - Reduced molybdsilicate spectrophotometric method - Part 1: Silicon contents between 0,05 and 1,0 %
ISO 4829-2:1988		5	Steel and iron - Determination of total silicon content - Reduced molybdsilicate spectrophotometric method - Part 2: Silicon contents between 0,01 and 0,05 %

2.23 Sn Tin

to be prepared

2.24 Ta Tantalum

to be prepared

2.25 Ti Titanium

under preparation

2.26 V Vanadium

Reference	Ed	Pages	Title
ISO 4942:1988		6	Steel and iron - Determination of vanadium content - N-BPHA spectrophotometric method
ISO 4947:1986		6	Steel and cast iron - Determination of vanadium content - Potentiometric titration method
ISO 9647:1989		8	Steel and iron - Determination of vanadium content - Flame atomic absorption spectrometric method

2.27 W Tungsten

to be prepared

2.28 Zr Zirconium

to be prepared

STANDARDSISO.COM : Click to view the full PDF of ISO/TR 9769:1990

3 Synopsis of method

3.1 Al Aluminium

3.1.1 ISO 9658: 1989, Flame atomic absorption spectrometric method

(1) Scope

Determination of acid-soluble and/or total aluminium content between 0,005 % (m/m) and 0,20 % (m/m) in non-alloyed steel

(2) Definition

Acid-soluble aluminium for the method is defined as the aluminium dissolved in the hydrochloric and nitric acids mixture as specified in the procedure.

(3) Principle

Dissolution of a test portion in dilute hydrochloric and nitric acids

Fusion of the acid-insoluble material with orthoboric acid-potassium carbonate mixture

Spraying of the solution into a dinitrogen monoxide acetylene flame

Spectrometric measurement of the atomic absorption of the 309,3 nm spectral line emitted by an aluminium hollow cathode lamp

(4) Precision: see informative annex A.

Figure A.1.1; Precision for the determination of acid-soluble aluminium content

Figure A.1.2; Precision for the determination of total aluminium content

3.2 As Arsenic

to be prepared

3.3 B Boron

under preparation

3.4 Bi Bismuth

to be prepared

3.5 C Carbon

3.5.1 ISO 437: 1982, Combustion gravimetric method

(1) Scope

Determination of total carbon content not less than 0,1 % (m/m) in steel and cast iron

(2) Principle

Combustion of a test portion at a high temperature (1 200°C to 1 350°C) in a current of pure oxygen, if necessary in the presence of a flux and transformation of carbon into carbon dioxide

Absorption of the carbon dioxide carried by current of oxygen in soda asbestos contained in a weighed absorption bulb, and determination of the increase in mass

3.5.2 ISO/TR 4830-1: 1978, Part I: Manometric (low-pressure) method after combustion

(1) Scope

Determination of carbon content between 0,002 % (m/m) and 0,1 % (m/m) in steel

(2) Principle

Combustion of a test portion at a high temperature (1 200°C to 1 350°C, depending on the type of material) in a current of pure oxygen, converting the carbon to carbon dioxide

Entrainment of the carbon dioxide by the current of oxygen, elimination of oxides of sulphur and of water vapour, and separation of the carbon dioxide by solidification in a freezing trap immersed in liquid oxygen

After elimination of oxygen from the measuring system, vaporization of the carbon dioxide, by raising the temperature, into a calibrated volume which has been evacuated

Determination of the carbon content of the test portion by measuring the pressure in the volume which has previously been calibrated using known volumes of carbon dioxide

3.5.3 ISO/TR 4830-2: 1978, Part II: Titrimetric method after combustion

(1) Scope

Determination of carbon content between 0,005 % (m/m) and 0,1 % (m/m) in pure iron and steel

(2) Principle

Combustion of a test portion in an electric resistance furnace in a current of oxygen, in the presence of a fluxing agent which encourages the combustion, converting the carbon to carbon dioxide, which is absorbed in a mixture of pyridine and 2-aminoethanol or of formdimethylamide and 2-aminoethanol, and which is at the same time titrated using thymol blue as indicator

Calculation of the carbon content from the consumption of the standard volumetric solution; this solution being standardized against calcium carbonate (primary standard), which is heated to a temperature between 1 250°C and 1 400°C in the same furnace

3.5.4 ISO/TR 4830-3: 1978, Part III: Conductimetric method after combustion

(1) Scope

Determination of carbon content between 0,005 % (m/m) and 0,1 % (m/m) in steels

(2) Principle

Combustion of a test portion at a high temperature ($>1\ 250^{\circ}\text{C}$) in a current of pure oxygen, converting the carbon to carbon dioxide

Entrainment of the carbon dioxide by the current of oxygen, separation from the other volatile oxides and absorption by a dilute solution of sodium hydroxide

Deduction of the carbon content of the test portion from measurement of the variation in conductivity of the sodium hydroxide solution with respect to a reference

3.5.5 ISO/TR 4830-4: 1978, Part IV: Coulometric method after combustion

(1) Scope

Determination of carbon content between 0,005 % (m/m) and 0,1 % (m/m) in steels

(2) Principle

Combustion of a test portion at a high temperature ($>1\ 250^{\circ}\text{C}$; see note below) in a current of pure oxygen, converting the carbon to carbon dioxide. Entrainment of the carbon dioxide by the current of oxygen, and separation from the other volatile oxides. Absorption of the carbon dioxide in a barium hydroxide solution containing barium perchlorate: during the absorption, re-establishment of the initial barium hydroxide concentration by electrolysis of the barium perchlorate, the variation in the pH of the solution being followed by a pH meter. Measurement of the quantity of electricity required for re-establishment of the initial pH, in order to deduce the quantity of barium hydroxide formed and hence the quantity of carbon dioxide neutralized.

The pH of the absorbing solution must always be equal to or greater than 9,0.

NOTE - Certain types of apparatus are incapable of obtaining the temperature of 1 250°C necessary to comply with the requirements of this Technical Report.

3.5.6 ISO 9556: 1989, Infrared absorption method after combustion in an induction furnace

(1) Scope

Determination of total carbon content between 0,003 % (m/m) and 4,5 % (m/m) in steel and iron

(2) Principle

Combustion of a test portion with accelerator at a high temperature in an induction furnace in a current of pure oxygen and transformation of carbon into carbon dioxide and/or carbon monoxide

Measurement by infrared absorption of the carbon dioxide and/or carbon monoxide carried by a current of oxygen

(3) Precision: see informative annex A.

Figure A.5.1; Precision for the determination of total carbon content by ISO 9556

3.6 Ca Calcium

under preparation

3.7 Ce Cerium

to be prepared

3.8 Co Cobalt

to be prepared

3.9 Cr Chromium

3.9.1 ISO 4936: 1984, Diphenylcarbazide spectrophotometric method

(1) Scope

Determination of chromium content between 0,01 % (m/m) and 0,25 % (m/m) in steel and cast iron

(2) Principle

Dissolution of a test portion in nitric and perchloric acids

Oxidation of chromium in a phosphoric perchloric medium by potassium permanganate

Oxidation of diphenylcarbazide by chromium(VI)

Spectrophotometric measurement of the oxidized form of diphenylcarbazide at a wavelength of about 540 nm

3.9.2 ISO 4937: 1986, Potentiometric or visual titration method

(1) Scope

Determination of chromium content between 0,25 % (m/m) and 35 % (m/m) in steel and iron (If vanadium is present, the visual titration is applicable only to test portions containing less than 3 mg of vanadium.)

(2) Principle

Dissolution of a test solution with appropriate acids

Oxidation of chromium in an acid medium to chromium(VI) by ammonium peroxydisulfate in the presence of silver sulfate

Reduction of manganese(VII) by hydrochloric acid

Reduction of chromium(VI) by ammonium iron(II) sulfate standard solution

In the case of potentiometric detection, determination of the equivalence point by measurement of the potential variation when the ammonium iron(II) sulfate standard solution is being added

In the case of visual detection, titration of the excess ammonium iron(II) sulfate by potassium permanganate standard solution which also acts as the indicator

(3) Precision: see informative annex A.

Figures A.9.1 and A.9.2; Precision for the determination of chromium content by ISO 4937

3.10 Cu Copper

3.10.1 ISO 4943: 1985, Flame atomic absorption spectrometric method

(1) Scope

Determination of copper content between 0,004 % (m/m) and 0,5 % (m/m) in steel and cast iron

(2) Principle

Dissolution of a test portion in a mixture of hydrochloric, nitric and perchloric acids

Spraying of the solution into an air-acetylene flame

Spectrometric measurement of the atomic absorption of the 324,7 nm spectral line emitted by a copper hollow cathode lamp

(3) Precision: see informative annex A.

Figure A.10.1; Precision for determination of copper content by ISO 4943

3.10.2 ISO 4946: 1984, 2,2'-Diquinolyl spectrophotometric method

(1) Scope

Determination of copper content between 0,02 % (m/m) and 5 % (m/m) in steel and cast iron

(2) Principle

Dissolution of a test portion with appropriate acids

Fuming with perchloric acid to remove hydrochloric and nitric acids and dehydrate silicic acid

Reduction of copper(II) to copper(I) in hydrochloric acid solution by means of ascorbic acid

Formation of a coloured compound of copper(I) with 2,2'-diquinolyl

Spectrophotometric measurement at a wavelength of about 545 nm

(3) Precision: see informative annex A.

Figure A.10.2; Precision for determination of copper content by ISO 4946

3.11 Mg Magnesium

to be prepared

3.12 Mn Manganese

3.12.1 ISO 629: 1982, Spectrophotometric method

(1) Scope

Determination of manganese content between 0,01 % (m/m) and 4 % (m/m) in steel and cast iron

(2) Principle

Dissolution of a test portion in sulphuric-phosphoric acid mixture and nitric acid

Treatment of the test solution with perchloric acid

Formation of the permanganate ion by sodium periodate

Spectrophotometric measurement of the test solution at wavelength of about 545 nm

3.13 Mo Molybdenum

3.13.1 ISO 4941: 1978, Photometric method

(1) Scope

Determination of molybdenum content between 0,003 % (m/m) and 9 % (m/m) in steel and cast iron

Vanadium and tungsten interfere with the measurement if, because of their contents, the V/Mo ratio is greater than 16 or the W/Mo ratio is greater than 8

NOTE - Greater V/Mo or W/Mo ratios (up to 300) may, however, be permitted, but in such cases it is necessary to carry out the measurement very quickly after the extraction.

(2) Principle

Dissolution of a test portion in an appropriate mixture of acids and decomposition of the carbides by oxidation

Quantitative formation of a coloured compound of molybdenum, in the presence of thiocyanate, iron(II) and/or copper(II) ions and extraction of this compound using n-butyl acetate

Photometric measurement of the coloured compound at a wavelength of about 470 nm

NOTE - When the conditions of the procedure are respected, the coefficient of molecular absorption is $18\,930 \pm 60$.

3.14 N Nitrogen

3.14.1 ISO 4945: 1977, Spectrophotometric method

(1) Scope

Determination of nitrogen content between 0,002 % (m/m) and 0,050 % (m/m) in non-alloy and low-alloy steels

This method allows the determination only of the nitrogen content which can be converted to an ammonium salt and is applicable to non-alloy and low-alloy steels less than 0,6 % (m/m) of silicon.

(2) Principle

Dissolution of a test portion in dilute sulphuric acid

After concentration, progressive increasing of the temperature to above 300°C

Separation of ammonia from the ammonium salt formed, by displacement and distillation in a boiling sodium hydroxide medium and collecting in an acid medium

At ambient temperature, formation of a blue-colored complex between the ammonium ions and phenol in the presence of sodium hypochlorite and sodium pentacyanonitrosylferrate(II) (sodium nitroprusside)

Spectrophotometric measurement of the complex at a wavelength of about 640 nm

3.15 Nb Niobium

3.15.1 ISO 9441: 1988, PAR spectrophotometric method

(1) Scope

Determination of niobium content between 0,005 % (m/m) and 1,3 % (m/m) in steel

(2) Principle

Dissolution of a test portion in hydrochloric acid followed by oxidation with hydrogen peroxide

Precipitation of niobium and tantalum with phenylarsonic acid, using zirconium as a carrier

Formation of a complex of niobium with 4-(2-pyridylazo)-resorcinol (PAR) in a sodium tartrate medium buffered by sodium acetate solution adjusted to pH 6,3

Spectrophotometric measurement of the coloured compound at a wavelength of about 550 nm

(3) Precision: see informative annex A.

Figure A.15.1; Precision for determination of niobium content by ISO 9441

3.16 Ni Nickel

3.16.1 ISO 4938: 1988, Gravimetric or titrimetric method

(1) Scope

Determination of nickel content between 0,5 % (m/m) and 30 % (m/m) in steel and iron

(2) Principle

Dissolution of a test portion with appropriate acids

Precipitation of the nickel as nickel dimethylglyoxime

- Cobalt, if present, is oxidized by potassium hexacyanoferrate(III).

- Copper, if present with cobalt, preferably is removed by controlled-potential electrolysis.

Acid dissolution of the precipitate and filtration of the solution, followed by a second precipitation of the nickel as nickel dimethylglyoxime

In the case of the gravimetric finish, weighing of the dried nickel dimethylglyoxime precipitate

In the case of the titrimetric finish, acid dissolution of the precipitate, addition of excess EDTA.Na₂ solution and back titration of the excess EDTA.Na₂ by zinc solution using xylenol orange as an indicator

(3) Precision: see informative annex A.

Figure A.16.1; Precision for determination of nickel content by ISO 4938 - Gravimetric method

Figure A.16.2; Precision for determination of nickel content by ISO 4938 - Titrimetric method

3.16.2 ISO 4939: 1984, Dimethylglyoxime spectrophotometric method

(1) Scope

Determination of nickel content between 0,10 % (m/m) and 4 % (m/m) in steel and cast iron

Cobalt, copper and manganese may cause interferences.

(2) Principle

Dissolution of a test portion in hydrochloric, nitric and perchloric acids

Formation of a coloured complex of nickel(III) with dimethylglyoxime in ammoniacal solution containing iodine and potassium iodide

Spectrophotometric measurement at a wavelength of about 535 nm

- (3) Precision: see informative annex A.

Figure A.16.3; Precision for determination of nickel content by ISO 4939

3.16.3 ISO 4940: 1985, Flame atomic absorption spectrometric method

- (1) Scope

Determination of nickel content between 0,002 % (m/m) and 0,5 % (m/m) in steel and cast iron

- (2) Principle

Dissolution of a test portion in a mixture of appropriate acids followed by evaporation to fuming with perchloric acid

Spraying of the solution into an air-acetylene flame

Spectrometric measurement of the atomic absorption of the 352,5 nm spectral line emitted by a nickel hollow cathode lamp

NOTE - With some instruments it is not possible to obtain sufficient sensitivity at the wavelength of 352,5 nm for low concentrations of nickel near the bottom end of the application range and in such cases the alternative wavelength of 232,0 nm must be used.

At the wavelength of 352,5 nm, the signal-to-noise ratio is higher than at a wavelength of 232,0 nm. In general, use of the 352,5 nm line will give better reproducibility.

- (3) Precision: see informative annex A.

Figure A.16.3; Precision for determination of nickel content by ISO 4940

3.17 O Oxygen

to be prepared

3.18 P Phosphorus

3.18.1 ISO 2732: 1984, Phosphovanadomolybdate spectrophotometric method

- (1) Scope

Determination of phosphorus content between 0,005 % (m/m) and 1,5 % (m/m) in steel and cast iron, provided that tungsten, niobium, tantalum and zirconium contents are not higher than 1 % (m/m) for each of these four elements and titanium content is not higher than 2 % (m/m)

(2) Principle

Dissolution of a test portion in an oxidizing acid mixture

Conversion of phosphorus to phosphovanadomolybdate in perchloric-nitric acid solution

Extraction of phosphovanadomolybdate into 4-methyl-2-pentanone with citric acid present to complex arsenic

Spectrophotometric measurement at a wavelength of about 425 nm

3.19 Pb Lead

to be prepared

3.20 S Sulfur

3.20.1 ISO 671: 1982, Combustion titrimetric method

(1) Scope

Determination of sulfur content in steel and cast iron

(2) Principle

Combustion of a test portion at a high temperature (1 450°C) in a current of pure oxygen, if necessary in the presence of a metal flux and transformation of sulfur into sulfur dioxide

Absorption of the gases resulting from combustion, freed from oxide dust, by a solution of potassium sulfate and hydrogen peroxide

Titration of the absorbent solution with a standard sodium borate solution

3.20.2 ISO 4934: 1980, Gravimetric method

(1) Scope

Determination of sulfur content greater than 0,003 % (m/m) in steel and cast iron, excluding steel containing selenium

The method is particularly suitable as a reference method for the standardization of samples on which certified standard values are to be established.

(2) Principle

Dissolution of a test portion in dilute nitric acid in the presence of bromine, or in dilute nitric acid and concentrated hydrochloric acid in the presence of bromine (with the aid of an appropriate device to prevent sulfur losses)

Addition of hydrofluoric acid and perchloric acid and evaporation of the solution until white fumes of perchloric acid are evolved

If necessary, volatilization of chromium as chromyl chloride

Chromatographic separation of the sulfate ions in an alumina column and elution with ammonium hydroxide solution

Precipitation of the sulfate ions as barium sulfate under carefully controlled conditions and filtering, washing, heating and weighing

3.20.3 **ISO 4935: 1989**, Infrared absorption method after combustion in an induction furnace

(1) Scope

Determination of sulfur content between 0,002 % (m/m) and 0,10 % (m/m) in steel and iron

(2) Principle

Combustion of a test portion with accelerator at a high temperature in a high frequency induction furnace in a current of pure oxygen and transformation of sulfur into sulfur dioxide

Measurement by infrared absorption of the sulfur dioxide carried by a current of oxygen

(3) Precision: see informative annex A.

Figure A.20.1; Precision for determination of sulfur content by ISO 4935

3.21 **Sb** Antimony

under preparation

3.22 **Si** Silicon

3.22.1 **ISO 439:1982**, Gravimetric method

(1) Scope

Determination of total silicon content between 0,10 % (m/m) and 8,0 % (m/m) in steel and cast iron

(2) Principle

Dissolution of a test portion in hydrochloric and nitric acids

Conversion of silica into hydrated silica by fuming with perchloric acid

Filtration of the hydrated silica, ignition of the impure silica and then weighing

Treatment of the ignited residue with hydrofluoric and sulfuric acids, followed by ignition and weighing

3.22.2 **ISO 4829-1: 1986**, Reduced molybdosilicate spectrophotometric method
- Part 1: Silicon contents between 0,05 and 1,0 %

(1) Scope

Determination of total silicon content between 0,05 % (m/m) and 1,0 % (m/m) in steel and iron soluble in one or the other of the alternative acid mixtures

(2) Principle

Dissolution of a test portion in an acid mixture appropriate to the alloy composition

Fusion of the acid-insoluble residue with sodium peroxide

Formation of the oxidized molybdosilicate (yellow) in weak acid solution

Selective reduction of the molybdosilicate complex to reduced blue complex with ascorbic acid, after increasing the sulfuric acid concentration and adding oxalic acid to prevent the interference of phosphorus, arsenic and vanadium

Spectrophotometric measurement of the reduced blue complex at a wavelength of about 810 nm

(3) Precision: see informative annex A.

Figure A.22.1; Precision for determination of silicon content by ISO 4829-1

3.22.3 **ISO 4829-2: 1988**, Reduced molybdosilicate spectrophotometric method
- Part 2: Silicon contents between 0,01 and 0,05 %

(1) Scope

Determination of total silicon content between 0,01 % (m/m) and 0,05 % (m/m) in steel and iron

(2) Principle

Dissolution of a test portion in a hydrochloric acid/nitric acid mixture

Fusion of the acid-insoluble residue with sodium peroxide

Formation of the oxidized molybdosilicate (yellow) complex in weak acid solution

Selective reduction of the molybdosilicate complex to a blue complex with ascorbic acid, after increasing the sulfuric acid concentration and adding oxalic acid to prevent the interference of phosphorus, arsenic and vanadium

Spectrophotometric measurement of the reduced blue complex at a wavelength of about 810 nm

(3) Precision: see table 1.

Table 1

Silicon, % (m/m)			
Content	<u>r</u>	<u>R_w</u>	<u>R</u>
0,008	0,002 0	0,002 8	0,005 1
0,015	0,002 2	0,005 7	0,007 2
0,024	0,004 5	0,005 3	0,005 2
0,043	0,006 0	0,007 0	0,009 8
0,055	0,003 8	0,003 2	0,003 8

3.23 Sn Tin

to be prepared

3.24 Ta Tantalum

to be prepared

3.25 Ti Titanium

under preparation

3.26 V Vanadium

3.26.1 ISO 4942: 1988, N-BPHA spectrophotometric method

(1) Scope

Determination of vanadium content between 0,005 % (m/m) and 0,50 % (m/m) in steel and iron

(2) Principle

Dissolution of a test portion with appropriate acids

Addition of orthophosphoric acid to an aliquot of the solution thus obtained to prevent the interference of iron, and addition of potassium permanganate to oxidize vanadium to the pentavalent state

Selective reduction of excess permanganate by sodium nitrite in the presence of urea and treatment with N-BPHA and hydrochloric acid to form a complex, followed by extraction of the complex into trichloromethane

Spectrophotometric measurement of the absorbance at approximately 535 nm

- (3) Precision: see informative annex A.

Figure A.26.1; Precision for determination of vanadium content by ISO 4942

3.26.2 ISO 4947: 1986, Potentiometric titration method

- (1) Scope

Determination of vanadium content between 0,04 % (m/m) and 2 % (m/m) in steel and cast iron

- (2) Principle

Dissolution of a test portion with appropriate acids

Addition of hydrofluoric acid to keep tungsten in solution

Oxidation of chromium and vanadium by potassium peroxydisulfate

Partial oxidation of chromium

While checking the potential of the solution,

- reduction of chromium(VI) and vanadium(V) by ammonium iron(II) sulfate;

- oxidation of vanadium by slight excess of potassium permanganate; reduction of the excess permanganate by sodium nitrite, and reduction of the excess sodium nitrite by sulfamic acid

Potentiometric titration of vanadium by ammonium iron(II) sulfate standard solution

- (3) Precision: see informative annex A.

Figure A.26.2; Precision for determination of vanadium content by ISO 4947

3.26.3 ISO 9647: 1989, Flame atomic absorption spectrometric method

- (1) Scope

Determination of vanadium content between 0,005 % (m/m) and 1,0 % (m/m) in steel and iron, provided that tungsten content in the test portion is not higher than 10 mg and/or titanium is not higher than 5 mg

(2) Principle

Dissolution of a test portion in hydrochloric, nitric and perchloric acids

Addition of aluminium solution as spectrochemical buffer

Spraying of the solution into a dinitrogen monoxide-acetylene flame

Spectrometric measurement of the atomic absorption of the 318,4 nm spectral line emitted by a vanadium hollow cathode lamp

(3) Precision: see informative annex A.

Figure A.26.3; Precision for determination of vanadium content by ISO 9647

3.27 **W** Tungsten

to be prepared

3.28 **Zr** Zirconium

to be prepared

STANDARDSISO.COM : Click to view the full PDF of ISO/TR 9769:1990


Informative annex A

Graphical representation of precision data

- A.1.1 **Aluminium** (acid-soluble aluminium) - Flame atomic absorption spectrometric method - ISO 9658: 1989
- A.1.2 **Aluminium** (total) - Flame atomic absorption spectrometric method - ISO 9658: 1989
- A.5.1 **Carbon** (total) - Infrared absorption method after combustion in an induction furnace - ISO 9556: 1989
- A.9.1 **Chromium** - Potentiometric titration method - ISO 4937: 1986
- A.9.2 **Chromium** - Visual titration method - ISO 4937:1986
- A.10.1 **Copper** - Flame atomic absorption spectrometric method - ISO 4943: 1985
- A.10.2 **Copper** - 2,2'-Diquinolyl spectrophotometric method - ISO 4946: 1984
- A.15.1 **Niobium** - PAR spectrophotometric method - ISO 9441: 1988
- A.16.1 **Nickel** - Gravimetric method - ISO 4938: 1988
- A.16.2 **Nickel** - Titrimetric method - ISO 4938: 1988
- A.16.3 **Nickel** - Dimethylglyoxime spectrophotometric method - ISO 4939: 1984
- A.16.4 **Nickel** - Flame atomic absorption spectrometric method - ISO 4940: 1985
- A.20.1 **Sulfur** - Infrared absorption method after combustion in an induction furnace - ISO 4935: 1989
- A.22.1 **Silicon** - Reduced molybdosilicate spectrophotometric method - ISO 4829-1: 1986
- A.26.1 **Vanadium** - N-BPHA spectrophotometric method - ISO 4942: 1988
- A.26.2 **Vanadium** - Potentiometric titration method - ISO 4947:1986
- A.26.3 **Vanadium** - Flame atomic absorption spectrometric method - ISO 9647: 1989


NOTE - The types of precision (r , R_w and R) and the conditions under which the tests were carried out are listed in informative annex B.

Figure A.1.1 Precision for determination of acid-soluble aluminium content - Flame atomic absorption spectrometric method

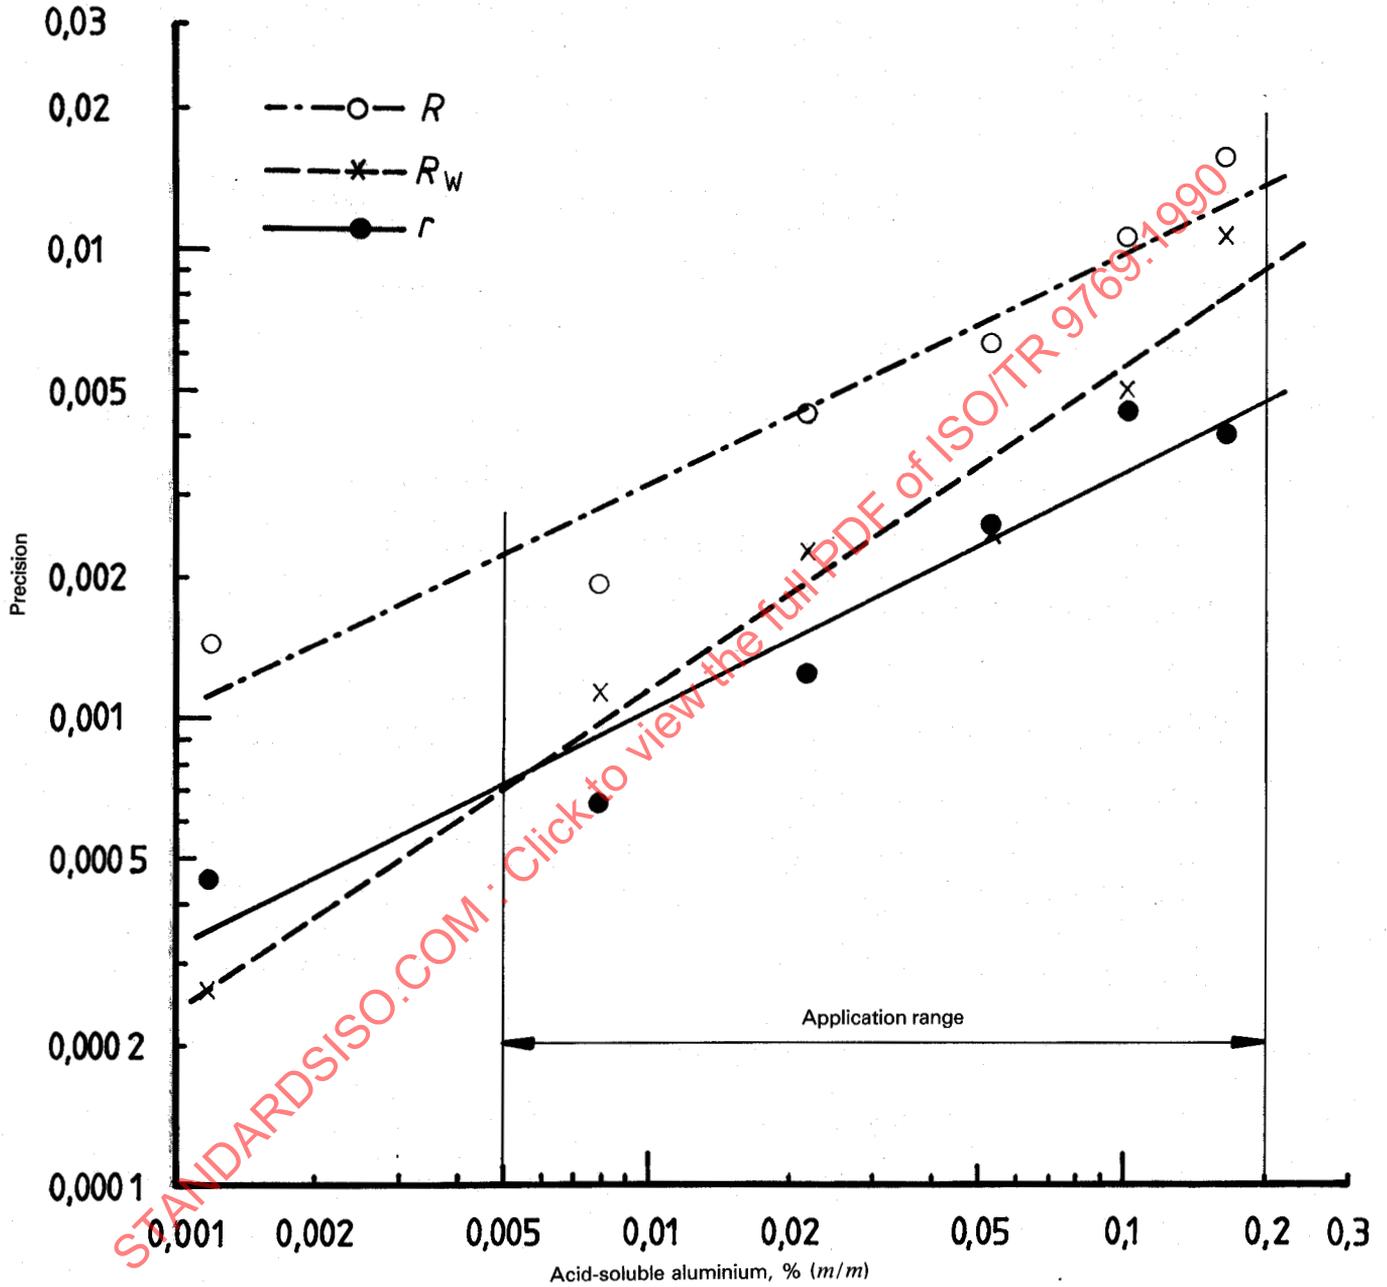


R : reproducibility
 R_w : within-laboratory reproducibility
 r : repeatability

Figure A.1.2 Precision for determination of total aluminium content - Flame atomic absorption spectrometric method

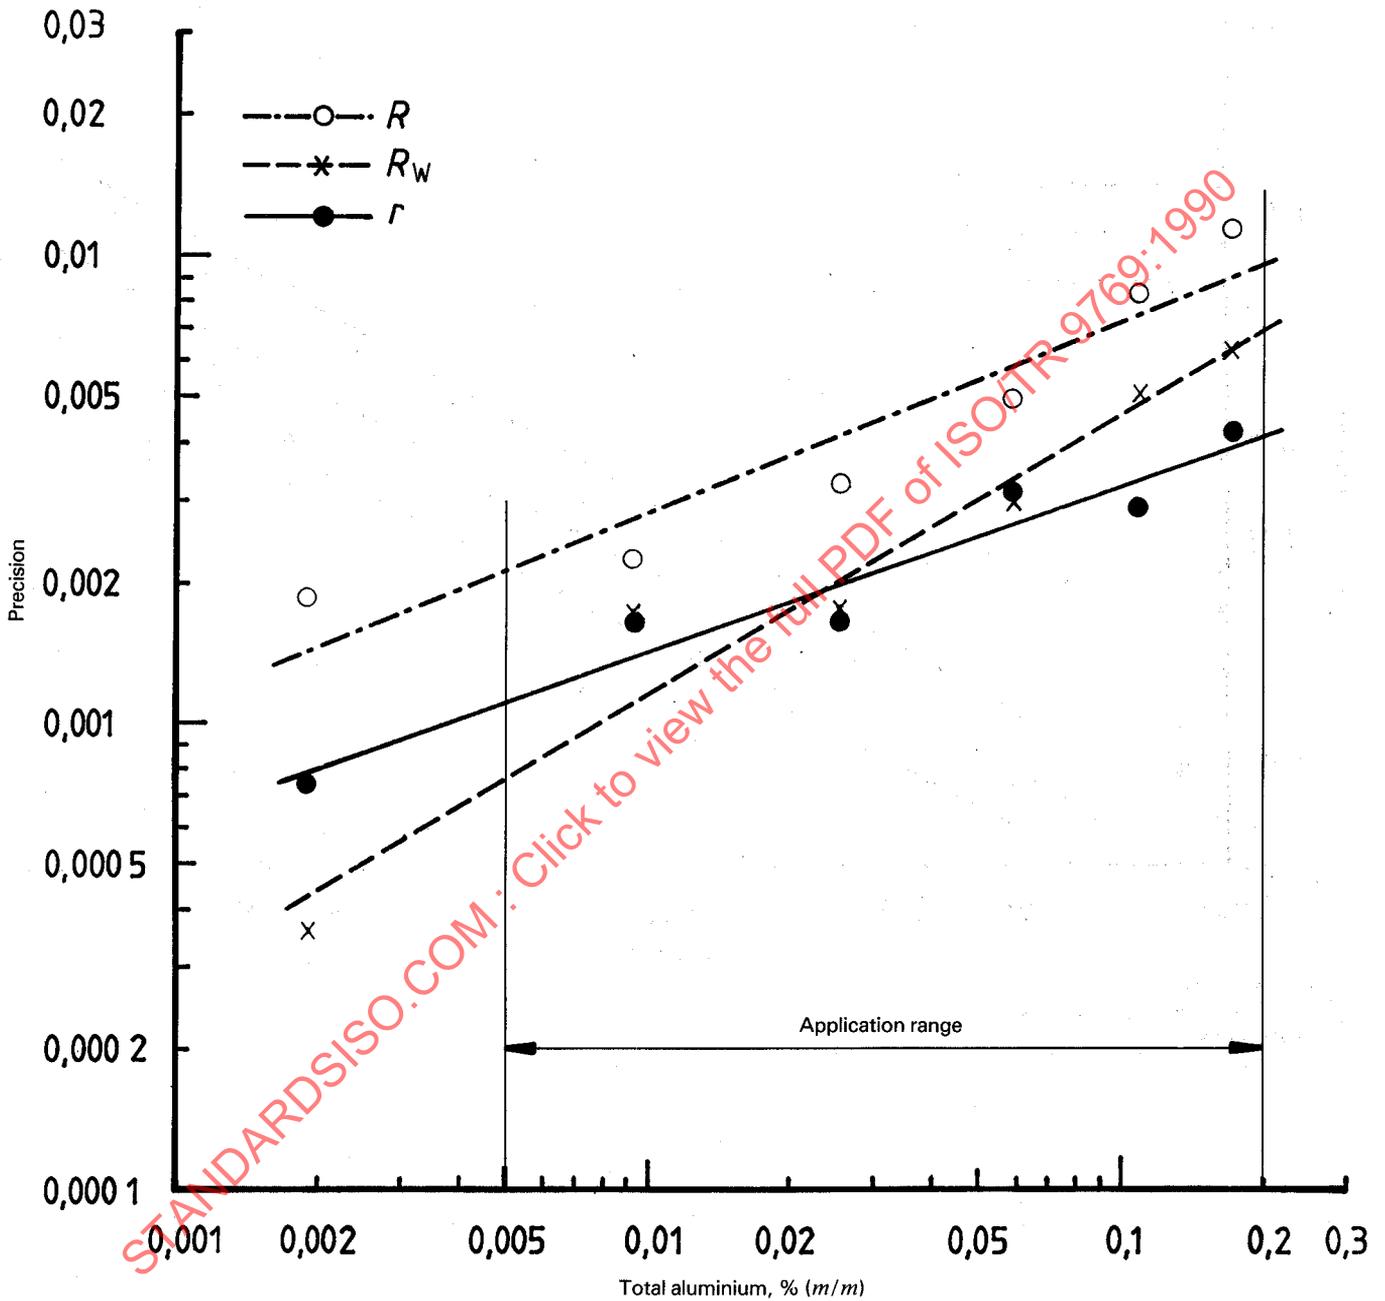

R : reproducibility
 R_w : within-laboratory reproducibility
 r : repeatability


Figure A.5.1 Precision for determination of total carbon content - Infrared absorption method after combustion in an induction furnace

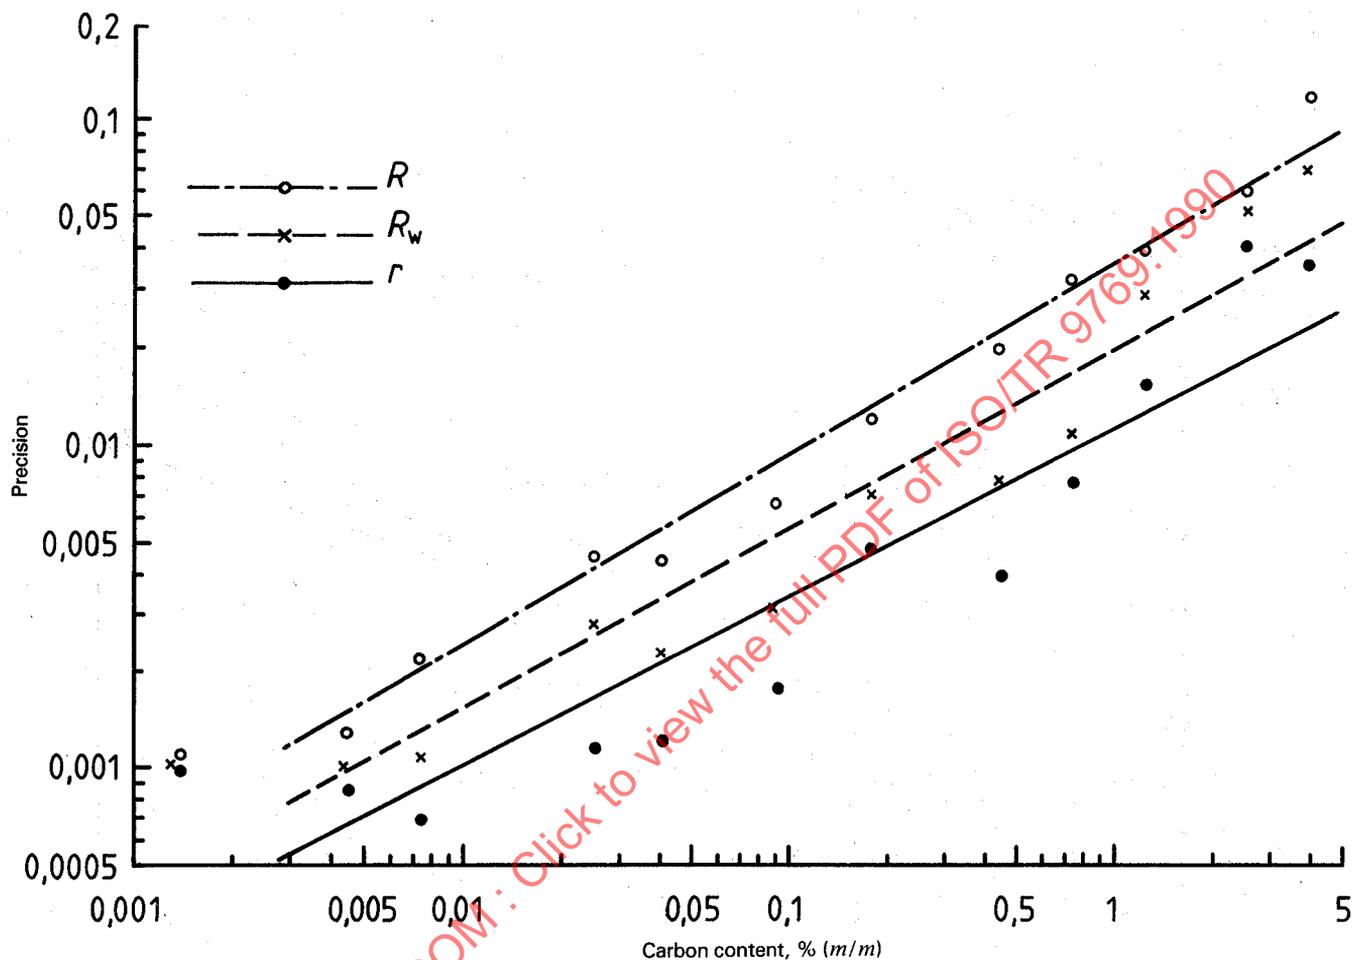

R : reproducibility
 R_w : within-laboratory reproducibility
 r : repeatability

STANDARDSISO.COM :: Click to view the full PDF of ISO/TR 9769:1990


Figure A.9.1 Precision for determination of chromium content - Potentiometric titration method

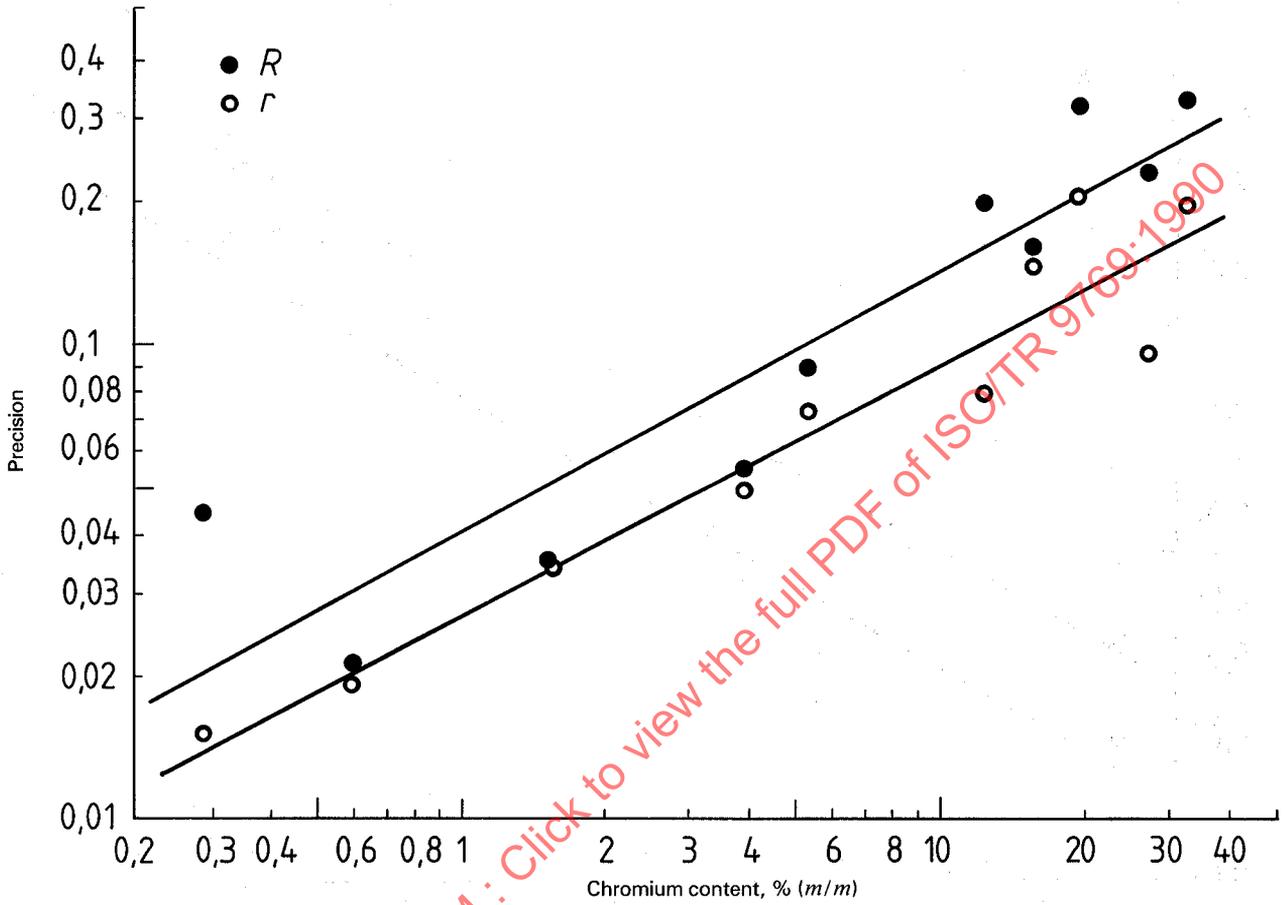

R : reproducibility
r : repeatability

STANDARDSISO.COM : Click to view the full PDF of ISO/TR 9769:1990


Figure A.9.2 Precision for determination of chromium content - Visual titration method

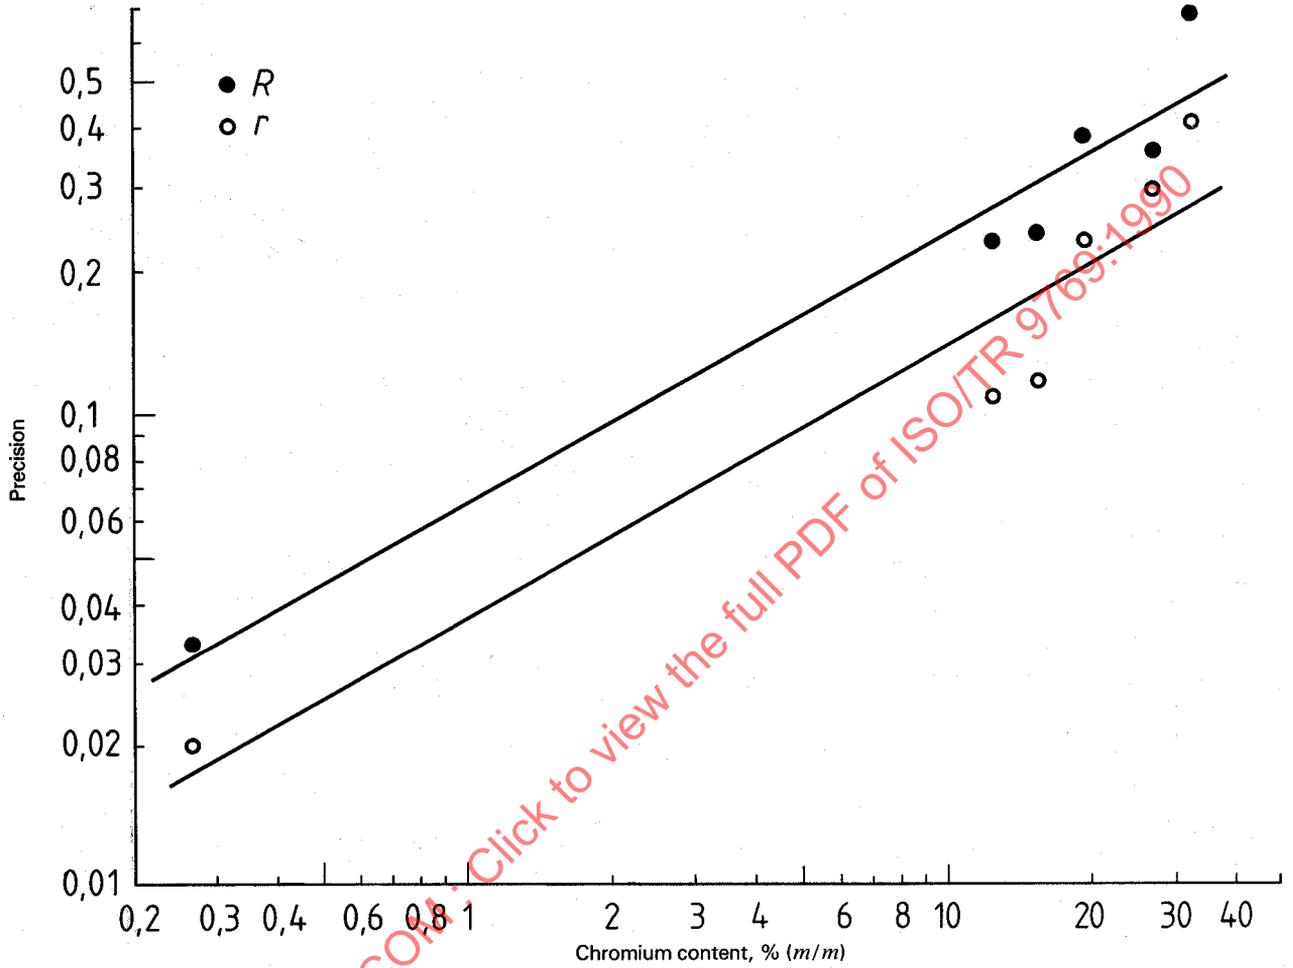

R : reproducibility
r : repeatability


STANDARDSISO.COM Click to view the full PDF of ISO/TR 9769:1990

Figure A.10.1 Precision for determination of copper content - Flame atomic absorption spectrometric method

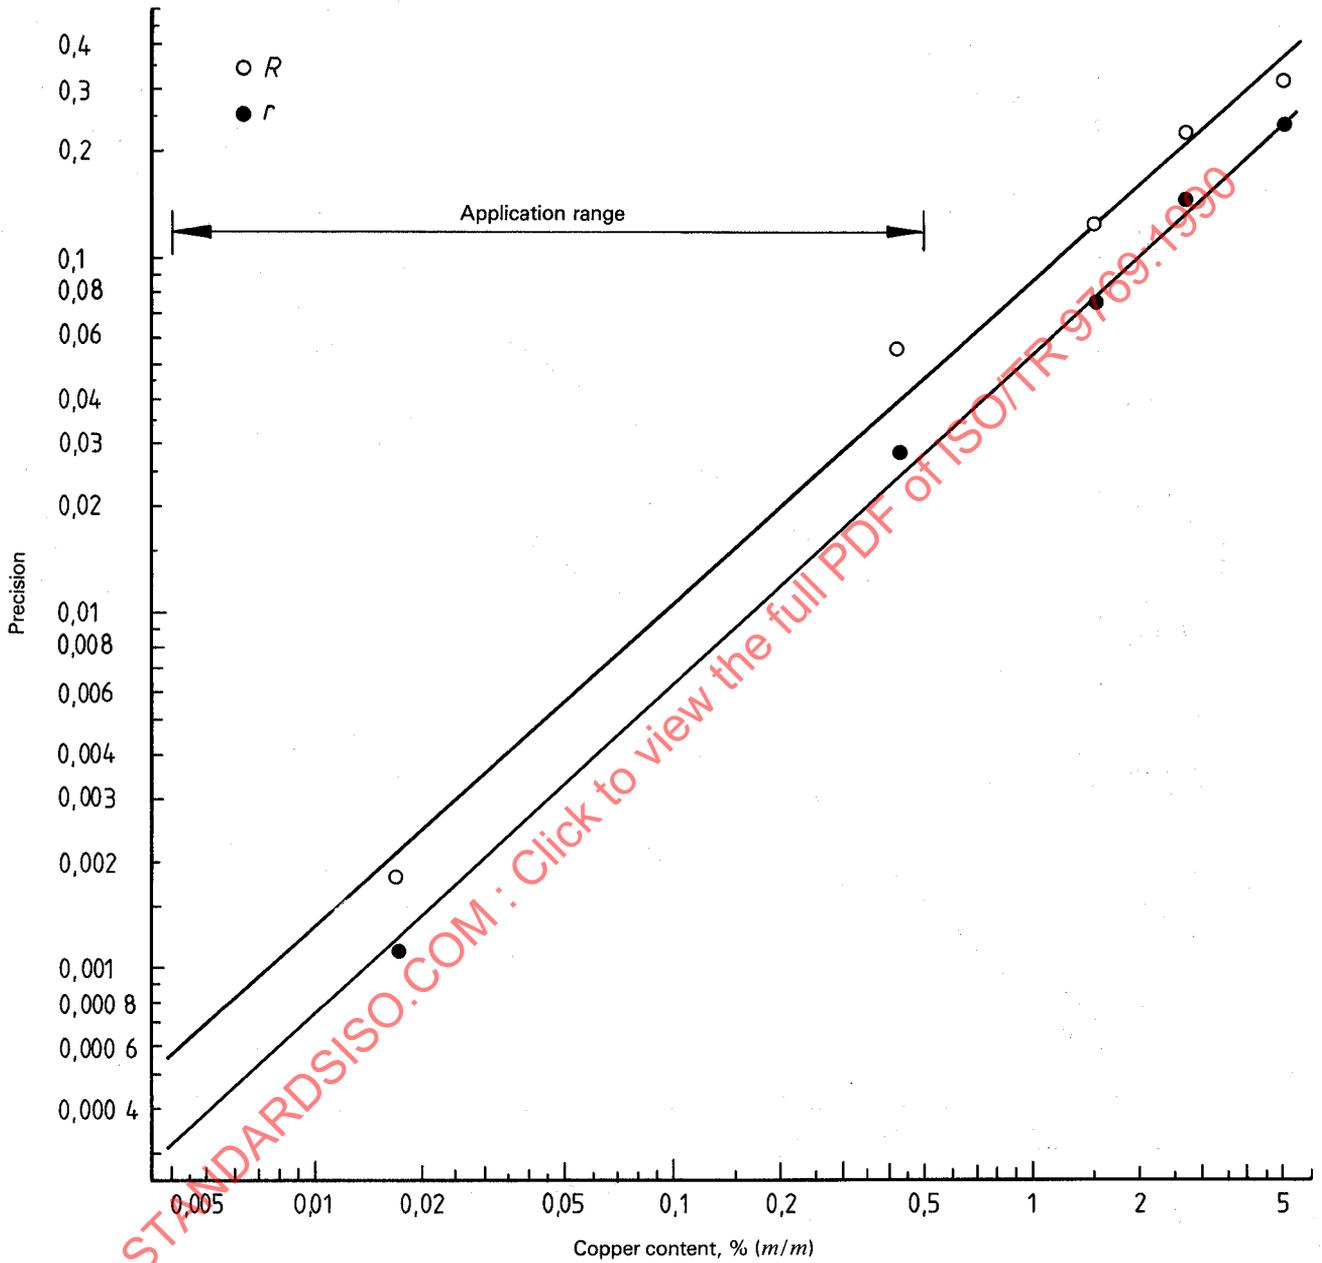


R : reproducibility
r : repeatability

Figure A.10.2 Precision for determination of copper content - 2,2'Diquinolyl spectrophotometric method

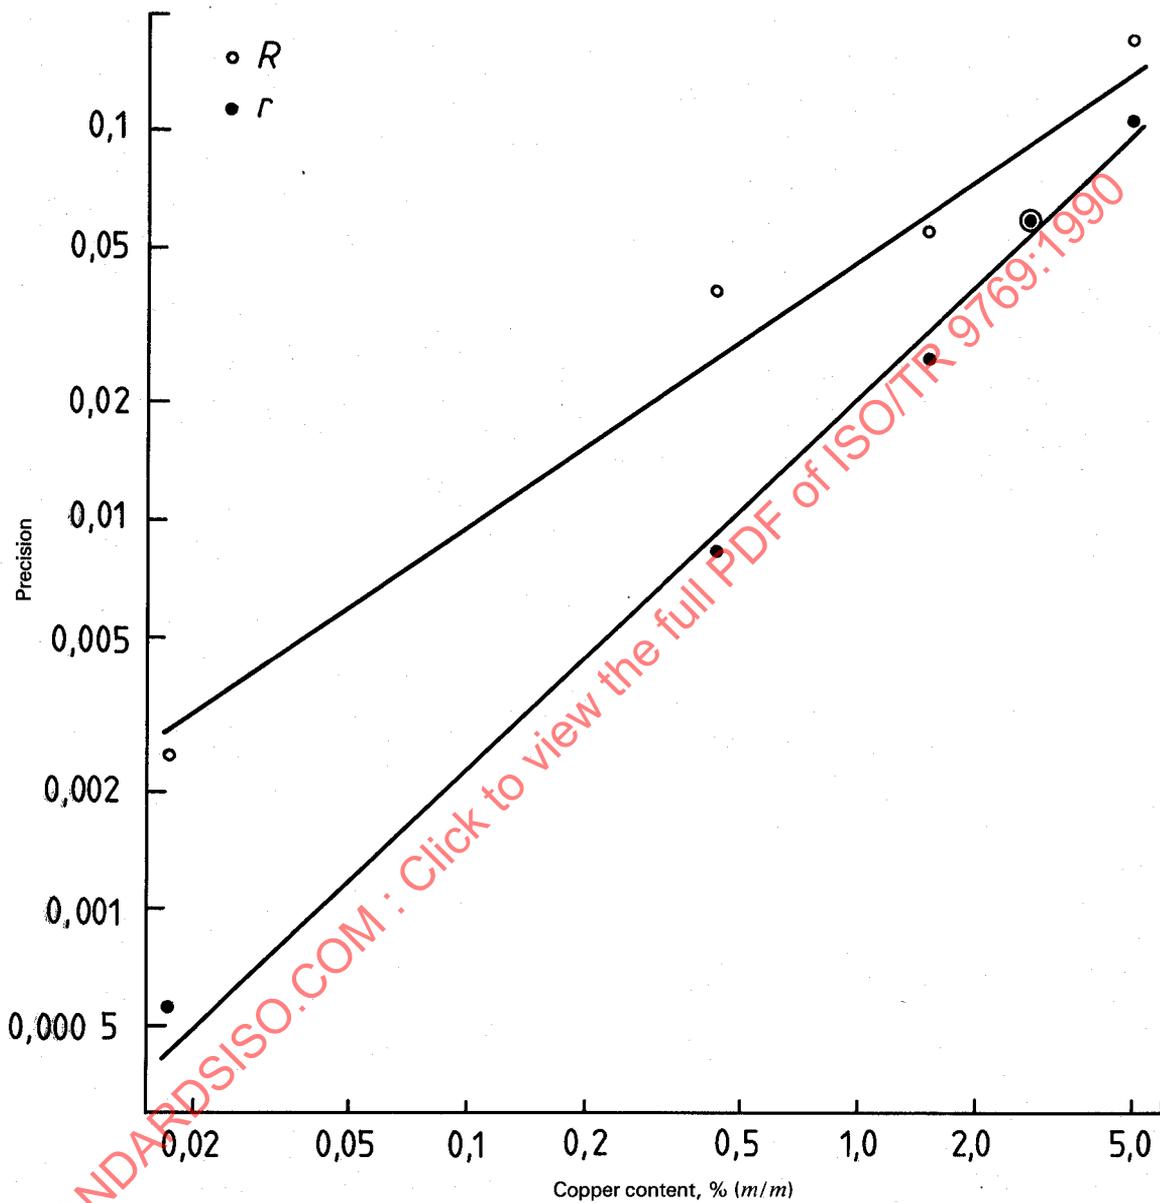


R : reproducibility
r : repeatability

Figure A.15.1 Precision for determination of niobium content - PAR spectrophotometric method

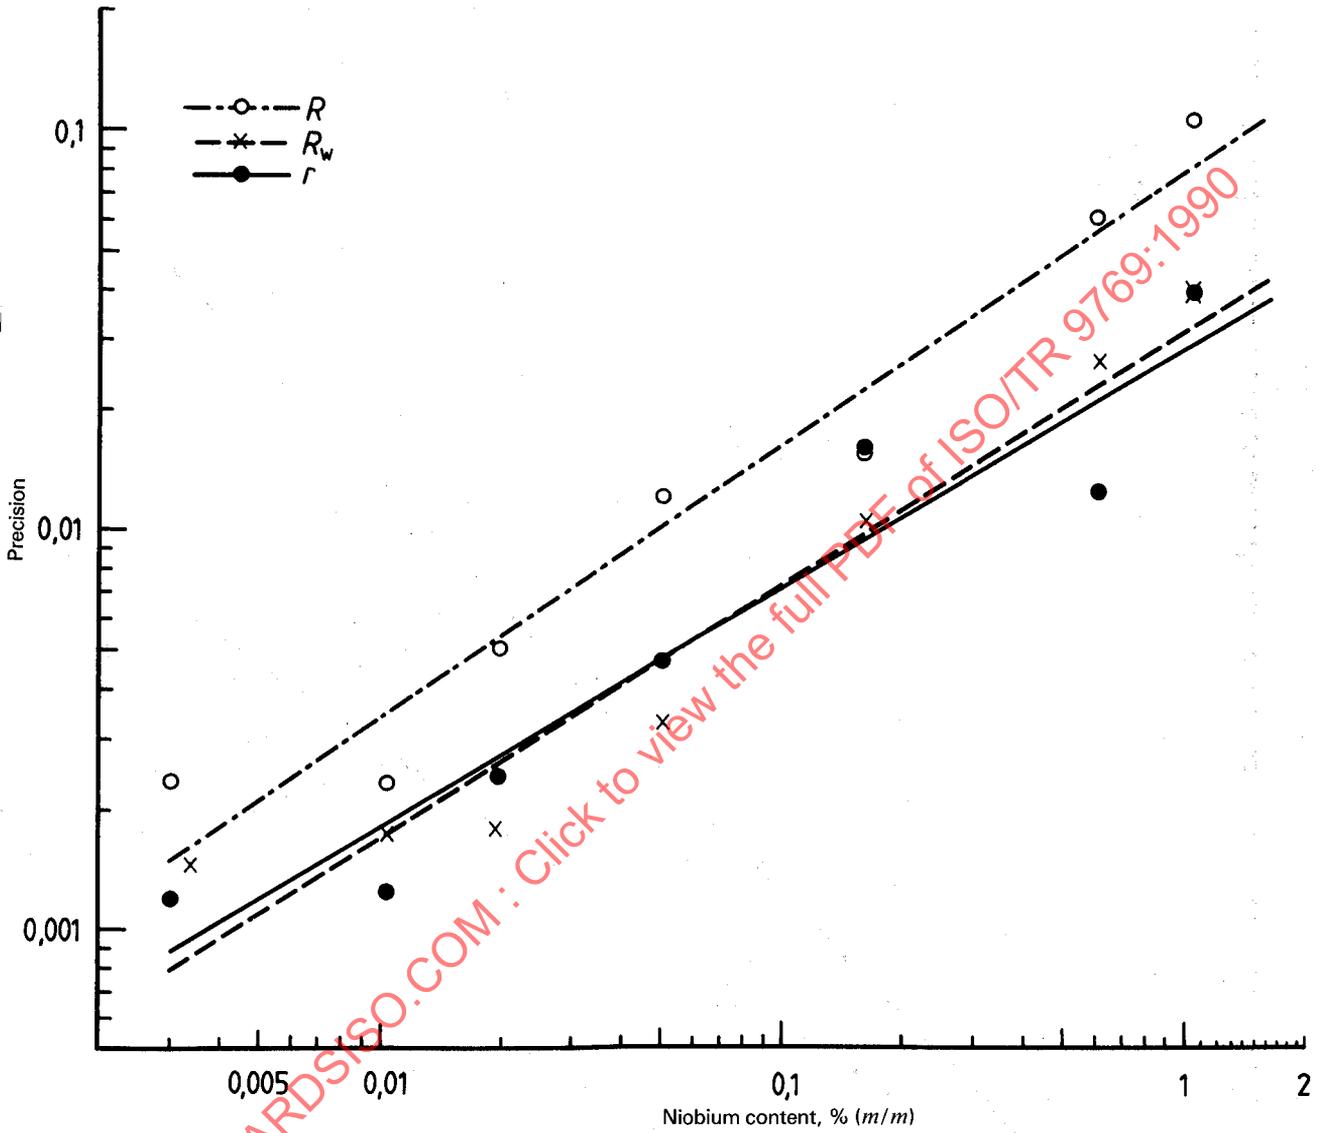


R : reproducibility
 R_w : within-laboratory reproducibility
 r : repeatability

Figure A.16.1 Precision for determination of nickel content - Gravimetric method

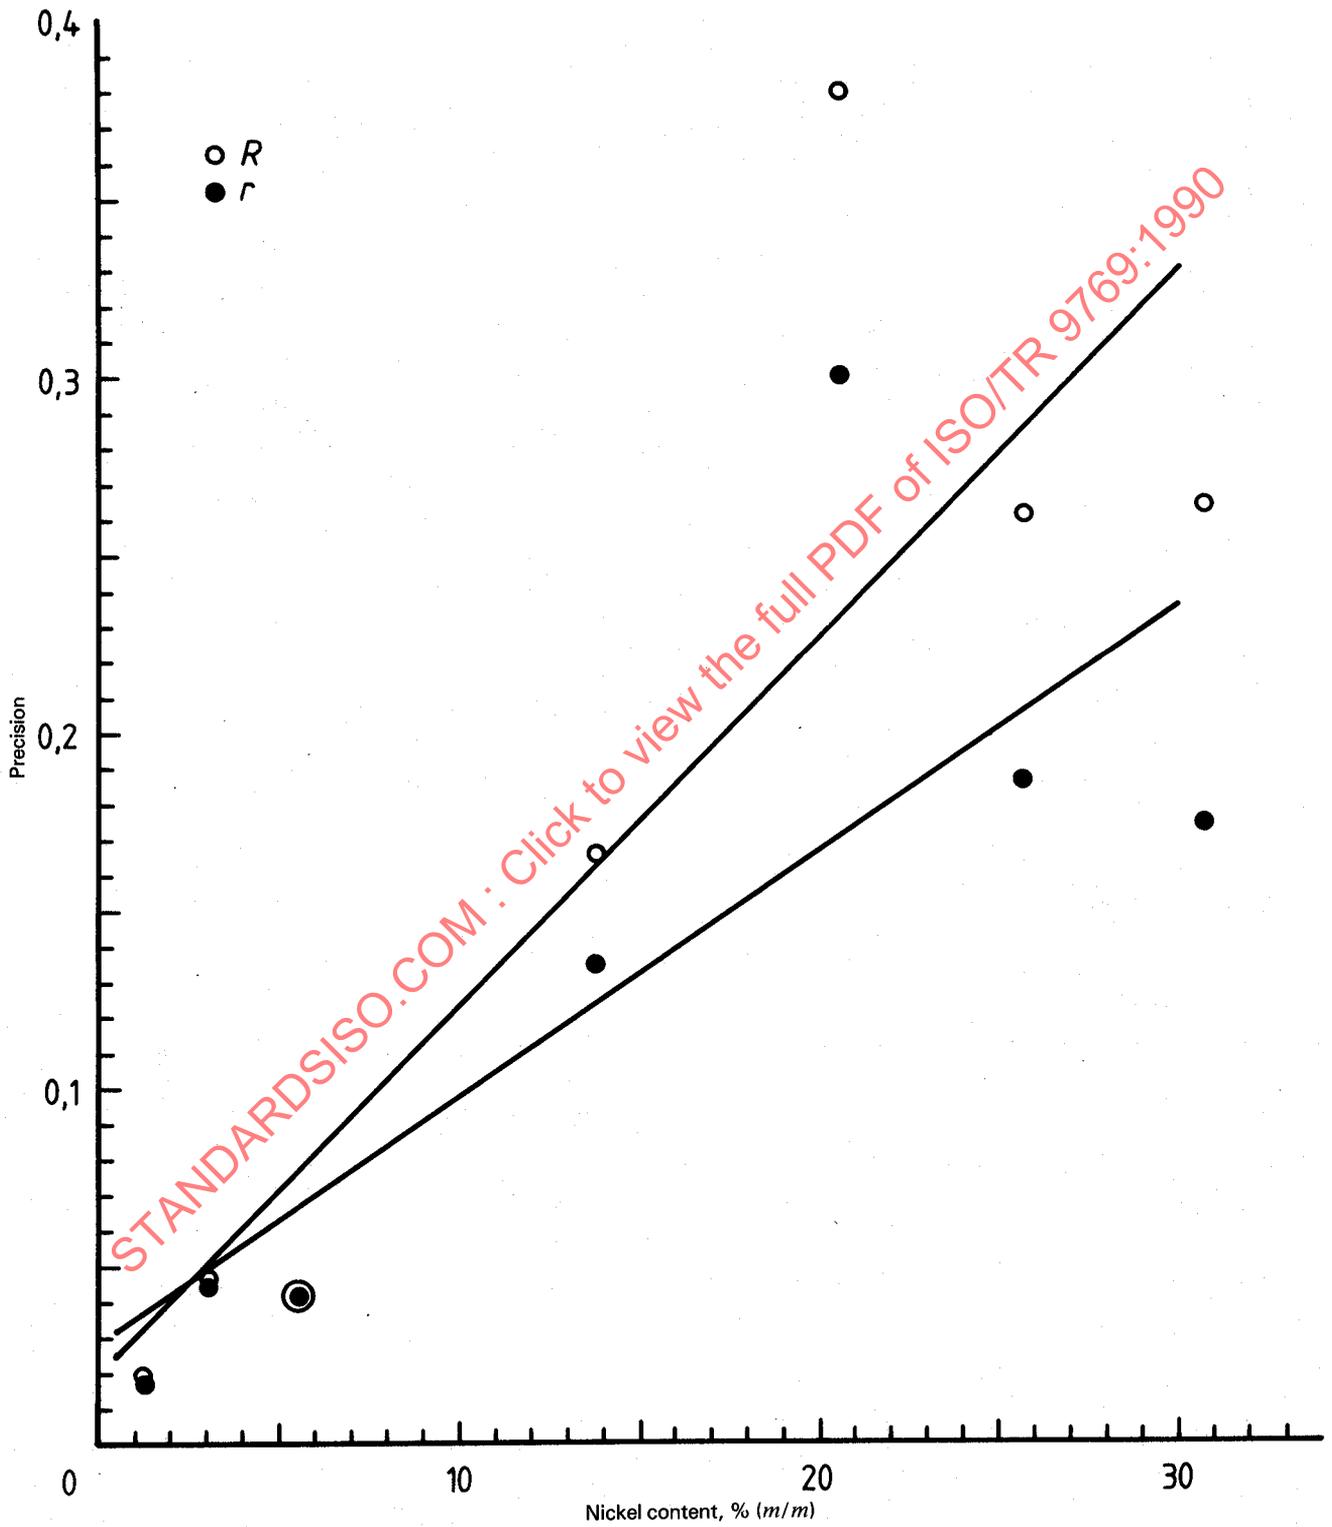


R : reproducibility
r : repeatability

Figure A.16.2 Precision for determination of nickel content - Titrimetric method

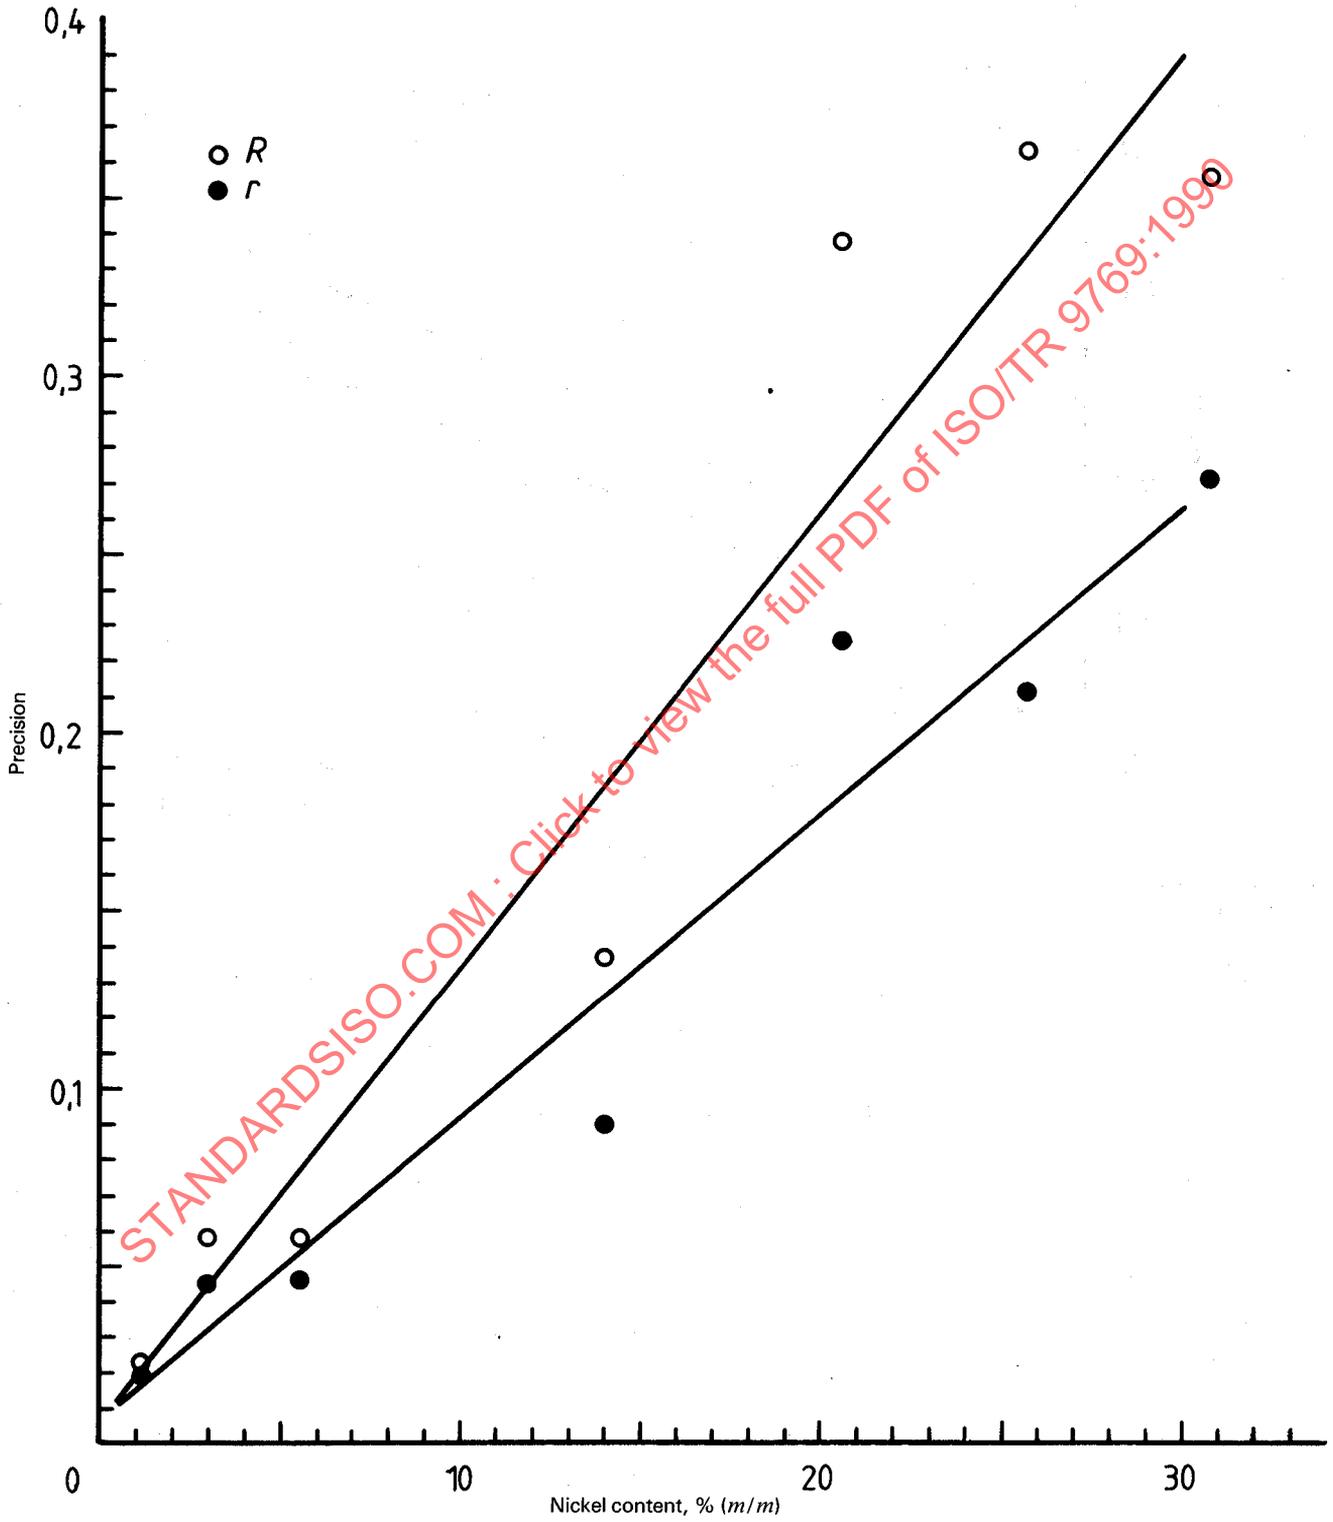

R : reproducibility
r : repeatability


Figure A.16.3 Precision for determination of nickel content -
Dimethylglyoxime spectrophotometric method

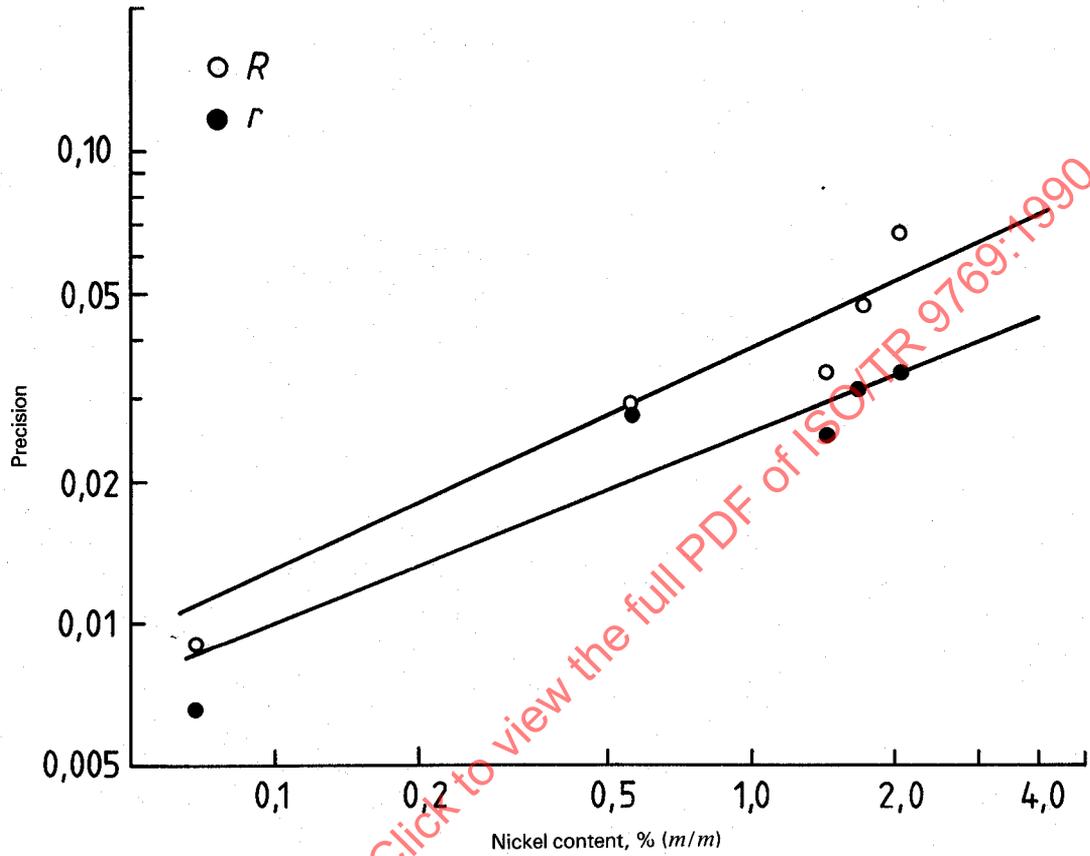

R : reproducibility
r : repeatability

STANDARDSISO.COM :: Click to view the full PDF of ISO/TR 9769:1990


Figure A.16.4 Precision for determination of nickel content - Flame atomic absorption spectrometric method

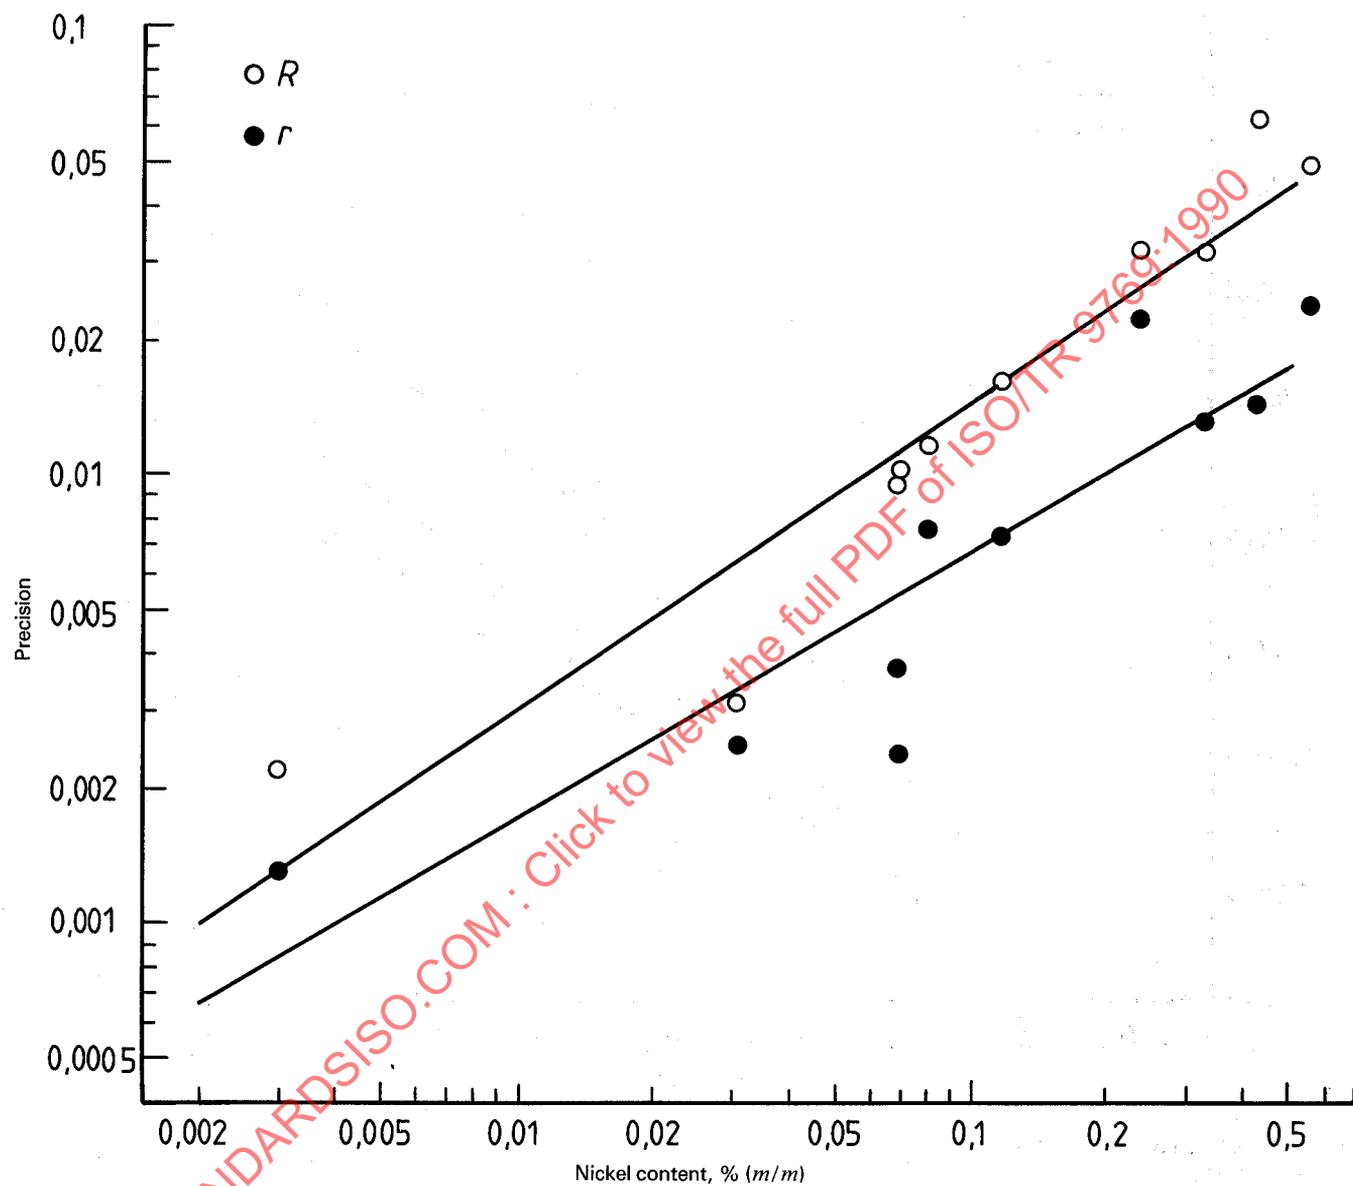

R : reproducibility
 r : repeatability

STANDARDSISO.COM :: Click to view the full PDF of ISO/TR 9769:1990

Figure A.20.1 Precision for determination of sulfur content - Infrared absorption method after combustion in an induction furnace

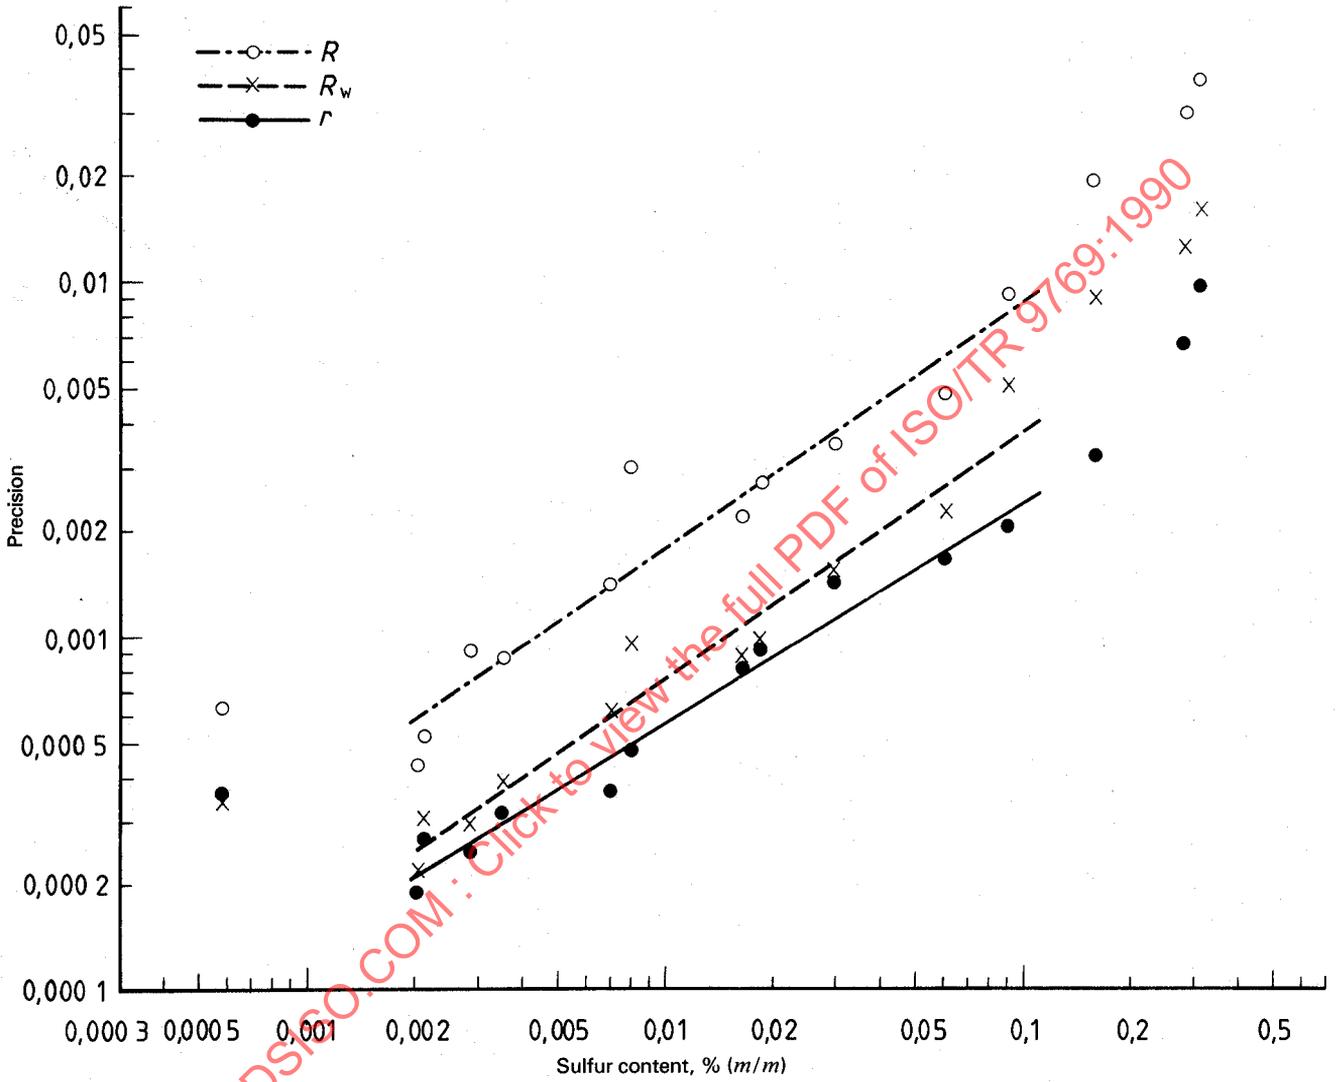

R : reproducibility
R_w : within-laboratory reproducibility
r : repeatability