



Technical Specification

ISO/TS 6857

Fine ceramics (advanced ceramics, advanced technical ceramics) — Physical properties of ceramic composites — Guidelines for determination of void and fibre contents in polished cross section by image analysis

Céramiques techniques (céramiques avancées, céramiques techniques avancées) — Propriétés physiques des composites céramiques — Lignes directrices pour la détermination du taux de porosité et de la teneur en fibre sur une section polie par analyse d'images

**First edition
2024-02**

STANDARDSISO.COM : Click to view the full PDF of ISO/TS 6857:2024



COPYRIGHT PROTECTED DOCUMENT

© ISO 2024

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Significance and use	2
6 Apparatus	2
7 Test specimen	2
7.1 Sampling.....	2
7.2 Mounting.....	3
7.3 Grinding and polishing.....	3
8 Procedures	3
8.1 Calibration.....	3
8.2 Image acquisition.....	3
8.3 Void area content.....	3
8.3.1 Binarization.....	3
8.3.2 Pixel counting.....	4
8.3.3 Removal of smaller voids.....	4
8.4 Fibre area content by simplified method.....	4
8.4.1 Tow counting.....	4
8.4.2 Determination of mean filament area per tow.....	4
8.5 Fibre area content by detailed method.....	5
8.5.1 Filament detection.....	5
8.5.2 Pixel counting.....	6
9 Calculation	6
9.1 Void area content.....	6
9.2 Fibre area content by simplified method.....	6
9.3 Fibre area content by detailed method.....	7
10 Report	7
Bibliography	8

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 206, *Fine ceramics*,

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Fine ceramics (advanced ceramics, advanced technical ceramics) — Physical properties of ceramic composites — Guidelines for determination of void and fibre contents in polished cross section by image analysis

1 Scope

This document describes the methods for the determination of void and fibre with specific orientation contents in a polished cross section of continuous fibre-reinforced ceramic matrix composites by image analysis.

The methods apply to all ceramic matrix composites with continuous fibre reinforcement: bidirectional (2D) and tridirectional (3D).

The methods also apply to carbon-fibre-reinforced carbon matrix composites (also known as: carbon/carbon or C/C).

NOTE The result obtained by the method is not volume content but area content.

2 Normative references

There are no normative references in this document.

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

fibre content

amount of fibre present in a cross section of composite

4 Principle

The test specimens are cut out of representative locations of samples or materials. The cutting sections of test specimens are carefully polished and subjected to observation with an optical microscope or similar. Digital images or photographs are taken at high magnification and analysed.

Voids are detected and discriminated based on the grayscale level differences compared to those of matrix and fibres. The threshold value is determined from the histogram of the image. The image is binarized and the void pixels are counted. The void area content is calculated as the ratio of the void pixels to the total pixels.

There are two different determination methods for the fibre area content. One is a simplified method and the other is a detailed method.

In the simplified method, the mean filament area is calculated from several tows chosen from the polished section at random. The number of tows is counted in the image or photograph. The fibre content in the polished section is determined as the product of the mean filament area per tow and the number of tows.

In the detailed method, the area of all filament sections in the image is detected by a pattern matching method with image analysis software, because the shape of the filament cross section is considered to be almost circular. By counting the number of pixels detected as filaments, the fibre content is determined as the pixel ratio of the filament area to the total image size.

5 Significance and use

The results obtained by the methods are not volume content but area content. In the case of fibre content, the result is the area content of the fibre of specific orientation. If a random cross section is representative of the volumetric fibre distribution, the volume content can be determined by measuring the adequate number of sections and calculating the mean value. Even the area content is useful to investigate the material properties and control the material quality for the purpose of material development.

Since the image quality affects the analysis result significantly, the preparation of test specimen is crucial for the image analysis. The polishing method, however, includes the know-how or the practical skills of laboratories and depends on the characteristic of material to be analysed. For these reasons, this document does not specify the details of polishing method, but describes the general principle.

NOTE With respect to fine ceramics, some guidelines on grinding and polishing are given in ISO 13383-1:2012, Annex A.

The detailed method to determine the fibre area content is performed by a pattern matching method to detect the filament area in the image. This algorithm is based on the characteristic that the cross section of filament is circle. Therefore, all filaments shall be cut perpendicular to their axes within $\pm 15^\circ$ so that the cross sections remain circle. In some woven materials it is difficult to cut the test specimen perpendicular to the fibre axis due to fibre waving. This method is not suitable for such woven materials.

6 Apparatus

6.1 Microscope should have high resolution to enable good object observation (i.e. a resolution of around one tenth of filament diameter or void size). A scanning electron microscope (SEM) may be used. A microscope with an automatic stage and automatic focus to stitch a number of digital images is recommended to cover larger cross sections for observation.

6.2 Calibrated rule or scale should be accurate within $\pm 0,5\%$. Its reading should be 0,5 mm or better.

6.3 Image analysis software is capable of the following:

- making a grayscale histogram, setting a threshold value automatically or manually and binarizing an image based on the threshold value;
- detecting a circular shape and counting the number of detected pixels.

7 Test specimen

7.1 Sampling

The test specimen should be cut perpendicular to the fibre orientation. If the material is reinforced in multiple orientations, the test specimen should be cut directional perpendicular to the fibre orientation of interest. The recommendations for the cross section are as follows:

- a) for 2D textile fabrics, the cross section should contain more than three plies;

b) for 3D textile fabrics, the cross section should contain more than three unit cells.

In cutting out the test specimen, care shall be taken to prevent the damage such as fibre cracking, fibre loss and so on.

7.2 Mounting

If the test specimen is hard to handle in grinding and polishing, mount the test specimen using appropriate mounting equipment. It is advisable to vacuum impregnate the test specimen with liquid mounting resin before encapsulating as this will provide some support during polishing.

NOTE It is not essential to encapsulate the test specimen. For example, it could be affixed to a metal holder. However, encapsulation in a polymer-based medium allows easy gripping and handling, especially of small irregularly shaped test specimens and of weak, friable material.

7.3 Grinding and polishing

Grind and polish the surface of the test specimen. Care shall be taken to ensure that grinding produces a planar surface with a minimum of damage. Employ successively smaller grit sizes, at each stage removing the damage from the previous stage until there is no change in appearance when examined by an optical microscope at high magnification. Care should be taken in choosing the sequence of grits and lap types. The final surface shall be free from optically visible scratches, or other damage introduced by polishing, which would interfere with the determination.

NOTE It is impossible within the scope of this document to make specific recommendations for all types of material. The general principle to be adopted is the minimization of subsurface damage, and its removal by progressively finer grits while retaining a flat surface. Some guidelines on grinding and polishing are given in ISO 13383-1:2012, Annex A.

8 Procedures

8.1 Calibration

Before image acquisition, measure a calibrated rule or scale using a stage micrometer and calculate the length per pixel.

8.2 Image acquisition

Place the test specimen on the microscope stage so that the test specimen surface is perpendicular to the optic axis. Obtain a grayscale image so as to contain the unit structures described in Clause 7. The resolution should be around one tenth the size of the object for detection. If multiple images are stitched to one image, it is recommended to use the same conditions for all images. Enhance the contrast of image in order to discriminate the void area and the filament area accurately. The edge of the sample causes poor contrast. Obtain a grayscale image so as to exclude the sample edge.

NOTE 1 In the digital image of the polished section taken using an optical microscope or SEM, the void area is darker than other areas.

NOTE 2 In general, the grayscale level range of filaments is similar to that of matrix.


8.3 Void area content

8.3.1 Binarization

Develop the grayscale histogram with image analysis software. Since the grayscale level in a void area is lower (darker) and that in other areas is higher (lighter), in general, the histogram shows a distribution with two peaks (bimodality distribution) as shown in [Figure 1](#). Set the threshold value to that indicated in the valley of the figure and binarize the image.

Lower void area content decreases the number of low grayscale pixels relatively and lowers the peak of the void pixels in the histogram. If setting a threshold value for binarization is difficult, adjust the contrast and attempt taking the image again.

The image analysis to the stitched file can be performed, although the size of image file becomes large. It is recommended to not have a compression of the image resulting from file stitching.

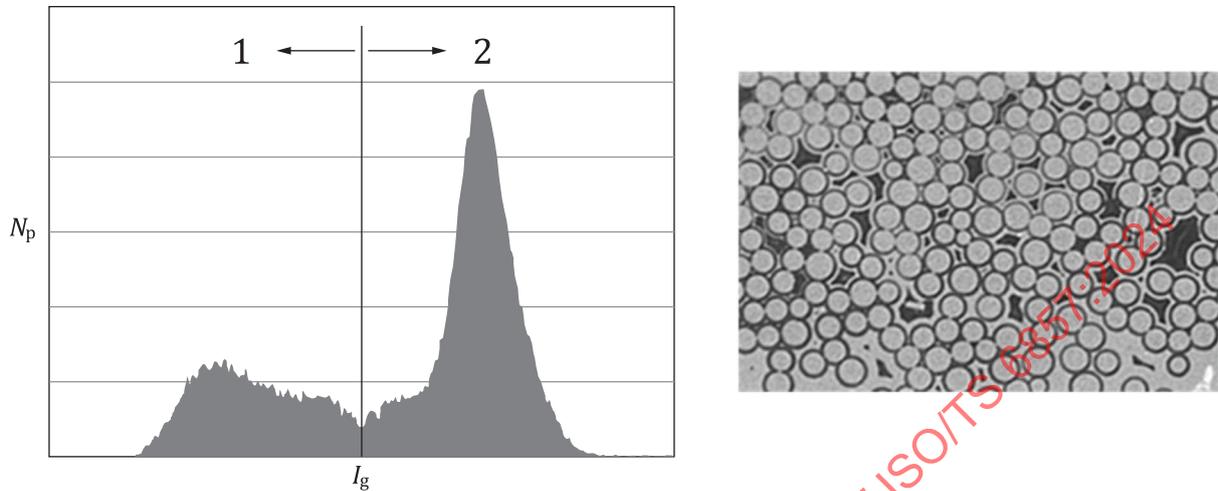

Key

- 1 void
- 2 fibre and matrix
- I_g gray scale intensity
- N_p number of pixels

Figure 1 — Grayscale histogram

8.3.2 Pixel counting

Count the number of black and white pixels, P_b , P_w , for the binary image using image analysis software.

8.3.3 Removal of smaller voids

Label all the detected voids and obtain their areas with image analysis software. Exclude the smaller voids agreed between the Parties.

8.4 Fibre area content by simplified method

8.4.1 Tow counting

Count the number of tows in the image. If a tow intersects the frame border, count the number of tows to the first decimal place considering the mean tow area as shown in [Figure 2](#).

8.4.2 Determination of mean filament area per tow


Measure the filament area in a tow with a planimeter, image analysis software or other methods and obtain the filament area in a tow. Continue this measurement for 30 % or more tows in the image and determine the mean area per tow. If it is difficult to measure the mean tow area directly, count the number of filaments and obtain the mean filament diameter. The mean filament diameter can be obtained from either direct

measurement for an adequate number of filaments or the inspection certificate by a filament manufacturer. The filament area in a tow is determined by [Formula \(1\)](#):

$$A_f = \frac{\pi m \bar{d}^2}{4} \quad (1)$$

where

- A_f is the filament area in a tow;
- m is the number of filaments in a tow;
- \bar{d} is the mean filament diameter.

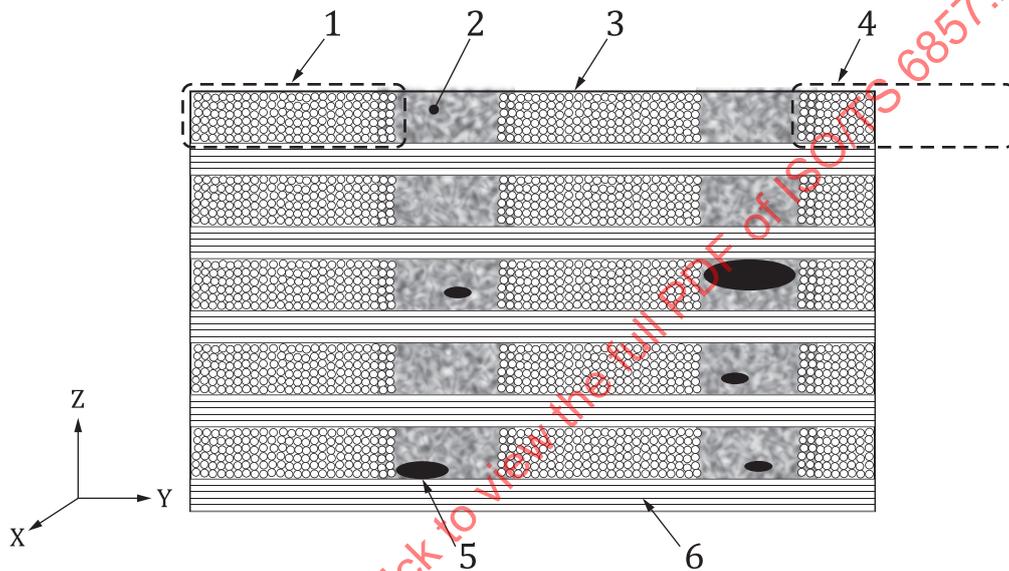

Key

- | | |
|-------------------------|-------------------------|
| 1 tow | 4 0,3 tow |
| 2 matrix | 5 void |
| 3 X direction filaments | 6 Y direction filaments |

Figure 2 — Illustration of polished cross-section

8.5 Fibre area content by detailed method

8.5.1 Filament detection

Detect each filament section with the circular shape recognition function of image analysis software. If pattern recognition of the image is difficult, the edges of filament as shown in [Figure 3](#) are detected first and pattern recognition can be performed on the detected edges.

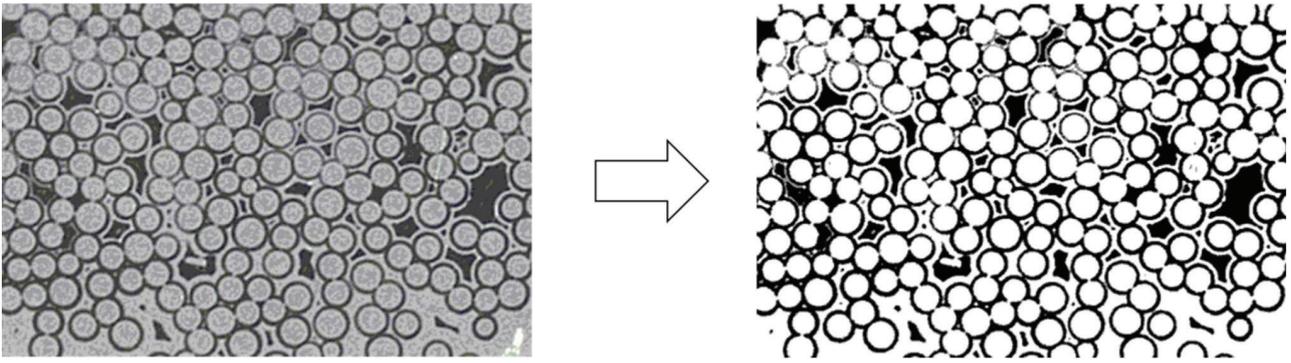


Figure 3 — Result of edge detection

8.5.2 Pixel counting

Count the number of pixels detected as the filament area P_f .

9 Calculation

9.1 Void area content

Calculate the void area content to the first decimal place by using [Formula \(2\)](#):

$$A_v = \frac{P_b - P_{cut}}{P_b + P_w} \times 100 \quad (2)$$

where

A_v is the void content in each image (%);

P_{cut} is the total number of void pixels agreed between the parties as the cut-off void;

P_b is the total number of pixels with a brightness of 0 (black) in a binary image;

P_w is the total number of pixels with a brightness of 255 (white) in a binary image.

9.2 Fibre area content by simplified method

Calculate the fibre content to the first decimal places by using [Formula \(3\)](#):

$$A_f = \frac{n \overline{A_f}}{A_t} \times 100 \quad (3)$$

where

A_f is the fibre content in a polished cross-section;

n is the number of tows;

$\overline{A_f}$ is the mean fibre area in a tow;

A_t is the total image area.

9.3 Fibre area content by detailed method

Calculate the fibre content to the first decimal places by using [Formula \(4\)](#):

$$A_f = \frac{P_f}{P_t} \times 100 \quad (4)$$

where

A_f is the fibre content in a polished cross-section;

P_f is the number of pixels detected in a filament;

P_t is the total number of pixels of image analysed.

10 Report

The test report shall contain, at least, the following information:

- a) reference to this document, i.e. ISO/TS 6857:2024;
- b) test laboratory and operator;
- c) date of measurement;
- d) description of the test material (material type, manufacturing data, etc.);
- e) preparation of test specimen (cutting method, polishing method, etc.);
- f) measurement devices;
- g) images before and after analysis;
- h) image analysis software (including version);
- i) individual values of the void area content and/or fibre area content;
- j) mean values of the void area content and/or fibre area content;
- k) cases different from the procedures or requirements of this document;
- l) any unusual features observed.