

Steel: Chemical Composition and Hardenability

RATIONALE

AIR4127 covers methods to classify steels based on composition and hardenability, replacing AMS-STD-66 and FED-STD-66.

TABLE OF CONTENTS

1.	SCOPE.....	2
2.	CLASSIFICATION AND DESIGNATION OF STEELS BY CHEMICAL COMPOSITION.....	2
2.1	Classification.....	2
2.2	Standard Steels.....	2
2.3	Former Standard Steels.....	2
2.4	Nonstandard Steels.....	2
2.5	H-Steels.....	2
3.	VERIFICATION OF CHEMICAL COMPOSITION.....	3
3.1	Definitions.....	3
3.2	Sampling for Cast or Heat Analysis.....	3
3.3	Reporting Cast or Heat Analysis.....	3
3.4	Sampling for Product Analysis.....	3
3.5	Tolerances for Product Analysis.....	4
4.	CARBON STEEL COMPOSITIONS.....	4
4.1	Description.....	4
5.	STAINLESS AND HEAT-RESISTING STEEL COMPOSITIONS.....	4
5.1	Forms.....	4
5.2	Description.....	4
6.	ALLOY STEEL COMPOSITIONS.....	4
7.	STANDARD H-STEELS.....	7
7.1	Identification.....	7
7.2	Hardenability Bands.....	7
FIGURE 1	DRILL LOCATIONS FOR OBTAINING PRODUCT ANALYSIS SAMPLES.....	7
FIGURE 2	EXAMPLES ILLUSTRATING ALTERNATE METHODS OF SPECIFYING REQUIREMENTS (TABULATED HARDNESS VALUES USED IN ORDERING).....	8
TABLE 1	NUMERICAL DESIGNATION OF STEELS BY COMPOSITION.....	5
TABLE 2	PROCEDURES FOR OBTAINING PRODUCT ANALYSIS SAMPLES.....	6

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

Copyright © 2007 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
Tel: 724-776-4970 (outside USA)
Fax: 724-776-0790
Email: CustomerService@sae.org
SAE WEB ADDRESS: <http://www.sae.org>

1. SCOPE

This document, as referenced in the applicable product specifications in procurement documents, contains:

- a. A catalog of the standard carbon steels, alloy steels (including H-steels), and stainless and heat-resisting steels that are designated by chemical composition, or (for H-steels) by chemical composition and hardenability limits by reference to standard industry documents.
- b. Rules for designating the chemical content of carbon steels, alloy steels, and stainless and heat-resisting steels that are not classified as standard.

2. CLASSIFICATION AND DESIGNATION OF STEELS BY CHEMICAL COMPOSITION

2.1 Classification

Chemical composition indicates only one aspect of a steel product and is not to be considered as a complete guide to quality and performance. Chemical composition, however, is the most common basis for the classification and designation of steels. The precise chemical content, together with the desired form (bar, sheet, strip, plate, etc.) and the size (primarily cross-sectional area or diameter, will determine whether a given product can be obtained simply by ordering a standard steel, or whether all the requirements must be specified in detail.

2.2 Standard Steels

Standard steels have specified compositions and are limited to particular forms and sizes. These steels have individual numerical designations assigned by industry to facilitate ordering, as shown in Table 1. The numbers are for identification and are not indicative of quality. The steel numbers used in this document are generally Unified Numbering System (UNS) numbers; Society of Automotive Engineers (SAE) numbers are included for further information.

In general, standard steels are used more often and are more readily available than other compositions.

2.3 Former Standard Steels

These steels were formerly listed as "standard steels" in previous editions of this document, the AISI manuals, and SAE Surface Vehicle Standards, but, because of decreased usage, they have been placed in separate tables in the referenced documents and in SAE Surface Vehicle Standard J1249.

2.4 Nonstandard Steels

Nonstandard steels are steels that do not fall into the category of standard steels because of differences in their composition. These unlisted steels must be ordered by specifying the chemical content in accordance with established ranges and limits.

2.5 H-Steels

A number of alloy steels, identified by the prefix or suffix letter "H" to the steel number, may be designated by a combination of hardenability and composition. The hardenability data compiled for each of these steels, have been derived from extensive standard (Jominy) end-quench hardenability testing, and have been incorporated into composite graphs. Each graph has two curves, plotted from the maximum and minimum hardness values reported for 1/16-inch distances from the quenched end of a standard 1-inch diameter specimen. The band created by these two curves defines the hardness limits for that composition. Hardenability bands and directions for their use in specifying H-steels are explained in 7.2.

2.5.1 Chemical Composition Limits

The chemical composition limits of the H-steels have been modified somewhat from the ranges or limits applicable to the same grades when specified by chemical composition only so that steel producers will be able to meet a common standard of hardenability limits. The modifications permit adjustments in manufacturing range of chemical composition to correct for individual plant melting characteristics which might otherwise influence the levels and widths of the hardenability bands. The modifications are not great enough to influence the general characteristics of the original compositions of the series under consideration.

3. VERIFICATION OF CHEMICAL COMPOSITION

3.1 Definitions

3.1.1 Cast or Heat Analysis

Cast or heat analysis is the determination of the chemical composition of a melt, blow, or heat of steel as represented by samples obtained from the first part or middle part of the heat during pouring of the steel from a ladle. This analysis is representative of the product of a heat of steel as delivered and as reported to the purchaser.

3.1.2 Product Analysis

Product analysis is a chemical analysis of steel in the semifinished or finished product form. The steel can be subjected to product analysis by the purchaser either for the purpose of verifying that the chemical composition is within specified limits for each element, including applicable tolerance for product analysis, or to determine variation in composition within a heat or lot; it is not used to confirm previous results. The results of analyses representing different locations in the same piece or taken from different pieces of a heat or lot may differ, within permissible limits, from each other and from the cast or heat analysis.

3.1.3 A "melt" of steel is the metallic output of one charge of an electric furnace.

3.1.4 A "heat" is the metallic output of one furnace charge in the open hearth or the basic oxygen process.

3.1.5 A "blow" is the metallic output of one furnace charge in the Bessemer process.

3.2 Sampling for Cast or Heat Analysis

Unless otherwise specified in the contract or order, sampling procedures for cast or heat analysis will be in accordance with standard industry practice. Usually, at least three samples are taken representing the first, middle, and last portions of the heat. Drillings taken from the first sample or middle sample are used in determining cast or heat analysis. The additional samples are used for survey of uniformity and for control purposes.

3.3 Reporting Cast or Heat Analysis

The chemical composition specified for cast or heat analysis is shown by percentages of the elements, expressed as minimum or maximum limits or as ranges. With the exception of phosphorus and sulfur, all elements are reported to two decimals. Phosphorus and sulfur, up to 0.060 percent inclusive, are usually reported to three decimals; above 0.060 percent they are usually reported to two decimals. Values are normally rounded off to the nearest hundredth percent.

3.4 Sampling for Product Analysis

In sampling for product analysis, each heat of steel in a lot is considered separately unless otherwise specified. The number of samples selected for analysis is usually indicated by the applicable product specification. Because of segregation, the location at which samples for product analysis are obtained is important. Product analysis must be performed on steel in the condition received from the producer because steel subjected to subsequent heating operations may not yield analytical results that correctly represent the original composition. The detailed procedures for obtaining product analysis chips or drillings (samples) for various forms and sizes of the product are shown in Table 2.

3.5 Tolerances for Product Analysis

Individual determinations may vary from the specified limits or ranges to the extent shown in the applicable product analysis tables, but the several determinations of any element in a heat may not vary both above and below the specified range.

Because of a characteristic lack of uniformity, no product analysis is ordinarily required for carbon, phosphorus, and sulfur in rimmed or capped steels, nor for phosphorus and sulfur in rephosphorized or resulfurized steels, unless misapplication (error in identification) is clearly indicated.

4. CARBON STEEL COMPOSITIONS

4.1 Description

The chemical composition, ranges and limits, and product analysis tolerances for carbon steels are covered in tables contained in SAE Surface Vehicle Standard SAE J401, J402, and J403.

4.1.1 The standard SAE nonresulfurized carbon steels for plates, sheet, strip, shapes, and welded tubing are identified by the same four-digit numbers used to identify the old standard AISI steels for bars, semifinished products, wire rods, wire, and seamless tubing. However, comparable compositions from both groups are not identical despite identification numbers; they differ in the range of content shown for particular elements (usually carbon). Therefore, in ordering, specify the identification number, the form desired (sheet, strip, etc.), and the prefix designation "SAE".

5. STAINLESS AND HEAT-RESISTING STEEL COMPOSITIONS

5.1 Forms

Stainless and heat-resisting steels specified by composition are ordered as standard steels and are available as bars, as semifinished products (blooms, billets, and slabs) 4 inches square or larger, and as plates, shapes, sheet, strip, and wire.

5.2 Description

The chemical composition and product analysis tolerances for stainless and heat-resisting steels are covered in SAE Surface Vehicle Standard J405.

6. ALLOY STEEL COMPOSITIONS

6.1 Forms

Standard alloy steels, ordered by identification number, are available as bars, billets, blooms, and slabs. They are generally also available as shapes, sheet, strip, wire, and seamless tubing. Some producers may not furnish standard alloy steels in all of these forms, or they may accept orders only if based on specifying such forms as "other-than-standard" steels.

TABLE 1 - NUMERICAL DESIGNATION OF STEELS BY COMPOSITION

Classification	Groupings	Series Designation			
		UNS	SAE		
Carbon steels	Plain (nonresul.) Low carbon Med. low carbon Med. high carbon High carbon High manganese	Up to G10130 G10130 TO G10220, incl. Over G10220 to G10410, incl. Over G10410 G15240 to G15520, incl.	Up to 1013 1013 to 1022, incl. Over 1022 to 1041, incl. Over 1041 1524 to 1552, incl.		
	Free-cutting (free- machining) Resulpherized Rephosphorized and resulpherized	---	11xx 11xx		
Alloy steels	Manganese	G13xxx	13xx		
	Boron	---	14xx		
	Nickel-chromium	---	31xx 33xx		
	Molybdenum	G40xxx G44xxx	40xx 44xx 45xx		
	Chromium-molybdenum	G41xxx	41xx		
	Nickel-chromium- molybdenum		G43xxx G47xxx G81xxx G86xxx G87xxx G88xxx ---	43xx 47xx 81xx 86xx 87xx 88xx 93xx 98xx	
		Nickel-molybdenum	G46xxx G48xxx	46xx 48xx	
		Chromium Low		G501xx G51xxx ---	50xx 51xx 501xx
			Low (bearing)	---	511xx
			Medium (bearing)	---	521xx
			High (bearing)	---	
	Chromium-vanadium	G61xxx	61xx		
	Silicon-manganese	G92xxx	92xx		
	Boron intensified	G504xx to G506xx, incl.	xxBxx		
Leaded	---	xxLxx			
Stainless and heat-resisting steels	Austenitic (nonhardenable) Chromium-nickel- manganese Chromium-nickel	S201xx, S202xx, S205xx S3xxx (certain designations only)	202xx 303xx		
	Martensitic (hardenable chromium)	S4xxx (certain designations only)	514xx		
	Ferritic (nonhardenable chromium)	S4xxx (certain designations only)	514xx		
	Special heat-resisting (low chromium)	S50xxx	515xx		

TABLE 2 - PROCEDURES FOR OBTAINING PRODUCT ANALYSIS SAMPLES

Form	Size characteristics	Cross-sectional area, sq. in. (sq. cm.)	Drill diameter, in. (mm) (approx.)	Sampling Instructions ^{a/}
Bars, rounds, squares, hexagons, shapes	Small sections	Not over 0.75 (4.84)	--	Chips shall be taken by milling or machining the full cross-section of the piece. ^{b/}
Bar-sized shapes; light flat bars	Width of cross-section greatly exceeds thickness	All	1/2 (12.7)	Chips shall be taken by milling or machining the full cross-section or by drilling through the steel at a point midway between the outside and center as shown in A, Figure 1. ^{b/}
Blooms, billets, slabs, rounds, squares, shapes	Large sections	Over 0.75 (4.84) to 16.0 (103.2)	1/2 (12.7)	Chips shall be taken at any point midway between the outside and center of the piece by drilling parallel to the axis. If impracticable, the piece may be drilled on the side as shown in B and C, Figure 1, provided chips are not taken until they represent the portion midway between the outside and center. ^{b/}
		Over 16.0 (103.2)	1 (25.4)	
Bored forgings	--	To 16.0 (103.2)	1/2 (12.7)	Samples from bored forgings shall be taken midway between the inner and outer surface of the wall.
		Over 16.0 (103.2)	1 (25.4)	
Plates	Thickness up to 2 inches (50.8 mm)	--	1/2 (12.7)	Chips shall be taken by drilling through the thickness of the plate. ^{b/}
	Thickness 2 inches and over (50.8 mm)	--	1 (25.4)	Chips shall be taken by drilling the edge of the plate at a point midway between the rolled surface and the midthickness. ^{b/}
Sheet, strip	Not of the full size rolled (out) from larger sheets	--	1/2 (12.7)	Chips shall be taken by milling or drilling entirely through the steel in a sufficient number of places so that the chips are representative of the entire sheet or strip. ^{b/} Sheet or strip may be folded both ways to facilitate sampling.
		--	1 (25.4)	
Sheet, strip	Rolled longitudinally	--	1/2 (12.7)	Specimen for sampling shall be out 2 inches (50.8 mm) in width and across full width as rolled.
		--	1 (25.4)	Specimen shall be cleaned and then folded piece pr more by bringing ends together and closing bend. Chips shall be taken in middle of length by milling inside sheared edges or by drilling entirely through from the flat surface. (Milling preferred.) Several light-gage pieces may be stacked together for folding simultaneously.
Sheet, strip	Rolled transversely	--	1 (25.4)	Specimen shall be out from side of as-rolled piece, halfway between the middle and end, and shall be 2 inches (50.8 mm) in width and 18 inches (457.2 mm) in length. Remainder of procedure is the same as for sheet and strip rolled longitudinally.
Sheet	Rolled transversely; 0.036-inch (0.914-mm) or less	--	1/2 (12.7)	Specimen shall be out from full length of sheet as rolled. Remainder of procedure is the same as for sheet and strip rolled longitudinally.
		--	1 (25.4)	
Tubular products	--	To 16.0 (103.2)	1/2 (12.7)	Drillings shall be taken from several points of each tube sampled as practicable. Chips shall be taken by milling or machining full cross-section.
		Over 16.0 (103.2)	1 (25.4)	
Wire rods and wire	--	--	--	Chip shall be taken by milling or machining the full cross section of the wire or wire rod.

^{a/} Each sample shall consist of not less than 2 ounces (56.7 grams) of drillings, unless otherwise specified. Drillings or chips shall be taken without the application of water, oil, or other lubricant, and all chips pr drillings shall be free from scale, grease, dirt, or other foreign substances. Chips or drillings shall not be overheated during cutting. Chips shall be well mixed, and shall pass ASTM No. 20 (2000 microns) sieve and shall be retained on an ASTM No. 30 (590 microns) sieve.

^{b/} When steel is subject to tests, drillings for product analysis may be taken from a tension test specimen or from, steel at the location of the tensile specimen, provided the specimen corresponds to the applicable sampling conditions.

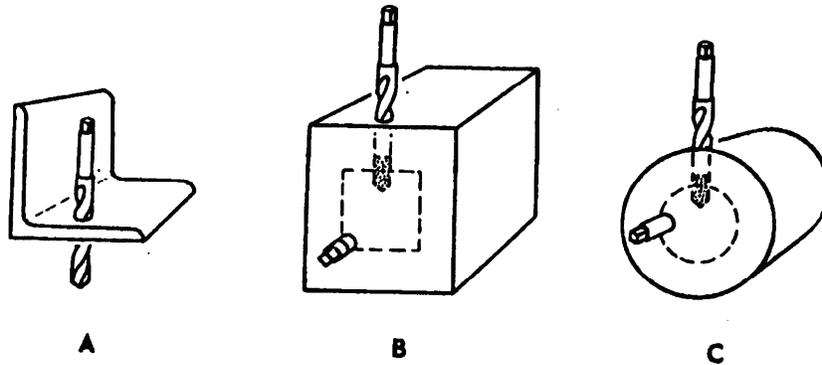


FIGURE 1 - DRILL LOCATIONS FOR OBTAINING PRODUCT ANALYSIS SAMPLES

6.2 Description

6.3 The chemical composition, ranges, and limits, and product analysis tolerances for alloy steels are covered in SAE Surface Vehicle Standard SAE J404.

Unlisted alloy steels include:

- a. Semifinished products (blooms, billets, and slabs) that exceed 200 square inches in cross-sectional area.
- b. Basic forms (bars, semifinished products, plates, shapes, sheet, strip, wire, and seamless tubing) ordered in compositions that are not standard, i.e., the percentages of some of the elements are outside of the chemical composition ranges shown in the tables for standard alloy steels.

7. STANDARD H-STEELS

7.1 Identification

H-steels are comprised of standard steels manufactured to fine-grain steel practices and available as bars, billets, blooms, and slabs, or seamless tubing. These steels are ordered by identification numbers including the prefix or suffix letter "H" as well as by hardenability limits selected in accordance with 7.2. Chemical composition for other sizes and forms, as well as hardenability limits for coarse-grain steels must be negotiated between the procuring agency and the contractor. The chemical compositions of standard H-steels are covered in Volume 1 of the SAE Handbook published by the Society of Automotive Engineers (SAE) and SAE Surface Vehicle Standard SAE J402.

7.2 Hardenability Bands

Typical hardenability band limits are shown graphically and as tabulations in Figure 2. In graphic form, the horizontal coordinate represents the distance from the quenched end of the standard (Jominy 1-inch, end-quench hardenability) test bar, while the vertical coordinate represents the Rockwell "C" hardness values derived from the test data. In tabular form, one column represents the distance away from the quenched end of the standard test bar, while two other columns indicate the minimum and maximum Rockwell "C" hardness values for each distance.

Hardenability band limits for all H-steels are contained in Volume 1 of the SAE Handbook published by SAE and in SAE Surface Vehicle Standard SAE J1268.

The graphs are used for estimating the hardness values obtainable at various depths, and also for comparing hardenability. To ensure accuracy and uniformity, the tabular values are used for specifying hardenability limits.

Hardenability limits are specified as a range; hence two or more values are selected to designate the desired hardenability. The preferable method is to designate only two values from the hardenability table. There are four methods of designating the two values, depending on known design requirements. Figure 2 illustrates each of the four methods of designating hardenability.