

Environmentally Compliant Processes for Landing Gear

RATIONALE

This document has been reaffirmed to comply with the SAE 5-Year Review policy.

TABLE OF CONTENTS

1. SCOPE 3

2. INTRODUCTION 3

2.1 Background 3

2.2 Applicable Regulations 4

2.3 Sources of Data 5

2.4 Specifications 5

3. REPLACEMENTS FOR CADMIUM 6

3.1 Candidates 6

3.2 Unscribed Neutral Salt Corrosion Resistance 7

3.3 Scribed Neutral Salt Corrosion Resistance 11

3.4 SO₂ Corrosion Resistance 15

3.5 Adhesion to Substrate 18

3.6 Hydrogen Embrittlement 20

3.7 Fatigue 24

3.8 Lubricity / Torque Tension 26

3.9 Paint Adhesion 27

4. PRIMERS 28

4.1 Reverse Impact Flexibility 28

4.2 Scribed Neutral Salt Corrosion 31

4.3 Unscribed SO₂ Corrosion 34

4.4 Adhesion 35

4.5 Fluid Resistance 37

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

Copyright © 2007 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
Tel: 724-776-4970 (outside USA)
Fax: 724-776-0790
Email: CustomerService@sae.org

SAE WEB ADDRESS: <http://www.sae.org>

SAE AIR5479

TABLE OF CONTENTS (Continued)

5. TOPCOATS	40
5.1 UV Resistance	40
6. COMPLETE SEQUENCE	41
6.1 Candidates	41
6.2 Unscribed Neutral Salt Corrosion	41
6.3 Scribed Neutral Salt Corrosion	44
6.4 Unscribed SO ₂ Corrosion	45
7. SUMMARY	46

SAENORM.COM : Click to view the full PDF of air5479

SAE AIR5479

1. SCOPE:

This SAE Aerospace Information Report (AIR) describes the performance of platings and coatings for landing gear that potentially provide environmental compliance benefits versus the current baseline processes. The hazardous systems addressed in this version of the document include cadmium plating, chromated primers, and high VOC (volatile organic compounds) topcoats.

Available data are presented for various standard tests in order to compare the replacement candidates. Conclusions are made as to the best performer(s) for each test section presented. These conclusions are not to be regarded as recommendations for or against any of the candidates.

The AIR applies to landing gear structures and mechanisms for all types of civil and military aircraft. The potential replacements apply to both original equipment manufacturer (OEM) hardware and overhaul of in-service landing gears.

2. INTRODUCTION:

2.1 Background:

This document addresses a number of materials and processes used in landing gear manufacturing and overhaul including cadmium, chromium, and volatile organic compounds (VOC). In the United States, these substances are controlled in three primary areas: 1) the Occupational Safety and Health Administration (OSHA) oversees exposure in the workplace, 2) the Environmental Protection Agency (EPA) oversees airborne emissions via the Clean Air Act, and 3) the EPA also oversees waterborne effluent via the Clean Water Act.

Cadmium is widely used as a sacrificial coating for corrosion protection of steel alloys. However, cadmium is easily removed during paint stripping operations, resulting in contamination of stripping media and large volumes of hazardous waste. Because low embrittlement cadmium is a soft, easily removable coating, it contaminates virtually everything it physically contacts (e.g. wiping rags, hydraulic oil, masking materials). The 1992 OSHA Expanded Standard for Cadmium established a permissible exposure limit (PEL) of $5 \mu\text{g}/\text{m}^3$ and reduced the Action Level (AL) to $2.5 \mu\text{g}/\text{m}^3$. This standard went into effect in 1996 and put nearly all overhaul operations at risk of violating AL and / or PEL, requiring the use of continually more stringent overhaul process control, worker medical surveillance and record keeping. Cadmium levels in effluent are regulated by the Clean Water Act, but the needs and capabilities of the local waste water treatment authority require their involvement in establishing individual discharge standards. The European Union (EU) has already banned the use of cadmium for various applications but exempted flight safety critical parts. European airlines expect the exemption to be phased out and are requesting a) harmonization of maintenance procedures and processes in which cadmium is involved, b) a policy commitment to replace cadmium for aircraft, engines and components and c) consensus on selection of cadmium alternatives.

SAE AIR5479

2.1 (Continued):

Chromium is a corrosion inhibitor used in chromated conversion coatings and chromated primers. Hexavalent chromium is a known carcinogen and the most dangerous form. Once in metallic form, such as hard chrome plate, chromium is not considered a significant environmental problem.

OSHA's proposed rule on occupational exposure to hexavalent chromium is expected in 2001. The rule is expected to lower the PEL for hexavalent Cr from the current ceiling limit of 52 $\mu\text{g}/\text{m}^3$ to an eight hour time weighted average of 0.5 $\mu\text{g}/\text{m}^3$ and an action level of 0.25 $\mu\text{g}/\text{m}^3$. Chromium is also regulated under the Clean Water Act. In January 2001, EPA submitted a proposal for new pretreatment wastewater effluent limits with the final limits expected to be determined in December 2002. The new limits will dramatically reduce effluent and some operations may need to update or replace existing pretreat facilities to meet these lower limits.

The Environmental Protection Agency (EPA) has finalized a National Emission Standard for Hazardous Air Pollutants (NESHAP) that includes coating operations at aerospace manufacturing and rework facilities. The standard requires existing and new major sources to control emissions to the level achievable by the Maximum Achievable Control Technology (MACT) consistent with section 112(d) of the Clean Air Act. The Hazardous Air Pollutants (HAPs) covered by this final rule include chromium, cadmium, methylene chloride, toluene, xylene, methyl ethyl ketone, ethylene glycol and glycol ethers. For existing sources, the requirements of this rule became effective September 1998. The NESHAP limits on VOC are 420 g / liter for topcoats and 350 g / liter for primers.

2.2 Applicable Regulations:

- Occupational Safety & Health Act, 19 U.S.C. s/s 61 et seq (1970)
- Clean Air Act, 42 U.S.C. s/s 7401 et seq (1970)
- Clean Water Act, 33 U.S.C. s/s 121 et seq (1977)
- Pollution Prevention Act, 42 U.S.C. s/s 1361 et seq (1990) - includes listing of EPA 17 Industrial Toxics

The Fall 2000 EPA / OSHA Unified Agenda Includes the following items:

Directive 1.2.3.3 – "Amendments to the Aerospace Manufacturing and Rework Facilities NESHAP for the HAP and VOC Content Limits for Primer Operations and Stay of Compliance"

Directive 2.1.1.1 – "Effluent Guidelines and Standards for the Metal Products and Machinery Category, Phase 1 and 2"

Directive 1.2.8.1 – "NESAHP: Miscellaneous Metal Parts and Products (Surface Coating)"

Directive 4.1.1.1 – "Hazardous Waste Identification Rule: Identification and Listing of Hazardous Wastes"

SAE AIR5479

2.2 (Continued):

Directive 1.2.5.1 – “MACT (Maximum Achievable Control Technology) Standards Review (Residual Air Toxics Risk)”

Directive 3.1.1.7 – “Occupational Exposure to Hexavalent Chromium (Preventing Occupational Illness: Chromium)”

2.3 Sources of Data:

“Elimination of Environmentally Hazardous Materials From the Landing Gear Overhaul Process”, Boeing Report MDC 98X0003 rev A, March 1999.

“Pollution Prevention Through Source Elimination: Environmentally Compliant Part Processing Sequence”, Boeing Report MDA 98P0067, October 1998.

“C-17 Pollution Prevention Non Chromated Primer Tests Report JGAPP / MDA Pilot Program”, Boeing Report MDC 98X0012, April 1997.

“C-17 Airlifter Weapon System Pollution Prevention Program”, contract CCP no. C-17A-0190C1 Task Order 012, September 1997.

2.4 Specifications:

2.4.1 SAE Publications: Available from SAE, 400 Commonwealth Drive, Warrendale, PA 15096-0001.

- AMS 2417E Plating, (Alkaline) Zinc-Nickel Alloy
- AMS 6345 Steel, Sheet, Strip, and Plate 0.95Cr - 0.20Mo (0.28-0.33C) (SAE 4130) Normalized or Otherwise Heat Treated
- AMS 6350 Steel, Sheet, Strip, and Plate 0.95Cr - 0.20Mo (0.28-0.33C) (SAE 4130)
- AMS 6351 Steel, Sheet, Strip, and Plate 0.95Cr - 0.20Mo (0.28-0.33C) (SAE 4130) Spheroidized
- AMS 6417E Steel, Bars, Forgings, and Tubing ... Electrode Vacuum Remelted

2.4.2 ASTM Publications: Available from ASTM, 100 Barr Harbor, West Conshohocken, PA 19428-2959.

- ASTM E 8 Standard Test Methods for Tension Testing of Metallic Materials
- ASTM G 85 Standard Practice for Modified Salt Spray (Fog) Testing
- ASTM B 117 Standard Practice for Operating Salt Spray (Fog) Apparatus
- ASTM F 519 Standard Test Method for Mechanical Hydrogen Embrittlement Evaluation
- ASTM D 1654 Evaluation ... Specimens Subjected to Corrosive Environments
- ASTM D 2794 Standard Test Method for Resistance ... Effects of Rapid Deformation
- ASTM D 3359 Standard Test Methods for Measuring Adhesion by Tape Test

SAE AIR5479

2.4.3 U.S. Government Publications: Available from DODSSP, Subscription Services Desk, Building 4D, 700 Robbins Avenue, Philadelphia, PA 19111-5094.

QQ-P-416	Plating, Cadmium, Electrodeposited
MIL-PRF-23377G	Primer Coatings: Epoxy, High Solids
MIL-R-81294	Remover, Paint, Epoxy, Polysulfide and Polyurethane Systems
MIL-PRF-83282D	Hydraulic Fluid, Fire Resistant, Synthetic Hydrocarbon Base
MIL-DTL-83488	Coating, Aluminum, Ion Vapor Deposited
MIL-PRF-85285C	Coating: Polyurethane, High Solids
MIL-PRF-85582C	Primer Coatings: Epoxy, Waterborne

2.4.4 Other Publications:

BAC 5637	Plating, (Acid) Zinc Nickel Alloy
MMS 423	Low VOC - Low Density Epoxy Primer
PS 21313	Coating Adhesion Tests
DMS 1786	Primer, Epoxy, Fluid Resistant

3. REPLACEMENTS FOR CADMIUM:

3.1 Candidates:

LE Cad (Baseline): Boeing PS13144 (QQ-P-416 equivalent). Iridite 8-P is used for chromate conversion coating unless otherwise specified.

IVD Aluminum: Ion vapor deposited aluminum per MIL-DTL-83488; requires dedicated vacuum chamber; cannot be applied to deep internal surfaces. No environmental hazard other than the possible use of chromated conversion coatings although non-chromated conversion coatings are acceptable. Iridite 14-2 is used for conversion coating unless otherwise specified.

Alkaline ZnNi: AMS 2417E w/ 24 hour hydrogen removal bake, chemical bath process. Zinic IZ-260 is the plating product name. Ni is a potential future hazard for EPA. Zinic IZ-268S is the conversion coating unless otherwise specified.

Acid ZnNi: BAC 5637, chemical bath process. Current specification limits use to low strength steels (<220 ksi) only. Ni is a potential future hazard for EPA. Corroban is the conversion coating unless otherwise specified.

Sermetel 984 / 985: Aluminum ceramic coating; 984 is primary coat; 985 is seal coat. Both coatings contain Cr, 985 is easily removed by mechanical means.

SnZn: BAC 5899, chemical bath process. Current specification limits use to low strength steels (≤ 180 ksi) and not for use with electrical applications (enclosures and connectors).

SAE AIR5479

3.1 (Continued):

Sputtered Aluminum: Aluminum deposition by linear magnetron sputtering.

Xylar 1/101: Aluminum ceramic coating. Xylar 1 is the base coat, while Xylar 101 is the seal coat.

Aalseal 518: Aluminum ceramic coating. Aalseal 598 is the seal coat.

Sermetel 249: Aluminum ceramic coating. Recommended as brush repair.

Sifco 4018: ZnNi brush repair to be used with the Zn-Ni plating process. Sifco 5030 is the conversion coating. Ni is a potential future hazard for EPA.

EM 6287: from EM Lubricants Inc.

3.2 Unscribed Neutral Salt Corrosion Resistance:

Conclusions: Most candidates were satisfactory with respect to the cadmium baseline except for Sermetel 984 by itself, EM6287, and Aalseal 518SC. All repair systems performed very well except for Sermetel 249 over the alkaline ZnNi.

In the Table 1 tests, 4 inch x 6 inch 0.040 thick panels were used as the test specimens. The panel material was 4130 steel in the normalized state per AMS 6345, AMS 6350, or AMS 6351. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. The testing consists of exposing the test panels to a pH neutral corrosive environment in a test chamber over an extended period of time. Red rust is the failure criterion.

In the Table 2 tests, 4 inch x 6 inch 0.040 thick panels were used as the test specimens. The panel material was 4130 steel in the normalized state per AMS 6345, AMS 6350, or AMS 6351. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. The testing consists of exposing the test panels to a pH neutral corrosive environment in a test chamber over an extended period of time. Red rust is the failure criterion.

In the Table 3 tests, 4 inch dia 0.065 inch thick tubes were used as the test specimens. The tube material was welded low carbon steel sheet per SAE 1010. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. The testing consists of exposing the test panels to a pH neutral corrosive environment in a test chamber over an extended period of time. Red rust is the failure criterion.

In the Table 4 tests, 4 inch x 6 inch 0.040 thick panels were used as the test specimens. The panel material was 4130 steel in the normalized state per AMS 6345, AMS 6350, or AMS 6351. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. The testing consists of exposing the test panels to a pH neutral corrosive environment in a test chamber over an extended period of time. Red rust is the failure criterion.

SAE AIR5479

TABLE 1 - Unscribed Neutral Salt Corrosion Resistance

Reference: ASTM B117
Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process
Tested by: McDonnell Douglas, 1996

<u>System</u>	<u>Specimen</u>	<u>Results</u> <u>Hrs to Failure</u>	<u>Prepared by</u>	<u>Comments</u>
LE Cad	4130 panel	10000	MDA	
LE Cad	4130 panel	10000	MDA	
LE Cad	4130 panel	10000	MDA	
LE Cad	4130 panel	10000	MDA	
IVD Alum	4130 panel	10000	MDA	
IVD Alum	4130 panel	10000	MDA	
IVD Alum	4130 panel	10000	MDA	
IVD Alum	4130 panel	10000	MDA	
ZnNi (BAC5637)	4130 panel	10000	Pure	
ZnNi (BAC5637)	4130 panel	10000	Pure	
ZnNi (BAC5637)	4130 panel	10000	Pure	
ZnNi (BAC5637)	4130 panel	10000	Pure	
Serm 984 / 985	4130 panel	10000	Sermatech	
Serm 984 / 985	4130 panel	10000	Sermatech	
Serm 984 / 985	4130 panel	10000	Sermatech	
Serm 984 / 985	4130 panel	10000	Sermatech	
ZnNi (AMS 2417E)	4130 panel	8106	Courter Hall	Dipsol Gumm
ZnNi (AMS 2417E)	4130 panel	8106	Courter Hall	Dipsol Gumm
ZnNi (AMS 2417E)	4130 panel	6066	Central Metal	McGean Rocho
ZnNi (AMS 2417E)	4130 panel	4386	Central Metal	McGean Rocho
ZnNi (AMS 2417E)	4130 panel	3384	Courter Hall	Dipsol Gumm
ZnNi (AMS 2417E)	4130 panel	2284	Courter Hall	Dipsol Gumm

SAENORM.COM : Click to view the full PDF of AIR5479

SAE AIR5479

TABLE 2 - Unscribed Neutral Salt Corrosion Resistance

Reference: ASTM B117 Source: USAF C-17 Pollution Prevention Program Tested by: McDonnell Douglas, 1997				
<u>System</u>	<u>Specimen</u>	<u>Results</u> <u>Hrs to Failure</u>	<u>Prepared by</u>	<u>Comments</u>
Serm 984/985	4130 panel	> 4000		
Serm 984/985	4130 panel	> 4000		
Serm 984/985	4130 panel	> 4000		
Serm 984/985	4130 panel	> 4000		
IVD + 518 / 598	4130 panel	> 4000		
IVD + 518 / 598	4130 panel	> 4000		
Alseal 518 / 598	4130 panel	> 4000		
Alseal 518 / 598	4130 panel	3120		
Zn-Ni (AMS 2417E)	4130 panel	3120		Dipsol Gumm
Zn-Ni (AMS 2417E)	4130 panel	2424		Dipsol Gumm
Zn-Ni (AMS 2417E)	4130 panel	2424		Dipsol Gumm
IVD + Alseal 518 SC	4130 panel	2424		
IVD + Serm 984/985	4130 panel	2304		
IVD + Xylar 1/101	4130 panel	2184		
IVD + EM 6287	4130 panel	2184		
IVD + EM 6287	4130 panel	2184		
Zn-Ni (AMS 2417E)	4130 panel	2112		Dipsol Gumm
Xylar 1/101	4130 panel	1776		
Xylar 1/101	4130 panel	1776		
Xylar 1/101	4130 panel	1776		
Xylar 1/101	4130 panel	1776		
LE Cad	4130 panel	1512		
LE Cad	4130 panel	1344		
E/M 6287	4130 panel	840		
E/M 6287	4130 panel	840		
E/M 6287	4130 panel	840		
IVD + Serm 984/985	4130 panel	840		
E/M 6287	4130 panel	744		
Alseal 518 SC	4130 panel	576		

SAENORM.COM : Click to buy the full PDF of air5479

SAE AIR5479

TABLE 3 - Unscribed Neutral Salt Corrosion Resistance

Reference: ASTM B117
Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process
Tested by: McDonnell Douglas, 1997

System	Thick, mils	Specimen	Results		Comments
			Hrs to Failure	Prepared by	
Sputtered Al		1010 tube	Pass 1680	Surface Solns	
Sputtered Al		1010 tube	Pass 1680	Surface Solns	
Sputtered Al		1010 tube	Pass 1680	Surface Solns	
Sputtered Al		1010 tube	Pass 1680	Surface Solns	
Ecoat + Boostercoat		1010 tube	Pass 1680	MDA	
Ecoat + Boostercoat		1010 tube	Pass 1680	MDA	
Ecoat + Boostercoat		1010 tube	Pass 1680	MDA	
Ecoat + Boostercoat		1010 tube	Pass 1680	MDA	
LE Cad		1010 tube	Pass 1680	MDA	
LE Cad		1010 tube	Pass 1680	MDA	
LE Cad		1010 tube	Pass 1680	MDA	
LE Cad		1010 tube	Pass 1680	MDA	
ZnNi (AMS 2417E)	0.55	1010 tube	Pass 1680	Courter Hall	Dipsol Gumm
ZnNi (AMS 2417E)	0.43	1010 tube	Pass 1680	Courter Hall	Dipsol Gumm
ZnNi (AMS 2417E)	0.82	1010 tube	Pass 1680	Courter Hall	Dipsol Gumm
ZnNi (AMS 2417E)	0.81	1010 tube	Pass 1680	Courter Hall	Dipsol Gumm
Serm 984	0.97	1010 tube	Pass 1680	Sermatech	
Serm 984	1.17	1010 tube	288	Sermatech	
Serm 984	1.24	1010 tube	480	Sermatech	
Serm 984	1.2	1010 tube	216	Sermatech	

TABLE 4 - Unscribed Neutral Salt Corrosion Resistance

Reference: ASTM B117
Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process
Tested by: McDonnell Douglas, 1997

System	Specimen	Results		Comments
		Hrs to Failure	Prepared by	
Brush Cd / Cd	4130 panel	>10000	MDA	
Brush Cd / Cd	4130 panel	>10000	MDA	
Brush Cd / Cd	4130 panel	>10000	MDA	
Brush Cd / Cd	4130 panel	>10000	MDA	
Serm 249 / IVD	4130 panel	>10000	MDA	
Serm 249 / IVD	4130 panel	>10000	MDA	
Brush ZnNi / IVD	4130 panel	>10000	MDA	
Brush ZnNi / IVD	4130 panel	>10000	MDA	
Serm 249 / acid ZnNi	4130 panel	>10000	MDA	
Serm 249 / acid ZnNi	4130 panel	>10000	MDA	
Brush ZnNi / acid ZnNi	4130 panel	>10000	MDA	
Brush ZnNi / acid ZnNi	4130 panel	>10000	MDA	
Brush ZnNi / Serm	4130 panel	>10000	MDA	
Brush ZnNi / Serm	4130 panel	>10000	MDA	
Brush ZnNi / alk ZnNi	4130 panel	>10000	MDA	
Brush ZnNi / alk ZnNi	4130 panel	>10000	MDA	
Serm 249 / Serm	4130 panel	>10000	MDA	
Serm 249 / Serm	4130 panel	>10000	MDA	
Serm 249 / alk ZnNi	4130 panel	1536	MDA	
Serm 249 / alk ZnNi	4130 panel	912	MDA	

SAE AIR5479

3.3 Scribed Neutral Salt Corrosion Resistance:

Conclusions: Many candidates were satisfactory, but generally not equal to cadmium for sacrificial corrosion protection. The barrier coatings failed immediately as expected. The aluminum coatings (IVD and sputtered) performed well as did most of the ZnNi platings. Sermetel 984/985 had results ranging from extremely poor to very good.

In the Table 5 tests, 4 inch x 6 inch 0.040 thick panels were used as the test specimens. The panel material was 4130 steel in the normalized state per AMS 6345, AMS 6350, or AMS 6351. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. Scribed tests call for making an "x" scribe that penetrates to the substrate of the specimen using the ASTM D 1654 scribe tool. The testing consists of exposing the test panels to a pH neutral corrosive environment in a test chamber over an extended period of time. Red rust is the failure criterion.

In the Table 6 tests, 4 inch x 6 inch 0.040 thick panels were used as the test specimens. The panel material was 4130 steel in the normalized state per AMS 6345, AMS 6350, or AMS 6351. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. Scribed tests call for making an "x" scribe that penetrates to the substrate of the specimen using the ASTM D 1654 scribe tool. The testing consists of exposing the test panels to a pH neutral corrosive environment in a test chamber over an extended period of time. Red rust is the failure criterion.

In the Table 7 tests, 4 inch dia. 0.065 inch thick tubes were used as the test specimens. The panel material was welded low carbon steel sheet per SAE 1010. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. Scribed tests call for making an "x" scribe that penetrates to the substrate of the specimen using the ASTM D 1654 scribe tool. The testing consists of exposing the test panels to a pH neutral corrosive environment in a test chamber over an extended period of time. Red rust is the failure criterion.

In the Table 8 tests, 4 inch dia. 0.065 inch thick tubes were used as the test specimens. The panel material was welded low carbon steel sheet per SAE 1010. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. Scribed tests call for making an "x" scribe that penetrates to the substrate of the specimen using the ASTM D 1654 scribe tool. The testing consists of exposing the test panels to a pH neutral corrosive environment in a test chamber over an extended period of time. Red rust is the failure criterion.

SAE AIR5479

TABLE 5 - Scribed Neutral Salt Corrosion Resistance

Reference: ASTM B117
Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process
Tested by: McDonnell Douglas, 1996

<u>System</u>	<u>Specimen</u>	<u>Results</u> <u>Hrs to Failure</u>	<u>Prepared by</u>	<u>Comments</u>
Serm 984 / 985	4130 panel	5130	Sermatech	3rd attempt Sermetel
Serm 984 / 985	4130 panel	5130	Sermatech	3rd attempt Sermetel
Serm 984 / 985	4130 panel	5130	Sermatech	3rd attempt Sermetel
Serm 984 / 985	4130 panel	5130	Sermatech	3rd attempt Sermetel
LE Cad	4130 panel	2376	MDA	
LE Cad	4130 panel	2376	MDA	
LE Cad	4130 panel	2376	MDA	
LE Cad	4130 panel	2376	MDA	
IVD Alum	4130 panel	2376	MDA	
IVD Alum	4130 panel	2376	MDA	
ZnNi (BAC5637)	4130 panel	2376	Pure	
ZnNi (BAC5637)	4130 panel	2376	Pure	
ZnNi (BAC5637)	4130 panel	2376	Pure	
IVD Alum	4130 panel	1704	MDA	
IVD Alum	4130 panel	1368	MDA	
ZnNi (AMS 2417E)	4130 panel	1032	Courter Hall	Dipsol Gumm
ZnNi (AMS 2417E)	4130 panel	1032	Courter Hall	Dipsol Gumm
ZnNi (AMS 2417E)	4130 panel	1032	Courter Hall	Dipsol Gumm
ZnNi (BAC5637)	4130 panel	816	Pure	
ZnNi (AMS 2417E)	4130 panel	816	Courter Hall	Dipsol Gumm
ZnNi (AMS 2417E)	4130 panel	360	Central Metal	McGean Rocho
ZnNi (AMS 2417E)	4130 panel	360	Central Metal	McGean Rocho
Serm 984 / 985	4130 panel	24	Sermatech	1st attempt Sermetel
Serm 984 / 985	4130 panel	24	Sermatech	1st attempt Sermetel
Serm 984 / 985	4130 panel	24	Sermatech	1st attempt Sermetel
Serm 984 / 985	4130 panel	24	Sermatech	1st attempt Sermetel
Serm 984 / 985	4130 panel	24	Sermatech	2nd attempt Sermetel
Serm 984 / 985	4130 panel	24	Sermatech	2nd attempt Sermetel
Serm 984 / 985	4130 panel	24	Sermatech	2nd attempt Sermetel
Serm 984 / 985	4130 panel	24	Sermatech	2nd attempt Sermetel

SAENORM.COM : Click to view the full PDF of air5479

SAE AIR5479

TABLE 6 - Scribed Neutral Salt Corrosion Resistance

Reference: ASTM B117
Source: USAF C-17 Pollution Prevention Program
Tested by: McDonnell Douglas, 1997

<u>System</u>	<u>Specimen</u>	<u>Results</u> <u>Hrs to Failure</u>	<u>Prepared by</u>	<u>Comments</u>
LE Cad	4130 panel	> 5000		
LE Cad	4130 panel	> 5000		
LE Cad	4130 panel	> 5000		
LE Cad	4130 panel	> 5000		
IVD + 518/598	4130 panel	4584		
IVD + 518/598	4130 panel	3744		
IVD + Aseal 518	4130 panel	3120		
IVD + Aseal 518	4130 panel	3120		
ZnNi	4130 panel	2952		Dipsol Gumm
ZnNi	4130 panel	2928		Dipsol Gumm
ZnNi	4130 panel	2808		Dipsol Gumm
ZnNi	4130 panel	2592		Dipsol Gumm
IVD + Serm 984/985	4130 panel	2184		
IVD + Serm 984/985	4130 panel	2184		
IVD + Serm 984/985	4130 panel	2184		
IVD + Xylar 1/101	4130 panel	2184		
IVD + Xylar 1/101	4130 panel	2184		
IVD + Zn-Ni (AMS2417E)	4130 panel	1632		
IVD + Zn-Ni (AMS2417E)	4130 panel	1632		
IVD + Serm 984/985	4130 panel	1512		
SermeTel 984/985	4130 panel	1248		
IVD + E/M 6287	4130 panel	1248		
IVD + E/M 6287	4130 panel	1248		
IVD + E/M 6287	4130 panel	1248		
IVD + E/M 6287	4130 panel	1248		
SermeTel 984/985	4130 panel	1128		
SermeTel 984/985	4130 panel	744		
SermeTel 984/985	4130 panel	672		
Xylar 1/101	4130 panel	576		
Xylar 1/101	4130 panel	312		
Xylar 1/101	4130 panel	312		
Aseal 518 SC	4130 panel	264		
Aseal 518 SC	4130 panel	216		
E/M 6287	4130 panel	72		
E/M 6287	4130 panel	72		
E/M 6287	4130 panel	72		
E/M 6287	4130 panel	72		
Aseal 518 SC/598	4130 panel	72		
Aseal 518 SC/598	4130 panel	72		
Xylar 1/101	4130 panel	72		

SAE AIR5479

TABLE 7 - Scribed Neutral Salt Corrosion Resistance

Reference: ASTM B117
Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process
Tested by: McDonnell Douglas, 1997

<u>System</u>	<u>Thick, mils</u>	<u>Specimen</u>	<u>Results Hrs to Failure</u>	<u>Prepared by</u>	<u>Comments</u>
Sputtered Al	0.69	1010 Tube	2000+	Surface Solns	
Sputtered Al	0.56	1010 Tube	2000+	Surface Solns	
LE Cad		1010 Tube	2000+	MDA	
LE Cad		1010 Tube	2000+	MDA	
LE Cad		1010 Tube	2000+	MDA	
ZnNi (AMS 2417E)	0.71	1010 Tube	1368	Courter Hall	
LE Cad		1010 Tube	1170	MDA	
ZnNi (AMS 2417E)	0.65	1010 Tube	1104	Courter Hall	
Sputtered Al	0.69	1010 Tube	1008	Surface Solns	
Sputtered Al	0.52	1010 Tube	1008	Surface Solns	
ZnNi (AMS 2417E)	0.71	1010 Tube	1008	Courter Hall	
ZnNi (AMS 2417E)	0.67	1010 Tube	960	Courter Hall	
Sermetal 984	0.92	1010 Tube	216	Sermatech	
Sermetal 984	1.07	1010 Tube	192	Sermatech	
Sermetal 984	1.19	1010 Tube	120	Sermatech	
Sermetal 984	0.93	1010 Tube	24	Sermatech	
Ecoat + Boostercoat		1010 Tube	24	MDA	Barrier for IVD
Ecoat + Boostercoat		1010 Tube	24	MDA	Barrier for IVD
Ecoat + Boostercoat		1010 Tube	24	MDA	Barrier for IVD
Ecoat + Boostercoat		1010 Tube	24	MDA	Barrier for IVD

TABLE 8 - Scribed Neutral Salt Corrosion Resistance, Puddling

Reference: ASTM B117
Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process
Tested by: McDonnell Douglas, 1997

<u>System</u>	<u>Thick, mils</u>	<u>Specimen</u>	<u>Results Hrs to Failure</u>	<u>Prepared by</u>	<u>Comments</u>
LE Cad		1010 Tube	3000	MDA	
LE Cad		1010 Tube	3000	MDA	
Sputtered Al	0.63	1010 Tube	3000	Surface Solns	
ZnNi (AMS 2417E)	0.58	1010 Tube	2520	Courter Hall	
Sputtered Al	0.54	1010 Tube	2020	Surface Solns	
ZnNi (AMS 2417E)	0.76	1010 Tube	1032	Courter Hall	
Sermetal 984	1.14	1010 Tube	24	Sermatech	
Sermetal 984	1.09	1010 Tube	24	Sermatech	
Ecoat + Boostercoat		1010 Tube	24	MDA	Barrier for IVD
Ecoat + Boostercoat		1010 Tube	24	MDA	Barrier for IVD

SAE AIR5479

3.4 SO₂ Corrosion Resistance:

Conclusions: The cadmium baseline performs relatively poorly in the sulfuric corrosion tests and some candidates easily surpassed that performance. The best sacrificial systems were the aluminum coatings (IVD and sputtered) followed by the Sermetel system. The ZnNi platings' performance was typically comparable to that of cadmium.

In the Table 9 tests, 4 inch x 6 inch 0.040 thick panels were used as the test specimens. The panel material was 4130 steel in the normalized state per AMS 6345, AMS 6350, or AMS 6351. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. The testing consists of exposing the test panels to an aggressive acidic corrosive environment in a test chamber over an extended period of time. Red rust is the failure criterion.

In the Table 10 tests, 4 inch x 6 inch 0.040 thick panels were used as the test specimens. The panel material was 4130 steel in the normalized state per AMS 6345, AMS 6350, or AMS 6351. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. The testing consists of exposing the test panels to an aggressive acidic corrosive environment in a test chamber over an extended period of time. Red rust is the failure criterion.

In the Table 11 tests, 4 inch dia. 0.065 inch thick tubes were used as the test specimens. The tube material was welded low carbon steel per SAE 1010. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. The testing consists of exposing the test panels to an aggressive acidic corrosive environment in a test chamber over an extended period of time. Red rust is the failure criterion.

SAE AIR5479

TABLE 9 - Unscribed SO₂ Corrosion Resistance

Reference: ASTM G85
 Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process
 Tested by: McDonnell Douglas, 1996

<u>System</u>	<u>Specimen</u>	<u>Results</u>		<u>Prepared by</u>	<u>Comments</u>
		<u>Hrs to Failure</u>			
IVD Alum	4130 panel	2016		MDA	
IVD Alum	4130 panel	1344		MDA	
Serm 984 / 985	4130 panel	1200		Sermatech	
Serm 984 / 985	4130 panel	1200		Sermatech	
Serm 984 / 985	4130 panel	1104		Sermatech	
IVD Alum	4130 panel	936		MDA	
IVD Alum	4130 panel	936		MDA	
Serm 984 / 985	4130 panel	696		Sermatech	
LE Cad	4130 panel	112		MDA	
LE Cad	4130 panel	96		MDA	
LE Cad	4130 panel	96		MDA	
LE Cad	4130 panel	96		MDA	
ZnNi (BAC5637)	4130 panel	72		Pure	
ZnNi (BAC5637)	4130 panel	72		Pure	
ZnNi (BAC5637)	4130 panel	72		Pure	
ZnNi (AMS 2417E)	4130 panel	72		Courter Hall	
ZnNi (BAC5637)	4130 panel	48		Pure	
ZnNi (AMS 2417E)	4130 panel	48		Courter Hall	
ZnNi (AMS 2417E)	4130 panel	48		Courter Hall	
ZnNi (AMS 2417E)	4130 panel	48		Courter Hall	

SAENORM.COM : Click to view the full PDF of SAE AIR5479

SAE AIR5479

TABLE 10 - Unscribed SO₂ Corrosion Resistance

Reference: ASTM G85 Source: USAF C-17 Pollution Prevention Program Tested by: McDonnell Douglas, 1997				
<u>System</u>	<u>Specimen</u>	<u>Results</u> <u>Hrs to Failure</u>	<u>Prepared by</u>	<u>Comments</u>
IVD + EM 6287	4130 panel	672		
IVD + EM 6287	4130 panel	504		
Serm 984/985	4130 panel	384		
IVD + EM 6287	4130 panel	384		
Serm 984/985	4130 panel	312		
Serm 984/985	4130 panel	312		
IVD + Xylar 1/101	4130 panel	312		
IVD + Xylar 1/101	4130 panel	312		
IVD + EM 6287	4130 panel	312		
Alseal 518 SC	4130 panel	240		
E/M 6287	4130 panel	240		
E/M 6287	4130 panel	240		
E/M 6287	4130 panel	240		
E/M 6287	4130 panel	240		
IVD + Xylar 1/101	4130 panel	240		
IVD + Alseal 518 SC	4130 panel	240		
IVD + Alseal 518 SC	4130 panel	240		
IVD + 518/598	4130 panel	240		
IVD + Serm 984/985	4130 panel	192		
IVD + Xylar 1/101	4130 panel	192		
IVD + 518/598	4130 panel	192		
IVD + Serm 984/985	4130 panel	144		
IVD + Serm 984/985	4130 panel	144		
IVD + Serm 984/985	4130 panel	144		
Serm 984/985	4130 panel	144		
Alseal 518 / 598	4130 panel	96		
Alseal 518 / 598	4130 panel	96		
LE Cad	4130 panel	96		
LE Cad	4130 panel	96		
LE Cad	4130 panel	96		
LE Cad	4130 panel	96		
Xylar 1/101	4130 panel	96		
Xylar 1/101	4130 panel	96		
Xylar 1/101	4130 panel	96		
Xylar 1/101	4130 panel	96		
Zn-Ni (AMS 2417E)	4130 panel	96		
Zn-Ni (AMS 2417E)	4130 panel	96		
Zn-Ni (AMS 2417E)	4130 panel	96		
Zn-Ni (AMS 2417E)	4130 panel	96		
Alseal 518 SC	4130 panel	48		
IVD + ZnNi	4130 panel	48		
IVD + ZnNi	4130 panel	48		
IVD + ZnNi	4130 panel	48		
IVD + ZnNi	4130 panel	48		

SAE AIR5479

TABLE 11 - Unscribed SO₂ Corrosion Resistance

Reference: ASTM G85 Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process Tested by: McDonnell Douglas, 1997					
<u>System</u>	<u>Thick, mils</u>	<u>Specimen</u>	<u>Results</u>	<u>Prepared by</u>	<u>Comments</u>
			<u>Hrs to Failure</u>		
Ecoat + Booster		1010 tube	3500+	MDA	
Ecoat + Booster		1010 tube	3500+	MDA	
Ecoat + Booster		1010 tube	3500+	MDA	
Ecoat + Booster		1010 tube	3500+	MDA	
Sputtered Al	0.78	1010 tube	912	Surface Solns	
Sputtered Al	0.85	1010 tube	768	Surface Solns	
Sputtered Al	0.71	1010 tube	648	Surface Solns	
Sputtered Al	0.63	1010 tube	648	Surface Solns	
Serm 984	0.99	1010 tube	216	Sermatech	
Serm 984	1.03	1010 tube	240	Sermatech	
Serm 984	1.15	1010 tube	120	Sermatech	
Serm 984	1.09	1010 tube	120	Sermatech	
ZnNi (AMS 2417E)	0.48	1010 tube	48	Courter Hall	Dipsol Gumm
ZnNi (AMS 2417E)	0.57	1010 tube	48	Courter Hall	Dipsol Gumm
ZnNi (AMS 2417E)	0.48	1010 tube	48	Courter Hall	Dipsol Gumm
ZnNi (AMS 2417E)	0.36	1010 tube	48	Courter Hall	Dipsol Gumm
LE Cad		1010 tube	48	MDA	
LE Cad		1010 tube	24	MDA	
LE Cad		1010 tube	24	MDA	
LE Cad		1010 tube	24	MDA	

3.5 Adhesion to Substrate:

Conclusions: Care should be taken to draw conclusions from the following adhesion data as the test is extremely severe relative to the service environment. The brittle metallic ceramic coating of Sermatel was not expected to pass this test but its adhesion has been proven through other tests. Also, IVD aluminum routinely passes steel adhesion tests in production and these failures were likely due to processing problems. All the repair systems failed except for the ZnNi systems with ZnNi repair.

SAE AIR5479

TABLE 12 - Bend to Break Adhesion

Reference: QQ-P-416 rev F
 Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process
 Tested by: McDonnell Douglas, 1996

System	Specimen	Results		Prepared by	Comments
		Pass or Fail			
LE Cad	4130 coupon	Pass		MDA	
LE Cad	4130 coupon	Pass		MDA	
LE Cad	4130 coupon	Pass		MDA	
LE Cad	4130 coupon	Pass		MDA	
ZnNi (BAC5637)	4130 coupon	Pass		Pure	
ZnNi (BAC5637)	4130 coupon	Pass		Pure	
ZnNi (BAC5637)	4130 coupon	Pass		Pure	
ZnNi (BAC5637)	4130 coupon	Pass		Pure	
ZnNi (AMS 2417E)	4130 coupon	Pass		Courter Hall	
ZnNi (AMS 2417E)	4130 coupon	Pass		Courter Hall	
ZnNi (AMS 2417E)	4130 coupon	Pass		Courter Hall	
ZnNi (AMS 2417E)	4130 coupon	Pass		Courter Hall	
IVD Alum	4130 coupon	Fail		MDA	
IVD Alum	4130 coupon	Fail		MDA	
IVD Alum	4130 coupon	Fail		MDA	
IVD Alum	4130 coupon	Fail		MDA	
Serm 984 / 985	4130 coupon	Fail		Sermatech	
Serm 984 / 985	4130 coupon	Fail		Sermatech	
Serm 984 / 985	4130 coupon	Fail		Sermatech	
Serm 984 / 985	4130 coupon	Fail		Sermatech	
IVD Alum	4130 coupon	Fail		MDA	2nd attempt for IVD Alum
IVD Alum	4130 coupon	Fail		MDA	2nd attempt for IVD Alum
IVD Alum	4130 coupon	Fail		MDA	2nd attempt for IVD Alum
IVD Alum	4130 coupon	Fail		MDA	2nd attempt for IVD Alum

SAENORM.COM : Click to view the full PDF of air5479

SAE AIR5479

TABLE 13 - Bend to Break Adhesion for Repairs

Reference: QQ-P-416 rev F Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process Tested by: McDonnell Douglas, 1996				
System	Specimen	Results	Prepared by	Comments
		Pass or Fail		
BAC5637 + ZnNi	4130 coupon	Pass	Pure	
BAC5637 + ZnNi	4130 coupon	Pass	Pure	
AMS 2417E + ZnNi	4130 coupon	Pass	Courter Hall	
AMS 2417E + ZnNi	4130 coupon	Pass	Courter Hall	
BAC5637 + Serm 249	4130 coupon	Fail	Pure	
BAC5637 + Serm 249	4130 coupon	Fail	Pure	
AMS 2417E + Serm 249	4130 coupon	Fail	Courter Hall	
AMS 2417E + Serm 249	4130 coupon	Fail	Courter Hall	
Cad + brush Cd repair	4130 coupon	Fail	MDA	
Cad + brush Cd repair	4130 coupon	Fail	MDA	
Cad + brush Cd repair	4130 coupon	Fail	MDA	
Cad + brush Cd repair	4130 coupon	Fail	MDA	
IVD + ZnNi repair	4130 coupon	Fail	MDA	
IVD + ZnNi repair	4130 coupon	Fail	MDA	
IVD + Serm 249	4130 coupon	Fail	MDA	
IVD + Serm 249	4130 coupon	Fail	MDA	
Serm 984/985 + ZnNi	4130 coupon	Fail	Sermatech	
Serm 984/985 + ZnNi	4130 coupon	Fail	Sermatech	
Serm 984/985 + S249	4130 coupon	Fail	Sermatech	
Serm 984/985 + S249	4130 coupon	Fail	Sermatech	

3.6 Hydrogen Embrittlement:

Conclusions: Cadmium and IVD aluminum appear to pass HE testing regularly. Several repeat tests were required with different baking and processing steps to enable the Sermetel and ZnNi systems to pass reliably.

In the Table 14 tests, notched round bar were used as the test specimens. The material was AISI 4340 steel heat treated to attain 50-53 HRC. Specimen machining was performed by Dirats Laboratories using a special grinding technique, which minimizes compressive residual stresses. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. The success criterion for the standard dry test requires that the specimen withstand 200 hours of sustained load at 75% of the notch fracture point.

SAE AIR5479

TABLE 14 - Hydrogen Embrittlement

Reference: ASTM F519, Dry, Para. 3.1 Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process Tested by: Dirats Laboratories, 1996				
<u>System</u>	<u>Specimen</u>	<u>Results</u> Pass or Fail	<u>Prepared by</u>	<u>Comments</u>
LE Cad	1a, 4340, Dirats	Pass	MDA	
LE Cad	1a, 4340, Dirats	Pass	MDA	
LE Cad	1a, 4340, Dirats	Pass	MDA	
LE Cad	1a, 4340, Dirats	Pass	MDA	
IVD Alum	1a, 4340, Dirats	Pass	MDA	
IVD Alum	1a, 4340, Dirats	Pass	MDA	
IVD Alum	1a, 4340, Dirats	Pass	MDA	
IVD Alum	1a, 4340, Dirats	Pass	MDA	
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	
ZnNi (BAC5637)	1a, 4340, Dirats	Pass	Central Metal Fin	
ZnNi (BAC5637)	1a, 4340, Dirats	Pass	Central Metal Fin	
ZnNi (BAC5637)	1a, 4340, Dirats	Pass	Central Metal Fin	
ZnNi (BAC5637)	1a, 4340, Dirats	Fail (64 hrs)	Central Metal Fin	
Serm 984 / 985	1a, 4340, Dirats	Fail (7.7 hrs)	Sermatech	
Serm 984 / 985	1a, 4340, Dirats	Fail (5 hrs)	Sermatech	
Serm 984 / 985	1a, 4340, Dirats	Pass	Sermatech	
Serm 984 / 985	1a, 4340, Dirats	Fail (9 hrs)	Sermatech	

3.6 (Continued):

In the Table 15 tests, notched round bar were used as the test specimens. The material was AISI 4340 steel heat treated to attain 50-53 HRC. Specimen machining was performed by Dirats Laboratories using a special grinding technique, which minimizes compressive residual stresses. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. The success criterion for the standard dry test requires that the specimen withstand 200 hours of sustained load at 75% of the notch fracture point.

SAE AIR5479

TABLE 15 - Hydrogen Embrittlement

Reference: ASTM F519, Dry, Para. 3.1 Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process Tested by: OO-ALC, 1997				
<u>System</u>	<u>Specimen</u>	<u>Results</u> <u>Pass or Fail</u>	<u>Prepared by</u>	<u>Comments</u>
Serm 984	1a, 4340, Dirats	Pass	Sermatech	Omission of 985 seal coat
Serm 984	1a, 4340, Dirats	Pass	Sermatech	Omission of 985 seal coat
Serm 984	1a, 4340, Dirats	Pass	Sermatech	Omission of 985 seal coat
Serm 984	1a, 4340, Dirats	Pass	Sermatech	Omission of 985 seal coat
Serm 984	1a, 4340, Dirats	Pass	Sermatech	Omission of 985 seal coat
Serm 984	1a, 4340, Dirats	Pass	Sermatech	Omission of 985 seal coat
Serm 984	1a, 4340, Dirats	Pass	Sermatech	Omission of 985 seal coat
Serm 984	1a, 4340, Dirats	Pass	Sermatech	Omission of 985 seal coat
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	addl 23 hr relief bake
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	addl 23 hr relief bake
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	addl 23 hr relief bake
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	addl 23 hr relief bake
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (0.5 hrs)	Courter Hall	
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (1.3 hrs)	Courter Hall	
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (1.3 hrs)	Courter Hall	
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (1.5 hrs)	Courter Hall	

3.6 (Continued):

In the Table 16 tests, notched round bar were used as the test specimens. The material was AISI 4340 steel heat treated to attain 50-53 HRC. Specimen machining was performed by Dirats Laboratories using a special grinding technique, which minimizes compressive residual stresses. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. The wet re-embrittlement test requires that the specimen be exposed to the embrittling agent (in this case Daraclean 232GF) while under 45% load, then withstand 200 hours of sustained load at 75% of the notch fracture point.

SAE AIR5479

TABLE 16 - Hydrogen Embrittlement

Reference: ASTM F519, Wet Re-embrittlement, Appendix A5 Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process Tested by: OO-ALC, 1997				
<u>System</u>	<u>Specimen</u>	<u>Results Pass or Fail</u>	<u>Prepared by</u>	<u>Comments</u>
Serm 984	1a, 4340, Dirats	Pass	Sermatech	
Serm 984	1a, 4340, Dirats	Pass	Sermatech	
Serm 984	1a, 4340, Dirats	Pass	Sermatech	
Serm 984	1a, 4340, Dirats	Pass	Sermatech	
Serm 984	1a, 4340, Dirats	Pass	Sermatech	
Serm 984	1a, 4340, Dirats	Pass	Sermatech	
Serm 984	1a, 4340, Dirats	Pass	Sermatech	
Serm 984	1a, 4340, Dirats	Pass	Sermatech	
Serm 984	1a, 4340, Dirats	Pass	Sermatech	
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	after addl relief bake
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	after addl relief bake
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	after addl relief bake
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	after addl relief bake
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (4.3 hr)	Courter Hall	
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (4.2 hr)	Courter Hall	
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (3.7 hr)	Courter Hall	
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (198 hr)	Courter Hall	

3.6 (Continued):

In the Table 17 tests, notched round bar were used as the test specimens. The material was AISI 4340 steel heat treated to attain 50-53 HRC. Specimen machining was performed by Dirats Laboratories using a special grinding technique, which minimizes compressive residual stresses. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. The success criterion for the standard dry test requires that the specimen withstand 200 hours of sustained load at 75% of the notch fracture point.

SAE AIR5479

TABLE 17 - Hydrogen Embrittlement

Reference: ASTM F519 Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process Tested by: OO-ALC, 1997				
System	Specimen	Results		Comments
		Pass or Fail	Prepared by	
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	48 hr bake after chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	48 hr bake after chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	48 hr bake after chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	48 hr bake after chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	24 hr bake after chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	24 hr bake after chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	24 hr bake after chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Pass	Courter Hall	24 hr bake after chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (8.3 hr)	Dipsol Gumm	24 hr bake before chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (17.8 hr)	Dipsol Gumm	24 hr bake before chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (11.7 hr)	Dipsol Gumm	24 hr bake before chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (8.3 hr)	Dipsol Gumm	24 hr bake before chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (0.1 hr)	Dipsol Gumm	3 hr bake before chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (0.1 hr)	Dipsol Gumm	3 hr bake before chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (0.1 hr)	Dipsol Gumm	3 hr bake before chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (0.1 hr)	Dipsol Gumm	3 hr bake before chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (22.2 hr)	Dipsol Gumm	24 hr bake after chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (15.2 hr)	Dipsol Gumm	24 hr bake after chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (22.0 hr)	Dipsol Gumm	24 hr bake after chromate
ZnNi (AMS 2417E)	1a, 4340, Dirats	Fail (17.8 hr)	Dipsol Gumm	24 hr bake after chromate

3.7 Fatigue Resistance:

Conclusions: As expected, fatigue performance is not severely affected by the soft, ductile coatings such as cadmium and IVD aluminum. The hard metal platings had the poorest performance with the acid ZnNi fatigue lives well below those of the alkaline ZnNi or the Sermetel.

Category: Unnotched Fatigue Resistance

Reference: ASTM E 8, constant amplitude, R=+0.1

Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process

Specimens: 300M round bar specimens, AMS 6417 heat treated to 280 ksi, degreased and deoxidized prior to coating

Tested by: Dirats Laboratories, Westfield, MA

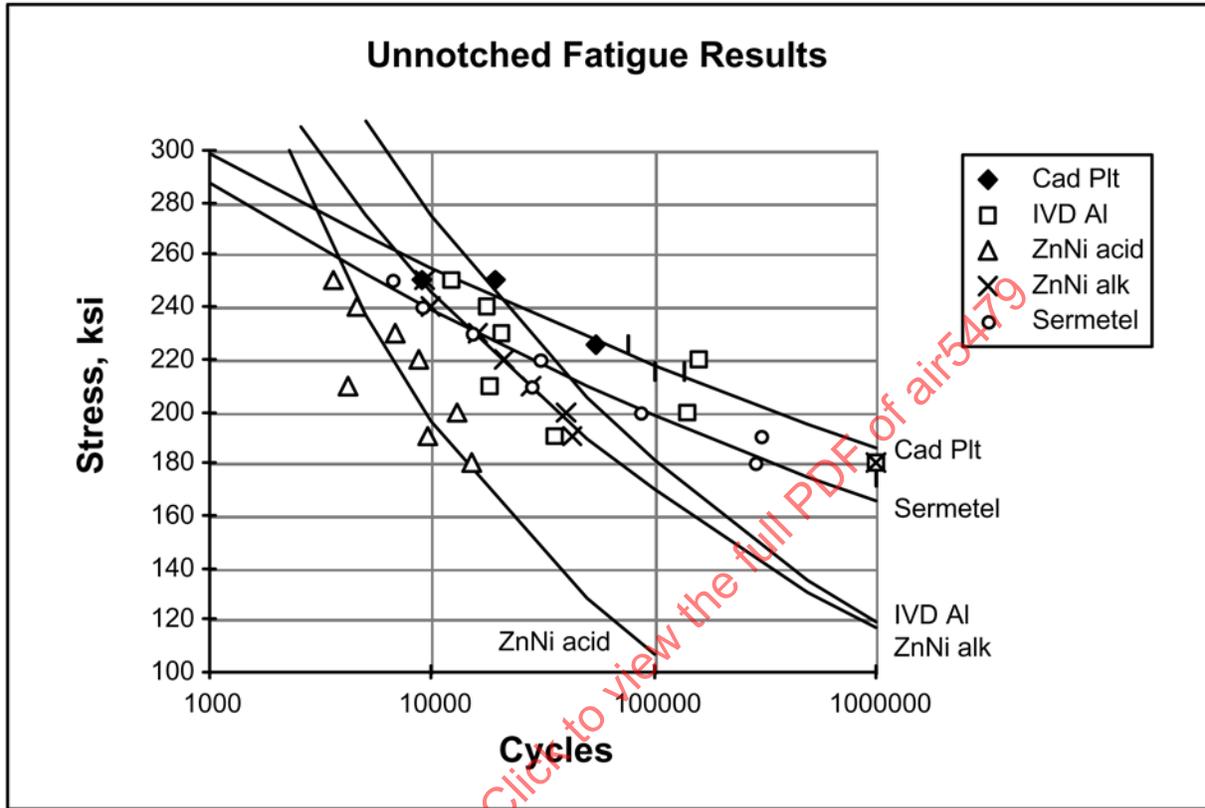


FIGURE 1 - Unnotched Fatigue Results

3.7 (Continued):

Category: Notched Fatigue Resistance

Reference: ASTM E 8, constant amplitude, R=+0.1, Kt=3

Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process

Specimens: 300M round bar specimens, AMS 6417 heat treated to 280 ksi, degreased and deoxidized prior to coating

Tested by: Dirats Laboratories, Westfield, MA

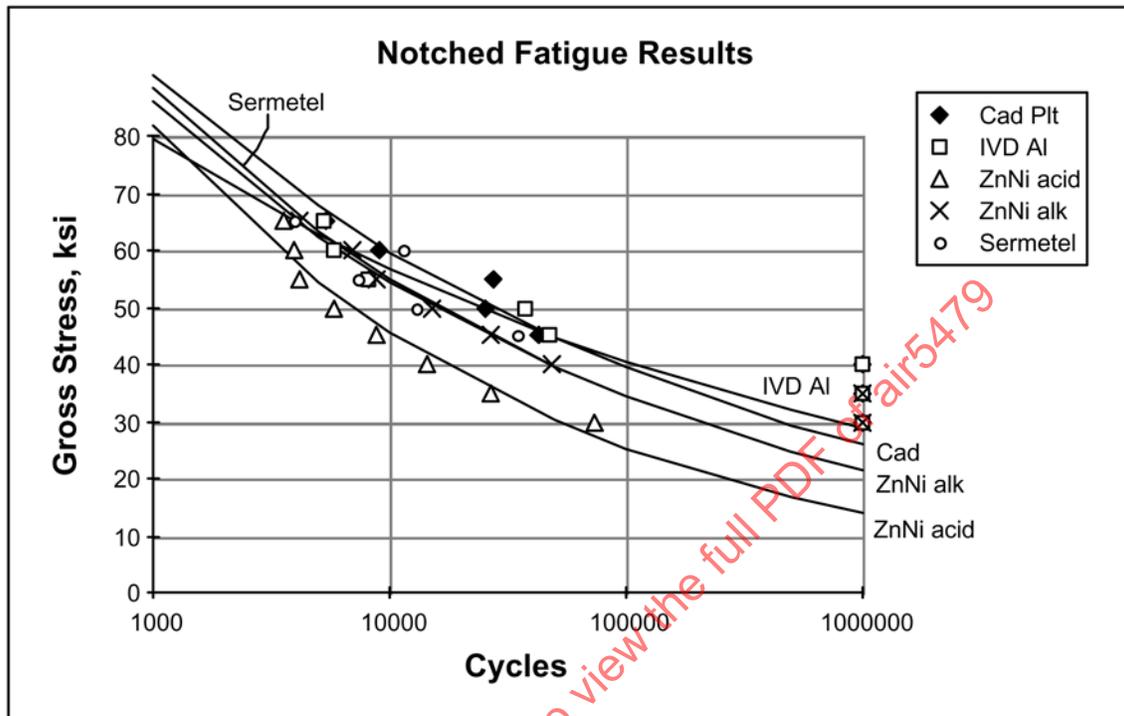


FIGURE 2--Notched Fatigue Results

3.8 Lubricity / Torque Tension:

Conclusions: All candidates exhibited similar torque tension characteristics.

In the Table 18 tests, four NAS 1308-10 bolts and four 47FLW-820 nuts were processed with each of the candidate replacements and with cadmium. The finished nuts were processed with a graphite dry film lubricant E/M 6286. MIL-T-5544 graphite petroleum lubricant was also brush applied to both the nuts and bolts prior to each of 15 remove / replace cycles. The test involved applying and measuring the torque required to reach a 20,000 pound tensile load.

SAE AIR5479

TABLE 18 - Lubricity / Torque Tension

Reference: none Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process Tested by: McDonnell Douglas, 1996						
<u>System</u>	<u>Specimen</u>	Torque, in lb <u>1st Cycle</u>	Torque, in lb <u>5th Cycle</u>	Torque, in lb <u>10th Cycle</u>	Torque, in lb <u>15th Cycle</u>	<u>Comments</u>
Serm 984/985	nut/bolt, 20kips	875	885	860	860	
ZnNi (AMS 2417E)	nut/bolt, 20kips	770	875	875	850	
ZnNi (BAC 5637)	nut/bolt, 20kips	850	850	825	820	
IVD Alum	nut/bolt, 20kips	970	860	875	940	
LE Cad	nut/bolt, 20kips	750	800	810	850	

3.9 Paint Adhesion:

Conclusions: All candidates exhibited acceptable paint stripping characteristics.

In the Table 19 tests, 4 inch by 6 inch 0.040 inch thick 4130 steel panels were processed with each of the candidate replacements. The panels were degreased and deoxidized with aluminum oxide grit prior to being primed with Deft 44GN36 epoxy primer. The panels were stripped using plastic bead media (MIL-R-81294 Type II urea, 12/16 mesh) at a pressure feed of 40 psi.

TABLE 19 - Paint Adhesion, Stripability

Reference: none Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process Tested by: McDonnell Douglas, 1996				
<u>System</u>	<u>Specimen</u>	<u>Results</u>		<u>Comments</u>
		Avg. Stripping Time, sec		
LE Cad	4130 panel	27	(3 panels)	PMB, 40 psi, 12/16 mesh
Serm 984/985	4130 panel	36	(1 panel)	PMB, 40 psi, 12/16 mesh
ZnNi (AMS 2417E)	4130 panel	37	(3 panels)	PMB, 40 psi, 12/16 mesh
IVD Alum	4130 panel	37	(4 panels)	PMB, 40 psi, 12/16 mesh
ZnNi (BAC 5637)	4130 panel	42	(3 panels)	PMB, 40 psi, 12/16 mesh

SAE AIR5479

4. PRIMERS:

4.1 Reverse Impact Flexibility:

Conclusions: All candidates, except for the Ecoat, failed to meet the required impact energy level when the anodize was present. Without anodize, only the Ecoat and the control baseline consistently passed. As for the elongation test, the Ecoat would surely have passed, but of those tested, only the chromated baseline primer passed.

In the Table 20 tests, four 2024-T3 aluminum panels were sulfuric acid anodized and processed with each of the candidate primers. The panels were subjected to impact from a steel ball peen at increasing energy levels until primer failure occurred. The required energy level per MMS 423 is 20 in lb.

TABLE 20 - Reverse Impact Flexibility

Reference: ASTM D2794 Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process							
System	Thick, mils	Results		Prepared by	Tested by	Test Date	Comments
		Impact, in-lb					
Ecoat	0.58	80		MDA	MDA	1996	Cathoguard 310
Ecoat	0.54	80		MDA	MDA	1996	Cathoguard 310
Ecoat	0.55	80		MDA	MDA	1996	Cathoguard 310
Ecoat	0.56	80		MDA	MDA	1996	Cathoguard 310
Defat 44-GN-36	0.88	2		MDA	MDA	1996	
Defat 44-GN-36	0.87	2		MDA	MDA	1996	
Defat 44-W-16	0.98	2		MDA	MDA	1996	
Defat 44-GN-36	0.85	0		MDA	MDA	1996	
Defat 44-GN-36	0.85	0		MDA	MDA	1996	
Spraylat EWDY048	0.98	0		MDA	MDA	1996	
Spraylat EWDY048	0.82	0		MDA	MDA	1996	
Spraylat EWDY048	0.82	0		MDA	MDA	1996	
Spraylat EWDY048	0.68	0		MDA	MDA	1996	
Defat 44-W-16	1.10	0		MDA	MDA	1996	
Defat 44-W-16	1.04	0		MDA	MDA	1996	
Defat 44-W-16	0.90	0		MDA	MDA	1996	
Boostercoat	1.65	0		MDA	MDA	1996	
Boostercoat	1.67	0		MDA	MDA	1996	
Boostercoat	1.75	0		MDA	MDA	1996	
Boostercoat	1.80	0		MDA	MDA	1996	

In the Table 21 tests, 2024-T3 aluminum panels were sulfuric acid anodized and processed with each of the candidate primers. The panels were subjected to increasing strain levels until primer failure occurred. The required elongation level per MIL-PRF-85582C is 10%.

SAE AIR5479

TABLE 21 - Percent Elongation

Reference: MIL-PRF-85582C Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process						
System	Thick, mils	Results % Elong	Prepared by	Tested by	Test Date	Comments
Deft 44-GN-36	0.85	10	MDA	MDA	1996	10% is Spec. Minimum
Deft 44-GN-36	0.90	10	MDA	MDA	1996	
Deft 44-GN-36	0.93	10	MDA	MDA	1996	
Deft 44-GN-36	0.78	10	MDA	MDA	1996	
Deft 44-W-16	1.06	5	MDA	MDA	1996	
Deft 44-W-16	1.02	5	MDA	MDA	1996	
Deft 44-W-16	1.17	5	MDA	MDA	1996	
Deft 44-W-16	1.09	5	MDA	MDA	1996	
Spraylat EWDY048	1.33	2	MDA	MDA	1996	
Spraylat EWDY048	1.40	2	MDA	MDA	1996	
Spraylat EWDY048	1.33	2	MDA	MDA	1996	
Spraylat EWDY048	1.20	2	MDA	MDA	1996	
Boostercoat	2.37	2	MDA	MDA	1996	
Boostercoat	2.41	2	MDA	MDA	1996	
Boostercoat	2.28	2	MDA	MDA	1996	
Boostercoat	2.39	2	MDA	MDA	1996	

4.1 (Continued):

In the Table 22 tests, four 2024-T3 bare aluminum panels were processed with each of the candidate primers. The panels were subjected to impact from a steel ball peen at increasing energy levels until primer failure occurred. The required energy level per MMS 423 is 20 in lb.

SAE AIR5479

TABLE 22 - Reverse Impact Flexibility

Reference: ASTM D2794 Source: JGAPP (C-17 Pollution Prevention)					
<u>System</u>	<u>Specimen</u>	<u>Results</u>	<u>Tested by</u>	<u>Test Date</u>	<u>Comments</u>
Courtaulds 513X332 / 910X457	bare 2024-T3	Pass	MDA	1996	control
Courtaulds 513X332 / 910X457	bare 2024-T3	Pass	MDA	1996	control
Deft 44-GN-36	bare 2024-T3	Pass	MDA	1996	control
Deft 44-GN-36	bare 2024-T3	Pass	MDA	1996	control
Courtaulds 515X386 / 910X831	bare 2024-T3	Pass	MDA	1996	control
Courtaulds 515X386 / 910X831	bare 2024-T3	Pass	MDA	1996	control
Spraylat EWDY048	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Spraylat EWDY048	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Deft 44-W-16	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Deft 44-W-16	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Deft 44-W-17	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Deft 44-W-17	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Crown Metro 10-PW22-2/ECW119	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Crown Metro 10-PW22-2/ECW119	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Ecoat: BASF G28AD012	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Ecoat: BASF G28AD012	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Sterling U-1201-NC/U-1202-F	bare 2024-T3	Pass	MDA	1996	High Solids
Sterling U-1201-NC/U-1202-F	bare 2024-T3	Pass	MDA	1996	High Solids
Spraylat EEAE136	bare 2024-T3	Pass	MDA	1996	High Solids
Spraylat EEAE136	bare 2024-T3	Pass	MDA	1996	High Solids
Crown Metro 10P22-3/EC-270	bare 2024-T3	Pass	MDA	1996	High Solids
Crown Metro 10P22-3/EC-270	bare 2024-T3	Pass	MDA	1996	High Solids
Spraylat EWDE 139A/EWAE 118B	bare 2024-T3	Pass	MDA	1996	Waterborne type II
Spraylat EWDE 139A/EWAE 118B	bare 2024-T3	Pass	MDA	1996	Waterborne type II
Courtaulds RW-3151/3151B001	bare 2024-T3	Fail	MDA	1996	Waterborne type I
Courtaulds RW-3151/3151B001	bare 2024-T3	Fail	MDA	1996	Waterborne type I
Sterling Lacquer U-4800-NC/U-4801	bare 2024-T3	Fail	MDA	1996	Waterborne type I
Sterling Lacquer U-4800-NC/U-4801	bare 2024-T3	Fail	MDA	1996	Waterborne type I
Lord Aeroglaze 9740	bare 2024-T3	Fail	MDA	1996	High Solids
Lord Aeroglaze 9740	bare 2024-T3	Fail	MDA	1996	High Solids

4.1 (Continued):

In the Table 23 tests, four 2024-T3 bare aluminum panels were processed with each of the candidate primers. The panels were subjected to impact from a steel ball peen at increasing energy levels until primer failure occurred. The required energy level per MMS 423 is 20 in lb.

SAE AIR5479

TABLE 23 - Reverse Impact Flexibility

Reference: ASTM D2794 Source: JGAPP (C-17 Pollution Prevention)					
<u>System</u>	<u>Specimen</u>	<u>Results</u>	<u>Tested by</u>	<u>Test Date</u>	<u>Comments</u>
Courtaulds 513X303 / 910X357	bare 2024-T3	Pass	MDA	1996	control
Courtaulds 513X303 / 910X357	bare 2024-T3	Pass	MDA	1996	control
Ecoat: BASF G28AD012	bare 2024-T3	Pass	MDA	1996	
Ecoat: BASF G28AD012	bare 2024-T3	Pass	MDA	1996	
Spraylat EWDY048	bare 2024-T3	Fail	MDA	1996	
Defat 44-W-16	bare 2024-T3	Fail	MDA	1996	
Defat 44-W-16	bare 2024-T3	Fail	MDA	1996	
Crown Metro 10-PW22-2/ECW119	bare 2024-T3	Fail	MDA	1996	
Crown Metro 10-PW22-2/ECW119	bare 2024-T3	Fail	MDA	1996	
Coutaulds RW-3181-64	bare 2024-T3	Fail	MDA	1996	
Coutaulds RW-3181-64	bare 2024-T3	Fail	MDA	1996	
Spraylat EWAE-118	bare 2024-T3	Fail	MDA	1996	
Spraylat EWAE-118	bare 2024-T3	Fail	MDA	1996	

4.2 Scribed Neutral Salt Corrosion:

Conclusions: The baseline chromated primers were more successful in the scribed corrosion resistance tests. Of the non-chromated primers, only the Crown Metro was comparable to the baseline. On aluminum, the Boostercoat was the best of those primers tested.

In the Table 24 tests, four 7075-T6 aluminum panels were chromate conversion coated with Iridite 14-2 followed by application of each of the candidate primers. Panels were cured at room temperature for 2 weeks prior to test. The panels were scribed using an ASTM D 1654 scribe tool. The testing consisted of exposing the test panels to an aggressive acidic corrosive environment in a test chamber over an extended period of time. 2000 hours exposure without any substrate corrosion is the success criterion of MIL-PRF-23377G and MIL-PRF-85582C.

SAE AIR5479

TABLE 24 - Scribed Neutral Salt Corrosion Resistance

Reference: ASTM B117 Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process							
System	Thick, mils	Results		Prepared by	Tested by	Test Date	Comments
		Hrs to Failure					
Deft 44-GN-36	0.88	Pass (>2000)		MDA	MDA	1996	
Deft 44-GN-36	0.92	Pass (>2000)		MDA	MDA	1996	
Deft 44-GN-36	0.97	Pass (>2000)		MDA	MDA	1996	
Deft 44-GN-36	1.03	Pass (>2000)		MDA	MDA	1996	
Boostercoat	2	Fail (1500)		MDA	MDA	1996	
Boostercoat	1.97	Fail (1500)		MDA	MDA	1996	
Boostercoat	1.95	Fail (1500)		MDA	MDA	1996	
Boostercoat	1.96	Fail (1500)		MDA	MDA	1996	
Spraylat EWDY048	0.83	Fail (1000)		MDA	MDA	1996	
Spraylat EWDY048	0.9	Fail (1000)		MDA	MDA	1996	
Spraylat EWDY048	0.85	Fail (1000)		MDA	MDA	1996	
Spraylat EWDY048	0.86	Fail (1000)		MDA	MDA	1996	
Deft 44-W-16	0.82	Fail (500)		MDA	MDA	1996	
Deft 44-W-16	0.91	Fail (500)		MDA	MDA	1996	
Deft 44-W-16	0.91	Fail (500)		MDA	MDA	1996	
Deft 44-W-16	0.9	Fail (500)		MDA	MDA	1996	
Ecoat	0.81	Fail (<500)		MDA	MDA	1996	
Ecoat	0.78	Fail (<500)		MDA	MDA	1996	
Ecoat	0.8	Fail (<500)		MDA	MDA	1996	
Ecoat	0.77	Fail (<500)		MDA	MDA	1996	

4.2 (Continued):

In the Table 25 tests, three 4 inch x 6 inch x 0.040 inch thick steel panels were used as the test specimens. The panel material was 4130 steel in the normalized state per AMS 6345, AMS 6350, or AMS 6351. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. Panels were cured at room temperature for 2 weeks prior to test. The panels were scribed using an ASTM D 1654 scribe tool. 2000 hours exposure without any substrate corrosion is the success criterion of MIL-PRF-23377G and MIL-PRF-85582C.

SAE AIR5479

TABLE 25 - Scribed Neutral Salt Corrosion Resistance

Reference: ASTM B117
Source: JGAPP (C-17 Pollution Prevention)

<u>System</u>	<u>Specimen</u>	<u>Results</u>	<u>Tested by</u>	<u>Test Date</u>	<u>Comments</u>
Courtaulds 519X303 / 910X357	4130, Cd	Pass	MDA	1996	
Courtaulds 519X303 / 910X357	4130, Cd	Pass	MDA	1996	
Courtaulds 519X303 / 910X357	4130, Cd	Pass	MDA	1996	
Crown Metro 10-PW22-2/ECW119	4130, Cd	Pass	MDA	1996	
Crown Metro 10-PW22-2/ECW119	4130, Cd	Pass	MDA	1996	
Crown Metro 10-PW22-2/ECW119	4130, Cd	Pass	MDA	1996	
Deft 44-W-16	4130, Cd	Pass	MDA	1996	
Deft 44-W-16	4130, Cd	Pass	MDA	1996	
Deft 44-W-16	4130, Cd	Fail	MDA	1996	
Spraylat EWDY048	4130, Cd	Pass	MDA	1996	
Spraylat EWDY048	4130, Cd	Fail	MDA	1996	
Spraylat EWDY048	4130, Cd	Fail	MDA	1996	
Spraylat EWAE-118	4130, Cd	Pass	MDA	1996	
Spraylat EWAE-118	4130, Cd	Fail	MDA	1996	
Spraylat EWAE-118	4130, Cd	Fail	MDA	1996	
Coutaulds RW-3181-64	4130, Cd	Fail	MDA	1996	
Coutaulds RW-3181-64	4130, Cd	Fail	MDA	1996	
Coutaulds RW-3181-64	4130, Cd	Fail	MDA	1996	
Ecoat: BASF G28AD012	4130, Cd	Fail	MDA	1996	
Ecoat: BASF G28AD012	4130, Cd	Fail	MDA	1996	
Ecoat: BASF G28AD012	4130, Cd	Fail	MDA	1996	
Courtaulds 513X303 / 910X357	4130, IVD	Pass	MDA	1996	
Courtaulds 513X303 / 910X357	4130, IVD	Pass	MDA	1996	
Courtaulds 513X303 / 910X357	4130, IVD	Pass	MDA	1996	
Spraylat EWAE-118	4130, IVD	Pass	MDA	1996	
Spraylat EWAE-118	4130, IVD	Pass	MDA	1996	
Spraylat EWAE-118	4130, IVD	Pass	MDA	1996	
Crown Metro 10-PW22-2/ECW119	4130, IVD	Pass	MDA	1996	
Crown Metro 10-PW22-2/ECW119	4130, IVD	Pass	MDA	1996	
Crown Metro 10-PW22-2/ECW119	4130, IVD	Fail	MDA	1996	
Coutaulds RW-3181-64	4130, IVD	Pass	MDA	1996	
Coutaulds RW-3181-64	4130, IVD	Fail	MDA	1996	
Coutaulds RW-3181-64	4130, IVD	Fail	MDA	1996	
Deft 44-W-16	4130, IVD	Fail	MDA	1996	
Deft 44-W-16	4130, IVD	Fail	MDA	1996	
Deft 44-W-16	4130, IVD	Fail	MDA	1996	
Ecoat: BASF G28AD012	4130, IVD	Fail	MDA	1996	
Ecoat: BASF G28AD012	4130, IVD	Fail	MDA	1996	
Ecoat: BASF G28AD012	4130, IVD	Fail	MDA	1996	
Spraylat EWDY048	4130, IVD	Fail	MDA	1996	
Spraylat EWDY048	4130, IVD	Fail	MDA	1996	
Spraylat EWDY048	4130, IVD	Fail	MDA	1996	

SAE AIR5479

4.3 Unscribed SO₂ Corrosion:

Conclusions: Most non-chromated primers including Boostercoat, Ecoat, and the Crown Metro were superior to the baseline in this test. Boostercoat's success was possibly due to its unusually high thickness.

In the Table 25 tests, three 4 inch x 6 inch x 0.040 inch thick steel panels were used as the test specimens. The panel material was 4130 steel in the normalized state per AMS 6345, AMS 6350, or AMS 6351. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. After being primed, panels were cured at room temperature for 2 weeks prior to test. The testing consisted of exposing the test panels to an aggressive acidic corrosive environment in a test chamber over an extended period of time. 500 hours exposure without any substrate corrosion is the success criterion.

TABLE 26 - Unscribed SO₂ Corrosion Resistance

Reference: ASTM G85 Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process							
System	Thick, mils	Results		Prepared by	Tested by	Test Date	Comments
		Hrs to Failure					
Boostercoat	2.03	2000		MDA	MDA	1996	
Boostercoat	2.37	2000		MDA	MDA	1996	
Boostercoat	2.21	2000		MDA	MDA	1996	
Boostercoat	2.38	2000		MDA	MDA	1996	
Ecoat	0.58	288		MDA	MDA	1996	Cathoguard 310
Ecoat	0.52	240		MDA	MDA	1996	Cathoguard 310
Ecoat	0.78	168		MDA	MDA	1996	Cathoguard 310
Spraylat EWDY048	1.53	150		MDA	MDA	1996	
Spraylat EWDY048	1.36	150		MDA	MDA	1996	
Spraylat EWDY048	1.29	150		MDA	MDA	1996	
Spraylat EWDY048	1.77	150		MDA	MDA	1996	
Ecoat	0.45	120		MDA	MDA	1996	Cathoguard 310
Deft 44-GN-36	1.33	100		MDA	MDA	1996	
Deft 44-GN-36	1.38	100		MDA	MDA	1996	
Deft 44-GN-36	1.51	100		MDA	MDA	1996	
Deft 44-GN-36	1.31	100		MDA	MDA	1996	
Deft 44-W-16	1.56	60		MDA	MDA	1996	
Deft 44-W-16	1.44	60		MDA	MDA	1996	
Deft 44-W-16	1.55	60		MDA	MDA	1996	
Deft 44-W-16	1.46	60		MDA	MDA	1996	

In the Table 25 tests, three 4 inch x 6 inch x 0.040 inch thick panels were used as the test specimens. The panel material was 7075-T6 aluminum. Prior to coating, specimens underwent degrease and deoxidize with aluminum oxide grit. After being primed, panels were cured at room temperature for 2 weeks prior to test. The testing consisted of exposing the test panels to an aggressive acidic corrosive environment in a test chamber over an extended period of time. 500 hours exposure without any substrate corrosion is the success criterion.

SAE AIR5479

TABLE 27 - Unscribed SO₂ Corrosion Resistance

Reference: ASTM G85 Source: JGAPP					
<u>System</u>	<u>Specimen</u>	<u>Results</u>	<u>Tested by</u>	<u>Test Date</u>	<u>Comments</u>
Ecoat: BASF G28AD012	7075-T6	Pass	MDA	1996	Cr conversion coat
Ecoat: BASF G28AD012	7075-T6	Pass	MDA	1996	Cr conversion coat
Ecoat: BASF G28AD012	7075-T6	Pass	MDA	1996	Cr conversion coat
Crown Metro 10-PW22-2/ECW119	7075-T6	Fail	MDA	1996	Cr conversion coat
Crown Metro 10-PW22-2/ECW119	7075-T6	Pass	MDA	1996	Cr conversion coat
Crown Metro 10-PW22-2/ECW119	7075-T6	Pass	MDA	1996	Cr conversion coat
Courtaulds 519X303 / 910X357	7075-T6	Pass	MDA	1996	Cr conversion coat
Courtaulds 519X303 / 910X357	7075-T6	Fail	MDA	1996	Cr conversion coat
Courtaulds 519X303 / 910X357	7075-T6	Fail	MDA	1996	Cr conversion coat
Deft 44-W-16	7075-T6	Fail	MDA	1996	Cr conversion coat
Deft 44-W-16	7075-T6	Fail	MDA	1996	Cr conversion coat
Deft 44-W-16	7075-T6	Fail	MDA	1996	Cr conversion coat
Coutaulds RW-3181-64	7075-T6	Fail	MDA	1996	Cr conversion coat
Coutaulds RW-3181-64	7075-T6	Fail	MDA	1996	Cr conversion coat
Coutaulds RW-3181-64	7075-T6	Fail	MDA	1996	Cr conversion coat
Spraylat EWDY048	7075-T6	Fail	MDA	1996	Cr conversion coat
Spraylat EWDY048	7075-T6	Fail	MDA	1996	Cr conversion coat
Spraylat EWDY048	7075-T6	Fail	MDA	1996	Cr conversion coat
Spraylat EWAE-118	7075-T6	Fail	MDA	1996	Cr conversion coat
Spraylat EWAE-118	7075-T6	Fail	MDA	1996	Cr conversion coat
Spraylat EWAE-118	7075-T6	Fail	MDA	1996	Cr conversion coat

4.4 Adhesion:

Conclusions: A variety of replacement candidates had satisfactory adhesion performance.

In the Table 28 tests, 4 inch x 6 inch x 0.125 inch thick bare 7075-T6 aluminum panels were used as the test specimens. Prior to primer, specimens were conversion coated with Iridite 14-2. After being primed, panels were cured at room temperature for 2 weeks prior to test. For test, the panels were scribed with a razor knife, creating a scribe pattern per ASTM D 3359 resulting in 100 small patches. Tape was applied to the patched surface and removed. The number of patches remaining after the tape is the success criterion.

SAE AIR5479

TABLE 28 - Cross Hatch Tape Adhesion

Reference: ASTM D3359, Method B Source: USAF Elimination of Environmentally Hazardous Materials from the LG Overhaul Process						
<u>System</u>	<u>Thickness,</u> <u>mils</u>	<u>Results</u> <u>Pass or Fail</u>	<u>Prepared by</u>	<u>Tested by</u>	<u>Test Date</u>	<u>Comments</u>
Deft 44-GN-36	0.92	Pass	MDA	MDA	1996	
Deft 44-GN-36	0.98	Pass	MDA	MDA	1996	
Deft 44-GN-36	0.90	Pass	MDA	MDA	1996	
Deft 44-GN-36	0.91	Pass	MDA	MDA	1996	
Spraylat EWDY048	0.69	Pass	MDA	MDA	1996	
Spraylat EWDY048	0.78	Pass	MDA	MDA	1996	
Spraylat EWDY048	0.90	Pass	MDA	MDA	1996	
Spraylat EWDY048	0.86	Pass	MDA	MDA	1996	
Deft 44-W-16	0.82	Pass	MDA	MDA	1996	
Deft 44-W-16	1.01	Pass	MDA	MDA	1996	
Deft 44-W-16	1.17	Pass	MDA	MDA	1996	
Deft 44-W-16	1.03	Pass	MDA	MDA	1996	
Boostercoat	1.98	Pass	MDA	MDA	1996	
Boostercoat	1.91	Pass	MDA	MDA	1996	
Boostercoat	1.89	Pass	MDA	MDA	1996	
Boostercoat	1.75	Pass	MDA	MDA	1996	
Ecoat	0.80	Pass	MDA	MDA	1996	BASF G28AD012-2
Ecoat	0.79	Pass	MDA	MDA	1996	BASF G28AD012-2
Ecoat	0.77	Pass	MDA	MDA	1996	BASF G28AD012-2
Ecoat	0.76	Pass	MDA	MDA	1996	BASF G28AD012-2

4.4 (Continued):

In the Table 29 tests, 4 inch x 6 inch x 0.040 inch thick bare 2024-T3 aluminum panels were used as the test specimens. Prior to primer, specimens were conversion coated with Iridite 14-2. After being primed, panels were cured at room temperature for 2 weeks prior to test. The wet tape adhesion test involves soaking the target area of the specimen with a wet cheesecloth for 24 hours, followed by application and abrupt removal of tape. The test is successful if the primer remains attached to the specimen.

SAE AIR5479

TABLE 29 - Scribed Wet Tape Adhesion

Reference: PS 21313 Source: JGAPP					
<u>System</u>	<u>Specimen</u>	<u>Results</u>	<u>Tested by</u>	<u>Test Date</u>	<u>Comments</u>
Courtaulds 513X332 / 910X457	bare 2024-T3	Pass	MDA	1996	control
Courtaulds 513X332 / 910X457	bare 2024-T3	Pass	MDA	1996	control
Deft 44-W-16	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Deft 44-W-16	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Ecoat: BASF G28AD012	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Ecoat: BASF G28AD012	bare 2024-T3	Pass	MDA	1996	Waterborne type I
Sterling U-1201-NC/U-1202-F	bare 2024-T3	Pass	MDA	1996	High Solids
Sterling U-1201-NC/U-1202-F	bare 2024-T3	Pass	MDA	1996	High Solids
Spraylat EEAE136	bare 2024-T3	Pass	MDA	1996	High Solids
Spraylat EEAE136	bare 2024-T3	Pass	MDA	1996	High Solids
Crown Metro 10P22-3/EC-270	bare 2024-T3	Pass	MDA	1996	High Solids
Crown Metro 10P22-3/EC-270	bare 2024-T3	Pass	MDA	1996	High Solids
Lord Aeroglaze 9740	bare 2024-T3	Pass	MDA	1996	High Solids
Lord Aeroglaze 9740	bare 2024-T3	Pass	MDA	1996	High Solids
Spraylat EWDE 139A/EWAE 118B	bare 2024-T3	Pass	MDA	1996	Waterborne type II
Spraylat EWDE 139A/EWAE 118B	bare 2024-T3	Pass	MDA	1996	Waterborne type II
Deft 44-GN-36	bare 2024-T3	Fail	MDA	1996	control
Deft 44-GN-36	bare 2024-T3	Fail	MDA	1996	control
Courtaulds 515X386 / 910X831	bare 2024-T3	Fail	MDA	1996	control
Courtaulds 515X386 / 910X831	bare 2024-T3	Fail	MDA	1996	control
Spraylat EWDY048	bare 2024-T3	Fail	MDA	1996	Waterborne type I
Spraylat EWDY048	bare 2024-T3	Fail	MDA	1996	Waterborne type I
Deft 44-W-17	bare 2024-T3	Fail	MDA	1996	Waterborne type I
Deft 44-W-17	bare 2024-T3	Fail	MDA	1996	Waterborne type I
Crown Metro 10-PW22-2/ECW119	bare 2024-T3	Fail	MDA	1996	Waterborne type I
Crown Metro 10-PW22-2/ECW119	bare 2024-T3	Fail	MDA	1996	Waterborne type I
Courtaulds RW-3151/3151B001	bare 2024-T3	Fail	MDA	1996	Waterborne type I
Courtaulds RW-3151/3151B001	bare 2024-T3	Fail	MDA	1996	Waterborne type I
Sterling Lacquer U-4800-NC/U-4801	bare 2024-T3	Fail	MDA	1996	Waterborne type I
Sterling Lacquer U-4800-NC/U-4801	bare 2024-T3	Fail	MDA	1996	Waterborne type I

4.5 Fluid Resistance:

Conclusions: Most candidates had satisfactory fluid resistance except for the Spraylat and Ecoat.

In the Table 30 tests, 4 inch x 6 inch x 0.032 inch thick 7075-T6 aluminum panels were used as the test specimens. Prior to primer, specimens were conversion coated with Iridite 14-2. After being primed, panels were cured at room temperature for 2 weeks prior to test. The panels were tested per Douglas Material Specification (DMS) 1786 which exposes the panels to Skydrol hydraulic fluid at room temperature for 30 days. There should be no film softening below level H for waterborne primers.