

Issued 1972-11
Reaffirmed 2007-02
Revised 2011-07

Superseding AMS2631C

(R) Ultrasonic Inspection
Titanium and Titanium Alloy Bar, Billet and Plate

RATIONALE

AMS2361D is a complete revision of this specification.

1. SCOPE

1.1 Purpose

This specification covers the procedure for ultrasonic inspection of wrought titanium and titanium alloy products 0.25 inch (6.4 mm) and over in cross-section (thickness) or diameter.

1.1.1 When specifically requested by purchaser, this specification may be used for metals other than titanium.

1.2 Application

This procedure has been used typically for locating internal defects, such as cracks, voids, spongy areas, and other structural discontinuities, which may or may not be exposed to the surface, but usage is not limited to such applications.

1.2.1 Testing normally will be by longitudinal wave procedure, but shear wave procedure may be used when agreed upon by purchaser and vendor.

1.2.2 The requirements of this specification may be met by performance of ultrasonic inspection to AMS2628 as follows:

1.2.2.1 Perform UT to AMS2628 for material up to and including 10 inch (254 mm) diameter to meet the Class AA requirements specified herein.

1.2.2.2 Perform UT to AMS2628 for material over 10 inch (254 mm) diameter to meet the Class A1 requirements specified herein.

2. APPLICABLE DOCUMENTS

The issue of the following documents in effect on the date of the purchase order forms a part of this specification to the extent specified herein. The supplier may work to a subsequent revision of a document unless a specific document issue is specified. When the referenced document has been cancelled and no superseding document has been specified, the last published issue of that document shall apply.

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

Copyright © 2011 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
Tel: +1 724-776-4970 (outside USA)
Fax: 724-776-0790
Email: CustomerService@sae.org
http://www.sae.org

**SAE values your input. To provide feedback
on this Technical Report, please visit
<http://www.sae.org/technical/standards/AMS2631D>**

SAE WEB ADDRESS:

2.1 SAE Publications

Available from SAE International, 400 Commonwealth Drive, Warrendale, PA 15096-0001, Tel: 877-606-7323 (inside USA and Canada) or 724-776-4970 (outside USA), www.sae.org.

- AMS2380 Approval and Control of Premium-Quality Titanium Alloys
- AMS2628 Ultrasonic Immersion Inspection-Titanium and Titanium Alloy Billet Premium Grade
- AMS4928 Titanium Alloy Bars, Wire, Forgings, Rings, and Drawn Shapes, 6Al - 4V, Annealed
- SAE J300 Crankcase Oil Viscosity Classification

2.2 ASTM Publications

Available from ASTM International, 100 Barr Harbor Drive, P.O. Box C700, West Conshohocken, PA 19428-2959, Tel: 610-832-9585, www.astm.org.

- ASTM E 127 Fabricating and Checking Aluminum Alloy Ultrasonic Standard Reference Blocks
- ASTM E 317 Evaluating Performance Characteristics of Ultrasonic Pulse-Echo Testing Systems Without the Use of Electronic Measurement Instruments
- ASTM E 428 Fabrication and Control of Steel Reference Blocks Used in Ultrasonic Inspection

2.3 AIA Publications

Available from Aerospace Industries Association, 1000 Wilson Boulevard, Suite 1700, Arlington, VA 22209-3928, Tel: 703-358-1000, www.aia-aerospace.org.

- NAS-410 NAS Certification & Qualification of Nondestructive Test Personnel

2.4 ANSI Publications

Available from American National Standards Institute, 25 West 43rd Street, New York, NY 10036-8002, Tel: 212-642-4900, www.ansi.org.

- ANSI B46.1 Surface Texture

2.5 ASNT Publications

Available from American Society for Nondestructive Testing, P.O. Box 28518, 1711 Arlingate Lane, Columbus, OH 43228-0518, Tel: 800-222-2768 (inside U.S. and Canada) or 614-274-6003 (outside USA), www.asnt.org.

- ASNT-TC-1A Recommended Practice, Personnel Qualification and Certification in Nondestructive Testing

2.6 ATA Publications

Available from Air Transport Association of America, Inc., 1301 Pennsylvania Avenue, NW, Suite 1100, Washington, DC 20004-1707, Tel: 202-626-4000, www.airlines.org.

- ATA-105 Guidelines for Training and Qualifying Personnel in Nondestructive Testing

3. TECHNICAL REQUIREMENTS

3.1 Qualification

3.1.1 Personnel

Shall be qualified and certified in accordance with NAS-410. Alternate procedures, i.e., ASNT-TC-1A or ATA-105, may be used if specified by the drawing or purchase order. It is the supplier's responsibility to ensure that personnel are certified and function within the limits of the applicable specification or procedure.

3.1.2 Facilities

Shall be subject to survey and approval by either the purchaser or a third party that is independent of the purchaser. Reference specifications, procedures, and documentation necessary to verify the qualification of equipment and test personnel shall be available to purchaser, when requested.

3.1.3 Written Procedure

Ultrasonic inspections performed in accordance with this specification shall be detailed in written procedures. Procedures shall identify the type of ultrasonic equipment, method(s) of test, ultrasonic test reference, search unit type, style, corrected beam/type focusing and frequency, method of reporting indications, and all other instructions that pertain to the actual test. Procedures shall be detailed sufficiently that another qualified investigator could duplicate the test and obtain equivalent information.

3.2 Equipment

3.2.1 Basic Ultrasonic Test Instrument

Shall be capable of producing, receiving, and displaying high-frequency electrical pulses at the required frequencies and energy levels. The ultrasonic instrument shall be of the pulse-echo type capable of operating at 2.25 through 10 MHz except as permitted in 3.2.2.2. Gates, distance-amplitude correction systems, and other electronic aids to ultrasonic testing and interpretation shall be used as required. An alarm system, a recorder, or an auto-stop device, or combination of these, may be used.

3.2.1.1 Instrument Linearity

The instrument performance characteristics shall be evaluated in accordance with ASTM E 317 except as follows:

3.2.1.1.1 The calibration block used for evaluating vertical linearity shall be as shown in Figure 1.

3.2.1.1.2 The vertical linearity plot and the tolerance limits shall be as shown in either Figure 2 or Figure 2A.

3.2.1.1.3 The horizontal linearity check shall be made by plotting signal displacement against known thickness in the range of 1 to 5 inches (25 to 125 mm) in 1-inch (25-mm) increments; the allowable difference in thickness between that indicated by the signal displacement and the actual measured thickness shall be within $\pm 3\%$ of the measured thickness of the respective block. Substitute performance checks are permissible when agreed upon by purchaser and vendor.

3.2.1.2 Instrument Sensitivity (example of formula use for amplitude ratio)

Instrument sensitivity or gain controls shall function so that a given amount or degree of sensitivity can be repeated or returned to with an accuracy of $\pm 10\%$ of the original pip height. If signal attenuators are used, they shall be accurate over the attenuation range and test frequency used so that the attenuation measurement will represent an amplitude ratio within $\pm 10\%$ of the correct value. The decibel (dB) attenuation value may be converted to an amplitude ratio by use of tables with dB versus voltage ratios. Alternately, it may be calculated from the relationship in Equation 1.

$$\text{Amplitude Ratio} = \text{Log} \frac{-1 \text{ dB}}{10 \text{ 20}} \quad (\text{Eq. 1})$$

3.2.2 Ultrasonic Search Units

Shall be capable of transmitting and receiving ultrasonic vibrations at the frequency and energy levels specified below. The frequency used shall be the highest practical ultrasonic frequency which will provide the required penetration, resolution, and signal to noise.

3.2.2.1 Search Unit Dimensions and Styles

For both contact and immersion tests with either longitudinal or shear mode, the choice of transducer dimension, style, type, etc is dependent on the test and the approved test procedure. In general, for immersion testing, flat-faced or corrected-beam transducers with diameters 3/8 through 1 inch (9.5 through 25.4 mm) or rectangular units with a maximum area of 1 square inch (6.5 cm²) are acceptable. Contact units with a maximum area of 1 square inch (6.5 cm²) with 1/2 inch (12.7 mm) minimum to 1-1/8 inch (28 mm) maximum dimensions are acceptable for longitudinal testing, while 1 square inch (6.5 cm²) or 1 by 1/2 inch (25 by 12.7 mm) transducers are acceptable for shear testing. Use of a focused, paint brush, liquid delay, special size, or other special transducer is acceptable when agreed upon by purchaser and vendor.

3.2.2.2 Shall be the highest practical frequency which will provide the penetration and resolution required. Frequencies lower than 2.25 MHz for longitudinal inspections or 1.0 MHz for shear inspections shall not be used unless agreed upon by purchaser and vendor.

3.2.3 Voltage Regulator

If fluctuations in line voltage cause variations exceeding $\pm 5\%$ in a signal with an amplitude equal to the upper linearity limit of the instrument, a voltage regulator shall be used on the power source; this requirement does not apply to battery-powered units.

3.2.4 Couplant

3.2.4.1 Immersion Method

For inspection by the immersion method, clean tap water shall be used as the couplant material; rust inhibitors, wetting agents, or both, may be added. The water shall be free of visible air bubbles which could interfere with the ultrasonic test.

3.2.4.2 Contact Method

For inspection by the contact method, SAE 30 motor oil in accordance with SAE J300 or cellulose gum shall be used as the couplant material. Other types of couplant materials that have been proven acceptable for a particular type of test may be used if agreed upon by purchaser and vendor. Chloroprene rubber sheet or similar material may be used between the transducer and the product being tested to prevent excessive transducer wear provided adequate compensation for its use is made.

3.2.5 Longitudinal Reference Standards

Shall be fabricated from AMS4928 titanium alloy or from other titanium alloy acoustically similar to the alloy to be tested. The procedures established in ASTM E 127 and ASTM E 428 are recommended for manufacturing ultrasonic reference blocks for straight beam testing.

3.2.5.1 Acoustic compatibility between the reference standard material and the material to be tested shall be within 12 dB. If the acoustic compatibility is within 2.5 dB, no gain compensation is required for inspection. If the acoustic compatibility differences are greater than 2.5 dB but less than 12 dB, the instrument sensitivity shall be increased to compensate for the differences in acoustic compatibility. If the acoustic compatibility differences are greater than 12 dB, a different reference standard shall be used.

3.2.5.1.1 Compare acoustic compatibility by comparing the first unsaturated back reflection from the reference standard and the part being tested. The db per inch (25 mm) comparison using back reflections is also frequently used. Other acoustic compatibility comparison measurements may be used when permitted by purchaser.

3.2.5.2 For testing flat surfaces, flat test blocks shall be used. For testing curved surfaces, the reference standards shall have similar contour within approximately $\pm 25\%$ of the radius of curvature of the dimensions being tested. Surface finish of the calibration standard shall be similar to that of the material being tested.

3.2.5.3 For longitudinal wave calibration, the calibration reflectors shall be flat-bottom holes. The distance from the entry face of the ultrasonic beam to the bottoms of the calibration holes (test metal distance) are recommended as follows, based on the material contour and section thickness "T". Alternate calibration points may be used as long as alternate FBH's for the shortest test metal distance FBH are not longer than specified herein and alternate FBH's for the longest test metal distance FBH are not shorter than specified herein.

3.2.5.3.1 Rounds 0.25 to 0.5 inch (6.35 to 12.7 mm) in Diameter

1/8 inch (3.2 mm), T minus (1/8 inch) 3.2 mm.

3.2.5.3.2 Rounds 0.5 to 2 inches (12.7 to 51 mm), Inclusive, in Diameter

1/2T and 1/4 inch (6.4 mm).

3.2.5.3.3 Rounds Over 2 to 5 inches (51 to 127 mm), Inclusive, in Diameter

1/2T, 1/4T, and 1/4 inch (6.4 mm).

3.2.5.3.4 Rounds Over 5 inches (127 mm) in Diameter

1/2T, 1/4T, 1/8T, and 3/8 inch (9.5 mm). If frequencies below 5 MHz are used, the minimum metal travel of 1/2 inch (12.7 mm) may be used.

3.2.5.3.5 Flat-Faced Material 0.25 to 0.5 inch (6.35 to 12.7 mm) in Cross-Section

1/2T.

3.2.5.3.6 Flat-Faced Material 0.5 to 2 inches (12.7 to 51 mm), Inclusive, in Cross-Section

T minus (1/8 inch) (3.2 mm), 1/2T, and 1/4 inch (6.4 mm).

3.2.5.3.7 Flat-Faced Material Over 2 to 5 inches (51 to 127 mm), Inclusive, in Cross-Section

T minus (1/2 inch) (12.7 mm) if material noise level permits, 1/2T, 1/4T, and 1/4 inch (6.4 mm).

3.2.5.3.8 Flat-Faced Material Over 5 to 9 inches (125 to 229 mm), Inclusive, in Cross-Section

1/2T, 1/4T, 1/8T, and 1/2 inch (12.7 mm). Include T minus (1/2 inch) (12.7 mm) if material noise level permits.

3.2.5.3.9 Flat-Faced Material Over 9 inches (229 mm) in Cross-Section

1/2T, 1/4T, 1/8T, and 1/2 inch (12.7 mm). If frequencies below 5 MHz are used, the minimum metal travel of 3/4 inch (19 mm) may be used.

3.2.5.3.10 Plate Material 0.5 to 2 inch (12.7 to 51 mm), Inclusive, in Cross-Section

T minus (1/8 inch) (3.2 mm), 1/2T, 1/4T and 1/4 Inch (6.4 mm).

3.2.5.3.11 Plate Material over 2 to 4 inches (51 to 102 mm), Inclusive, in Cross-Section

T minus (1/2 inch) (12.7 mm), 1/2T, 1/4T, and 1/4 inch (6.4 mm).

3.2.6 Angle Beam Reference Standards

Angle beam testing may use the longitudinal mode with the beam refracted at a predetermined angle (usually 45 degrees) or the true shear (transverse) wave may be used with the refracted angle between 30 and 60 degrees, usually 45 degrees. The same acoustical compatibility requirements between reference standard material and test material as is required for longitudinal wave standards shall apply to angle beam reference standards.

3.2.6.1 In immersion testing to establish an approximate 45 degree refracted longitudinal angle in titanium, a 10 degree incident angle shall be used.

3.2.6.2 In immersion testing to establish an approximate 45 degree refracted shear angle in titanium, a 20 degree incident angle shall be used.

3.2.6.3 For contact testing, the refracted angle in the part is determined by the angle of the wedge or shoe that is used between the transducer and the part being tested.

3.2.6.4 Shear Wave Ultrasonic References (Angle Beam)

May be of several distinct types as follows; because of the variety of types and sizes of acceptable shear wave calibration standards, the shear wave standard(s) to be used shall be acceptable to purchaser:

3.2.6.4.1 Flat-bottom holes drilled at approximately 45 degrees to the entry surface may be used to test flat surfaces (See Figure 3A and 3B).

3.2.6.4.2 For testing cylinders, flat-bottom holes drilled in the center of the wall and perpendicular to the radius of the cylinder may be used. Figures 4 and 5 illustrate two types of construction.

3.2.6.4.3 Side-drilled holes may be used for shear wave calibration for both flat and curved entry surfaces. A 0.020 inch (0.51 mm) side-drilled hole 0.25 inch (6.4 mm) long is approximately equivalent to a #3 (1.2 mm diameter) FBH, while the same diameter side-drilled hole 0.50 inch (12.7 mm) long is roughly equivalent to a #5 (2.0 mm diameter) FBH (See Figure 6). Comparisons of SDH to FBH sensitivity should include consideration of the actual beam diameter intercepting the SDH. For example, if the beam diameter is only 0.25 inch (6.4 mm), then the sensitivity would be approximately equivalent to a #3 FBH even if the SDH is 0.5 inch (12.7 mm) long.

3.2.6.4.4 Various styles of notches may be used; these include V-notches, usually with a 60 degree included angle, square, or "U" bottomed notches, and slots. The sizes of the notches are generally equated to the test area thickness (typically, 1 inch (25.4 mm) maximum length x 3% of the part thickness) or the notch area is equated to a flat-bottom hole area; as an example, a 5/64 inch (2.0 mm) FBH has an area of 0.0047 square inch (3.03 mm²) and a slot with a depth of 0.050 inch (1.27 mm) and a length of 0.10 inch (2.5 mm) has an area of 0.005 square inch (3.2 mm²); therefore the notch and FBH are approximately equal.

3.3 Surface Preparation

3.3.1 The surfaces to be inspected shall be common geometrical sections such as round, square, and octagonal. Flat-face product shall be prepared to ensure flatness of the various faces.

3.3.2 Texture of surfaces to be inspected shall be not rougher than 250 microinches (6 µm). For longitudinal mode tests to Class AA or A1 requirements and for shear mode tests, surface texture of approximately 125 microinches (3 µm) is desirable. Surface texture is defined in ANSI B46.1.

3.3.3 Surface discontinuities remaining after surface preparation shall not be removed before ultrasonic inspection because local grinding depressions will cause sonic wave attenuation, loss of back reflection, and inability to locally meet standards. Surfaces shall be free from loose scale, machining or grinding particles, oil, grease, cutting compounds, and other foreign material.

3.4 Calibration of Apparatus

Before inspecting the product, the apparatus shall be adjusted, using appropriate reference blocks, to produce, from the simulated imperfections, clearly defined indications of sufficient height to ensure that the product under test can be inspected as required to locate any imperfections of detrimental size, nature, and location. The minimum pip height shall be not less than 20%, the maximum pip height shall be not greater than 80% of the vertical limit or the upper linearity limit, whichever is less. Set up height shall be twice the noise level or as otherwise approved by purchaser.

3.4.1 Instruments of the vacuum tube type shall be warmed up for not less than 30 minutes before being used; instruments using solid state electronic components shall be warmed up for not less than 10 minutes before being used. Sufficient time shall also be allowed for temperature of water, reference blocks, and product to stabilize before calibration and testing.

3.4.2 Calibration Check

To ensure valid results, a calibration check shall be made prior to the test of each part configuration or start of each shift of operation and at the completion of each test or shift, as appropriate. Calibration checks performed at the start of an immediately subsequent shift shall satisfy end of shift requirements. Any change in equipment operation that requires a recalibration of the test system shall require retesting of all product or parts tested since the previous calibration.

3.5 General Scanning Procedure

3.5.1 Calibration for determination of loss in the back reflection pattern shall be performed on parallel surfaces of the product being tested. The back reflection pattern from the full material thickness section of the test block at the scanning sensitivity shall be observed. If the back reflection pattern from the product being tested averages a variation of more than -50% from that recorded from the test block, testing shall be stopped until corrective action is taken.

3.5.2 The permissible background noise shall not exceed 50% of the response height from the reference standard of the same alloy as the product being tested. Greater background noise levels may be permitted by purchaser or lesser background noise levels may be specified.

3.5.3 Whenever possible, a dynamic alarm check shall be made to determine the operational scanning speeds, pulse repetition rates, and index increments, and to ensure that the alarm system is capable of detecting all rejectable defects at these operating conditions.

- 3.5.4 If a dynamic alarm check cannot be made or if alarms cannot be used, the operational parameters shall be as follows:
- 3.5.4.1 Pulse repetition rate should be a minimum of 600 pulses per second (600 PPS). The exact rate used shall be based on the beam diameter and surface speed.
 - 3.5.4.2 For manual scanning without alarm systems, a scanning speed not greater than 5.0 inches (127 mm) per second is recommended.
 - 3.5.4.3 For alarm systems with or without automatic scanning, a scanning speed not greater than 20 inches (508 mm) per second is recommended. The exact speed shall be based on the beam diameter and repetition rate.
- 3.5.5 When the alarm system is used during testing, it shall be set at the equivalent of "Hold" or "Manual Reset".
- 3.5.6 The instrument control settings and test parameters established during calibration shall not be changed during testing of the product. The pulse length and reject control shall be set at the minimum that will afford the proper resolution without affecting acceptable linearity.
- 3.5.7 Distance Amplitude Correction

Electronic distance amplitude correction is recommended; however, distance amplitude curves plotted on the screen face (Cathode Ray Tube) using distance amplitude calibration blocks may be used if the minimum pip height complies with 3.4. Testing using the highest sensitivity from the distance amplitude calibration blocks and evaluating to the proper metal travels is also permitted provided noise levels do not obscure required information.

- 3.5.8 Zone testing may be used with separate calibrations and/or transducers for each zone.

3.6 Immersion Testing

3.6.1 Longitudinal (Straight) Beam Testing

The sound beam entry angle shall be adjusted until the sound beam is perpendicular to the test surface. Where appropriate, the maximum signal amplitude from the entry surface may be used to determine this condition. Where not appropriate (e.g., a highly-focused search unit), an alternate procedure such as multiple reflections may be used. During testing, the angle established shall not vary more than ± 2 degrees.

3.6.2 Angle Beam Testing

Products may be inspected with both longitudinal and shear wave motions at preselected angles. Once established, the surface entry angle shall not vary more than ± 2 degrees.

3.6.3 Water Travel

The water travel distance shall be the optimum for the transducer and the metal travels encountered during testing. The water travel distance for testing shall be within ± 0.25 inch (± 6.4 mm) of that used for calibration.

- 3.6.4 The maximum indexing increment used in scanning a product shall be 70% of the effective beam diameter. The effective beam diameter is determined by recording of the total traverse distance at the appropriate gain settings across the hole which yields the smallest effective beam width in the test block through which not less than 50% signal amplitude is displayed.

3.7 Contact Testing

3.7.1 Straight Beam Testing

Visual inspection of the search unit shall be made to verify that the wear face surface is intact. Periodic visual inspections shall be made during tests to ensure that the search unit facing has not degraded. Any cracking, chipping, break-up, or uneven wear conditions shall disqualify the search unit and the test.

3.7.2 Angle Beam Testing

Angle beam entry and testing mode shall be established as part of the test procedure.

3.7.3 Indexing

Indexing increments used in scanning a product shall be not greater than one-half the transducer diameter or the effective beam diameter, determined in accordance with 3.6.4, whichever is less. When practical, transducer indexing shall be controlled by a mechanical system.

3.8 Surface Area of Product to be Scanned

3.8.1 Rounds, Flat-Faced Products and Plate

3.8.1.1 Rounds, All Diameters

The entire circumference.

3.8.1.2 Flat-Faced Product <2 inches (51 mm), in Cross-Section

Test 100% of one wide side.

3.8.1.3 Flat-Faced Product 2 to 5 inches (51 to 127 mm), Inclusive, in Cross-Section

Test all adjacent faces representing 50% of the periphery. If unable to set up on T-(1/2 inch)(12.7 mm) FBH, then inspection through opposite side is required.

3.8.1.4 Flat-Faced Product Over 5 inches (127 mm) in Cross-Section

Test all four sides, representing 100% of the periphery, except if set up is accomplished with T-(1/2 inch)(12.7 mm) FBH, then inspection on opposite side is not required.

3.8.1.5 Plate Material less than 4 inches (102 mm), Inclusive, in Cross-Section

If unable to set up on T minus (1/2 inch)(12.7 mm) FBH, then inspection through opposite side is required.

3.8.1.6 Alternate tests of rectangular product are allowed as follows. These tests may be subject to approval by the purchaser.

3.8.1.6.1 Single-face or opposite-face tests of all flat-faced rectangular product may be made if shear or refracted longitudinal wave testing in the transverse direction, with the transducer angled toward the edges is substituted for the adjacent face test.

3.8.1.6.2 If inspection half way through the width is not practical, such as in the case of a high ratio width to cross-section rectangle, an alternate method of inspecting through both sides of the width, at a depth equal to the cross-section is permitted.

4. QUALITY ASSURANCE PROVISIONS

4.1 Acceptance Classes

4.1.1 Four classes of ultrasonic quality for longitudinal wave inspection are defined in Table 1. Drawings, quality control specifications, or purchase orders will specify the applicable class. Melting parameters are defined in AMS2380.

TABLE 1 - ULTRASONIC QUALITY CLASSES

| Ultrasonic Classification | Single Discontinuity Hole Size No.* | Single Discontinuity Hole Size No.* |
|---------------------------|-------------------------------------|-------------------------------------|
| | Grade 1 or non-premium material | Grades 2,3,4 |
| AA | 2 | 2 |
| A1 | 3 | 3 |
| A | 5 | 4 |
| B | 8 | 6 |

* Diameter, in 64ths of an inch, of a flat-bottom hole (FBH) in the reference standard (1/64 inch = 0.4 mm).

- 4.1.1.1 All indications 75% or greater than the rejection level for each class shall be explored and evaluated.
- 4.1.1.2 Any discontinuity with an indication greater than the response from a reference flat-bottom hole at the estimated discontinuity depth of the size given is not acceptable.
- 4.1.1.3 Loss of unsaturated back reflection pattern greater than 50%, when compared with non-defective material in the same, similar, or like product, is not acceptable when this loss of back reflection pattern is accompanied by any increase in signal, at least double the normal background noise signal, between the front and back surfaces.
- 4.1.1.4 Noise levels exceeding the limits of 3.5.2 are not acceptable.
- 4.1.2 Acceptance standards for inspection by procedures other than normal longitudinal and standards not covered in Table 1 shall be as agreed upon by purchaser and vendor.
- 4.1.3 Disposition
- 4.1.4 Product exhibiting evaluated indications not in excess of established standards may be accepted without remedial operations.
- 4.1.5 Product exhibiting evaluated indications in excess of established standards but in a location which will be removed during manufacturing operations may be approved by authorized personnel for acceptance and shall be reported to purchaser.
- 4.1.6 Product containing discontinuities in excess of established standards and not covered by 4.2.2 shall be rejected.

4.2 Records

The testing source shall prepare and maintain on file, for the time specified by purchaser, records of the requirements and techniques for each size and configuration of product. When requested by purchaser, these records shall be made available for inspection.

4.3 Reports

The supplier shall document equipment used, set-up parameters, results of inspection, and personnel performing inspection on a report. The report shall provide enough detail such that a duplication of the original setup can be accomplished.

5. PREPARATION FOR DELIVERY

Not applicable.

6. ACKNOWLEDGMENT

A vendor shall mention this specification number and its revision letter in all quotations and when acknowledging purchase orders.

7. REJECTIONS

Product inspected in accordance with this specification and not meeting specified requirements, or modifications authorized by purchaser, will be subject to rejection.

8. NOTES

8.1 A change bar (I) located in the left margin is for the convenience of the user in locating areas where technical revisions, not editorial changes, have been made to the previous issue of this document. An (R) symbol to the left of the document title indicates a complete revision of the document, including technical revisions. Change bars and (R) are not used in original publications, nor in documents that contain editorial changes only.

8.2 Test Conditions

It is essential that thorough understanding be developed between purchaser and vendor regarding interpretation of the results of inspection and how they shall be recorded and reported. Ultrasonic testing is so comprehensive that it is necessary that all interested parties fully recognize that indications may appear which do not reflect conditions detrimental to use of the product. Agreement between purchaser and vendor should be established in advance on the following:


Surface finish
Internal structure
Location and extent of areas to be scanned
Size of transducer and type of search unit
Test frequency
Type and grade of couplant
Method of calibration of equipment

8.3 Local grinding depressions will cause sonic wave attenuation, loss of back reflection, and inability to locally meet standards.

8.4 Terms used in AMS are clarified in ARP1917.

8.5 Dimensions and properties in inch/pound units and the Fahrenheit temperatures are primary; dimensions and properties in SI units and the Celsius temperatures are shown as the approximate equivalents of the primary units and are presented only for information.

PREPARED BY AMS COMMITTEE "K"

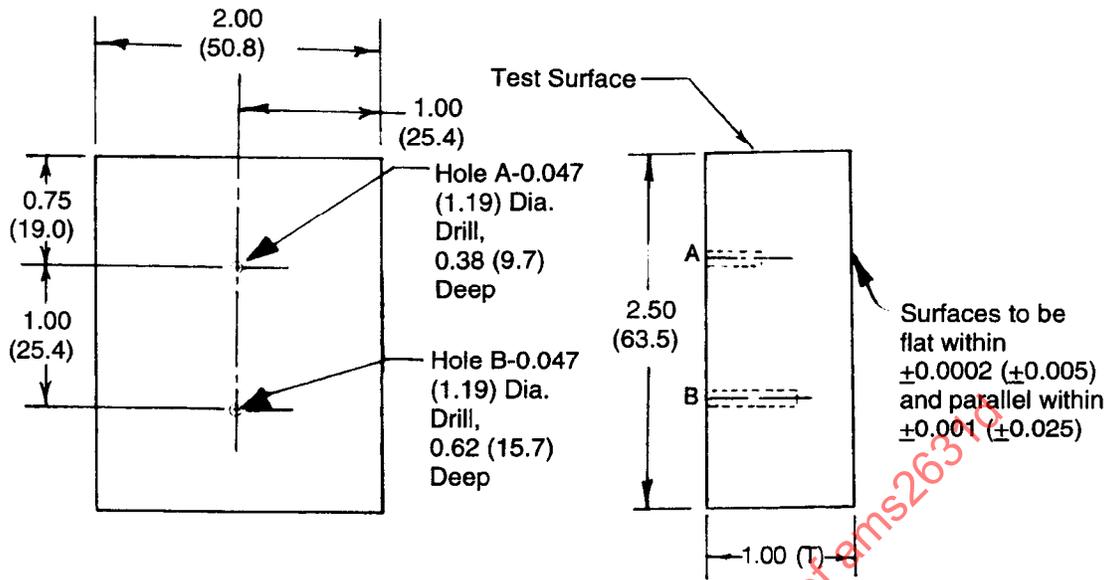

Note 1: Thickness (T) may be increased to accommodate larger search units provided the depth of hole A is $T/2 - 0.12$ (3.0) and the depth of hole B is $T/2 + 0.12$ (3.0).

Note 2: Dimensions are in inches (millimeters) except as noted.

(R) Note 3: All surfaces $63\sqrt{1.6 \mu m}$

FIGURE 1 - CALIBRATION BLOCK USED FOR EVALUATING VERTICAL LINEARITY


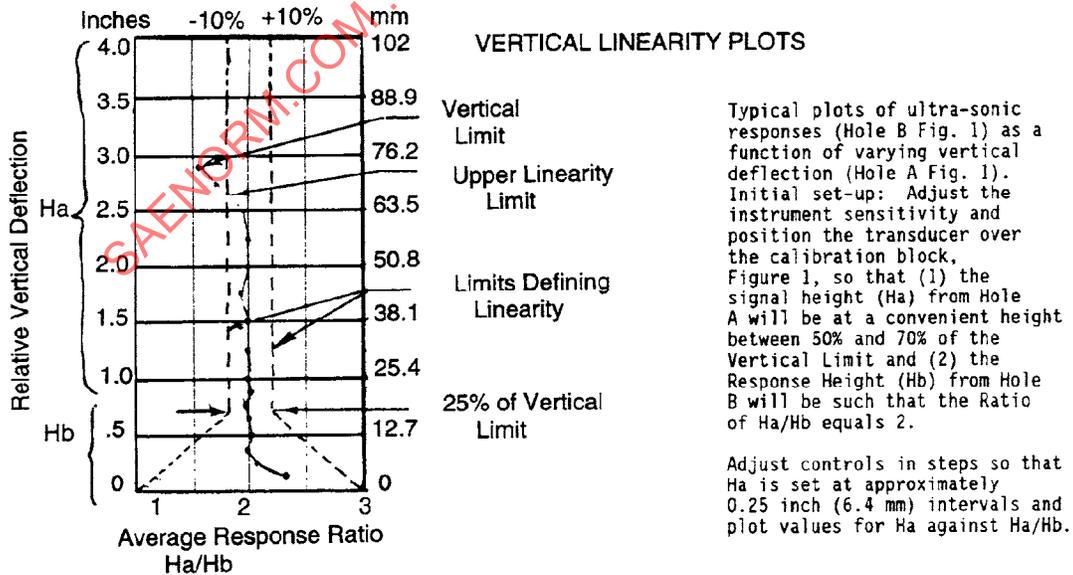


FIGURE 2

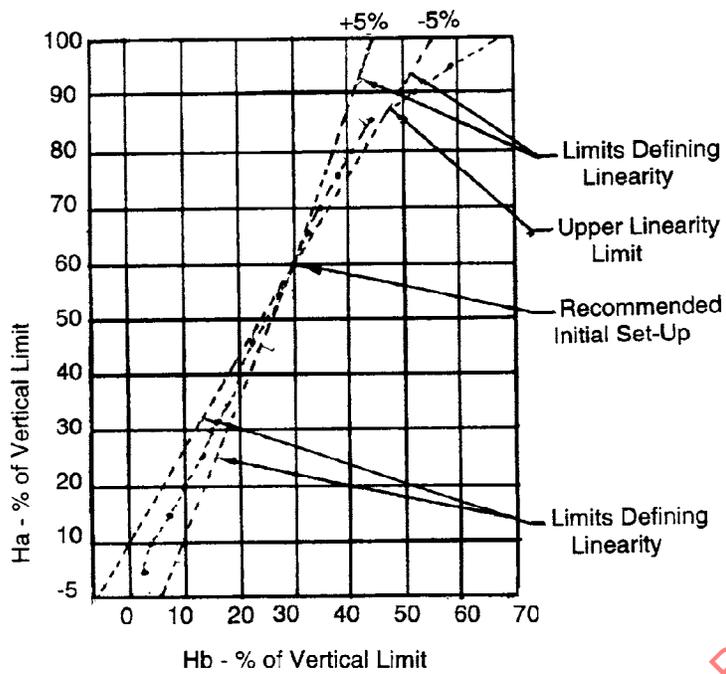

Set-up and plotting same as in Fig. 2 except all screen heights are converted to % of Vertical Limits and % H_a is plotted against % H_b rather than ratio of H_a/H_b .

Note that limit lines originate at the initial set-up point and will change if the set-up is changed.

The Vertical Limit equals 100%.

FIGURE 2A

SAENORM.COM : Click to view the full PDF of ams2631D

