



AEROSPACE MATERIAL SPECIFICATION

Society of Automotive Engineers, Inc.
TWO PENNSYLVANIA PLAZA, NEW YORK, N. Y. 10001

AMS 7469A

Superseding AMS 7469

Issued 6-30-64

Revised 11-1-70

BOLTS AND SCREWS, NICKEL ALLOY, CORROSION AND HEAT RESISTANT
Upset Headed, Heat Treated, Roll Threaded
2050 F (1121.1 C) Solution and 1650 F (898.9 C) Precipitation Heat Treatment

1. **ACKNOWLEDGMENT:** A vendor shall mention this specification number and its revision letter in all quotations and when acknowledging purchase orders.
2. **APPLICATION:** High quality bolts and screws requiring high strength and good resistance to relaxation at temperatures up to 1600 F (871 C) and oxidation resistance up to 1800 F (982 C).
3. **MATERIAL:** Shall be AMS 5712 alloy heading stock.
4. **FABRICATION:**
 - 4.1 **Blanks:** Heads shall be formed by hot forging or cold forging; machined heads will not be permitted.
 - 4.2 **Heat Treatment:** Headed blanks shall, before finishing the shank and the bearing surface of the head, cold working the head-to-shank fillet radius when specified, and rolling the threads, be solution heat treated as follows; precipitation heat treatment shall follow cold working of the fillet radius and rolling the threads:
 - 4.2.1 **Heating Equipment:** Furnaces may be any type ensuring uniform temperature throughout the parts being heated and shall be equipped with, and operated by, automatic temperature controllers. The heating medium or atmosphere shall cause no surface hardening by carburizing or nitriding. The total sulfur content of the atmosphere shall be maintained at less than 5 grains per 100 cu feet.
 - 4.2.2 **Solution Heat Treatment:** Blanks shall be solution heat treated by uniformly heating to $2050\text{ F} \pm 25$ ($1121.1\text{ C} \pm 14$), holding at heat for 30 min., and quenching in oil or air.
 - 4.2.3 **Precipitation Heat Treatment:** After cold working the fillet radius as in 4.4 and rolling the threads as in 4.5, parts shall be precipitation heat treated by heating to $1650\text{ F} \pm 15$ ($898.9\text{ C} \pm 8.3$), holding at heat for 4 hr, and cooling in air. Parts should be heated rapidly through the temperature range 1200 - 1400 F (648.9 - 760 C).
 - 4.3 **Oxide Removal:**
 - 4.3.1 The solution heat treated blanks, before cold working the fillet radius and rolling the threads, shall have the full body and the bearing surface of the head free from surface oxide and oxide penetration caused by prior heat treatment. The metal removed from the bearing surface of the head and the full body diameter of the shank shall be as little as practicable to obtain a clean, smooth surface and in no case shall be so great as to produce more cutting of flow lines in the head-to-shank junction than shown in Fig. 1B.
 - 4.3.2 After precipitation heat treatment, parts shall be treated to remove all surface oxide and oxide penetration caused by heat treatment. The oxide removal process shall produce no intergranular attack or corrosion of the parts.

SAE Technical Board rules provide that: "All technical reports, including standards, specifications, and practices recommended, are advisory only. Their use by anyone engaged in industry or trade is entirely voluntary. There is no agreement to adhere to any SAE standard or recommended practice, and no commitment to conform to or be guided by any technical report. In formulating and approving technical reports, the Board and its Committees will not investigate or consider patents which may apply to the subject matter. Prospective users of the report are responsible for protecting themselves against liability for infringement of patents."

- 4.4 Cold Working of Fillet Radius: After removal of oxide as in 4.3.1, the head-to-shank fillet radius of parts having the radius complete throughout the circumference of the part shall be cold worked sufficiently to remove all visual evidence of grinding or tool marks. Distortion due to cold working shall not raise metal more than 0.002 in. above the contour at "A" or depress metal more than 0.002 in. below the contour at "B" as shown in Fig. 2; distorted areas shall not extend beyond "C" as shown in Fig. 2. In configurations having an undercut associated with the fillet radius, the cold working will be required only for 90 deg of fillet arc, starting at the point of tangency of the fillet radius and the bearing surface of the head.
- 4.5 Thread Rolling: Threads shall be formed on the finished blanks by a single rolling process after removal of oxide as in 4.3.1.
- 4.6 Cleaning: Parts, after finishing, shall be degreased and then immersed in one of the following solutions for the time and at the temperature shown:
- (a) One volume of nitric acid (sp gr 1.42) and 9 volumes of water for not less than 20 min. at room temperature.
 - (b) One volume of nitric acid (sp gr 1.42) and 4 volumes of water for 30 - 40 min. at room temperature.
 - (c) One volume of nitric acid (sp gr 1.42) and 4 volumes of water for 10 - 15 min. at 140 - 160 F (60 - 71.1 C).
5. TECHNICAL REQUIREMENTS: Parts shall conform to the metallurgical and mechanical requirements specified below, determined in accordance with MIL-STD-1312 except as otherwise specified herein; when ASTM methods are specified for determining conformance, tests shall be conducted in accordance with the issue of the ASTM method listed in the latest issue of AMS 2350. Parts shall also conform to the latest issue of the following:
- AS 1177 - Nondestructive Inspection Standards for Bolts and Screws
 - AS 3062 - Bolts, Screws, and Studs, Screw Thread Requirements
 - AS 3063 - Bolts, Screws, and Studs, Straightness, Concentricity, and Squareness Requirements
- 5.1 Macroscopic Examination: Parts or sections of parts, as applicable, shall be etched in a solution of approximately 50% hydrochloric acid (sp gr 1.19), 20% hydrofluoric acid (sp gr 1.15), 4% nitric acid (sp gr 1.42), and 26% water at room temperature for 10 - 30 min. or in other suitable etchant and shall then be examined at approximately 20X magnification to determine conformance to the following requirements, except that examination for the thread imperfections of 5.1.3 may be made by microscopic examination of specimens polished and etched as in 5.2.
- 5.1.1 Flow Lines:
- 5.1.1.1 Examination of a longitudinal section through the part shall show flow lines in the shank, head-to-shank fillet, and bearing surface which follow the contour of the part as shown in Fig. 1A, except that slight cutting of flow lines by the oxide removal process of 4.3 is permissible, as shown in Fig. 1B; excessive cutting of flow lines in the shank, head-to-shank fillet, and bearing surface, as shown in Fig. 1C, is not permissible except when an undercut is associated with the fillet radius. The head style shown in Figs. 1A through 1C is for illustrative purposes only but other symmetrical head styles shall conform to the above requirements. Flow lines in heads on parts having special heads, such as Dee- or Tee-shaped heads or thinner-than-standard heads, shall be as agreed upon by purchaser and vendor.
- 5.1.1.2 Flow lines in threads shall be continuous, shall follow the general thread contour, and shall be of maximum density at root of thread (See Fig. 3).

- 5.1.2 Internal Defects: Examination of longitudinal sections of the head and shank and of the threads shall reveal no cracks, laps, or porosity. The head and shank section shall extend not less than $D/2$ in. \emptyset from the bearing surface of the head and the threaded section shall extend not less than $D/2$ in. beyond the thread runout where "D" is the nominal diameter of the shank after heading. If the two sections would overlap, the entire length of the part shall be sectioned and examined as a whole.
- 5.1.3 Threads:
- 5.1.3.1 Root defects such as notches, slivers, folds, roughness, and oxide scale are not permissible (See Fig. 4).
- 5.1.3.2 Multiple laps on the flanks of threads are not permissible regardless of location. Single laps on the flanks of threads that extend toward the root are not permissible (See Figs. 5 and 6).
- 5.1.3.3 There shall be no laps along the flank of the thread below the pitch diameter (See Fig. 7). A single lap is permissible along the flank of the thread above the pitch diameter on either the pressure or non-pressure flank (one lap at any cross section through the thread) provided it extends toward the crest and generally parallel to the flank (See Fig. 7).
- 5.1.3.4 Crest craters, crest laps, or a crest lap in combination with a crest crater are permissible, provided the imperfections do not extend deeper than 20% of the basic thread height (See Table I) as measured from the thread crest when the thread major diameter is at minimum size (See Fig. 8). The major diameter of the thread shall be measured prior to sectioning. As the major diameter of the thread approaches maximum size, values for depth of crest crater and crest lap imperfections listed in Table I may be increased by $1/2$ of the difference between the minimum major diameter and the actual major diameter as measured on the part.
- 5.2 Microscopic Examination: Specimens cut from parts shall be polished, etched in Kalling's reagent (100 ml of absolute ethyl alcohol, 100 ml of hydrochloric acid (sp gr 1.19), and 5 g of cupric chloride), \emptyset Marble's reagent (20 ml of hydrochloric acid (sp gr 1.19), 20 ml of water, and 4 g of cupric sulfate pentahydrate), or other suitable etchant and then examined at not lower than 100X magnification to determine conformance to the following requirements:
- 5.2.1 Microstructure: Parts shall have microstructure of completely recrystallized material except in the area of the threads and the head-to-shank fillet radius.
- 5.2.2 Grain Size: Shall be 1 or finer as determined by comparison of the specimen with the chart in ASTM E112.
- 5.2.3 Surface Hardening: Parts shall have no surface hardening except as produced during cold working of the head-to-shank fillet radius and during rolling of threads. Evidence of carburization or nitriding \emptyset will not be permitted. In case of dispute over results of the microscopic examination, microhardness testing shall be used as a referee method; a Vickers hardness reading within 0.003 in. of the surface more than 30 points higher than the reading in the core will be evidence of nonconformance to this requirement.
- 5.3 Properties: Parts shall conform to the requirements of 5.3.1.1 or 5.3.1.2, as applicable, 5.3.3, and 5.3.4.1 or 5.3.4.2, as applicable, and shall be capable of meeting the requirements of 5.3.2.1 or \emptyset 5.3.2.2, as applicable. Threaded members of gripping fixtures for tensile and stress-rupture tests shall be of sufficient size and strength to develop the full strength of the part without stripping the thread. For tensile and stress-rupture tests on finished parts, the parts shall be aligned in fixtures so that three full turns of thread are exposed in the gage section.
- 5.3.1 Tensile Properties at Room Temperature:

5.3.1.1 **Finished Parts:** Parts shall have breaking load not lower than that specified in Table II. If the size or shape of the part is such that failure would occur outside the threaded section but the part can be tested satisfactorily, such as parts having a shank diameter equal to or less than the thread minor diameter or having an undercut, parts shall conform to only the tensile strength requirement of 5.3.1.2; for such parts, the diameter on which stress is based shall be the actual measured minimum diameter of the part and parts shall fracture only in the unthreaded shank section or the undercut, not in the area of the head-to-shank fillet radius except when this radius is associated with an undercut.

5.3.1.2 **Machined Test Specimens:** If the size or shape of the part is such that a tensile test cannot be made on the part, tensile tests shall be conducted in accordance with ASTM A370 on specimens machined from finished parts or from coupons of the same heat of material heat treated with the parts. Specimens shall conform to the following requirements:

Tensile Strength, psi	155,000 min
Elongation, % in 2 in. or 4D	8 min
Reduction of Area, %	10 min

5.3.1.2.1 When permitted by purchaser, hardness tests on the end of parts may be substituted for tensile tests of machined specimens.

5.3.2 **Tensile Properties at 1400 F (760 C):**

5.3.2.1 **Finished Parts:** Parts heated to 1400 F \pm 10 (760 C \pm 5.6), held at heat for 30 min. before testing and tested at 1400 F \pm 10 (760 C \pm 5.6), shall have breaking load not lower than that specified in Table II. If the size or shape of the part is such that failure would occur outside the threaded section but the part can be tested satisfactorily, such as parts having a shank diameter equal to or less than the thread minor diameter or having an undercut, parts shall conform to only the tensile strength requirement of 5.3.2.2; for such parts, the diameter on which stress is based shall be the actual measured minimum diameter of the part.

5.3.2.2 **Machined Test Specimens:** If the size or shape of the part is such that a tensile test cannot be made on the part, tensile test specimens prepared as in 5.3.1.2, heated to 1400 F \pm 10 (760 C \pm 5.6), held at heat for 30 min. before testing, and tested at 1400 F \pm 10 (760 C \pm 5.6) in accordance with 5.3.1.2 shall conform to the following requirements:

Tensile Strength, psi	126,000 min
Elongation, % in 2 in. or 4D	8 min
Reduction of Area, %	10 min

5.3.3 **Hardness:** Shall be uniform and not lower than Rockwell C 30 or equivalent but hardness of the threaded section and of the head-to-shank fillet area may be higher than that of other areas as a result of the cold working operations.


5.3.4 **Stress-Rupture Test at 1350 F (732.2 C):**

5.3.4.1 **Finished Parts:** Parts, maintained at 1350 F \pm 5 (732.2 C \pm 2.8) while the load specified in Table II is applied continuously, shall not rupture in less than 30 hours. If the shank diameter of the part is less than the maximum minor (nominal minor) diameter of the thread but the part can be tested satisfactorily, parts shall conform to the requirements of 5.3.4.1.1.


5.3.4.1.1 Parts having a shank diameter less than the maximum minor (nominal minor) diameter of the part shall be tested as in 5.3.4.1 except that the load shall be as specified in 5.3.4.2. The diameter on which stress is based shall be the actual measured minimum diameter of the part.

- 5.3.4.2 Machined Test Specimens: If the size or shape of the part is such that a stress-rupture test cannot be made on the part, a test specimen, maintained at $1350\text{ F} \pm 5$ ($732.2\text{ C} \pm 2.8$) while a load sufficient to produce an initial axial stress of 85,000 psi is applied continuously, shall not rupture in less than 30 hours. Specimens shall be machined from finished parts, or from coupons of the same heat of material heat treated with the parts, to the dimensions shown in ASTM A370. Tests shall be conducted in accordance with ASTM E139.
- 5.4 Resampling and Retesting: If any part or specimen used in the above tests fails to meet the specified requirements, acceptance of the parts may be based on the testing of three additional parts or specimens for each original nonconforming part or specimen, all of which additional parts or specimens shall conform to specified requirements. Failure of any retest part or specimen to meet the specified requirements shall be cause for rejection of the parts represented and no additional testing shall be permitted. Results of all tests shall be reported.
6. QUALITY: Parts shall be uniform in quality and condition, clean, sound, smooth, and free from burrs and foreign materials and from internal and external imperfections detrimental to their performance.
7. SAMPLING: Shall be in accordance with the latest issue of AMS 2373.
8. REPORTS: Unless otherwise specified, the vendor of parts shall furnish with each shipment three copies of a report stating that the chemical composition of the parts conforms to the requirements of the applicable material specification and showing the results of tests to determine conformance to the room temperature tensile property, hardness, and stress-rupture strength requirements of this specification and a statement that the parts conform to all other requirements of this specification. This report shall include the purchase order number, AMS 7469A, contractor or other direct supplier of material, part number, and quantity.
9. REJECTIONS: Parts not conforming to this specification or to authorized modifications will be subject to rejection.

SAENORM.COM : Click to view the full text of AMS 7469A

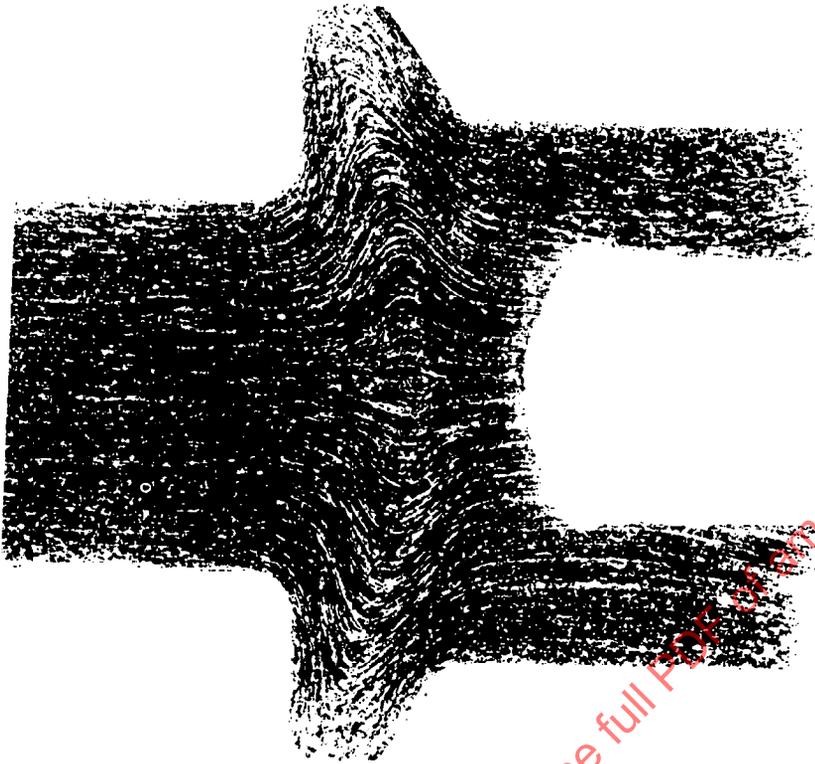


SATISFACTORY GRAIN FLOW
FIGURE 1A

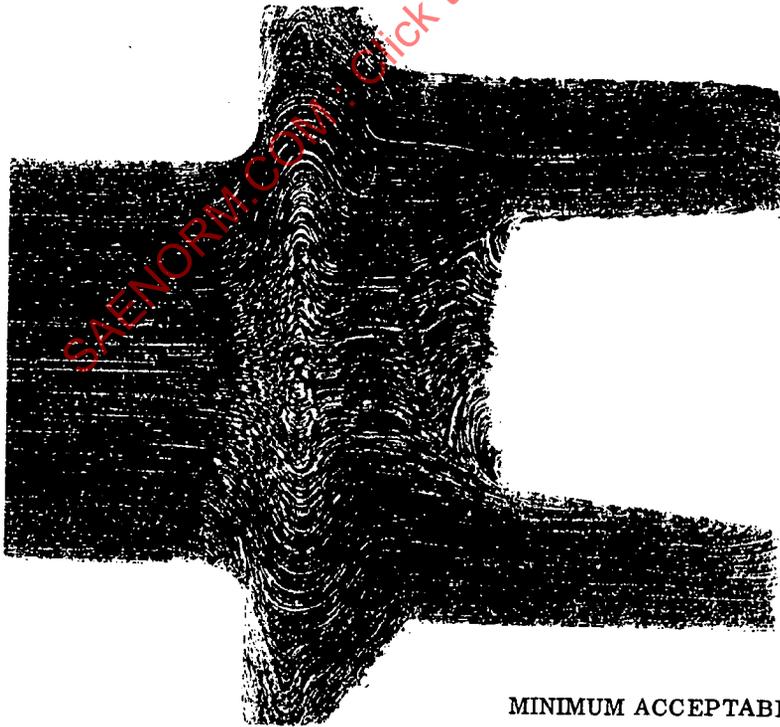

MINIMUM ACCEPTABLE STANDARD

Showing maximum permissible cutting of flow lines after machining to remove oxide and decarburization as in 4.3.


FIGURE 1B

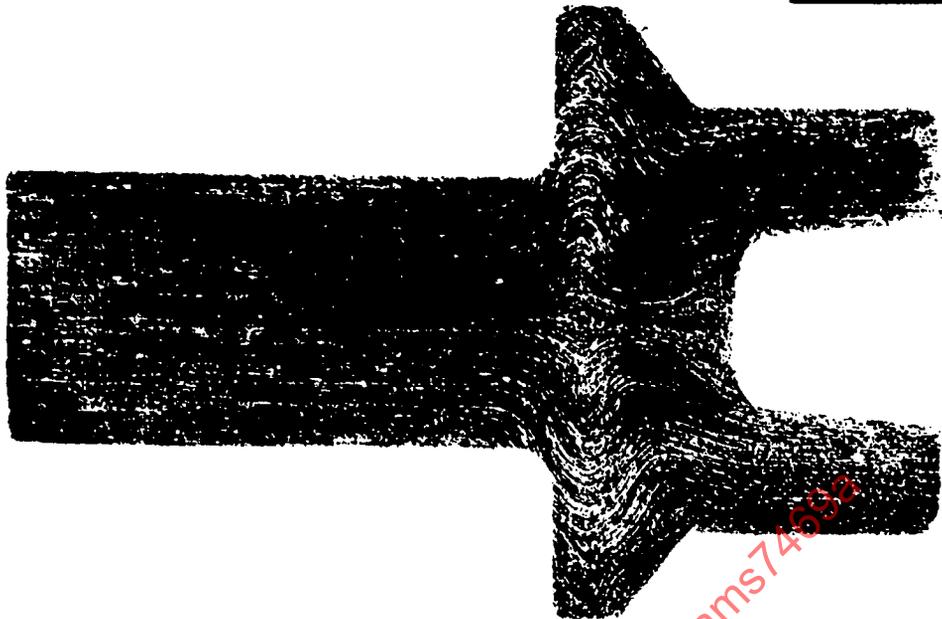

UNACCEPTABLE GRAIN FLOW

Excessive cutting of flow lines in the shank, head to shank fillet, and bearing surface is not permissible.

FIGURE 1C

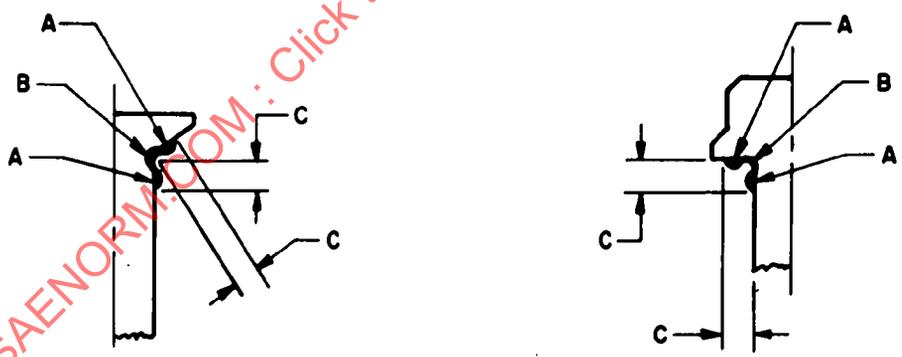


Nominal Bolt Diameter	C, max
Up to 0.3125, excl	0.062
0.3125 and 0.375	0.094
0.4375 - 0.625, incl	0.125
0.750 - 1.000, incl	0.156
Over 1.000	0.188


PERMISSIBLE DISTORTION FROM FILLET WORKING
FIGURE 2




FLOW LINES, ROLLED THREAD
FIGURE 3

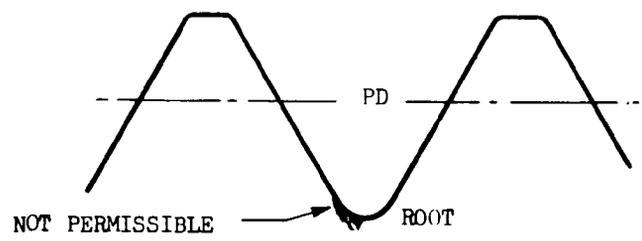

ROLLED THREAD
FIGURE 4

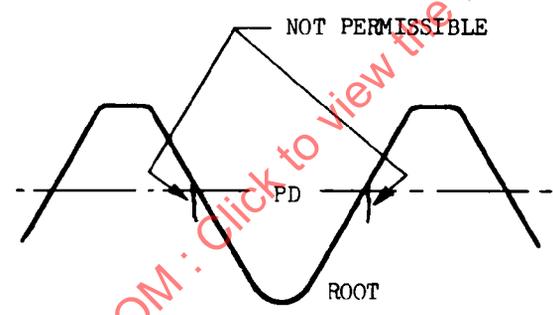

ROLLED THREAD
FIGURE 5

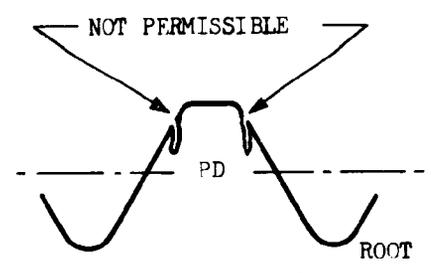

ROLLED THREAD
FIGURE 6

SAENORM.COM : Click to view the full PDF of ams7469a