

AEROSPACE MATERIAL SPECIFICATION

Peening of Metals

NOTICE

This document has been taken directly from U.S. Military Specification MIL-P-81985(AS), Amendment 1, and contains only minor editorial and format changes required to bring it into conformance with the publishing requirements of SAE technical standards. The initial release of this document is intended to replace MIL-P-81985(AS), Amendment 1. Any part numbers established by the original specification remain unchanged.

The original Military Specification was adopted as an SAE standard under the provisions of the SAE Technical Standards Board (TSB) Rules and Regulations (TSB 001) pertaining to accelerated adoption of government specifications and standards. TSB rules provide for (a) the publication of portions of unrevised government specifications and standards without consensus voting at the SAE Committee level, and (b) the use of the existing government specification or standard format.

Under Department of Defense policies and procedures, any qualification requirements and associated qualified products lists are mandatory for DOD contracts. Any requirement relating to qualified products lists (QPL's) has not been adopted by SAE and is not part of this SAE technical document.

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

Copyright 2001 Society of Automotive Engineers, Inc.
All rights reserved.

Printed in U.S.A.

QUESTIONS REGARDING THIS DOCUMENT:
TO PLACE A DOCUMENT ORDER:
SAE WEB ADDRESS:

(724) 772-7161
(724) 776-4970
<http://www.sae.org>

FAX: (724) 776-0243
FAX: (724) 776-0790

1. SCOPE:

1.1 Scope:

This specification covers procedures and requirements for dry peening the surfaces of metals by impingement of metallic shot or glass beads for the purpose of increasing the fatigue strength and resistance to stress corrosion cracking by inducing residual compressive stresses in specified surfaces.

2. APPLICABLE DOCUMENTS:

The following publications, of the issue in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein.

2.1 U.S. Government Publications:

Available from DODSSP, Subscription Services Desk, Building 4D, 700 Robbins Avenue, Philadelphia, PA 19111-5094.

RR-S-366	Sieves, Standard for Testing Purposes
MIL-S-851	Steel Grit, Shot and Cut Wire Shot; and Iron Grit and Shot-Blast Cleaning and Peening
MIL-S-5002	Surface Treatments and Coatings for Metal Surfaces of Weapons Systems
MIL-C-5541	Chemical Conversion Coating on Aluminum and Aluminum Alloys
MIL-I-6866	Inspection, Penetrant, Method of
MIL-I-6868	Inspection Process, Magnetic Particles
MIL-A-8625	Anodic Coatings for Aluminum and Aluminum Alloys
MIL-G-9954	Glass Beads: For Cleaning and Peening
MIL-S-13165	Shot Peening of Metal Parts

3. REQUIREMENTS:

3.1 Peening equipment:

The peening equipment shall provide means for a controlled rate propelling of dry metallic shot by air pressure or centrifugal force or of dry glass beads by air pressure against the work. The peening machine shall be equipped with suitable nozzles, deflectors or baffles to direct the peening medium against the part where desired and to prevent peening of areas not to be peened. The machine shall be so designed that the part to be peened is securely fastened. Mechanical means shall be provided to move uniformly either the part or the shot stream in either translation or rotation or both during peening. This movement shall be powered by a speed device such as a synchronous motor, induction motor, differential pressure cylinder or other controlled speed devices capable of automatically replenishing and maintaining an adequate quantity of shot at all times for maximum effectiveness and consistent reproduction of required peening intensities. Series motors and single acting cylinder activating mechanism are prohibited. All work shall be moved mechanically unless manual movement is permitted by the procuring activity in the contract or order.

3.2 Peening material:

Peening material shall be either metallic shot or glass beads. Metallic shot shall conform to MIL-S-851 as hardened cast steel (Type I), cast iron (Type II) or stainless steel cut wire (Type III). Glass beads shall be essentially solid spheres hard tempered, chemically pure crown glass and shall conform to MIL-G-9954, except for sieve analysis. Peening materials shall be capable of producing the required peening intensity without excessive fracturing or deformation of the particles.

- 3.2.1 Size: Unless otherwise specified, the as-received particle size distribution of the metallic shot shall conform to the applicable tables of MIL-S-851 for both cast shot and for cut stainless steel wire. Glass beads shall range in size from 0.0024 to 0.0661 inch (0.061 to 1.68 mm) in diameter. Unless otherwise specified, the particle size distribution of the as-received glass beads shall conform to MIL-G-9954 or to Table I, as selected by the peening contractor. Unless otherwise specified, the nominal size of the peening media charged into a machine shall be at the option of the supplier.
- 3.2.2 Uniformity: The shot or beads shall be free from sharp edges and broken pieces. Cast shot shall be spherical in shape and form and shall be free as practical from elongated, angular particles. Cut wire shot shall be free from shear cracks and laps, shall not contain seams or burrs, and shall be preused or otherwise conditioned to remove sharp edges before being used for peening, and shall be spherically formed. When visually examined the maximum number of deformed cast shot shall not exceed the values stated in Table II.
- 3.2.3 Shot maintenance: Equipment shall have a separator for continuous removal of broken or defect shot material during peening. Metallic shot shall be maintained in the equipment and shall not require replacement until more than 20 percent by weight shall pass through the sieve size specified in Table III for the shot peening number used. Glass beads used for peening over steel shot peened surfaces shall be replaced every two hours of operation.
- 3.2.4 Usability: Ferrous and non-ferrous metals shall not be peened interchangeability with the same peening medium in the same machine. Neither glass beads nor metal shot used on ferrous parts shall later be used on non-ferrous parts.
- 3.2.5 Hardness of shot: Hardness of the shot shall be in accordance with MIL-S-851. Parts to be shot peened having a hardness above Rc 50 should be shot peened with shot having a hardness of Rc 52 to Rc 62.

TABLE I - Glass Bead Sizes Through Sieves

	83	70	59	49	41	35	29	24
<p><u>1/</u> Sieves shall be as specified in RR-S-366</p>								
100								
98-100	100							
-	98-100	100						
0-8	-	98-100	100					
0	0-8	-	98-100	100				
	0	0-8	-	98-100	100			
		0	0-8	-	98-100	100		
			0	0-8	-	98-100	100	
				0	0-8	-	98-100	100
					0	0-8	-	98-100
						0	0-8	-
							0	0-8
								0

SAENORM.COM · Click to view the full PDF of amsp81985

TABLE I - Glass Percent Passing (Cont'd)

Sieve Number <u>1/</u>	Nominal B							
	331	280	232	197	165	138	117	98
18	100							
20	98-100	100						
25	-	98-100	100					
30	0-8	-	98-100	100				
35	0	0-8	-	98-100	100			
40		0	0-8	-	98-100	100		
45			0	0-8	-	98-100	100	
50				0	0-8	-	98-100	100
60						0-8	-	98-100
70						0	0-8	-
80							0	0-8
100								0
120								
140								
170								
200								
230								
270								
325								
400								

TABLE II - Uniformity of Cast Shot

Shot Peening Number (See MIL-S-851, Table III)	Number of Acceptable Deformed Shot - Maximum	Area-Square Inch	Shot Peening Number (See MIL-S-851, Table III)	Number of Acceptable Deformed Shot - Maximum	Area-Square Inch
930 and 780	5	1	320, 280, 230,	20	1/2
660 and 550	12	1	190 and 170		
460	15	1	130	30	1/4
390	20	1	110 and 70	40	1/4

TABLE III - Uniformity of Steel Shot in the Equipment

Shot Peening Number (See MIL-S-851, Tables III and IV)		20% - Maximum Amount Passing Through Sieve <u>1/</u>		Shot Peening Number (See MIL-S-851, Tables III and IV)		20% - Maximum Amount Passing Through Sieve <u>1/</u>	
Cast shot	Cut steel wire	Sieve number	Nominal opening - inch	Cast shot	Cut steel wire	Sieve number	Nominal opening - inch
930	-	16	0.0469	280	CW 28	45	0.0139
780	-	18	0.0394	230	CW 23	50	0.0117
660	CW 62	20	0.0331	190	-	60	0.0098
550	CW 54	25	0.0278	170	CW 20	70	0.0083
460	CW 47	30	0.0234	130	-	100	0.0059
390	CW 41	35	0.0197	110	-	120	0.0049
330	CW 35	40	0.0165	70	-	170	0.0035
-	CW 32	40	0.0165				

1/ Sieves shall be as specified in RR-S-366

3.3 Preparation procedures:

- 3.3.1 Dimensions and conditions of parts: Areas of parts to be peened shall be within dimensional requirements and surface finish requirements before peening. Except as otherwise permitted (see 3.5.1), all heat treatments to meet requirements for mechanical properties, all machining, grinding and required polishing of areas shall be completed before peening. All fillets shall be properly formed, all burrs shall be removed, and all sharp edges and corners to be peened shall be provided with sufficient radii to result in complete coverage without any distortion prior to peening.
- 3.3.2 Cleaning and stripping: Unless otherwise specified, all areas shall be cleaned in accordance with MIL-S-5002. Procedures for stripping coatings shall be as specified or approved in the contract or order (see 6.11).

- 3.3.3 Masking: Areas of the part or work piece which are designated in the contract or applicable drawing as having critical surface finishes that must be free from peening shall be suitably masked or otherwise handled to protect such surfaces. When it is impractical to mask areas designated to be free from peening marks, sufficient stock may be provided in these areas for subsequent removal of affected material for compliance with dimensional requirements of the applicable drawings. Masking shall be optional for areas not requiring peening and whose surface finish is not critical.
- 3.3.4 Magnetic particle or penetrant inspection: Unless otherwise specified, where magnetic particle or penetrant inspection is required, parts shall be subjected to such inspection in accordance with MIL-I-6868 or MIL-I-6866 before and after peening.
- 3.3.5 Sustained stress (preload): Unless otherwise specified, peening shall be accomplished on parts or areas of parts which do not have any sustained stress as the results of fabrication. When manufacturing operations induce residual stresses which may be detrimental to service after peening, the part shall be given a suitable stress relief heat treatment prior to peening.
- 3.4 Peening procedures:
- 3.4.1 Peening intensity: Unless otherwise specified on the drawings or in the contract, the peening intensity as indicated by a specified arc height value shall be as listed in Table IV for the thickness involved. If only a minimum intensity is specified, the maximum intensity should not exceed the minimum intensity by more than 0.004A for steel shot or 0.006N for glass beads. The maximum intensity shall not cause undue warpage of the part and shall be below the threshold of erosion of the basis material. Unless otherwise specified, for peening to intensities where the arc-height-inch is stated as A and C, metallic shot shall be used and where the arc-height-inch is stated as N, glass beads shall be used.
- 3.4.2 Coverage: Areas of parts, peened as referenced on applicable drawings, purchase orders or contracts, shall be peened to complete 100 percent visual coverage (see 4.2.4 and 6.10). Each portion of the critical surface shall show visible evidence of plastic flow, that is a uniform peened or hammered appearance, to indicate complete coverage and obliteration of the original surface finish as indicated by overlapping impressions. On parts having a hardness of Rockwell C50 and greater, such coverage appearance may not be apparent. However, such parts shall show a noticeable difference in luster from an unpeened part. The length of time to achieve complete visual coverage shall be measured. Unless otherwise specified, the final operation shall last twice the time for steel shot and four times as long for glass bead shot, that is 200 percent minimum coverage for steel shot and 400 percent minimum coverage for glass shot. Coverage for holes and internal diameters shall be in accordance with Table V.

TABLE IV - Peening Intensity for Complete Coverage in Arc-Height-Inch 1/ 2/

Thickness- Inch	Materials				
	Steel- 200 KSI or less	Steel-over 200 KSI	Titanium and titanium alloys	Aluminum and aluminum alloys (metallic steel shot) <u>3/</u>	Aluminum and aluminum alloy (glass beads)
Up thru 0.090	0.003 to 0.006A	0.003 to 0.006A	0.003 to 0.006A	-	0.004 to 0.008N
0.091 to 0.375	0.006 to 0.012A	0.006 to 0.010A	0.006 to 0.010A	0.006 to 0.010A	0.008 to 0.012N
0.376 and over	0.012 to 0.016A	0.006 to 0.010A	0.006 to 0.010A	0.010 to 0.014A	0.012 to 0.014N

1/ The suffix letter A indicates that the values have been determined by the use of the test strip A (see 4.4.2). Test strip A is used for arc heights up to 0.024A. For greater intensity test strip C should be used. Test strip N is used if the intensity is less than 0.004A (see 6.9).

2/ Magnesium alloy responds to peening is different from that of other materials. It is essential to avoid broken or deformed peening media. Peening must be done with such media and under such conditions which do not induce cracks.

3/ Cast steel or stainless steel cut wire shot as specified.

TABLE V - Coverage for Holes and Internal Diameters

Nominal Hole Diameter- Inch	Ratio- Diameter to Depth	Minimum Coverage- Percent
0.750 or greater	Any	200
Less than 0.750	1 or greater	200
Less than 0.750	Less than 1	100 to depth of 1/2 inch diameter

- 3.4.3 Area limitations: Unless otherwise specified, the variations in boundaries of areas to be peened, when limited, shall be -0 to + 1/8 inch.
- 3.4.4 Shot selection: The nominal shot size shall be the smallest size practical to produce the required intensity. For aluminum only, use as large a shot size as possible, taking into consideration surface finish and smallest fillet radii because the larger the shot size on aluminum for any given intensity, the deeper will be the depth of compression.
- 3.4.4.1 Fillet surfaces: If fillet surfaces on parts are required to be peened, the shot or bead size used shall be such that the nominal diameter of the peening medium is not greater than one-half the smallest nominal fillet radius to be peened, except that the nominal diameter of the shot need not be smaller than 0.007 inch (Shot No. 70 of MIL-S-851) and the nominal diameter of the beads need not be smaller than 0.002 inch (No. 13 size of MIL-G-9954 or No. 24 of Table I) when fillet radii of less than twice these dimensions require peening.
- 3.4.4.2 Shielded areas: If the shot or beads must pass thru slots, recesses or apertures to peen required shielded surfaces, the nominal diameter of the peening medium shall not be greater than 25 percent of the diameter or width of the opening, except that limitations as to minimum shot and bead specified for peening fillets (see 3.4.4.1) shall also apply. Except as otherwise specified or permitted, such as when shielded areas are involved, nonferrous materials shall not be peened with shot smaller than the following for the intensities given:

<u>Intensity</u>	<u>Shot Numbers (MIL-S-851)</u>	
	<u>Types I and II</u> (cast iron and steel)	<u>Type III</u> (cut wire)
0.012A	280	CW28
0.016A	390	CW41
0.020A	550	CW54

3.4.5 Angle of impact: The nozzle or nozzles of the equipment shall be kept as nearly as possible at an angle of 90 degrees to the surface of the part being peened. Effective peening intensity will vary directly as the sine of the angle of impact. Nozzle angles 45 degrees or lower do not produce effective compressive residual stresses and should be avoided.

3.5 Post-treatments:

3.5.1 Post operations: After peening, areas of parts shall still be within the dimensional and surface finish requirements. Manufacturing operations, such as straightening, machining and heat treating, grinding, or etching, which relieve stresses, developed by peening or which develop detrimental residual stresses shall not be permitted after peening. If straightening is required for peened parts, any means other than peen forming shall be prohibited. When peened parts are heated after peening as for baking of paints or protective coating systems, for hydrogen embrittlement relief after electroplating or other thermal treatments, the temperatures employed shall be limited as follows (see 6.12).

Titanium and Titanium Alloy Parts	800°F (427°C)
Carbon and Alloy Steel Parts	475°F (246°C)
Aluminum and Aluminum Alloy Parts	200°F (93°C)
Magnesium Alloy Parts	200°F (93°C)

3.5.2 Cleaning: After peening and removal of protective masking all shot, shot fragments and particles shall be removed from surfaces of parts. Only methods which will not erode or scratch surfaces shall be used. Aluminum and aluminum alloy parts which have been peened with steel shot shall be cleaned either by an approved cleaning solution or other methods (see 3.5.2.1) which will not erode, scratch or otherwise damage the surface. This shall also be applicable to titanium and titanium alloy parts. For improving the maximum adhesion of subsequent coatings, the peened surfaces may be treated just prior to coating application with a very fine aluminum oxide abrasive material.

3.5.2.1 Aluminum parts: Unassembled aluminum and aluminum alloy parts without inserts may be cleaned by immersion in a nitric acid solution for 20 to 40 minutes at 120° to 140°F (49° to 60°C). The solution shall consist of the following:

Nitric acid (Sp. gr. 1.42)	200 to 500 ml.
Water	to make 1.1.

Nitric acid base deoxidizer solutions used prior to the application of anodic and chemical conversion coatings may be used provided they meet the acid strength requirements (see 6.14).

3.5.3 Surface finish improvement: It shall be permissible to improve the surface finish after peening by polishing, lapping, honing or vapor blasting provided such operations do not generate temperatures in excess of the applicable limitations (see 3.5.1) and do not remove material layers in excess of 10 percent of the induced compressive layer. For example, a part peened to a 0.007 A intensity may have up to 0.0007 inch or 0.7 mil removed.

- 3.5.4 Protection from corrosion: Peened parts shall be protected from corrosion during processing and until final coating, installation and packaging (see 5.1) is completed. The method of protection shall be as specified or approved in the contract or order.
- 3.5.4.1 Aluminum and aluminum alloy parts: For aluminum and aluminum alloy parts, it is recommended that peened parts either coated with a light corrosion-preventive oil, or given either an anodic treatment in accordance with MIL-A-8625 or a chemical conversion coating treatment in accordance with MIL-C-5541 within two days after completion of the shot peening operation.
- 3.6 Qualification of peening operator:
- 3.6.1 Demonstration of proficiency: To achieve qualified status, each peening operator shall demonstrate his skill and proficiency by satisfactorily conducting peening tests in accordance with 4.2.3 using the equipment, materials and tools which he is required for peening parts in production as well as by various production processes.
- 3.6.2 Record of proficiency: The facility using the peening operator will complete and retain a record of the peening operator's qualification.
- 3.6.3 Equipment and materials: The peening operator shall satisfactorily peen a specimen on each machine, with the applicable media, and all equipment which he is to use in production.
- 3.6.4 Record of peening variables: Information concerning peening variables shall be observed and recorded while the respective specimens are being peened. Factors to be recorded, which can affect the degree of intensity are as follows:
- Air pressure or wheel speed, nozzle size and type, nozzle placement and direction, wheel angle and direction of hot spot.
 - Size, shape, density and hardness of peening medium.
 - Length of exposure time, angle of impact, peening medium flow rate or velocity of shot stream.
 - Speed of work piece movement in either translation or rotation or both.
- 3.6.5 Properties of peened specimens: The peened specimens shall be tested and exhibit properties conforming to all the requirements specified herein.
- 3.6.6 Eligibility for peening: No peening operator shall be permitted to perform any peening operation in connection with any contract until qualified.
- 3.6.7 Qualification tests: The qualification tests for peening operators shall consist of peening and inspection of specimens regularly used in production peening of the basis metals. The test shall be as specified in 4.2.3 under various conditions of materials and equipment settings.
- 3.6.7.1 Acceptance criteria: The peened specimen shall be considered satisfactory when the operator reproduces a coverage curve (see Figure 1) for the equipment within ± 1 Mil Almen A.

- 3.6.8 Rejection and retest: When the operator fails on one specimen, he shall be permitted to submit two other specimens of the same saturation coverage curve. If either of these two specimens fail to conform to the requirements specified, the operator shall be disqualified. If reexamination is desired after the above tests, the operator shall be required to submit a complete series of saturation curves as specified in 3.6.7. In addition to the above, the operator will be required to submit one additional specimen of the saturation curve which resulted in the disqualification.
- 3.6.9 Report of tests: Upon successful completion of the specified tests, an inspection test report that contains the essential information shall be signed by a responsible official of the contractor.
- 3.6.10 Qualification maintenance:
- 3.6.10.1 Status maintenance: Qualified status of operators may be maintained by a continuing record of satisfactory workmanship in compliance with 3.6.10.3 or by successfully completing reexamination tests every six months as specified in 3.6.10.2. Examination or reexamination of an operator will be required whenever there is reason to question the operator's proficiency, equipment operation, or the quality of parts. Periodic reexamination will not be required for operators when records indicate a satisfactory level is being maintained in production peening.
- 3.6.10.2 Reexamination: This reexamination will be required when a continuous record of workmanship is not maintained. Operators shall be reexamined every 6 months by peening parts representative of production. When the operator fails the above test, he shall be reexamined in accordance with 3.6.8.
- 3.6.10.3 Continuous record of workmanship: The determination of a satisfactory record of workmanship shall be based on approval, periodical scheduled inspection of parts, or by nondestructive methods normally conducted by the contractor for inspecting production peening capable of disclosing improper coverage and insufficient intensity (4.3).

4. QUALITY ASSURANCE:

4.1 Responsibility for inspection:

Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification when such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Peening intensity:

4.2.1 Sampling: At least one intensity determination as defined in 4.2.3 shall be made to represent each peening machine for each two hours of continuous operation or fraction thereof where cast iron shot or glass beads are used and for each eight hours of continuous operation or fraction thereof where cast steel or cut steel wire is used. In all cases, at least one intensity determination shall be made at the start and one at the finish of each operation change and at least once for each eight hours of continuous operation.

4.2.2 Test specimens: One test specimen shall be used for each intensity determination. Test specimens shall be A, C or N type as specified. They shall be made of SAE 1070 cold rolled spring steel properly hardened and then tempered between flats to the hardness stated in Table VI. All specimens shall be free from carburization and decarburization to the extent that the differences in hardness between the surface and a noncarburized or nondecarburized depth under the surface shall not be more than two points on the Rockwell Superficial 30N scale. Specimens shall be flat within the tolerances shown in Table VI, when measured with a gage of the form and dimensions shown in Figure 6 of MIL-S-13165. In determining flatness of the N type specimen, measurements shall be made from both surfaces of specimen and the results averaged. Sides and ends of the specimens shall be smooth.

Table VI - Test Specimen Requirements

Specimen	Type A	Type C	Type N
Dimensional-length, inch	3.000 \pm 0.015	3.000 \pm 0.015	3.000 \pm .015
width, inch	0.745 to 0.750	0.745 to 0.750	0.745 to 0.750
thickness, inch	0.051 \pm 0.001	0.094 \pm 0.001	0.031 \pm 0.001
Arc height as measured on gauge (inch)	0.000 \pm 0.0015	0.000 \pm 0.0015	0.000 \pm 0.0015
Rockwell hardness	C44 to C50	C44 to C50	A72.5 to A76

4.2.3 Test procedure: The test specimens, selected in accordance with 4.2.2 shall be examined for flatness and set for zero curvature position with a micrometer gage of the form and dimensions detailed in Figure 6 of MIL-S-13165. In using the gage, the central portion of the side of the test strip that will not be peened shall be placed against the indicator stem of the gage. The test specimen shall be attached, as shown in Figure 5 of MIL-S-13165, to the solid holder, as detailed in Figure 4 of MIL-S-13165, so that the surface of the test strip which contacted the gage shall be facing down. The test strip, mounted on the holding block, shall be supported on a fixture which stimulates in its exposure to the blast of the equipment, the critical surface of the part to be peened. Test specimens may also be retained in milled slots of a simulated part rather than the holder for testing. To achieve the required peening intensity for compliance with 3.4.1 and Table IV, the test specimen shall be exposed to the shot, the speed of work movement in translation and rotation, the air pressure or wheel speed of the equipment, the work distance of the nozzle or wheel for a time that will be used for the production part or article to provide uniform surface coverage. After

4.2.3 (Continued):

exposure, the test strip shall be removed from the holder and the amount of deflection shall be measured with the gage, always placing the unpeened side against the gage stem. A peened test strip shall not be re-peened after being removed from the test strip holder.

4.2.4 Coverage: The peening operation shall be repeated for different exposure times with a fixed equipment setting using a series of test strips to obtain a series of test points to establish a coverage or saturation curve as illustrated in Figure 1. If the curve shows an arc height within ± 1 mil at full coverage point, the conditions shall be considered satisfactory. If the specified intensity cannot be obtained in a reasonable time, shot velocity or that of the shot size shall be increased for higher arc heights or decreased for lower heights as illustrated in Figure 1 and the test shall be repeated (see 6.10).

4.2.5 Intensity information: Test specimens shall accompany peened parts and shall be inspected along with the appropriate lot. The following information shall be recorded for each specimen.

- a) Lot number and other production control numbers.
- b) Part number and name.
- c) Number of parts in lot.
- d) Date peened.
- e) Shot peening machine identification, air pressure or wheel speed, nozzle size and type, nozzle placement and direction, wheel angle and angle of hot spot, velocities of shot stream (rotation, translation or combination).
- f) Shot material and size with length of exposure time to peening.
- g) Specified peening intensity and actual peening intensity as shown by accompanying test strip.
- h) Percentage coverage.

This information shall be kept on file for the period of the contact. Applicable information shall also be kept on file necessary for qualification of peening operators (see 3.6.2, 3.6.4 and 3.6.7).

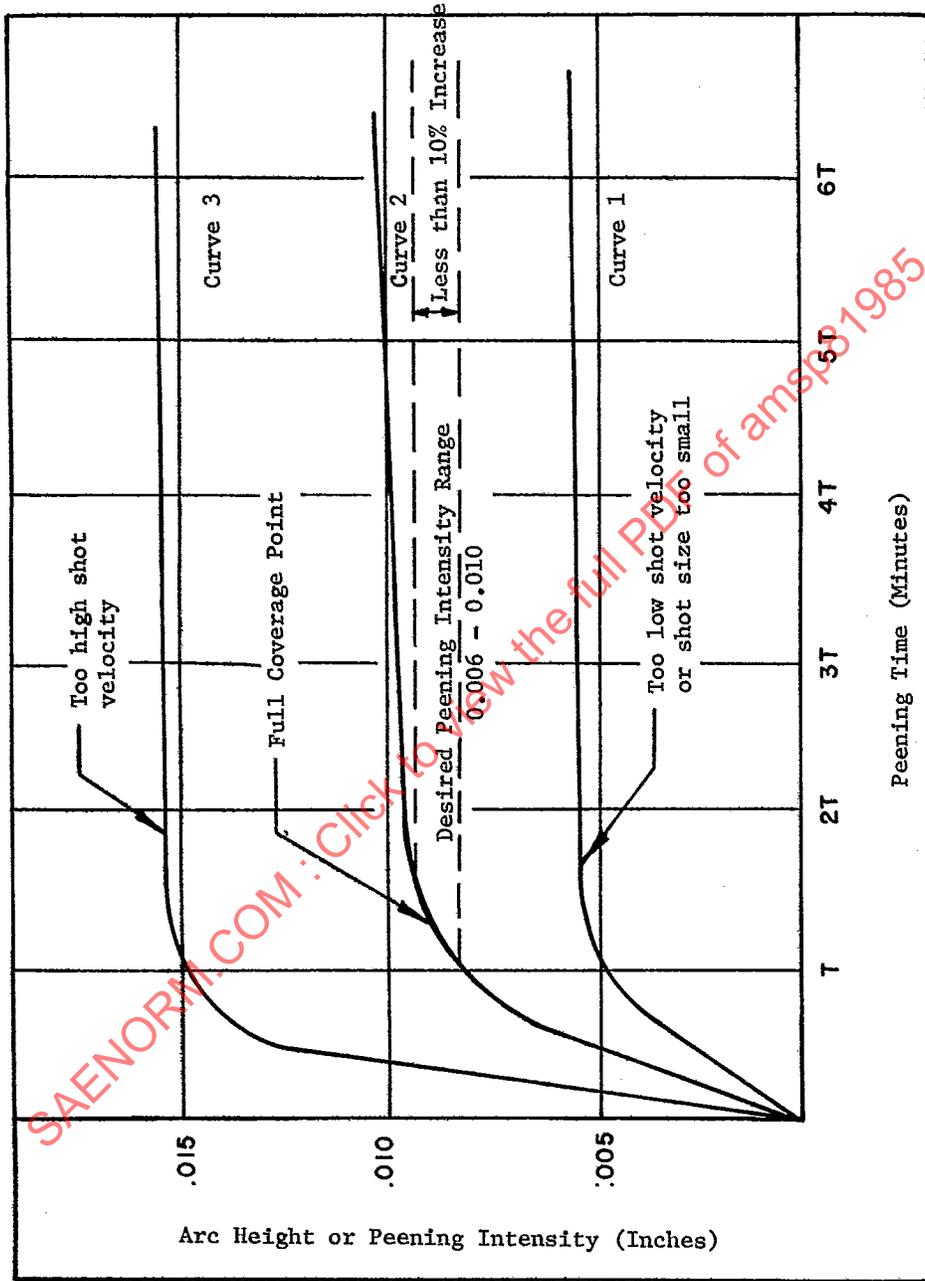


FIGURE 1 - 100% Coverage (Saturation) - Arc Height - Exposure Curve

4.3 Inspection of shot:

- 4.3.1 Sampling: At least one sample for determination for shot size and uniformity shall be taken for each two hours of continuous operation when cast iron shot is used or for each eight hours of continuous operation or fraction thereof when cast steel or cut wire shot is used. In all cases, whether metallic shot or glass beads are used, at least one sample shall be taken at the beginning and one at the end of each period of operation.
- 4.3.2 Visual examination: Cut wire shot and glass beads shall be examined for freedom from sharp edges, broken pieces and other defects detailed in 3.2.2. A single layer of cast shot which completely fills an area of 1, 1/2 or 1/4 inch square, as applicable for the shot number, shall be examined for deformed shot to determine conformance to 3.2.2 and Table II. The criteria for the determination of deformation shall be the acceptable and unacceptable shapes as shown in Figure 7 of MIL-S-13165.
- 4.3.3 Shot size: Sieves conforming to RR-S-366 shall be used for tests involving shot size and uniformity. Shot size distribution shall be determined for conformance to 3.2.1, 3.2.2, Table I and Table III as mixed, nonuniform shot is uneconomical and takes longer to obtain the correct intensity.

4.4 Inspection of peened articles:

- 4.4.1 Inspection lot: A lot shall consist of an identifiable quantity of parts or articles of the same metal composition, produced and formed under the same conditions, approximately of the same shape and size and subject to inspection at one time.
- 4.4.2 Sampling: Each peened part or article shall be examined to determine conformance to this specification with respect to coverage and workmanship. Examination for area limitations shall be made to insure conformance to the tolerances specified. On approval of the procuring activity, the supplier may use a system of statistical quality control for coverage, area limitation and workmanship examination.
- 4.4.3 Peened coverage: Articles shall be visually inspected (see 4.4.3.1) for compliance with the coverage requirement of 3.4.2. Visual examination shall show a uniform and complete overlapping impression, obliterating the original surface of the article. Holes shall be inspected with a suitable optical instrument. Surfaces of articles shall be bare or coated with a light transparent oil.
- 4.4.3.1 Visual coverage: Complete visual coverage is defined as uniform denting or obliterating of the original surface of the part or work piece as determined by either of the following methods:
- 4.4.3.1.1 Visual examination using a ten power magnifying glass.

4.4.3.1.2 Peenscan process described as follows:

Prepare a control specimen of the same material as the actual work piece. Coat this control specimen with tracer liquid (Dyescan #220 and/or #226 or equal) by dipping, spraying or painting and allow the tracer liquid to dry. Check coating under a black light to insure complete coverage of the coated area to be shot peened has been accomplished. Shot peen the control specimen under proper shot peening conditions for the required intensity and coverage as prescribed. Re-examine under the black light in order to determine if the tracer liquid has been completely removed. Full coverage is indicated by complete removal of the tracer liquid.

Areas which do not produce full coverage will show a white color under the black light whereas full coverage will give off a dark color.

Coverage of actual production pieces can be established by using the same procedure used for control specimens. This can be done by utilizing the tracer liquid for each part or on a statistical sampling basis.

4.4.4 Peening: The peening conditions, type of machine (air pressure or centrifugal), nozzles or wheels, size of nozzles or wheels, air pressure, wheel speed, work distance, material for shot, size of shot, work movement, shall be the same for parts or articles being peened as for the test strips (see 4.2.3). Since shape of a part or article to be shot peened will differ from Almen test strip, exposure time will depend on time required to achieve full coverage on part. See paragraph 3.4.2 and 4.4.3. For holes and internal diameter the requirements for 3.4.2 shall be used

5. PREPARATION FOR DELIVERY:

5.1 Packaging and packing:

The preservation, packaging, and packing methods for peened parts or articles employed by a supplier shall be such as to preclude any physical damage during handling and shipment (see 3.5.4).

6. NOTES:

6.1 Intended use:

Peening with metallic shot or glass beads is intended to induce surface compressive stresses in metal parts such as axles, springs (helical, torsional and leaf), gears, shafting, aircraft landing gear assemblies, wing structures, jet engine support members, helicopter rotor hub assemblies, etc. which are subjected to repeated applications of load pattern for the purpose of improving resistance to fatigue and stress corrosion cracking. Metallic shot peening is also used for applications such as to close porosity in castings and to straighten or form applicable parts. Peening with glass beads, is used primarily where contamination presents a special problem, where a fine surface finish is required, or when peening in a very sharp radius, such as a thread root, is required.