

Issued 1998-11
Revised 2001-01
Reaffirmed 2007-01

Superseding AS1975B

(R) Hose Assembly, Polytetrafluoroethylene, Para-Aramid Reinforced,
3000/4000 psi, 275 °F, Standard Duty, Hydraulic, Aircraft Systems

RATIONALE

This document has been reaffirmed to comply with the SAE 5-year Review policy.

1. SCOPE:

This Aerospace Standard (AS) defines the requirements for a polytetrafluoroethylene (PTFE) lined, para-aramid fiber reinforced, hose assembly suitable for use up to 4000 psi, and up to 275 °F, aircraft and missile hydraulic and pneumatic systems.

1.1 Product Classification:

CLASS 3000 - For use in pressure systems of 3000 psig, or lower, at the reduced bend radius per Table 1.

CLASS 4000 - For use in pressure systems of 4000 psig, or lower, at the bend radius per Table 1.

1.2 Field of Application:

1.2.1 For use with phosphate ester or silicate ester hydraulic fluids. The oil immersion samples in 3.5.2.7 shall be preconditioned per 4.5.2.2 using both type of system fluids as specified. Due precaution must be taken in handling any toxic hydraulic fluid.

1.2.2 This is not recommended for gaseous service where minor effusion is detrimental.

2. REFERENCES:

2.1 Applicable Documents:

The following publications form a part of this document to the extent specified herein. The latest issue of SAE publications shall apply. The applicable issue of other publications shall be the issue in effect on the date of the purchase order. In the event of conflict between the text of this document and references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has obtained.

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

Copyright © 2007 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
Tel: 724-776-4970 (outside USA)
Fax: 724-776-0790
Email: CustomerService@sae.org
SAE WEB ADDRESS: <http://www.sae.org>

SAE AS1975 Revision C

2.1.1 SAE Publications: Available from SAE, 400 Commonwealth Drive, Warrendale, PA 15096-0001.

AMS 2486	Conversion Coating of Titanium Alloys Fluoride-Phosphate Type
AMS 4928	Titanium Alloy, Bars, Wire, Forgings, and Rings, 6Al 4V, Annealed
AMS 4945	Titanium Alloy, Tubing, Seamless, Hydraulic, 3Al 2.5V, Texture Controlled, 105 ksi Yield Strength Cold Worked, Stress Relieved
AMS 4965	Titanium Alloy, Bars, Wire, Forgings, and Rings 6.0Al 4.0V Solution Heat Treated and Aged
AMS 5536	Steel Bars, Corrosion Resistant, 18 Cr 8.5 Ni (SAE 30302) Cold Drawn, 100 ksi
AMS 5556	Steel, Corrosion and Heat Resistant, Seamless or Welded Tubing, 18Cr 11Ni 0.70(Cb+Ta) (SAE 30347), Hydraulic, Solution Heat Treated
AMS 5557	Steel Tubing, Seamless and Welded, Corrosion and Heat Resistant, 18.5Cr 10.5Ni 0.40Ti (SAE 30321), Hydraulic, Solution Heat Treated
AMS 5561	Steel Tubing, Welded and Drawn, Corrosion and Heat Resistant, 9.0Mn 20Cr 6.5Ni 0.28N (SAE 21-6-9), High-Pressure Hydraulic
AMS 5567	Steel Tubing, Seamless or Welded, Corrosion Resistant, 19Cr 10Ni (SAE 30304), Hydraulic, Annealed
AMS 5570	Steel, Corrosion and Heat Resistant, Seamless Tubing, 18Cr 11Ni 0.40Ti (SAE 30321), Solution Heat Treated
AMS 5571	Steel, Corrosion and Heat Resistant, Seamless Tubing, 18Cr 10.5Ni 0.70(Cb+Ta) (SAE 30347), Solution Heat Treated
AMS 5575	Steel, Corrosion and Heat Resistant, Welded Tubing, 18Cr 10.5Ni 0.70(Cb+Ta) (SAE 30347), Solution Heat Treated
AMS 5576	Steel, Corrosion and Heat Resistant, Welded Tubing, 18Cr 10.5Ni 0.40Ti (SAE 30321), Solution Heat Treated
AMS 5636	Steel, Corrosion and Heat Resistant, Bars and Wire, 18Cr 9.0Ni (SAE 30302) Solution Heat Treated and Cold Drawn, 100 ksi Tensile Strength
AMS 5637	Steel, Corrosion and Heat Resistant, Bars and Wire, 18Cr 9.0Ni (SAE 30302) Solution Heat Treated and Cold Drawn, 125 ksi Tensile Strength
AMS 5639	Steel, Corrosion Resistant, Bars, Wire, Forgings, Tubing and Rings, 19Cr 10Ni (SAE 30304), Solution Heat Treated
AMS 5643	Steel, Corrosion Resistant, Bars, Wire, Forgings, Tubing and Rings, 16Cr 4.0Ni 0.30(Cb+Ta) 4.0Cu (SAE 17-4PH), Solution Heat Treated, Precipitation Hardenable
AMS 5644	Steel Bars and Forgings, Corrosion Resistant, 17Cr 7.0Ni 1.0Al (SAE 17-4PH)
AMS 5645	Steel, Corrosion and Heat Resistant, Bars, Wire, Forgings, Tubing and Rings, 18Cr 10Ni 0.40Ti (SAE 30321), Solution Heat Treated
AMS 5646	Steel, Corrosion and Heat Resistant, Bars, Wire, Forgings, Tubing and Rings, 18Cr 11Ni 0.60Cb (SAE 30347), Solution Heat Treated
AMS 5647	Steel, Corrosion Resistant, Bars, Wire, Forgings, Tubing and Rings, 19Cr 9.5Ni (SAE 30304L), Solution Heat Treated
AMS 5659	Steel, Corrosion Resistant, Bars, Wire, Forgings, Rings and Extrusions, 15Cr 4.5Ni 0.30Cb 3.5Cu (SAE 15-5PH), Consumable Electrode Melted, Solution Heat Treated, Precipitation Hardenable

SAE AS1975 Revision C

2.1.1 (Continued):

AMS 5743	Steel, Corrosion and Heat Resistant, Bars and Forgings 15.5Cr 4.5Ni 2.9Mo 0.10N (SAE AM-355), Solution Heat Treated, Sub-Zero Cooled, Equalized, and Over-Tempered
AMS-QQ-P-35	Passivation Treatment for Corrosion Resistant Steels
AMS-QQ-S-763	Steel Bars, Wire Shapes, and Forgings, Corrosion Resistant
AS150	Hose Assembly, Type Classifications of, Basic Performance and Fire Resistance
ARP603	Impulse Testing of Hydraulic Hose Assemblies, Tubing and Fittings
AS611	Hose Assembly and Tubing, Polytetrafluoroethylene, Cleaning Methods
ARP908	Hose Fitting - Installation and Qualification Test Torque Requirements
AS1055	Fire Testing of Flexible Hose, Tube Assemblies, Coils, Fittings and Similar System Components
AS1072	Sleeve, Hose Assembly, Fire Protection
AIR1228	Standard Impulse Machine Equipment and Operation
AS1241	Fire Resistant Phosphate Ester Hydraulic Fluid for Aircraft
AS1703	Sleeve, Hose Assembly, Heat Shrinkable
ARP1835	Preparation for Delivery, General Requirements for Hose Assemblies
AS2078	Test Methods, Hose Assemblies, Polytetrafluoroethylene (PTFE)
AS4375	Fitting End, External Thread, Flareless Design Standard
AS4395	End Fitting - Flared Tubing Connections, Design Standard
AS4488	Tubular Assemblies, Fusion Welded, Inspection Processes and Acceptance Standards for
AS4658	Fitting End, External Thread, Short, Flareless
AS4659	Fitting End, Bulkhead, External Thread, Short, Flareless
AS4660	Nut, Short, Flareless
AS4700	Installation Procedures and Torques for Short Flareless Fittings
AS4702	Nut, Swivel, Wired On, Short, Flareless
AS4703	Fitting End, Acorn, Short, Flareless
AS5272	Lubricant, Solid Film, Heat Cured, Corrosion Inhibiting, Procurement Specification
AS7003	National Aerospace and Defense Contractors Accreditation Program (NADCAP)
AS7112	National Aerospace and Defense Contractors Accreditation Program Requirements for Fluid System Components
AS8879	Screw Threads - UNJ Profile, Inch
AS21900	Adapter, Flareless Tube to AN Flared Tube
AS33514	Fitting End, Standard Dimensions for Flareless Tube Connection and Gasket Seal
AS85421	Fittings, Tube, Fluid Systems, Separable, High Pressure Dynamic Beam Fitting

SAE AS1975 Revision C

2.1.2 ASTM Publications: Available from ASTM, 100 Barr Harbor, West Conshohocken, PA 19428-2959.

ASTM A 262	Standard Recommended Practices for Detecting Susceptibility to Intergranular Attack in Stainless Steel
ASTM B 348	Titanium Alloy
ASTM D 638	Precipitation Hardening Iron Base Superalloy Bars, Forgings, and Forging Stock for High Temperature Service, Standard Specification for

2.1.3 NAS Standards: Available from Aerospace Industries Association, 1250 Eye Street NW, Washington, DC 20005.

NAS 847	Caps and Plugs, Protective, Dust and Moisture Seal
NAS 1760	Fitting End, Flareless Acorn, Standard Dimensions for

2.1.4 U.S. Government Publications: Available from DODSSP, Subscription Services Desk, Building 4D, 700 Robbins Avenue, Philadelphia, PA 19111-5094.

MIL-PRF-680	Degreasing Solvent
TT-I-735	Isopropyl Alcohol

MIL-F-8815	Filter and Filter Elements, Fluid Pressure, Hydraulic Lines, 15 Micron Absolute and 5 Micron Absolute, Type II Systems
------------	--

MIL-PRF-83282	Hydraulic Fluid, Fire Resistant Synthetic Hydrocarbon Base, Metric, NATO Code Number H-537
---------------	--

MIL-L-46010	Lubricant, Solid Film, Heat Cured, Corrosion Inhibiting
MIL-F-85421/1	Fitting End, Standard Dimensions for Dynamic Beam Seal, Male
MIL-PRF-87257	Hydraulic Fluid, Fire Resistant; Low Temperature, Synthetic Hydrocarbon Base, Aircraft and Missile

MIL-STD-100	Engineering Drawing Practices
MIL-STD-129	Standard Practice for Military Marking
MIL-STD-130	Identification Marking of U.S. Military Property
MIL-HDBK-831	Test Reports, Preparation of
MIL-STD-1839	Calibration and Measurement Requirements
MIL-STD-1916	DoD Preferred Methods for Acceptance of Products
SAE-AMS-STD-2219	Fusion Welding for Aerospace Applications

2.1.5 ASME Publications: Available from ASME, 22 Law Drive, Box 2900, Fairfield, NJ 07007-2900.

ASME B46.1	Surface Texture
------------	-----------------

SAE AS1975 Revision C

2.1.6 PRI Publications: Available from Performance Review Institute, 161 Thornhill Road, Warrendale, PA 15086-7527.

PD2001 Qualified Product Management Council Procedures for Qualified Products Group

PD2101 Aerospace Quality Assurance, Product Standard, Qualification procedures, fluid Systems

2.2 Hose Assembly Procurement Specifications:

Refer to AS1975SUP1 for a listing of applicable hose assembly procurement standards applicable to this document.

3. TECHNICAL REQUIREMENTS:

3.1 Qualification:

Hose assemblies supplied in accordance with this document shall be representative of products which have been subjected to and which have successfully passed the qualification tests specified in this standard.

3.1.1 Manufacturer Qualification: A manufacturer producing a product in conformance to this procurement specification shall be accredited in accordance with the requirements of PD2101, AS7003 and AS7112, and shall be listed in a Performance Review Institute (PRI) Qualified Manufacturers List (QML) for this type product.

3.1.2 Product Qualification: All hose assemblies shall conform to the requirements of this procurement specification and shall be approved in accordance with the requirements of PD2001, and PD2101, for listing in a Performance Review Institute (PRI) Qualified Parts List QPL-AS1975.

3.2 Materials:

The hose assembly materials shall be uniform in quality, free from defects, consistent with good manufacturing practice, shall conform to applicable specifications and the requirements specified herein, and suitable for the purpose intended.

SAE AS1975 Revision C

3.2.1 Metals: Metals used in the hose and fittings shall be corrosion-resistant and shall conform to the following specifications:

a. Bars and Forgings:

- | | |
|-----------------|---|
| 1. AMS-QQ-S-763 | Class 302 - Cond. A or Cond. B (AMS 5636 or AMS 5637) |
| 2. AMS-QQ-S-763 | Class 304 - Cond. A or Cond. B (AMS 5639) |
| 3. AMS-QQ-S-763 | Class 304L - Cond. A (AMS 5647) |
| 4. AMS-QQ-S-763 | Class 321 - Cond. A (AMS 5645) |
| 5. AMS-QQ-S-763 | Class 347 - Cond. A (AMS 5646) |
| 6. AMS 5643 | 17-4PH |
| 7. AMS 5644 | 17-7PH |
| 8. AMS 5659 | 15-5PH |
| 9. AMS 5743 | AM-355 |
| 10. AMS 4928 | Titanium 6AL-4V Annealed |
| 11. AMS 4965 | Titanium 6AL-4V Heat Treated |
| 12. ASTM B 348 | Titanium Alloy - Grade 2 |

b. Tubing:

- | | |
|-------------|--|
| 1. AMS 5556 | Type 1 or Type 2 Stainless Steel Tubing, 347 |
| 2. AMS 5557 | Type 1 or Type 2 Stainless Steel Tubing, 321 |
| 3. AMS 5561 | Welded Stainless Steel Tubing, 21-6-9 |
| 4. AMS 5567 | Type 1 or Type 2 Stainless Steel Tubing, 304 |
| 5. AMS 5570 | Seamless Stainless Steel Tubing, 321 |
| 6. AMS 5571 | Seamless Stainless Steel Tubing, 347 |
| 7. AMS 5575 | Welded Stainless Steel Tubing, 347 |
| 8. AMS 5576 | Welded Stainless Steel Tubing, 321 |
| 9. AMS 4945 | Titanium 3AL-2.5V Texture Controlled |

3.2.2 Reinforcement: Para-aramid textile treated and applied to the hose with an outer polyester braid or polybenzimidazol/para-aramid blend braid cover to meet all the requirements herein.

3.3 Design and Construction:

The hose assembly shall consist of a seamless polytetrafluoroethylene (PTFE) inner tube, treated para-aramid reinforcement, polyester or polybenzimidazol/para-aramid blend outer braid cover with optional PTFE tape interlayer, and corrosion-resistant steel and/or titanium alloy end fittings as required to meet the construction and performance requirements of this specification.

3.3.1 Inner Tube: The inner tube shall be of a seamless construction of virgin PTFE resin of uniform gage. It shall have a smooth bore and shall be free from pitting or projections on the inner surface. Additives may be included in the compound from which the tube is extruded.

SAE AS1975 Revision C

- 3.3.2 Reinforcement: The reinforcement shall consist of a treated para-aramid braid and/or wraps with optional PTFE tape interlayer and polyester or polybenzimidazol/para-aramid blend braided outer cover. The reinforcement shall be arranged over the inner tube to provide sufficient strength and protection to ensure conformance with the requirements specified herein. Broken reinforcing cords shall be cause for rejection. The outer braid shall provide 100% coverage to protect the para-aramid reinforcement from exposure to ultraviolet light. A continuous lay line interrupted with AS1975, or AS/MA1975, and the hose manufacturer's name and trademark shall be permanently marked in contrasting color along the length of the hose.
- 3.3.3 Fittings: All fittings shall be permanently attached and proven to meet the requirements herein. Standard hose assemblies shall have flared fittings to mate with AS4395; flareless fittings according to NAS1760 to mate with AS33514 or AS4375 (-20 size and larger configurations may be per AS4703 to mate with AS4658 or AS4659 with nuts per AS4660 or AS4702) or dynamic beam seal fittings to mate with male end per MIL-F-85421/1 or AS4207 or other suitable end connections. Antitorque hexes/flats shall be provided and shall fit standard wrench openings. All internal surfaces of fitting nuts shall be lubricated with dry film per MIL-L-46010 Type 1 or AS5272. Dry film on external surfaces is permitted.
- 3.3.3.1 Straight Fittings: Straight fittings shall be of one piece construction. Welded or brazed joints must not be located in the fluid paths. Elbow fittings may be classified per 3.3.3.2 for construction.
- 3.3.3.2 Other Fittings: Other fittings, including elbow fittings, shall be of one piece construction to the maximum extent possible. However, those made with other than one piece construction can use welded and redrawn corrosion-resistant steel tubing or seamless titanium tubing in accordance with 3.2.1. Fitting welds shall employ a butt weld joint design and be welded per SAE-AMS-STD-2219 or AS4488. If welding is used to attach stainless steel components, a stabilized grade of stainless steel shall be used.
- 3.3.3.3 End Fitting Collars (Sockets): All end fitting collars (sockets) crimped or swaged, and if fabricated from Type 304 stainless steel, are required to be capable of passing an embrittlement test as specified in ASTM A 262 Practice E, prior to assembly to the nipple and crimp or swaging operation. Sockets fabricated from stabilized austenitic steel (304L, 321, or 347) or titanium are acceptable without being subjected to the embrittlement test. Titanium collars are per ASTM B 348 - Grade 2.
- 3.3.3.4 Fitting Finish:
- 3.3.3.4.1 Corrosion Resistant Steel Parts: Unless otherwise specified, corrosion resistant steel parts shall be passivated in accordance with AMS-QQ-P-35.
- 3.3.3.4.2 Titanium Alloy Parts: If fluoride conversion coating is used, it shall be per AMS 2486.

SAE AS1975 Revision C

TABLE 1 - Physical Requirements of Hose Assemblies and Weight of Hose

Hose Size	(Nominal Tube Size)	Hose Weight Max ¹ lb/in	Operating Pressure ² Max psi	Proof Pressure Min -0/+1000 psi	Burst Pressure Room Temperature Minimum ² psi	Burst Pressure High Temperature Minimum ² psi	Bend Radius at Inside of Bend Minimum in		Volumetric Expansion Maximum cm ³ /in
							3000 psi	4000 psi	
04	0.250	0.006	4000	8000	16,000	12,000	1.50	1.50	0.089
06	0.375	0.008	4000	8000	16,000	12,000	2.50	2.50	0.132
08	0.500	0.012	4000	8000	16,000	12,000	2.88	5.75	0.187
10	0.625	0.020	4000	8000	16,000	12,000	3.25	6.50	0.383
12	0.750	0.025	4000	8000	16,000	12,000	4.00	7.75	0.493
16	1.000	0.040	4000	8000	16,000	12,000	7.50	12.00	1.134
20	1.250	0.050	4000	8000	16,000	12,000	15.00	21.00	TBD
24	1.500	TBD	TBD	TBD	TBD	TBD	TBD	TBD	TBD

¹ Hose weight shall be determined on a minimum length of 12 in.

² For 3000 psi service, 12,000 psi minimum room temperature and 9000 psi high temperature is acceptable

3.4 Dimensions:

The hose assembly dimensions, except for length, shall be as specified in Figure 1 and Table 2.

3.4.1 Hose Weight: Hose consisting of inner tube and reinforcement as outlined in 3.3.1 and 3.3.2 shall not exceed the maximum hose weights specified in Table 1.

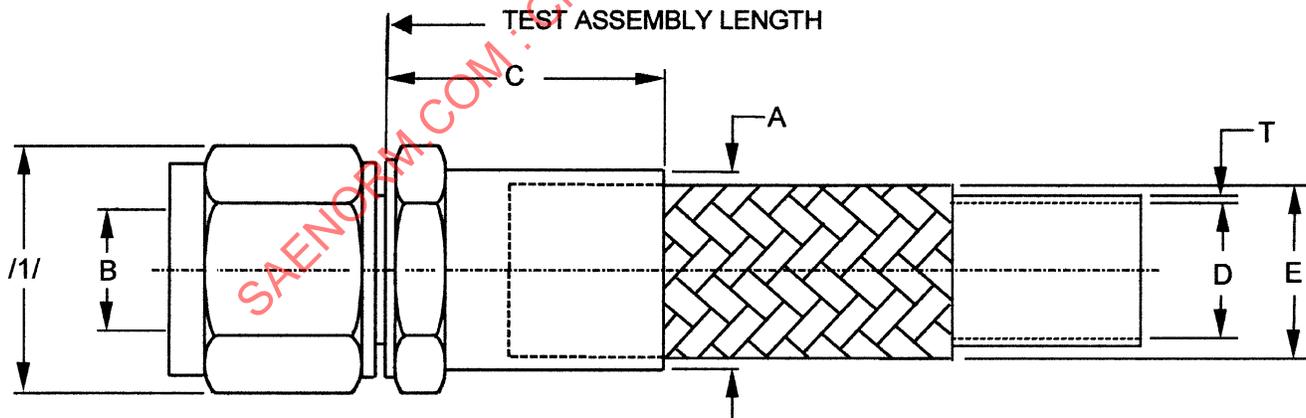


FIGURE 1 - Hose and Fitting Dimensions

SAE AS1975 Revision C

TABLE 2 - Hose and Fitting Dimensions as Shown in Figure 1 (in)

Hose Size	Rigid Tube OD (Ref)	Fitting OD A Max	Fitting ID B ²⁾ Min	Socket Length C Max	Hose ID D Min	Hose OD E Min	Hose OD E Max	Unbraided Inner Tube Wall T Min	Unbraided Inner Tube Wall T Max	Spherical Ball Size for Determining Min Hose Assy. ID ²⁾ in Straight Fittings	Spherical Ball Size for Determining Min Hose Assy. ID ²⁾ in Elbow Fittings
										0.122	0.115
04	0.250	0.690	0.135	1.25	0.212	0.405	0.465	0.035	0.046	0.122	0.115
06	0.375	0.800	0.240	1.45	0.298	0.495	0.555	0.035	0.046	0.216	0.204
08	0.500	0.970	0.340	1.78	0.391	0.650	0.710	0.040	0.051	0.306	0.289
10	0.625	1.150	0.410	2.25	0.485	0.850	0.920	0.045	0.056	0.369	0.349
12	0.750	1.380	0.510	2.50	0.602	0.995	1.075	0.045	0.056	0.459	0.434
16	1.000	1.660	0.760	3.00	0.852	1.285	1.365	0.045	0.056	0.684	0.646
20	1.250	TBD	TBD	TBD	TBD	TBD	TBD	TBD	TBD	TBD	TBD
24	1.500	TBD	TBD	TBD	TBD	TBD	TBD	TBD	TBD	TBD	TBD

/1/ Cross corners of nut and socket hex may exceed "A" dimension.

²⁾ Minimum specified inside diameter shall be verified by passing a spherical ball through the hose assembly.

3.5 Performance:

The inner tube and hose assembly shall meet the following performance requirements:

3.5.1 PTFE Inner Tube:

- 3.5.1.1 Tube Roll: The tube shall not leak, split, burst, or show any evidence of malfunction when rolled to the flattening and rounding gaps of AS2078 (3000 psi and higher) values. The test method is specified in 4.6.2.1.
- 3.5.1.2 Tube Proof Pressure: The tube, without reinforcement, shall not leak, burst, or show any evidence of malfunction when tested to the AS2078 (3000 psi and higher) proof pressure values. The test method is specified in 4.6.2.1.
- 3.5.1.3 Tensile Strength: The longitudinal tensile strength for all sizes of tubes shall be 2200 psi minimum. The transverse tensile strength for sizes -10 and larger shall be 1800 psi minimum. For sizes -08 and smaller, the transverse tensile strength need not be tested. The test method is specified in 4.6.2.2.
- 3.5.1.4 Elongation: Elongation shall be a minimum of 200%. The test method is specified in 4.6.2.3.
- 3.5.1.5 Specific Gravity: The specific gravity values of the hose inner tube shall not exceed 2.155 apparent and 2.190 relative. The test method is specified in 4.6.2.4.

3.5.2 Hose Assembly: The hose, complete with reinforcement and assembled with end fittings, shall meet the following performance requirements:

- 3.5.2.1 Proof Pressure: The hose assembly shall withstand the proof pressure listed in Table 1 without malfunction or leakage. The test method is specified in 4.6.3.
- 3.5.2.2 Elongation and Contraction: The hose assembly shall not change in length by more than ±2% in 10 inches of hose length when subjected to the maximum operating pressure in Table 1 for a minimum of 5 min. The test method is specified in 4.6.4.

SAE AS1975 Revision C

- 3.5.2.3 Volumetric Expansion: The volumetric expansion of the hose assemblies shall not exceed the limits specified in Table 1. The test method is specified in 4.6.5.
- 3.5.2.4 Leakage: The hose assembly shall not leak (no external wetting) when subjected to two pressure cycles of 66% of minimum room temperature burst pressure. The test method is specified in 4.6.6.
- 3.5.2.5 Burst Pressure:
- 3.5.2.5.1 Room Temperature Burst Pressure: The hose assembly shall not leak nor burst at any pressure below the room temperature burst value specified in Table 1. The test method is specified in 4.6.7.1.
- 3.5.2.5.2 High Temperature Burst Pressure: The hose assembly shall not leak nor burst at any pressure below the high temperature burst value specified in Table 1. The test method is specified in 4.6.7.2.
- 3.5.2.6 Thermal Shock: The hose assemblies shall not leak nor show any evidence of malfunction when subjected to the Table 1 proof and high temperature burst pressure, after being thermally shocked by rapidly increasing hose temperature from -65 to 275 °F. The test method is specified in 4.6.8 .
- 3.5.2.7 Impulse: The hose assemblies shall be capable of withstanding 250,000 pressure impulse cycles for 3000 psi or 100,000 pressure impulse cycles for 4000 psi when tested in accordance with 4.6.9. Any hose or fitting leakage, hose burst, fitting blow-off, or any evidence of malfunction during the test shall constitute failure.
- NOTE: For -20 size and larger, 100,000 pressure impulse cycles is acceptable for 3000 psi service.
- 3.5.2.8 Assembly Flexibility: The hose assembly shall not leak nor show any evidence of failure or malfunction when subjected to the Table 1 proof pressure after 400,000 flexure cycles when tested from -65 to 275 °F . The test method is specified in 4.6.10.
- 3.5.2.9 Stress Degradation (Air Leakage): The air leakage rate from the hose and two end fittings (not including "B" nuts) when held at the maximum operating pressure shown in Table 1 after completion of the stress degradation test shall not exceed 2.0 cm³/in/min. The test method is specified in 4.6.11.
- 3.5.2.10 Pneumatic Surge: There shall be no evidence of inner tube collapse, sponging, or shedding of PTFE particles from the inner tube after 16 cycles of rapid reduction in pneumatic pressure from Table 1 maximum operating pressure to 0 psi. The test method is specified in 4.6.12.
- 3.5.2.11 Pneumatic Effusion: The effusion rate for any hose size shall not exceed 8.0 cm³/ft of hose length. The test method is specified in 4.6.13.

SAE AS1975 Revision C

3.5.2.12 Repetitive Assembly Torque: The flared and flareless fittings shall withstand the repetitive assembly torque values specified in ARP908, or beam seal fittings per AS85421. There shall be no leakage, galling, or other malfunction of the fitting nut and interface connection during the specified pressure test. The test method is specified in 4.6.14.

3.5.2.13 Electrical Conductivity: Hose assembly shall conduct a direct current equal to 900 μ A minimum to 10,000 mA maximum with a test potential of 1000 V DC. The test method is specified in 4.6.15.

3.5.2.14 Push-Pull Test: The hose assembly shall withstand 50,000 push-pull cycles without leakage, kinking, or other failure when tested per 4.6.16.

3.6 Screw Threads:

Coupling nut threads shall be in accordance with AS8879 (ISO 3161). Thread tolerance increase of 10% during assembly or testing shall not be cause for rejection of the hose assembly. For inspection purposes, all threads are categorized "other threads" per 3.1 and 6.2.7 of AS8879 unless otherwise required by the purchaser.

3.7 Length:

Tolerances on hose assembly lengths shall be as follows:

- a. ± 0.125 in for lengths under 18 in
- b. ± 0.250 in for lengths from 18 to 36 in exclusive
- c. ± 0.500 in for lengths from 36 to 50 in exclusive
- d. $\pm 1\%$ for lengths of 50 in and over

3.8 Part Numbering of Interchangeable Parts:

All parts having the same manufacturer's part number shall be functionally and dimensionally interchangeable. The item identification and part number requirement of MIL-STD-100 shall govern the manufacturer's part numbers and changes thereto.

3.9 Identification of Product:

Equipment, assemblies, and parts shall be marked for identification in accordance with MIL-STD-130. The following special marking shall be added:

3.9.1 Fittings: The manufacturer's name or trademark shall be permanently marked on all end fittings.

SAE AS1975 Revision C

3.9.2 Assembly: A permanent marking shall be applied on a fitting or on a permanent band, or bands, securely attached on the hose. If a metallic band is used on a bare hose, it shall be covered with a translucent shrink sleeve per AS1703 code "A" and extend beyond the edge of the band by approximately 0.125 in. A permanent metallic band may be used on the collar or over a firesleeve. The band shall be no wider than 1 in and shall not impair the flexibility or the performance of the hose. Unless otherwise specified, the marking on the fitting or band shall include the following information:

- a. Assembly manufacturer's name or trademark and assembly specification AS1975
- b. CAGE code and complete hose assembly part number
- c. Operating pressure "3000 psi" or "4000 psi" as applicable
- d. Operating temperature "275 °F"
- e. Pressure test symbol "PT"
- f. Date of hose assembly manufacture expressed in terms of month and year
- g. Hose manufacturer's CAGE code number (required only when hose manufacturer is different than hose assembly manufacturer)
- h. Fire resistance type per AS1055, Type and Class, or AS150 and Type (when applicable)

3.10 Workmanship:

The hose assembly, including all parts, shall be constructed and finished in a thoroughly workmanlike manner. All surfaces shall be free from burrs. All sealing surfaces shall be smooth, except that annular tool marks up to 100 μ m Ra maximum per ASME B46.1 will be acceptable.

3.10.1 Dimensions and Tolerances: All pertinent dimensions and tolerances, where interchangeability, operation, or performance of the hose assembly may be affected, shall be specified on all drawings.

3.10.2 Cleaning: All hose assemblies shall be free from oil, grease, dirt or other foreign materials, both internally and externally. Unless otherwise specified, hose assemblies shall be cleaned to Class 0 of AS611, using approved alkaline cleaners only. Do not use chlorinated solvents.

4. QUALITY ASSURANCE PROVISIONS:

4.1 Responsibility for Inspection:

Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the procuring activity. The procuring activity reserves the right to perform any of the inspections set forth in the specification, where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

SAE AS1975 Revision C

4.2 Classification of Inspections:

The examining and testing of hose assemblies shall be classified as:

- a. Qualification inspections (see 4.3)
- b. Quality conformance inspections (see 4.4)

4.3 Qualification Inspections:

4.3.1 Qualification Test Samples: The number and length of test samples required to qualify each hose size are specified in Table 3. All specimens for each hose size are required for qualifying each of the methods of end fitting attachment and for each method of end fitting construction, bent tube or forged. Simultaneous qualification of different types of end fittings may be accomplished by having fittings of one type on one hose end and fittings of another type on the other end. If a supplier qualifies one end fitting outlet design and at a later date desires to qualify others, two hose assemblies of each size to be qualified shall be subjected to the tests specified in 4.5.1.1.

4.3.2 Qualification Test Sequence: Test sequence and procedure shall be as specified in Table 4 and, if applicable, 4.5.1.1.

4.3.3 Test Report, Test Samples and Data for the Procuring Agency: When the tests are conducted at a location other than the laboratory of the procuring activity, the following shall be furnished to that activity:

- a. Test Report: The test report shall be in accordance with MIL-HDBK-831, which shall include a report of all tests and outline description of the tests and conditions.
- b. Test Samples: Test samples when requested by the procuring activity. Samples subjected to qualification testing shall not be shipped as part of contract or order.
- c. Drawings: Three sets of assembly and subassembly drawings. The assembly drawings shall have a cut-away section showing all details in their normal assembly position and shall define all details and subassemblies.
- d. Sources: List of sources of hose or hose components, including source's name and product identification for inner tube, hose and assembly.

NOTE: Log sheets and recorded test data shall remain on file at the source test facility and are not to be sent to the qualifying activity unless specifically requested.

SAE AS1975 Revision C

4.3.4 Qualification Inspection Methods: Qualification inspection methods shall consist of all the examinations and tests specified under 4.6.

TABLE 3 - Length of Hose Assemblies for Test (in)
(Refer to Figure 1)

Hose Assy Size	Six Assemblies for Impulse Test (4.6.9)		Two Assemblies for Flex Test (4.6.10)		Six Assemblies for Other Tests /3/	Two Assemblies for Push/Pull (4.6.16) /2/ Max Free Hose Length
	3000 psi	4000 psi	3000 psi	4000 psi		
04	10.5	10.5	14.0	14.0	18	13
06	14.5	14.5	18.0	18.0	18	15
08	17.0	26.0	20.5	29.5	18	18
10	20.5	30.5	24.0	34.0	18	21
12	24.0	36.0	27.5	39.45	18	24
16	38.0	52.0	41.5	55.0	18	-
20	TBD	TBD	TBD	TBD	TBD	-
24	TBD	TBD	TBD	TBD	TBD	-

NOTES:

1. The six test specimens required for the impulse test (4.6.9) shall have a straight end fitting on one end and a 90° elbow end fitting on the other end. All remaining test samples shall have straight end fittings on both ends.
- /2/ Samples of each size in lengths shown shall be used for examination, push/pull test, and conductivity test (Samples No. 15 and 16, Table 4).
- /3/ Two additional samples of each size are required if tests in accordance with 4.5.1.1 are conducted.

SAE AS1975 Revision C

TABLE 4 - Qualification Test Sequence and Number of Test Specimens

Test Para.	Relevant Inspection/Test	Inner Tube	Sample Hose Assemblies																	
			Test Specimen No.																	
			1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16	17	18
4.6.1.1	Examination of Product ¹⁾	X																		
4.6.2.1	Proof Pressure ¹⁾	X																		
4.6.2.1	Tube Roll ¹⁾	X																		
4.6.2.2	Tensile Strength ¹⁾	X																		
4.6.2.3	Elongation ¹⁾	X																		
4.6.2.4	Specific Gravity ¹⁾	X																		
4.6.1.2	Examination of Product		X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X
4.6.3	Proof Pressure		X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X
4.6.4	Elongation and Contraction		X	X																
4.6.5	Volumetric Expansion				X	X														
4.6.6	Leakage						X	X												
4.6.8	Thermal Shock						X	X												
4.6.9	Impulse	Un-aged									X	X								
		Air-aged											X	X						
		Oil-aged													X	X				
4.6.10	Assembly Flexure		X	X																
4.6.11	Stress Degradation								X	X										
4.6.12	Pneumatic Surge								X	X										
4.6.13	Pneumatic Effusion				X	X														
4.6.7.1	Room Temperature Burst Pressure				X															
4.6.7.2	High Temperature Burst Pressure					X														
4.6.14	Repeated Assembly		X	X																
4.6.16	Push / Pull															X	X			
4.6.15	Electrical Conductivity															X	X			
6.1.1	Fire Resistance (when required)																	X	X	X

Key: X means one inspection/test

1) Production lot records may be used to verify conformance to these tests if the PTFE tube or hose assembly is an established production item.

SAE AS1975 Revision C

4.4 Quality Conformance Inspections:

Quality conformance inspections shall consist of the following tests:

- a. Individual tests (see 4.4.1) (100% inspection)
- b. Sampling tests (see 4.4.2)
- c. Periodic control tests (see 4.4.3)

4.4.1 Individual Tests: Each hose assembly shall be subjected to the following tests:

- a. Examination of product (see 4.6.1)
- b. Proof pressure test (see 4.6.3)

NOTE: Production samples that are proof pressure tested with water should be air dried prior to capping (see cleaning requirements, 3.10.2).

4.4.2 Sampling Tests: The following inspections and tests shall be performed in the order indicated on eight hose assemblies with straight fittings at each end selected at random from each sampling lot. The sampling lot shall consist of approximately, but not more than, 3000 hose assemblies, all of one dash number size manufactured under essentially the same conditions, but not necessarily during one continuous run. One hose assembly tested from each lot of 375 hose assemblies is also permitted for protracted or small assembly run condition.

- a. Internal cleanliness (AS611, Class 0)
- b. Leakage tests (see 4.6.6)
- c. Room temperature burst pressure test (see 4.6.7.1)

4.4.3 Periodic Control Tests: The following inspections and tests shall be performed as indicated on eight hose assemblies manufactured from bulk hose lengths selected at random from each periodic control lot. The periodic control lot shall consist of not more than 20,000 ft of hose, all of one dash number size, manufactured under essentially the same conditions, but not necessarily during one continuous run. Two hose assemblies manufactured and tested from each lot of 5000 ft of hose is also permitted.

4.4.3.1 Four hose assemblies or one hose assembly from a lot of 5000 ft in accordance with Table 3 shall be subjected to the following tests in the order indicated:

- a. Elongation and contraction test (see 4.6.4)
- b. Impulse test (see 4.6.9) (unaged samples only and may have straight fittings on both ends.)

SAE AS1975 Revision C

- 4.4.3.2 Four hose assemblies or one hose assembly from a lot of 5000 ft in accordance with Table 3 shall be subjected to the following tests in the order indicated:
- a. Stress degradation test (see 4.6.11)
 - b. Electrical Conductivity test (see 4.6.15)
 - c. Specific gravity tests (tubing only) (see 4.6.2.4)
- 4.4.4 Rejection and Retest: Where one or more items selected from a lot fails to meet the specification, all items in the lot shall be rejected.
- 4.4.4.1 Resubmitted Lots: Once a lot (or part of a lot) has been rejected by a procuring activity (Government or industry) and before it can be resubmitted for tests, full particulars concerning the cause of previous rejection, and the action taken to correct the defects in the lot, shall be furnished, in writing, by the contractor.
- 4.4.5 Inspection Procedure: All inspection plans shall be single sample plans with an accept number of zero.
- 4.4.6 Destructive Test Sample: Prior to testing, a letter "D" shall be permanently marked on each end fitting of those assemblies used for destructive tests (see 4.4.2 and 4.4.3).
- 4.5 Test Conditions:
- 4.5.1 Fitting Ends: Qualification tests shall be conducted on assemblies using straight type swivel ends, except for the impulse test samples requiring 90° elbow fitting at one end. Satisfactory completion of qualification tests on these hose assemblies shall also constitute qualification approval for hose assemblies having nonstandard fittings that have an identical attachment method and design and meet the requirements of this document.
- 4.5.1.1 Additional Fitting End Designs: If qualification approval is desired for other type of standard mating end fitting designs, two additional hose assemblies with the type fittings and of the size to be qualified shall be subjected to the following tests in the sequence indicated:
- a. Examination of product (see 4.6.1)
 - b. Proof pressure test (see 4.6.3)
 - c. Leakage test (see 4.6.6)
 - d. Repetitive assembly torque test (see 4.6.14)
 - e. Room temperature burst pressure test (see 4.6.7.1)
- 4.5.2 Preparation of Sample:
- 4.5.2.1 Unless otherwise specified, length of sample assemblies shall be in accordance with Table 3.

SAE AS1975 Revision C

- 4.5.2.2 Oil Aging: In all tests using oil aged samples, the hose assemblies shall be fully preconditioned in MIL-PRF-83282 or AS1241 Type IV or other system fluid, as specified. Preconditioning shall be done in two phases:
- a. The hose assemblies shall be filled with applicable system fluid and shall then be pressurized to 4000 psi operating pressure. While maintaining the pressure at room temperature, the hose assembly shall be immersed in applicable system fluid for 8 to 10 min then allowed to air dry for the remainder of 1 h. This sequence of immersion and air drying shall be repeated for a total of not less than 50 times.
 - b. After completing item (a), the hose shall be filled with applicable system fluid (excluding all air), and the hose shall then be pressurized to 4000 psi operating pressure and aged at 275 °F in air for 168 h.
- 4.5.2.3 Air Aging: Air aged samples shall be kept in air at a temperature of 275 °F for 168 h.
- 4.5.2.4 Unaged Samples: Unaged assemblies shall be as manufactured.
- 4.5.3 Test Fluids: Unless otherwise specified, the pressure test fluid shall be hydraulic fluid conforming to MIL-PRF-87257 or water. Where a high temperature test fluid is specified, the test fluid shall be MIL-PRF-83282 hydraulic fluid.
- 4.5.4 Pressure Measurements: Unless otherwise specified, all pressures shall have a tolerance of ± 100 psi.
- 4.5.5 Temperature Measurements: Unless otherwise specified, temperature measurements shall be taken within 6 in of the hose assemblies under test. Unless otherwise specified, all temperatures shall have a tolerance of +15 °F, -5 °F.
- 4.5.6 End Connections: Except as otherwise noted, each hose end shall be connected to a male fitting end as per 3.3.3, and utilizing the installation torque range specified in ARP908, AS85421, or AS4700, as applicable. The use of test fluid as a lubricant for flared and flareless fitting is permitted.
- 4.6 Inspection Methods:
- 4.6.1 Examination of Product:
- 4.6.1.1 Inner Tube (PTFE): Each length of tubing shall be examined to determine conformance to this specification with respect to material, size, workmanship, and dimensions.
 - 4.6.1.2 Hose Assembly: All hose assemblies shall be visually inspected to determine conformance to this document with respect to material, size and workmanship. Broken or missing reinforcing strands or evidence of kink or any other evidence of malfunction shall be cause for rejection. Crossed over reinforcing strands shall not be cause for rejection.

SAE AS1975 Revision C

4.6.2 Inner Tube Tests:

4.6.2.1 Tube Roll and Proof Pressure Test: Each length of tubing shall be subjected to a tube roll and proof pressure test in accordance with AS2078. The flattening gap, rounding gap, and proof pressure values shall be as specified for 3000 psi and higher. The test media shall be air or water.

4.6.2.2 Tensile Strength: The tube shall be subjected to the tensile strength test in accordance with AS2078.

4.6.2.3 Elongation: The tube shall be subjected to the elongation in accordance with AS2078.

4.6.2.4 Specific Gravity of the Tube:

4.6.2.4.1 Apparent Specific Gravity: Apparent specific gravity shall be determined in accordance with AS2078. When test samples are prepared from braided hose, the braid impression must be removed prior to testing

4.6.2.4.2 Relative Specific Gravity: Relative specific gravity shall be determined in accordance with AS2078.

4.6.3 Proof Pressure Test: All hose assemblies shall be pressure tested to the values specified in Table 1 in accordance with AS2078. The test fluid may be either water or hydraulic fluid conforming to MIL-PRF-87257 for test conducted at room temperature. Proof pressure test of hose assemblies having fire sleeves shall be tested before sleeving, when possible, using water as the test media. Proof pressure shall be held for a minimum of 2 min during which time the fire sleeve, if installed, shall be pulled back from the end fittings.

4.6.4 Elongation and Contraction Test: Two hose assemblies of each size shall be subjected to the elongation and contraction test in accordance with AS2078 when subjected to the maximum operating pressure values specified in Table 1.

4.6.5 Volumetric Expansion Test: Two hose assemblies of each size shall be subjected to the volumetric expansion test in accordance with AS2078. The volumetric expansion of the test assemblies shall be in accordance with the values shown in Table 1 for 4000 psi operating pressure and 0.75 times Table 1 for 3000 psi operating pressure.

4.6.6 Leakage Test: Two hose assemblies of each size shall be subjected to the leakage test in accordance with AS2078 except the pressure shall be 66% of the minimum room temperature burst pressure shown in Table 1.

4.6.7 Burst Pressure Tests:

4.6.7.1 Room Temperature Burst Pressure Test: One hose assembly of each size shall be oil aged per 4.5.2.2 with MIL-PRF-83282 hydraulic fluid then subjected to a room temperature burst test in accordance with AS2078. The assembly shall be observed throughout the test and the type of failure and the pressure when failure occurred shall be recorded.

SAE AS1975 Revision C

4.6.7.2 High Temperature Burst Pressure Test: One hose assembly of each size shall be oil aged per 4.5.2.2 with MIL-PRF-83282 hydraulic fluid then subjected to a high temperature burst test in accordance with AS2078 except that the maximum temperature shall be 275 °F. The assembly shall be monitored throughout the test and the type of failure and the pressure when failure occurred shall be recorded.

4.6.8 Thermal Shock Test: The thermal shock test shall be as follows:

- a. Two hose assemblies of each size shall be subjected to this test. One assembly shall be air aged and one assembly shall be unaged. The assemblies shall be subjected to the proof pressure specified in Table 1 for a minimum of 5 min.
- b. The test assemblies shall then be mounted empty in a low and high temperature test fixture (typical setup shown in Figure 2). The ambient temperature shall be reduced to $-65\text{ }^{\circ}\text{F} \pm 2\text{ }^{\circ}\text{F}$ for a minimum of 2 h. At the end of this period, while maintaining this temperature, high temperature test fluid at a temperature of 275 °F shall be quickly introduced at a minimum pressure of 50 psi. Immediately after the hot fluid has filled the assembly, the pressure shall be raised to the proof pressure specified in Table 1 for a minimum of 5 min. Not more than 15 s shall elapse between the introduction of the high temperature fluid at 50 psi and the raising of the pressure to proof pressure.

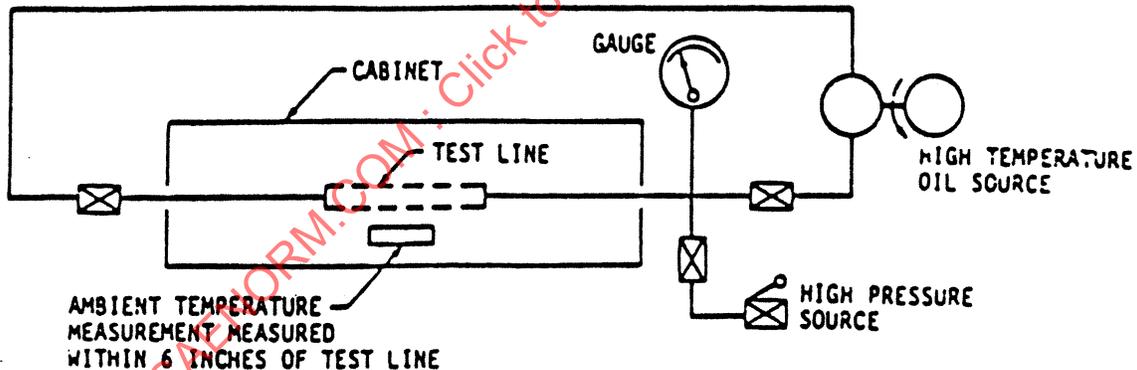


FIGURE 2 - Typical Setup for Thermal Shock Testing

- c. The air aged assembly shall then be filled with MIL-PRF-83282 fluid at a pressure of $75\text{ psi} \pm 24\text{ psi}$ and soaked with ambient and fluid temperature maintained at 275 °F for 1 h. At the end of this period, the assembly shall be pressurized to the proof pressure specified in Table 1 for a minimum of 5 min. The pressure shall then be released and, while still maintaining the 275 °F, the pressure shall then be increased at the same rate of rise as specified in 4.6.7.2 until failure is obtained. The hose assembly pressure shall be under continuous observation during the preceding test, and the pressure when failure occurred and the type of failure shall be recorded.

SAE AS1975 Revision C

4.6.8 (Continued):

- d. The unaged assembly at room temperature will be filled with the test fluid and pressurized to the proof pressure specified in Table 1 for a minimum of 5 min. The pressure shall then be released to "0" psi and then increased at the same rate of rise specified in 4.6.7.1 until failure is obtained. The assembly and the pressure will be under observation during this test and the pressure when failure occurred and the type of failure shall be recorded.
- e. During (b) and the proof portion of (c) and (d) of the test, any evidence of leakage from the hose or fittings, hose burst, fitting blow off, or other evidence of malfunction, shall constitute failure. During the burst portion of (c) and (d), any of the above occurring below the minimum high temperature or room temperature burst pressure value respectively of Table 1 shall constitute failure.

4.6.9 Impulse Test: Impulse testing shall be performed as follows on six straight-to-90° elbow hose assemblies of each pressure and size. If the 3000 psi operating bend radius is used for the 4000 psi operating pressure, then only six assemblies need be tested to cover both pressure ranges. The impulse test equipment shall conform to ARP603 and AIR1228.

- a. Two hose assemblies shall be oil aged per 4.5.2.2, one assembly with MIL-PRF-83282 fluid and one assembly with AS1241 Type IV fluid, two assemblies shall be air aged, and two assemblies shall be unaged. The assemblies shall then be subjected at room temperature to the proof pressure specified in Table 1 for a minimum of 5 min.
- b. The test assemblies shall be connected to rigid supports and bent in a U-shape as illustrated in Figure 3 with a bend radius at the apex of the bend as specified in Table 1 for the 3000 or 4000 psi, as applicable, except that size -20 and larger shall be bent in a 90° shape to reduce fluid volume.
- c. The impulse pattern shall be as specified in ARP603 with peak pressures of $150\% \pm 5\%$ of operating pressure measured at the inlet manifold. Impulse shall occur at a rate of $70 \text{ cpm} \pm 10 \text{ cpm}$. The test fluid shall be MIL-PRF-83282 hydraulic fluid. Fluid temperature shall be maintained at 275 °F for all hose sizes and measured at the test manifold. Ambient temperature shall be 275 °F measured at a point within 6 in from the hose assemblies.