


RATIONALE

AS21447 REV A IS A FIVE YEAR REVIEW AND UPDATE OF THIS SPECIFICATION. FIGURE AND TABLES REFORMATTED, CADMIUM PLATE WARNING ADDED, MATERIALS AND HEAT TREATMENTS CLARIFIED.

REV.
A

AS21447

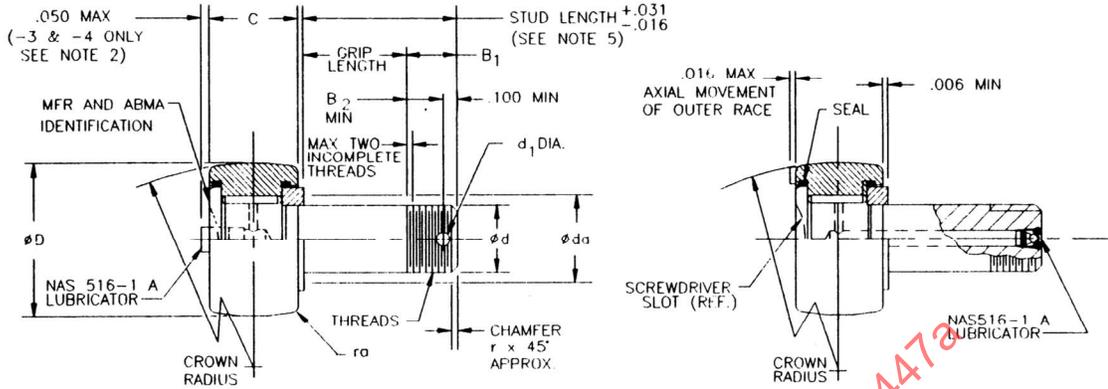

FIRST DASH NO.	Ø d STUD DIA.	Ø D OUTER RING OUTSIDE DIA.	C OUTER RING WIDTH	CROWN RADIUS (REF)	THREAD SIZE UNJF-3A	B ₁ THREAD LENGTH REF.	Ø d _c CLAMPING DIA. MIN.	B ₂ MIN.	Ø d ₁ COTTER PIN HOLE DIA.	r _s RAD MIN.	r	TOTAL RADIAL PLAY MAX.	LIMIT LOAD RATING lb _t	1/ lb-in MAX.	TRACK CAPACITY 40 HRC lb _t	LOAD RATING AS A TRACK ROLLER lb _t	MASS (APPROX) lb
-3	.1900	.5000	.281	10	.1900-32	.344	.297	.211	.070	.022	.031	.0017	700	8	385	395	.014 + (GRIPLENGTH NO. x .0005)
-4	.2500	.6875	.281	10	.2500-28	.344	.359	.224	.076	.022	.031	.0017	940	20	525	470	.031 + (GRIPLENGTH NO. x .0009)
-5	.3125	.7500	.344	10	.3125-24	.359	.422	.234	.076	.022	.047	.0017	1860	42	725	830	.043 + (GRIPLENGTH NO. x .0014)
-6	.3750	.8750	.469	10	.3750-24	.359	.500	.265	.106	.032	.047	.0017	2720	55	1100	1360	.081 + (GRIPLENGTH NO. x .0020)
-7	.4375	1.0000	.531	10	.4375-20	.422	.562	.283	.106	.032	.047	.0017	3860	150	1425	1930	.125 + (GRIPLENGTH NO. x .0026)
-8	.5000	1.1250	.656	10	.5000-20	.422	.625	.314	.106	.046	.047	.0017	6080	205	1975	3040	.190 + (GRIPLENGTH NO. x .0035)


1/ INSTALLATION TORQUE LUBRICATED THREADS.

TABLE 1 - TOLERANCE VALUES

Ø d BASIC STUD DIA.		ALLOWABLE DEVIATION FROM d OF SINGLE MEAN DIA., d _{mp}		ALLOWABLE DEVIATION FROM COTTER PIN DIA., d ₁	
OVER	INCL	HIGH	LOW	HIGH	LOW
.1250	.5000	+0	-.0015	+0.010	-0

Ø D BASIC OUTER RING OUTSIDE DIA.		ALLOWABLE DEVIATION FROM D OF SINGLE MEAN DIA., D _{mp}		ALLOWABLE DEVIATION FROM OUTER RING WIDTH C	
OVER	INCL	HIGH	LOW	HIGH	LOW
.4375	1.1250	+0.0010	-.0005	+0	-.005

THIRD ANGLE PROJECTION



CUSTODIAN: SAE AIRFRAME CONTROL BEARINGS GROUP

PROCUREMENT SPECIFICATION: AS39901

SAE Aerospace
An SAE International Group

AEROSPACE STANDARD

(R) BEARING, ROLLER, NEEDLE, TRACK ROLLER, CROWN RADIUS O.D. INTEGRAL STUD, TYPE VII ANTIFRICTION, INCH

AS21447
SHEET 1 OF 4

REV. A

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user." SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

REQUIREMENTS:

1. MATERIAL:

OUTER RING AND NEEDLES: 52100 STEEL PER AMS 6440, AMS 6444, AMS 6447 OR ASTM A295/A295M.

STUD: 52100 STEEL PER AMS 6440 OR AISI 8620 STEEL PER AMS 6274.

ENDWASHER: 52100 STEEL PER AMS 6440 OR AISI 1010, 1018, 1117 OR 1231 STEEL PER AMS-STD-66.

SEALS: ACETAL RESIN PER ASTM D 6778 POM 111 OR NYLON PER L-P-410, OR PTFE PER AMS 3652, OR PTFE IMPREGNATED FIBERGLASS PER AMS 3666.

2. HEAT TREAT:

OUTER RING: HARDEN AND TEMPER TO 58-62 HRC.

NEEDLES: HARDEN AND TEMPER TO 60-64 HRC.

ENDWASHER: HARDEN AND TEMPER TO 52-56 HRC. AISI 1010, 1018, 1117, OR 1213 HARDENED TO A DEPTH OF .005 MINIMUM WITH A SURFACE HARDNESS OF 51-59 HRC ON THE WEAR SURFACE. REMAINDER MAY BE SOFTENED FOR MANUFACTURING.

STUD (RACEWAY): CARBURIZE WITH A SURFACE HARDNESS OF 60 HRC MINIMUM OR INDUCTION HARDEN TO 60 HRC MINIMUM.

STUD (FLANGE): SURFACE HARDNESS 51 HRC MINIMUM.

STUD (SHANK): HARDEN AND TEMPER TO 36-46 HRC.

3. FINISH OR PLATING:

OUTER RING: CHROME PLATE PER AMS-QQ-C-320, CLASS 2. O.D. AND CORNERS .0004 TO .0010 in THICKNESS. FACES MINIMUM .0003 in THICKNESS.

ENDWASHER: ALL EXPOSED SURFACES ZINC-NICKEL IN ACCORDANCE WITH AMS 2417, TYPE 2, OR CADMIUM PLATED IN ACCORDANCE WITH AMS-QQ-P-416, TYPE I, CLASS 2, WITH A THICKNESS OF .0003 TO .0006 in.

STUD: ALL EXPOSED SURFACES ZINC-NICKEL IN ACCORDANCE WITH AMS 2417, TYPE 2, OR CADMIUM PLATED IN ACCORDANCE WITH AMS-QQ-P-416, TYPE I, CLASS 2, WITH A THICKNESS OF .0003 TO .0006 in.


4. MARKING: THE MARKING SHALL CONSIST OF THE MS PART NUMBER AND THE MANUFACTURERS CAGE CODE MARKED IN ACCORDANCE WITH MIL-STD-130 AND LOT CONTROL NUMBER IF SPACE IS AVAILABLE.

SAE INTERNATIONAL . Click to view the full PDF of AS21447a

 An SAE International Group	AEROSPACE STANDARD	AS21447 SHEET 2 OF 4	REV. A
	(R) BEARING, ROLLER, NEEDLE, TRACK ROLLER, CROWN RADIUS O.D. INTEGRAL STUD, TYPE VII ANTIFRICTION, INCH		

5. PART NUMBER: THE PART NUMBER SHALL CONSIST OF THE MS SPECIFICATION NUMBER FOLLOWED BY A DASH NUMBER TAKEN FROM THE TABLE AND THE APPLICABLE SUFFIXES.

EXAMPLE OF PART NUMBER -

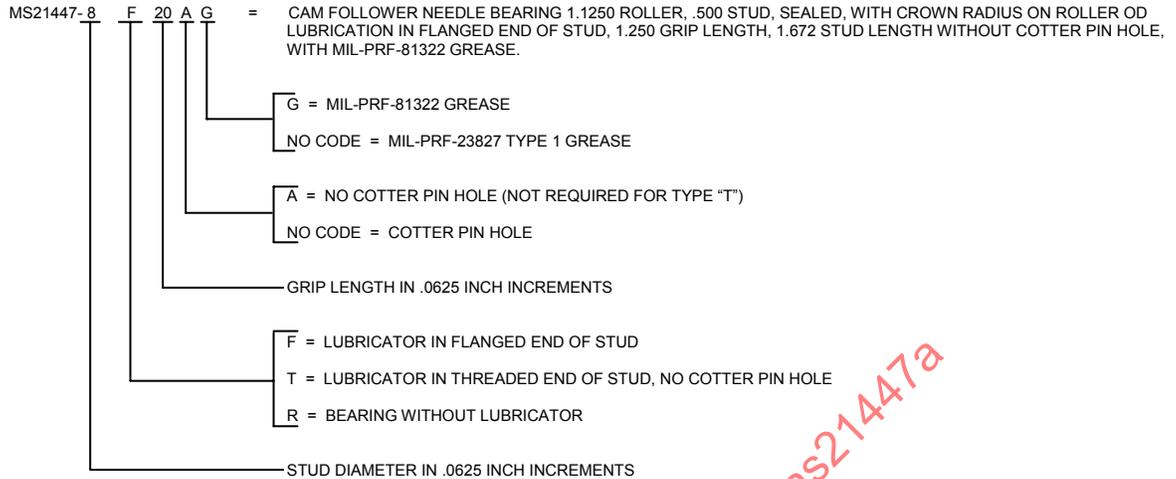

6. LUBRICANT: MIL-PRF-23827 TYPE 1 OR MIL-PRF-81322. ALL BEARINGS SHALL BE PREPACKED WITH GREASE CONFORMING TO MIL-PRF-23827 TYPE 1 UNLESS OTHERWISE SPECIFIED. IF MIL-PRF-81322 IS REQUIRED, ADD THE SUFFIX "G" TO THE MS PART NUMBER.

7. PACKAGING: BEARINGS SHALL BE INDIVIDUALLY PACKAGED TO THE REQUIREMENTS OF MIL-DTL-197. PACKAGE MARKED WITH MANUFACTURER'S NAME OR TRADEMARK, AND DATE OF LUBRICATION BY MONTH AND YEAR AND LOT CONTROL NUMBER.

8. TEMPERATURE:

OPERATING TEMPERATURE RANGE -65 TO 250 °F FOR MIL-PRF-23827 LUBRICATED BEARINGS.

OPERATING TEMPERATURE RANGE -65 TO 350 °F FOR MIL-PRF-81322 LUBRICATED BEARINGS.

NOTES:

NOTICE

THIS DOCUMENT REFERENCES A PART WHICH CONTAINS CADMIUM AS A PLATING MATERIAL. CONSULT LOCAL OFFICIALS IF YOU HAVE QUESTIONS CONCERNING CADMIUM'S USE.

- MS21447-3 MAY BE RELUBRICATED IN THE FLANGED END ONLY. LUBRICATION FITTING FOR THE MS21447-3 MAY BE SHIPPED SEPERATELY AND INSTALLED ON ASSEMBLY. LUBRICATORS INSTALLED IN THE FLANGED END OF STUD ON MS21447-3 AND -4 MAY BE EXTENDED .05 in BEYOND THE FLANGED END THEREBY NECESSITATING AN INCREASE IN "W" OF .05 in, ON ALL OTHER SIZES THE LUBRICATOR SHALL BE FLUSH OR INDENTED.
- THE LIMIT LOAD RATING LISTED CAN BE DEFINED AS THE MAXIMUM LOAD WHICH CAN BE APPLIED TO A BEARING WITHOUT IMPAIRING THE SUBSEQUENT FUNCTIONING OF THE BEARING IN AIRFRAME APPLICATIONS. THE ULTIMATE OR STATIC FRACTURE LOAD RATING IS NOT LESS THAN 1.5 TIMES THE LIMIT LOAD RATING.
- FOR INSPECTION PURPOSES NOMINAL STUD LENGTH IS THE SUM OF NOMINAL GRIP AND THE THREAD LENGTH (B₁ DIMENSION).

 An SAE International Group	AEROSPACE STANDARD	AS21447 SHEET 3 OF 4	REV. A
	(R) BEARING, ROLLER, NEEDLE, TRACK ROLLER, CROWN RADIUS O.D. INTEGRAL STUD, TYPE VII ANTIFRICTION, INCH		