

REV.

SAE AS22759/191

FEDERAL SUPPLY CLASS
6145

RATIONALE


THIS SPECIFICATION HAS BEEN DEVELOPED AT THE REQUEST OF NAVAL AIR SYSTEMS COMMAND AND THE UNITED STATES AIR FORCE. THIS PRODUCT IS BASED ON AS22759/91 WITH ADDITIONAL REQUIREMENTS INCLUDING A SMOOTH OUTER FLUOROPOLYMER SURFACE.

NOTICE

THE REQUIREMENTS FOR ACQUIRING THE PRODUCT DESCRIBED HEREIN SHALL CONSIST OF THIS SPECIFICATION SHEET AND THE ISSUE OF THE FOLLOWING SPECIFICATION LISTED IN THAT ISSUE OF THE DEPARTMENT OF DEFENSE INDEX OF SPECIFICATIONS AND STANDARDS (DODISS) SPECIFIED IN THE SOLICITATION: AS22759

FP / POLYIMIDE / FP TAPE

FP TAPE

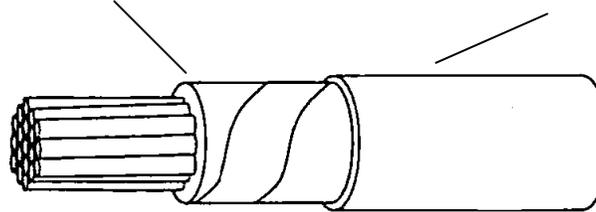

SIZE 26 THROUGH 10

FP – FLUOROCARBON POLYMER MODIFIED POLYTETRAFLUOROETHYLENE (PTFE)
CONDUCTOR – STRANDED SILVER COATED COPPER CONDUCTOR

FIGURE 1. GENERAL CONFIGURATION

TABLE 1. CONSTRUCTION DETAILS

PART NO. 1/	WIRE SIZE	CONDUCTOR				FINISHED WIRE 3/				
		STRANDING (NUMBER OF STRANDS X AWG GAUGE OF STRANDS)	DIAMETER (IN)		RESISTANCE AT 20°C (68°F) (OHMS/ 1000 FT MAX)	DIAMETER (IN)		WEIGHT (LB/1000 FT) 2/		
			MIN	MAX		MIN	MAX	MIN	TARGET	MAX
M22759/191-26-*	26	19 x 38	0.0175	0.0194	38.4	0.030	0.034	1.16	1.31	1.45
M22759/191-24-*	24	19 x 36	0.0225	0.0244	24.3	0.034	0.038	1.70	1.85	2.00
M22759/191-22-*	22	19 x 34	0.0285	0.0304	15.1	0.040	0.043	2.55	2.75	2.96
M22759/191-20-*	20	19 x 32	0.0365	0.0384	9.19	0.048	0.051	4.02	4.26	4.50
M22759/191-18-*	18	19 x 30	0.0455	0.0484	5.79	0.056	0.060	6.16	6.43	6.70
M22759/191-16-*	16	19 x 29	0.0515	0.0554	4.52	0.063	0.067	7.75	8.09	8.40
M22759/191-14-*	14	19 x 27	0.0645	0.0684	2.88	0.076	0.080	12.0	12.5	12.9
M22759/191-12-*	12	37 x 28	0.0835	0.0874	1.90	0.096	0.100	18.4	19.2	19.9
M22759/191-10-*	10	37 x 26	0.106	0.110	1.19	0.119	0.123	28.5	30.0	30.8


1/ PART NUMBER: THE ASTERISKS IN THE PART NUMBER COLUMN OF TABLE 1 SHALL BE REPLACED BY THE COLOR CODE DESIGNATORS IN ACCORDANCE WITH MIL-STD-681. M22759/191-20-93 IS A 20 AWG WHITE WITH ORANGE STRIPE.

2/ THE ACCEPTABLE VALUE FOR THE CPK FOR THE FINISHED WIRE WEIGHT LISTED SHALL BE 1.3, USING A NORMAL (GAUSSIAN) DISTRIBUTION TO OBTAIN THOSE CPK VALUES.

3/ THE WIRE CONSTRUCTION SHALL HAVE A SMOOTH POLYTETRAFLUOROETHYLENE (PTFE) OUTER LAYER WITH COMPLETE BONDING BETWEEN THE HOMOGENEOUS LAYERS.

SAE values your input. To provide feedback
on this Technical Report, please visit
<http://www.sae.org/technical/standards/AS22759/191>

THIRD ANGLE PROJECTION



CUSTODIAN: AE-8 / AE-8D

PROCUREMENT SPECIFICATION:

SAE Aerospace
An SAE International Group

AEROSPACE STANDARD
WIRE, ELECTRICAL,
POLYTETRAFLUOROETHYLENE/POLYIMIDE INSULATED,
SMOOTH SURFACE, LIGHT WEIGHT, SILVER-COATED
COPPER CONDUCTOR, 200 °C, 600 VOLTS

SAE AS22759/191
SHEET 1 OF 5

REV.

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

ISSUED 2010-02

Copyright 2010 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
Fax: 724-776-0790

Tel: +1 724-776-4970 (outside USA)
Email: CustomerService@sae.org

SAE WEB ADDRESS: <http://www.sae.org>

TABLE 2 – WIRE INSULATION MATERIAL 1/

TAPE CODE	THICKNESS (NOM)	MATERIAL
1	0.0012	0.00045 (FP) / 0.00065 (Polyimide) / 0.0001 (FP)
2	0.002	FP (Unsintered)
3	0.0025	FP (Unsintered)

1/ PHYSICAL PROPERTIES OF THE FP UNSINTERED TAPES SHALL BE IN ACCORDANCE WITH AS22759 REQUIREMENTS.

TABLE 3 – PHYSICAL PROPERTIES OF FP/POLYIMIDE /FP TAPES

TENSILE STRENGTH	20,000 LB/IN SQ (AVERAGE MINIMUM)
TENSILE MODULUS	400,000 LB/IN SQ (AVERAGE MINIMUM)
ELONGATION	40 PERCENT (AVERAGE MINIMUM)
DIELECTRIC STRENGTH	4,000 VOLTS/MIL (AVERAGE MINIMUM)
0.00045 FP LAYER	DISTINGUISHABLE COLOR (NEXT TO CONDUCTOR)

TABLE 4 – TAPE OVERLAP REQUIREMENTS 1/

WIRE SIZE	WRAP 1			WRAP 2			NOMINAL WALL THICKNESS (MILS)
	TAPE CODE	PERCENT OVERLAP		TAPE CODE	PERCENT OVERLAP		
		MIN	MAX		MIN	MAX	
26	1	50.5	54.0	2	50.5	54.0	5.8
24	1	50.5	54.0	2	50.5	54.0	5.8
22	1	50.5	54.0	2	50.5	54.0	5.8
20	1	50.5	54.0	2	50.5	54.0	5.8
18	1	50.5	54.0	2	50.5	54.0	5.8
16	1	50.5	54.0	2	50.5	54.0	5.8
14	1	50.5	54.0	2	50.5	54.0	5.8
12	1	50.5	54.0	3	50.5	54.0	6.7
10	1	50.5	54.0	3	50.5	54.0	6.7

1/ WRAP 1 IS THE INNERMOST TAPE WHICH IS IN CONTACT WITH THE CONDUCTOR WITH THE 0.00045 INCH FP SIDE OF THE TAPE AGAINST THE CONDUCTOR.

RATINGS:

TEMPERATURE RATING: 200 °C (392 °F) MAXIMUM CONTINUOUS CONDUCTOR TEMPERATURE.

VOLTAGE RATING: 600 VOLTS (RMS) AT SEA LEVEL.

ADDITIONAL REQUIREMENTS:

DRY ARC PROPAGATION RESISTANCE (TEST REQUIRED FOR INITIAL QUALIFICATION ONLY): TEST IN ACCORDANCE WITH AS4373 METHOD 508. MEASURE THE DAMAGE OF THE BUNDLE ALONG THE AXIS. THE WIRE IS ACCEPTABLE IF THE FOLLOWING ARE MET:

1. A MINIMUM OF 70 WIRES PASS THE DIELECTRIC TEST.
2. TWO WIRES OR LESS FAIL THE DIELECTRIC TEST IN ANY ONE BUNDLE.
3. ACTUAL DAMAGE TO THE WIRE IS NOT MORE THAN 1.0 INCHES IN ANY TEST BUNDLE.

BLOCKING: 200 °C ± 2 °C (392 °F ± 3.6 °F)

COLOR: WHITE IS THE PREFERRED COLOR AND SHALL BE IN ACCORDANCE WITH MIL-STD-104, CLASS 2. COLORS SHALL BE LASER MARKABLE AND MEET THE COLOR LIMITS BELOW. FOR WIRE TESTING ASSOCIATED WITH QUALIFICATION, RETENTION OF QUALIFICATION AND QUALITY CONFORMANCE, CONFORMITY OF COLOR SHALL NOT BE REQUIRED AFTER OVEN EXPOSURE.

 An SAE International Group	AEROSPACE STANDARD	SAE AS22759/191 SHEET 2 OF 5	REV.
	WIRE, ELECTRICAL, POLYTETRAFLUOROETHYLENE/POLYIMIDE INSULATED, SMOOTH SURFACE, LIGHT WEIGHT, SILVER-COATED COPPER CONDUCTOR, 200 °C, 600 VOLTS		

TABLE 5 - MUNSELL COLOR LIMITS FOR UV MARKABLE WIRE

COLOR	HUE		VALUE		CHROMA	
	FROM	TO	From	To	From	To
BLACK	2.5N	2.5N	7	8.5	N/A	N/A
BLUE	5PB	7.5B	7	8	4	6
GREEN	2.5G	7.5G	7	9	2	6
RED	10RP	5R	7	8	4	6
YELLOW	5Y	10Y	8	9	4	6
BROWN	2.5YR	7.5R	7	9	2	4
ORANGE	10R	2.5YR	6	7	8	10
VIOLET	2.5P	7.5R	7	8	4	8
GRAY	SAME AS BLACK		SAME AS BLACK		SAME AS BLACK	

COLOR STRIPING OR BAND DURABILITY: 125 CYCLES (250 STROKES), 250 GRAM WEIGHT

CONDUCTOR STRAND ADHESION: REQUIRED

CONTINUOUS LENGTHS: SCHEDULE B

DYNAMIC CUT-THROUGH (TEST REQUIRED FOR INITIAL QUALIFICATION ONLY): BLADE SHALL BE STANDARD CUTTING BLADE EXCEPT THE CUTTING EDGE RADIUS SHALL BE 0.005 INCH ± 0.001 INCH. MINIMUM AVERAGE DYNAMIC CUT-THROUGH (LB) SHALL BE AS FOLLOWS:

WIRE SIZE	23°C ± 5°C	150°C ± 5°C	200°C ± 5°C
26	10 LB	8 LB	6 LB
20	25 LB	20 LB	15 LB
16	20 LB	15 LB	15 LB

FLAMMABILITY: TEST IN ACCORDANCE WITH AS4373, METHOD 801.

REQUIREMENTS:

DURATION AFTER-FLAME 3.0 SECONDS (MAXIMUM)
 FLAME TRAVEL 3.0 INCHES (MAXIMUM)
 NO FLAMING OF TISSUE

FORCED HYDROLYSIS: (TEST REQUIRED FOR INITIAL QUALIFICATION ONLY) 5000 HOURS AT 70 °C. TEST 5 UNCONDITIONED AND 5 CONDITIONED SAMPLES OF 20 AWG WIRE.

HIGH FREQUENCY SPARK TEST: (WHEN USED IN LIEU OF THE IMPULSE DIELECTRIC TEST) 5.7 KILOVOLTS (RMS). TEST 100 PERCENT OF THE WIRE.

HUMIDITY RESISTANCE: REQUIRED. AFTER HUMIDITY EXPOSURE, THE WIRE SHALL MEET THE REQUIREMENTS FOR INITIAL INSULATION RESISTANCE.

IDENTIFICATION OF PRODUCT: NOT REQUIRED FOR SIZE 26. COLOR CODE DESIGNATOR NOT REQUIRED.

IDENTIFICATION DURABILITY: 125 CYCLES (250 STROKES) 250 GRAM WEIGHT.

IMMERSION: (TEST REQUIRED FOR INTITAL QUALIFICATION ONLY) TEST IN ACCORDANCE WITH AS4373, METHOD 601. USE MANDRELS AND WEIGHTS LISTED IN TABLE 6 FOR BEND TESTING. DIELECTRIC TEST, 2500 VOLTS (RMS), 60 HZ. FOR TURBINE FUEL IMMERSION TEST OF AS4373, EITHER JP-4 OR MIL-DTL-83133 TYPE JP-8 (NATO TYPE F-34) MAY BE USED.

IMPULSE DIELECTRIC TEST: 8.0 KILOVOLTS (PEAK). TEST 100 PERCENT OF THE WIRE

INSULATION RESISTANCE: 5000 MEGOHMS PER 1000 FEET (MINIMUM)

INSULATION STATE OF SINTER: (QUALIFICATION AND QUALITY CONFORMANCE INSPECTION PERFORMED ON ONE SAMPLE PER LOT) EVALUATE FLUOROPOLYMER LAYERS ONLY. THE DIFFERENCE IN ENERGY TO MELT BETWEEN FIRST AND SECOND HEATS SHALL BE LESS THAN OR EQUAL TO 3 JOULES PER GRAM.

 An SAE International Group	AEROSPACE STANDARD	SAE AS22759/191 SHEET 3 OF 5	REV.
	WIRE, ELECTRICAL, POLYTETRAFLUOROETHYLENE/POLYIMIDE INSULATED, SMOOTH SURFACE, LIGHT WEIGHT, SILVER- COATED COPPER CONDUCTOR, 200 °C, 600 VOLTS		

INSULATION STRIP FORCE: (QUALIFICATION AND GROUP II QUALITY CONFORMANCE TEST) TEST WIRE SIZES 26 THROUGH 14 ONLY. THE LENGTH OF THE INSULATION SLUG SHALL BE 0.25 INCHES. STRIP FORCE (LB) SHALL BE AS FOLLOWS. NO EVIDENCE OF INSULATION SHALL BE LEFT ON THE CONDUCTOR WHEN VIEWED WITH THE UNAIDED EYE.

WIRE SIZE	MIN FORCE	MAX FORCE
26-20	0.25 LB	6.0 LB
18-14	0.5 LB	7.0 LB

LAMINATION SEALING: (QUALIFICATION AND GROUP II QUALITY CONFORMANCE TEST) WHEN TESTED IN ACCORDANCE WITH AS4373, METHOD 809 AT 260 °C ± 2 °C (500 °F ± 3.6 °F) FOR 6 HOURS, THERE SHALL BE NO EVIDENCE OF TAPE SEPARATION OR LIFTING. THREE SAMPLES PER LOT SHALL BE TESTED.

LIFE CYCLE: 500 HOURS AT 230 °C ± 2 °C (446 °F ± 3.6 °F). DIELECTRIC TEST, 2500 VOLTS (RMS), 60 HZ. USE MANDRELS COATED WITH POLYTETRAFLUOROETHYLENE SUCH THAT THE DIAMETER OF THE MANDRELS, AFTER COATING, STILL CONFORM TO THE REQUIRED TEST MANDRELS DIAMETERS OF TABLE 6. AFTER OVEN EXPOSURE, LAYERS SHALL NOT SEPARATE AND OR TAPES SHALL NOT LIFT ALONG THE INSULATION OR AT THE ENDS.

LOW TEMPERATURE (COLD BEND): USE MANDRELS AND WEIGHTS SPECIFIED IN TABLE 6. CHAMBER TEMPERATURE, -65 °C ± 2 °C (-85 °F ± 3.6 °F). DIELECTRIC TEST, 2500 VOLTS (RMS), 60 HZ.

OUTER INSULATION LAYER SURFACE SMOOTHNESS: (QUALIFICATION AND GROUP II QUALITY CONFORMANCE TEST) WHEN TESTED IN ACCORDANCE WITH AS4373, METHOD 110, THE DIFFERENCE IN WALL THICKNESS OF THE OUTER PTFE INSULATION LAYER AT THE DISCERNABLE TAPE EDGE SHALL NOT EXCEED 10.0 PERCENT.

SCRAPE ABRASION (NEEDLE): (INITIAL QUALIFICATION AND RETENTION OF QUALIFICATION) WIRE SIZE 20 ONLY. WHEN TESTED IN ACCORDANCE WITH AS4373, METHOD 301, THE AVERAGE CYCLES TO FAILURE ON 8 READINGS, AFTER DROPPING THE HIGHEST AND LOWEST VALUE OF THE 10 READINGS TESTED, SHALL NOT BE LESS THAN THE VALUES LISTED BELOW WHEN APPLYING A 1.10 LB ± 0.01 LB LOAD.

TEMPERATURE (°C (°F))	CYCLES TO FAILURE (MIN)
21-25 (67-77)	2000
68-72 (153-163)	1000
148-152 (297-307)	350

SHRINKAGE: TEST AT 230 °C ± 2 °C (446 °F ± 3.6 °F). MAXIMUM CHANGE IN MEASUREMENT, 0.091 INCH.

SMOKE: 200 °C ± 5 °C (392 °F ± 9 °F); NO VISIBLE SMOKE.

SOLDERABILITY: REQUIRED.

STRIPPABILITY: (QUALIFICATION AND GROUP II QUALITY CONFORMANCE TEST) AFTER STRIPPING, NO FRAGMENTS OF ANY LAYER SHALL EXTEND MORE THAN 0.031 INCHES BEYOND THE END OF THE POLYIMIDE TAPE LAYER.

TAPE OVERLAP: TEST IN ACCORDANCE WITH AS4373, METHOD 109.

TENSILE MODULUS: TEST COMPOSITE FILM IN ACCORDANCE WITH ASTM D 882, METHOD A.

THERMAL INDEX: (TEST REQUIRED FOR INITIAL QUALIFICATION ONLY). TEST WIRE SIZE 20 ONLY, 200 °C (392 °F) MINIMUM FOR 10 000 HOURS.

THERMAL SHOCK RESISTANCE: OVEN TEMPERATURE, 200 °C ± 2 °C (392 °F ± 3.6 °F). MAXIMUM CHANGE IN MEASUREMENT, 0.091 INCH, NO CRACKING.

UV LASER MARKING: (QUALIFICATION AND GROUP I QUALITY CONFORMANCE TEST) APPLICABLE TO WHITE INSULATION ONLY. TEST IN ACCORDANCE WITH AS4373, METHOD 1001. CONTRAST SHALL BE A 62 PERCENT MINIMUM AVERAGE ON SIX READINGS.

UV LASER CONTRAST AFTER THERMAL AGING: (INITIAL QUALIFICATION AND RETENTION OF QUALIFICATION) WIRE SIZE 20 ONLY. PREPARE SAMPLE IN ACCORDANCE WITH AS4373 METHOD 1001. PLACE SAMPLE IN AN AIR CIRCULATING OVEN AT 230 °C ± 2 °C (446 °F ± 3.6 °F) FOR 168 HOURS. MINIMUM AVERAGE CONTRAST AFTER AGING SHALL NOT BE LESS THAN 40 PERCENT.

 An SAE International Group	AEROSPACE STANDARD	SAE AS22759/191 SHEET 4 OF 5	REV.
	WIRE, ELECTRICAL, POLYTETRAFLUOROETHYLENE/POLYIMIDE INSULATED, SMOOTH SURFACE, LIGHT WEIGHT, SILVER-COATED COPPER CONDUCTOR, 200 °C, 600 VOLTS		