

SAE-AS27642

ADOPTION NOTICE

SAE-AS27642, "Bearings, Ball, Airframe, Extra Light Duty," was adopted on 23 July 1998, for use by the Department of Defense (DoD). Proposed changes by DoD activities must be submitted to the DoD Adopting Activity: Commander, Naval Air Warfare Center Aircraft Division, Code 414100B120-3, Highway 547, Lakehurst, NJ 08733-5100. DoD activities may obtain copies of this standard from the Standardization Document Order Desk, 700 Robbins Avenue, Building 4D, Philadelphia, PA 19111-5094. The private sector and other government agencies may purchase copies from SAE, 400 Commonwealth Drive, Warrendale, PA 15096-0001.

SAE-AS27642 should be used instead of MS27642G, which was canceled on 23 July 1998.

Custodians:

Army - AV
Navy - AS
Air Force - 99

Adopting Activity
Navy - AS
(Project 3110-1086)

Review Activities:

Army - AR, AT, MI
Navy - SH
Air Force - 84
DLA - GS

AMSC N/A

FSC 3110

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Submitted for recognition as an American National Standard

Form Approved
OMB No. 0704-0188

AS27642

NOTICE

THIS DOCUMENT HAS BEEN TAKEN DIRECTLY FROM U.S. MILITARY SPECIFICATION MS27642F AND CONTAINS ONLY MINOR EDITORIAL AND FORMAT CHANGES REQUIRED TO BRING IT INTO CONFORMANCE WITH THE PUBLISHING REQUIREMENTS OF SAE TECHNICAL STANDARDS. THE INITIAL RELEASE OF THIS DOCUMENT IS INTENDED TO REPLACE MS27642F. ANY PART NUMBERS ESTABLISHED BY THE ORIGINAL SPECIFICATION REMAIN UNCHANGED.

THE ORIGINAL MILITARY SPECIFICATION WAS ADOPTED AS AN SAE STANDARD UNDER THE PROVISIONS OF THE SAE TECHNICAL STANDARDS BOARD (TSB) RULES AND REGULATIONS (TSB 001) PERTAINING TO ACCELERATED ADOPTION OF GOVERNMENT SPECIFICATIONS AND STANDARDS. TSB RULES PROVIDE FOR (A) THE PUBLICATION OF PORTIONS OF UNREVISED GOVERNMENT SPECIFICATIONS AND STANDARDS WITHOUT CONSENSUS VOTING AT THE SAE COMMITTEE LEVEL, AND (B) THE USE OF THE EXISTING GOVERNMENT SPECIFICATION OR STANDARD FORMAT.

ANY MATERIAL RELATING TO QUALIFIED PRODUCT LISTS HAS NOT BEEN ADOPTED BY SAE. THIS MATERIAL WAS PART OF THE ORIGINAL MILITARY SPECIFICATION AND IS REPRINTED HERE FOR HISTORIC REFERENCE ONLY.

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user." SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

SAENORM.COM : Click to view the full PDF of as27642

ISSUED 1998-04

PREPARED BY AIRFRAME CONTROL BEARINGS GROUP (ACBG)



AEROSPACE STANDARD

BEARING, BALL, AIRFRAME,
EXTRA LIGHT DUTY

AS27642
SHEET 1 OF 4

Copyright 1998 Society of Automotive Engineers, Inc.
All rights reserved.

Printed in the U.S.A.

QUESTIONS REGARDING THIS DOCUMENT: (724) 772-8510
TO PLACE A DOCUMENT ORDER: (724) 776-4970

FAX: (724) 776-0243
Distributed under license from the IHS Archive

SAE WEB ADDRESS: <http://www.sae.org>

AS27642

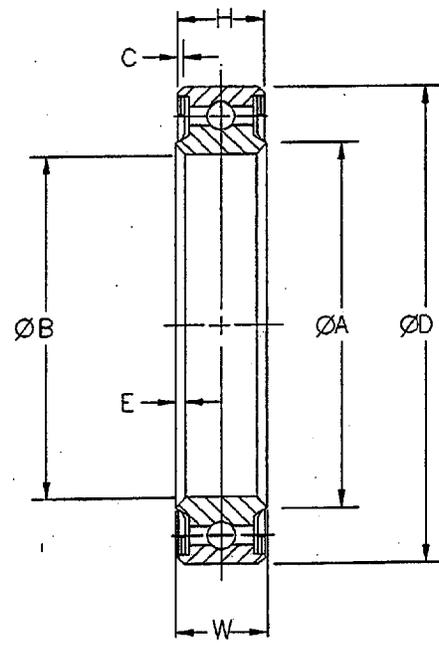


TABLE I. BEARING DIMENSIONS AND MAXIMUM TORQUE

MS DASH NO.	øB 3/	BORE TOLERANCE		øD 2/ 3/	W 2/	H 2/	øA SHOULDER DIAMETER INNER RING (APPROX)	E AND C 4/ 5/		RADIAL CLEARANCE		WEIGHT POUNDS (APPROX)	MAXIMUM STARTING TORQUE (INCH-OZ)	
		WITHOUT SUFFIX S	WITH SUFFIX S					INNER & OUTER RING CORNER CHAMFER X 45°		WITHOUT SUFFIX S	WITH SUFFIX S			
		+0.000 -0.0010	+0.000 -0.005											
-16	1.0000	+0.0000	-0.0005	1.7500	.437	.375	1.141	.024		.0003 TO .0010			.14	5
-21	1.3130			2.0625			1.454						.16	7
-23	1.4380			2.1875			1.575						.17	8
-25	1.5630			2.3125			1.693						.19	9
-29	1.8130			2.5625			1.931						.21	12
-33	2.0630			2.8125			2.231						.23	14
-37	2.3130			3.0625			2.468						.26	17
-47	2.9380	+0.0000	-0.0010	3.8750	.531	.469	3.093	.0001 TO .0005					.49	24
-49	3.0630			4.0000			3.222						.53	25
-52	3.2500			4.1875			3.479						.55	26
-56	3.5000			4.4375			3.775						.58	28
-60	3.7500			4.6875			4.014						.61	28
-64	4.0000			4.9375			4.253						.64	
-68	4.2500			5.3125			4.517						.73	
-72	4.5000			5.5625			4.774						.76	
-76	4.7500			5.8125			5.046						1.00	
-80	5.0000			6.0625			5.246						1.04	1/
-84	5.2500	6.3125	5.506	1.09										
-88	5.5000	6.5625	5.770	1.14										
-92	5.7500	6.8125	6.033	1.18										
-96	6.0000	7.0625	6.303	1.23										

1/ TORQUE VALUES FOR THESE SIZE BEARINGS SHALL BE SPECIFIED IN PURCHASE ORDERS.
 2/ ALL DIMENSIONS TO BE MET AFTER PLATING.
 3/ OUT-OF-ROUND TOLERANCES: BORE: -16 THRU -49 +.0003, -.0013, -52 THRU -96 +.0005, -.0015.
 OUTER DIAMETER: +.0010, -.0021
 4/ A RADIUS GIVING APPROXIMATELY THE SAME GRIP FOR STAKING THE BEARING IN THE HOUSING WILL BE ACCEPTABLE.
 5/ A RADIUS GIVING APPROXIMATELY THE SAME FILLET CLEARANCE WILL BE ACCEPTABLE.

(F) DENOTES CHANGES

SAE The Engineering Society
 For Advancing Mobility
 Land Sea Air and Space
INTERNATIONAL
 400 Commonwealth Drive, Warrendale, PA 15096-0001

AEROSPACE STANDARD
 BEARING, BALL, AIRFRAME,
 EXTRA LIGHT DUTY

AS27642
 SHEET 2 OF 4

AS27642

TABLE II. BEARING ECCENTRICITIES AND LOADS

MS DASH NO.	ECCENTRICITIES				RADIAL LIMIT LOAD RATING LBS.	THRUST LIMIT LOAD RATING LBS.	RADIAL LOAD RATING (LBS.) FOR AVERAGE LIFE OF 10,000 COMPLETE 90° CYCLES	
	RADIAL		LATERAL				1/	2/
	INNER	OUTER	INNER	OUTER			CASE I	CASE II
-16					8085	3600	4260	3960
-21					9840	4400	4590	4290
-23					10500	4700	4650	4360
-25					11300	5000	4680	4420
-29	.0010	.0016	.0010	.0016	12700	5600	4760	4530
-33					14400	6400	4820	4630
-37					15800	7000	4880	4690
-47					24700	10900	6600	6390
-49					27500	12100	8150	7840
-52					28700	12600	8210	7880
-56					31200	13700	8240	7970
-60	.0012	.0016	.0010	.0016	33100	14600	8290	8010
-64					35000	15400	8350	8100
-68					41900	18400	10280	9900
-72					44300	19500	10330	10000
-76					46700	20500	10350	10050
-80					48200	21200	10360	10090
-84	.0014	.0018	.0012	.0018	50600	22300	10420	10120
-88					53000	23300	10480	10200
-92					55400	24400	10550	10240
-96	.0014	.0020	.0016	.0020	57700	25400	10520	10210

1/ CASE 1 = LOAD FIXED WITH RESPECT TO OUTER RING

CASE 2 = LOAD FIXED WITH RESPECT TO INNER RING

2/ THESE RATINGS ARE FOR OPERATIONS UP TO 250°F, FOR OPERATIONS UP TO 350°F, THE RATINGS SHALL BE REDUCED BY 20%.

REQUIREMENTS:

1. MATERIAL: RINGS: 52100 STEEL PER AMS6440, OR E52100 STEEL PER FED-STD-66.
 BALLS: 52100 STEEL PER AMS6440 OR 51100 STEEL PER AMS6449, OR E51100 OR E52100 STEEL PER FED-STD-66.
 SEALS: POLYTETRAFLUOROETHYLENE PER AMS3652 OR POLYTETRAFLUOROETHYLENE SHEET, GLASS FABRIC REINFORCED PER AMS3666.
 SEAL RETAINERS: ANY CORROSION RESISTANT STEEL.
2. LUBRICANT: MIL-G-81322 OR MIL-G-23827. ALL BEARINGS SHALL BE PACKED WITH GREASE CONFORMING TO MIL-G-81322 UNLESS OTHERWISE SPECIFIED. IF MIL-G-23827 IS REQUIRED, ADD THE LETTER "G" AFTER THE MS27642 DASH NUMBER. MIL-G-23827 SHALL NOT BE USED FOR OPERATION WHERE TEMPERATURES EXCEED 250°F.
3. HARDNESS: HEAT TREAT RINGS AND BALLS TO ROCKWELL "C" 60 TO 66 AND STABILIZE FOR OPERATION AT 250°F.
4. SURFACE ROUGHNESS: RACEWAYS AND BALLS SHALL BE 8 MICROINCHES Ra PER ANSI/ASME B46.1.
5. PLATING: ALL EXTERNAL SURFACES EXCEPT BORE, SEALS AND SEAL RETAINERS SHALL BE ZINC-NICKEL IN ACCORDANCE WITH AMS 2417, TYPE 2, OR CADMIUM PLATED IN ACCORDANCE WITH QQ-P-416, TYPE I, CLASS 2, WITH A THICKNESS OF .0003 TO .0006 INCHES.