

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user." SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

REV. B

AS3563

FEDERAL SUPPLY CLASS
5310


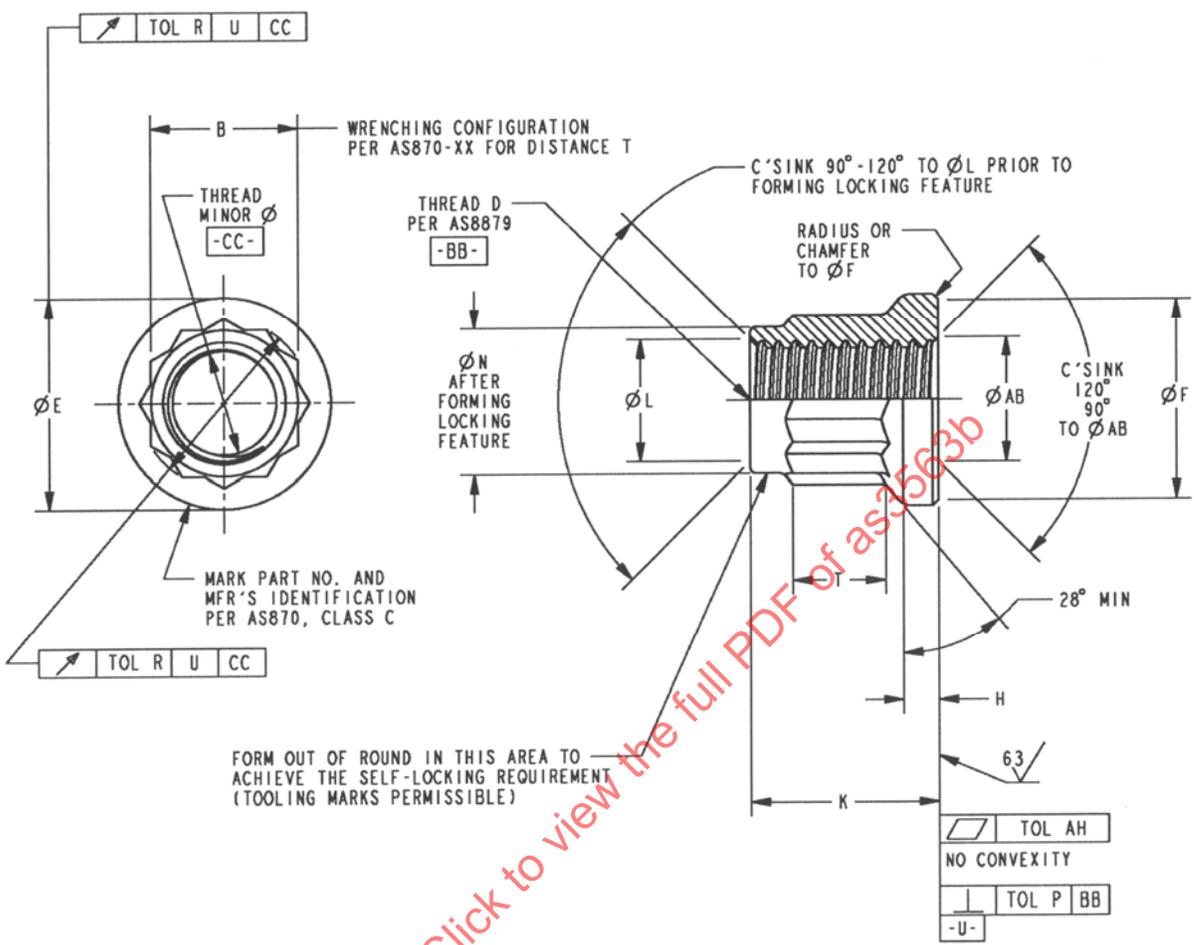


FIGURE 1

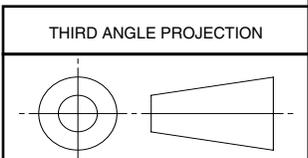

CUSTODIAN: SAE E-25

SAE Aerospace
An SAE International Group

AEROSPACE STANDARD

NUT, SELF-LOCKING, DOUBLE HEXAGON, SOLID
FILM LUBRICATED, EXTENDED WRENCH PAD,
160 KSI, 800 °F, UNS S66286

AS3563
SHEET 1 OF 3

REV. B

ISSUED 1995-10 REVISED 2004-06

REV.
B

AS3563

TABLE 1A

PART NUMBER	THREAD D	B NOM	DASH NO.	ØE MAX	ØF MIN	ØAB	H MIN	K MAX
AS3563-09	.1900-32UNJF-3B	.2500	08	.340	.325	.190-.220	.045	.305
AS3563-10	.2500-28UNJF-3B	.3125	10	.450	.410	.250-.280	.045	.400
AS3563-11	.3125-24UNJF-3B	.3750	12	.525	.495	.312-.342	.060	.455
AS3563-12	.3750-24UNJF-3B	.4375	14	.600	.560	.375-.405	.070	.520
AS3563-13	.4375-20UNJF-3B	.5625	18	.690	.650	.438-.468	.080	.595
AS3563-14	.5000-20UNJF-3B	.6250	20	.780	.740	.500-.532	.100	.680
AS3563-15	.5625-18UNJF-3B	.6875	22	.880	.840	.562-.597	.110	.758
AS3563-16	.6250-18UNJF-3B	.7812	25	.970	.925	.625-.660	.120	.850
AS3563-17	.7500-16UNJF-3B	.9375	30	1.230	1.180	.750-.785	.130	1.032

TABLE 1B

PART NUMBER	ØL	ØN MAX	T MIN	P	R	AH	APPROX MASS LB/100
AS3563-09	.190-.210	.262	.082	.004	.006	.0014	.28
AS3563-10	.250-.270	.326	.130	.005	.007	.0014	.51
AS3563-11	.312-.332	.392	.170	.005	.008	.0016	.83
AS3563-12	.375-.395	.458	.210	.005	.009	.0016	1.34
AS3563-13	.438-.458	.588	.230	.005	.010	.0020	2.74
AS3563-14	.500-.520	.654	.260	.006	.012	.0020	3.34
AS3563-15	.562-.582	.720	.320	.006	.014	.0020	4.92
AS3563-16	.625-.645	.817	.370	.007	.015	.0020	7.12
AS3563-17	.750-.770	.980	.500	.007	.016	.0020	13.01

NOTES:

- MATERIAL: CORROSION AND HEAT RESISTANT STEEL PER AMS 5731 OR AMS 5734 (UNS S66286).
HEAT TREATMENT: AFTER FORMING, NUTS SHALL BE HEAT TREATED PER AMS 2759/3 TO MEET THE HARDNESS SPECIFIED IN NOTE 3.
- PROCUREMENT SPECIFICATION: AS4393 EXCEPT AS FOLLOWS:
 - COATING: SOLID FILM LUBRICANT PER AS1701, TYPE VI, IN LIEU OF SILVER PLATE PER AMS 2411.
 - PRETREATMENT: PRIOR TO APPLYING THE SOLID FILM LUBRICANT, NUTS MAY BE PLATED WITH COPPER (AMS 2418) OR NICKEL (AMS 2403) TO .0001 MAXIMUM THICKNESS.
 - DIMENSIONS APPLY AFTER PRETREATMENT PLATING AND BEFORE COATING WITH SOLID FILM LUBRICANT.
 - BAKE AT 800 °F ± 15 °F IN LIEU OF 1200 °F FOR NUTS TESTED AFTER BAKE.
- HARDNESS: 32-42 HRC.
- BREAK SHARP EDGES .003 TO .015, UNLESS OTHERWISE SPECIFIED.



SAE Aerospace
An SAE International Group

AEROSPACE STANDARD

NUT, SELF-LOCKING, DOUBLE HEXAGON, SOLID FILM LUBRICATED, EXTENDED WRENCH PAD, 160 KSI, 800 °F, UNS S66286

AS3563
SHEET 2 OF 3

REV.
B