

Issued 1992-02
Revised 2003-01

Superseding AS4468A

(R) Hose Assembly, 125 psi,
Lined Silicone, Potable Water, Procurement Specification

1. SCOPE:

This SAE Aerospace Standard (AS) covers the requirements for a flexible, lightweight, low pressure, self-extinguishing, silicone hose assembly. The hose has a fully fluorinated fluoropolymer inner liner and is primarily intended for use in aircraft potable water systems.

2. REFERENCES:

2.1 Applicable Documents:

The following publications form a part of this document to the extent specified herein. The latest issue of SAE publications shall apply. The applicable issue of other publications shall be the issue in effect on the date of the purchase order. In the event of conflict between the text of this document and references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

2.1.1 SAE Publications: Available from SAE, 400 Commonwealth Drive, Warrendale, PA 15096-0001.

| | |
|----------|---|
| AMS 2472 | Anodic Treatment of Aluminum Alloys Sulfuric Acid Process, Dyed Coating |
| AMS 4124 | Aluminum Alloy, Rolled or Cold Finished Bars, Rods, and Wire - 5.6Zn - 2.5Mg - 1.6Cu - 0.23Cr (7075-T7351) - Solution Heat Treated, Stress Relieved by Stretching, and Overaged |
| AMS 4771 | Brazing Filler Metal, Silver, 50 Ag 16 Cd 15.5 Zn 15.5 Cu 3.0 Ni (BAg-3) (1170° - 1270 °F) |
| AMS 4772 | Brazing Filler Metal, Silver, 54 Ag 40 Cu 5.0 Zn 1.0 Ni (BAg-13) (1325° - 1575 °F) |
| AMS 4777 | Brazing Filler Metal - Nickel Alloy, 82 Ni - 4.5 Si - 7.0 Cr - 3.1B - 3.0 Fe |
| AMS 4778 | Brazing Filler Metal, Nickel, 92 Ni - 4.5 Si - 3.1 B (BNi-3) |
| AMS 5556 | Tubing, Seamless or Welded, Hydraulic - 18 Cr - 11Ni - 0.70 (Cb + Ta), Solution Heat Treated (30347) |

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

Copyright 2003 Society of Automotive Engineers, Inc.

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
Tel: 724-776-4970 (outside USA)
Fax: 724-776-0790
Email: custsvc@sae.org
SAE WEB ADDRESS: <http://www.sae.org>

SAE AS4468 Revision B

2.1.1 (Continued):

| | |
|--------------|---|
| AMS 5557 | Tubing, Seamless or Welded, Hydraulic - 18 Cr - 11 Ni - Ti Solution Heat Treated (30321) |
| AMS 5567 | Tubing, Seamless or Welded, 19 Cr - 10 Ni, Hydraulic, Solution Heat Treated (30304) |
| AMS 5570 | Tubing, Seamless, 18 Cr - 11 Ni - 0.40 Ti, Solution Heat Treated (30321) |
| AMS 5571 | Tubing, Seamless - 18 Cr - 11 Ni - 0.70 (Cb + Ta) Solution Heat Treated (30347) |
| AMS 5575 | Tubing, Welded - 18 Cr - 10.5 Ni - 0.70 (Cb + Ta), Solution Heat Treated (30347) |
| AMS 5636 | Bars - 18 Cr - 9 Ni, Cold Drawn, 100,000 TS (30302) |
| AMS 5637 | Bars - 18 Cr - 9 Ni, Cold Drawn, 125,000 TS (30302) |
| AMS 5639 | Bars, Forgings, Tubing, and Rings, 19 Cr - 10 Ni, Solution Heat Treated (30304) |
| AMS 5640 | Bars, Wire, and Forgings, Free Machining 19 Cr 9 Ni |
| AMS 5645 | Bars, Forgings, Tubings, and Rings - 18 Cr - 10Ni - 0.40 Ti, Solution Heat Treated (30321) |
| AMS 5646 | Bars, Forgings, Tubing, and Rings - 18 Cr - 11 Ni - 0.60 (Cb + Ta), Solution Heat Treated (30347) |
| AMS 5647 | Steel Bars, Forgings, Tubing and Rings, Corrosion Resistant - 19 Cr - 9.5 Ni (SAE 304L) Solution Heat Treated |
| AMS 5648 | Bars, Forgings, Tubing, and Rings - 17 Cr - 12 Ni - 2.5 Mo (30316) |
| AMS 5688 | Wire - 18 Cr - 9.0 Ni - Spring Temper (30302) |
| AMS 5689 | Wire - 18 Cr - 9.5 Ni - 0.40 Ti (30321), Solution Heat Treated |
| AMS 5690 | Wire - 17 Cr - 12 Ni - 2.5 Mo, Solution Heat Treated (30316) |
| AMS 5697 | Wire - 19 Cr - 9.5 Ni (30304) |
| AMS-QQ-P-35 | Passivation Treatments for Corrosion Resisting Steel |
| AMS-QQ-A-225 | Aluminum and Aluminum Alloy Bar, Rod, Wire, or Special Shapes, Rolled, Drawn or Cold Finished General Specification For |
| AMS-QQ-S-763 | Steel Bars, Wire, Shapes, and Forgings, Corrosion Resisting |
| AMS-STD-2219 | Fusion Welding for Aerospace Applications |
| AS611 | Hose Assembly and Tubing, Polytetrafluoroethylene, Cleaning Methods |
| ARP908 | Hose Fitting - Installation and Qualification Test Torque Requirements |
| AS1073 | Sleeve, Hose Assembly, Heat Shrinkable |
| AS1472 | Hose Assembly, Low Pressure, Flareless, Potable Water |
| AS1650 | Coupling Assembly, Threadless, Flexible, Fixed Cavity |
| AS1656 | Fitting End Threadless Coupling - Ferrule or Sleeve, Design Standard |
| AS1791 | Wire, Retainer, Tube Coupling Nut |
| AS4330 | Tubing End, Standard Dimensions for |
| AS4370 | Nut, Fitting, Retained |
| AS4375 | Fitting End, External Thread, Flareless, Design Standard |
| AS4395 | Fitting End, Flared Tube Connection, Design Standard |
| AS5272 | Lubricant, Solid Film, Heat Cured, Corrosion Inhibiting, Procurement Specification |

SAE AS4468 Revision B

2.1.1 (Continued):

| | |
|---------|---|
| AS7003 | National Aerospace and Defense Contractors Accreditation Program (NADCAP) |
| AS7112 | National Aerospace and Defense Contractors Accreditation Program Requirements for Fluid System Components |
| AS8879 | Screw Threads, Controlled Radius With Minor Diameter, General Specification For |
| AS21921 | Nut, Sleeve, Coupling, Flareless |

2.1.2 U.S. Government Publications: Available from DODSSP, Subscription Services Desk, Building 4D, 700 Robbins Avenue, Philadelphia, PA 19111-5094.

| | |
|-------------|---|
| MIL-A-8625 | Anodic Coating for Aluminum and Aluminum Alloys |
| MIL-STD-129 | Military Marking |
| MIL-STD-810 | Environmental Test Methods |

2.1.3 ASTM Publications: Available from ASTM, 100 Barr Harbor Drive, West Conshohocken, PA 19428-2959.

| | |
|-------------------|--|
| ASTM A 313/A 313M | Standard Specification for Stainless Steel Spring Wire |
| ASTM D 570 | Standard Method of Test for Water Absorption of Plastics |
| ASTM A 580/A 580M | Stainless and Heat-Resisting Steel Wire, Condition A |
| ASTM A 582/A 582M | Specification for Free Machining Stainless and Heat Resistant Steel Bars, Hot Rolled and Cold Finished |
| ASTM E 1417 | Inspection, Penetrant Method of |

2.1.4 NAS Publications: Available from Aerospace Industries Association, 1250 Eye Street NW, Washington, DC 20005.

| | |
|---------|--|
| NAS847 | Caps and Plugs, Protective, Dust and Moisture Seal |
| NAS1760 | Fitting End, Flareless Acorn, Standard Dimension for |

2.1.5 AWS Publications: Available from American Welding Society, 550 NW 42nd Street, Miami, FL 33126-5671.

| | |
|------------------|---|
| AWS A5.9 | Rods and Wire, Welding, Corrosion and Heat Resistant Alloys |
| AWS A5.14/A5.14M | Rods and Wire, Welding, Corrosion Resistant Alloys |
| AWS C3.6 | Specification for Furnace Brazing |

2.1.6 PRI Publications: Available from Performance Review Institute, 161 Thornhill Road, Warrendale, PA 15086-7527.

| | |
|--------|--|
| PD2001 | Qualified Product Management Council Procedures for Qualified Products Group |
| PD2101 | Aerospace Quality Assurance, Product Standard, Qualification Procedures, Fluid Systems |

SAE AS4468 Revision B

2.1.7 Public Health Service Publication: Available from U.S. Department of Health and Human Services, 200 Independence Avenue, Washington, DC 20201.

USPHS No. 308 Handbook of Sanitation of Airlines (United States Public Health Service, Department of Health Education and Welfare)

3. REQUIREMENTS:

3.1 Qualification:

Hose assemblies supplied in accordance with this procurement specification shall be representative of products which have been subjected to and which have successfully passed the qualification tests specified in this specification.

3.1.1 Manufacturer Qualification: A manufacturer producing a product in conformance to this procurement specification shall be accredited in accordance with the requirements of PD2101, AS7003 and AS7112, and shall be listed in a Performance Review Institute (PRI) Qualified Manufacturers List (QML).

3.1.2 Product Qualification: All products shall conform to the requirements of this procurement specification and shall be approved in accordance with the requirements of PD2001 and PD2101 for listing in a Performance Review Institute (PRI) Qualified Parts List (QPL).

3.2 Materials:

The hose assembly materials shall be uniform in quality, free from defects, suitable for the intended use, consistent with good manufacturing practices, and shall conform to the applicable specifications and the requirements specified herein.

Materials used in these hose assemblies shall be selected from those listed in Table 1.

SAE AS4468 Revision B

TABLE 1 - Assembly Materials

| Component | Material Designation | Material Specification | Finish |
|---|--|--|---|
| Nut (Coupling) AS21921, AS4370 or Equivalent | AISI 300 Series Corrosion-Resistant Steel | AMS 5636, AMS 5637, AMS 5639, AMS 5645, AMS 5646 | Passivate per AMS-QQ- P-35, Type VI or VII and Solid Film Lubricate per AS5272 Type I |
| | Type 2024 Aluminum Alloy | AMS-QQ-A-225/6 | Anodize per AS2472 or MIL-A-8625 Type II, Class 2, Color Optional, Solid Film Lubricate per AS5272 Type I |
| | Type 7075 Aluminum Alloy | AMS 4124 or AMS-QQ- A-225/9 | Anodize per AMS 2472 or MIL-A-8625, Type II, Class 2, Brown Color, Solid Film Lubricate per AS5272 Type I |
| Hose (Inner Tube) | Fully Fluorinated Fluoropolymer Lined Silicone Inner Tube | | As Manufactured |
| Hose (Wire Reinforcement) | AISI 300 Series Corrosion-Resistant Steel | ASTM A 313/A 313M, ASTM A 580/A 580M (AMS 5688, AMS 5689, AMS 5690, AMS 5697) | Passivate per AMS-QQ- P-35, Prior to Forming or Applying to Hose |
| Hose (Nonmetal- lic Braid, Rein- forcement, and/or Covering) | Aramid Fiber, Nylon, Polyester, Fire Resistant Composite Fiber, Fiberglass, or Similar Yarns | Commercial | Dark |
| Insert Fitting (Nipple or Elbow) | AISI Type 303 SE, 304, 304L, 316, or 321 or 347 | AMS 5567, AMS 5556, AMS 5557, AMS 5570, AMS 5571, AMS 5575, AMS-QQ-S-763 (AMS 5648) ASTM A 582/A 582M, AMS 5640 | Passivate per AMS-QQ- P-35, Type VI or VII |
| Socket | AISI Type 303SE, 304, 304L, 321, or 347 Corrosion-Resistant Steel | AMS 5567, AMS-QQ- S-763 (AMS 5639) AMS 5645, AMS 5646 or AMS 5647) ASTM A 582/A 582M, AMS 5650 | Passivate per AMS-QQ- P-35, Type VI or VII |
| | Aluminum 6061 | AMS-QQ-A-225/8 | Anodize per AS2472 or MIL-A-8625 Tye II, Class 2 Color Optional |

SAE AS4468 Revision B

TABLE 1 - Assembly Materials (Continued)

| Component | Material Designation | Material Specification | Finish |
|---|--|--|--|
| Band (Identification) | Polyester Film or Polyolefin with Permanent Marking, Corrosion-Resistant Steel | | |
| Nut Retaining Wire AS1791 or Equivalent | AISI Type 302, 304 or 305 Corrosion- Resistant Steel | ASTM A 313/A 313M and A580/A 580M Condition A (AMS 5688, AMS 5689, AMS 5690, AMS 5697) | Passivate per AMS-QQ- P-35, Type VI or VII and Solid Film Lubricate per AS5272 Type |

3.3 Design and Construction:

The hose assembly shall consist of a smooth inner tube with reinforcement braid or covering to meet the requirements of this document and as required for its intended use. Unless other fittings are specified, hose assemblies may have flared fittings to mate with AS4395, flareless fittings per NAS1760 to mate with AS4375 fitting ends, or threadless coupling ends per AS1656-1 or -3. Hose end fittings shall be permanently attached to the hose by crimping or swaging. Hose splicing shall be used only for economical construction of long assemblies. Splices shall not be used in assembly lengths under 120 in. Splice design and attachment method shall be the same as the hose end fitting.

3.3.1 End Fitting:

- 3.3.1.1 **Insert Fitting (Nipple and Elbow):** Inserts (nipples and elbows) shall be made of corrosion-resistant steel. They may be one-piece construction, welded or brazed assemblies. Only fusion welded butt joints or brazed lap joints shall be used.
- 3.3.1.2 **Coupling Nuts:** Coupling nuts shall be corrosion-resistant steel or aluminum as specified on the standard or drawing. Flareless fitting nuts shall be dimensionally equivalent to AS21921 or AS4370. Nut threads and internal surfaces shall be solid film lubricated in accordance with AS5272 Type I. Lubricant on external nut surfaces shall not be reason for rejection. Thread tolerances shall be maintained after the application of the lubricant.
- 3.3.1.3 **Sockets (Collars):** Sockets (collars) shall be corrosion resistant steel or aluminum as specified on the standard or drawing. Sockets shall be crimped or swaged.
- 3.3.1.4 **Screw Threads:** All fitting threads shall be in accordance with AS8879, Class 3A or 3B as applicable. A 10% increase to the maximum thread tolerances is permissible after fitting connection.

SAE AS4468 Revision B

3.3.1.5 Joining of End Fittings: Fusion welds shall be per AMS-STD-2219 with 100% penetration. Filler wire, if required, shall be AISI Type 347 per AWS A5.9 or AWS A5.14/A5.14M. Brazed joints shall be per AWS C3.6, Class C, using a brazing alloy having the following composition, weight percent (BNi12):

| | | | | | | | | | | | | | |
|-----------|-----------|------|-----|------|----------|-----|------|------|------|------|------|-------|---------|
| Ni | Cr | B | Si | Fe | C | P | S | Al | Ti | Zr | Co | Se | Other " |
| Remainder | 24.0-26.0 | 0.02 | 0.2 | 0.06 | 9.0-11.0 | 0.2 | 0.05 | 0.05 | 0.05 | 0.05 | 0.10 | 0.005 | 0.50 |

FIGURE 1

Brazing alloys AMS 4777, AMS 4778, AMS 4772 and AMS 4771 are optional. Brazing shall be accomplished without flux in a vacuum, inert or dry hydrogen atmosphere. All welds shall be penetrant inspected (water washable) per ASTM E 1417.

3.3.1.6 Threadless Coupling: Hose assemblies with threadless couplings per AS1650 series standards shall have insert ends per AS1656-1-(size) or AS1656-3-(size).

3.3.2 Hose:

3.3.2.1 Inner Tube: The inner tube shall be fully fluorinated fluoropolymer lined silicone of a seamless construction. It shall have a smooth inner surface, free of cracks, and shall be nonshedding or particle producing. Only virgin materials shall be used for the inner tube.

3.3.2.1.1 Inner Tube Liner: The inner liner shall be a fully fluorinated fluoropolymer. It shall be free of splits or holes. There shall be no leakage during 2 psi pneumatic proof testing of the fully chlorinated fluoropolymer inner liner, or visible defects when visually inspected against light. No rerun or reclaimed materials shall be used. The inner liner shall be white, no carbon shall be added. No material or combination of materials that are known to produce toxic effects shall be used. The hose shall not cause an objectionable odor or taste in the water.

3.3.2.2 Reinforcement and Covering: The inner tube shall be reinforced with plies of nonmetallic material and/or wire of sufficient number to meet the requirements of this document. A nonmetallic reinforcement braid may be utilized as the hose outer cover.

3.3.3 Service Life: The hose assembly shall be designed such that it will meet all the requirements of this document. Expected service life (no age limit or environmental degradation) is 20 years.

3.3.4 Corrosion Resistance: Materials (see Table 1) used shall not corrode or have detrimental effect on each other when the hose assembly is exposed to conditions normally encountered in service.

3.3.5 Public Health Service Compliance: All hose assembly materials (see Table 1) which come in contact with the potable water shall comply with Public Health Service Publication 308. The supplier shall obtain Public Health Service approval for any material not already approved.

SAE AS4468 Revision B

3.3.6 Temperature Compliance: Each type hose assembly shall be capable of operating at the fluid and ambient temperature between -65 °F (-54 °C) and +160 °F (71 °C).

3.4 Dimensions and Weights:

3.4.1 Hose Dimensions: Minimum hose inside diameters and bend radii shall be in accordance with Table 2.

TABLE 2 - Hose Data, Dimensions, and Performance Ratings

| Hose Size Code | Hose ID Min | Hose OD Max | Minimum Inside Bend Radius (in) | Operating Pressure psi max | Proof Pressure psi min | Burst Pressure psi min | Weight lb/in max |
|----------------|-------------|-------------|---------------------------------|----------------------------|------------------------|------------------------|------------------|
| 04 | .230 | .48 | .50 | 125 | 250 | 500 | .0060 |
| 06 | .355 | .59 | .75 | 125 | 250 | 500 | .0080 |
| 08 | .475 | .73 | 1.00 | 125 | 250 | 500 | .0088 |
| 10 | .600 | .85 | 1.25 | 125 | 250 | 500 | .0120 |
| 12 | .725 | .98 | 1.50 | 125 | 250 | 500 | .0146 |
| 16 | .975 | 1.23 | 2.00 | 125 | 250 | 500 | .0194 |

3.4.2 Fitting Dimensions: Basic fitting dimensions shall be as specified on the applicable standard or drawing.

3.4.3 Assembly Length: Hose assembly length designations shall be as specified on the applicable standard or drawing. Flareless hose assemblies with NAS1760 ends shall be measured from gage point to gage point. Flareless hose assemblies with combinations NAS1760 to AS4375 end terminations shall be measured from the NAS1760 gage point to the AS4375 end surface. Hose assemblies with AS1656 fitting ends for threadless coupling shall be measured to the end of the fitting.

3.4.4 Weights: Maximum bulk hose weights shall be in accordance with Table 2. Weights of hose assemblies with standard end fittings shall be determined as shown in the applicable standard or drawing. Weights of hose assemblies with nonstandard end fittings shall be listed on the supplier's drawing when submitted to purchaser for approval.

3.5 Performance:

The hose dimensions and ratings, shown in Table 2, shall be verified by meeting or exceeding the following requirements and quality assurance provisions as specified herein.

3.5.1 Examination of Product: Each assembly shall conform dimensionally and materially to this document and the applicable standard or drawing, when examined in accordance with 4.6.1.

3.5.2 Proof Pressure: The hose assembly shall withstand proof pressure of 250 psi at room temperature (70 °F) for 5 min without wetting, leakage, or evidence of permanent deformation or malfunction when tested in accordance with 4.6.2.

SAE AS4468 Revision B

3.5.3 Hose Length and Diameter Change: The hose assembly shall not change in length and diameter by more than plus or minus the percentage values shown in Table 3 when subjected to operating pressure shown in Table 2 for not less than 30 min. The hose assembly shall be tested in accordance with 4.6.3.

TABLE 3 - Percent Change in Hose Length, Diameter, and Flattening

| Hose Size Code | Length ± percent | Diameter ± percent | Flattening Percent Max |
|----------------|---------------------|-----------------------|---------------------------|
| 04 | 2 | 4 | 10 |
| 06 | 2 | 4 | 11 |
| 08 | 2 | 4 | 12 |
| 10 | 2.5 | 4 | 13 |
| 12 | 3 | 4 | 13 |
| 16 | 5 | 4 | 14 |

3.5.4 Repeated Freezing: The hose assembly, shall be capable of withstanding at least 20 repeated freezing cycles without rupture, bulging or collapsing hose cross section in excess of 10% of the original hose diameter when tested in accordance with 4.6.4.

3.5.5 Bend Radius: The hose assembly shall be capable of being bent a minimum of 180° around a mandrel having a diameter equal to two times minimum bend radius given in Table 2 without cracking or flattening of hose in excess of the flattening percentage of Table 3 of the original diameter. The test shall be conducted at -20 °F (-29 °C) and +160 °F (71 °C). The hose assembly shall be tested in accordance with 4.6.5.

3.5.6 Hose Droop: The hose assembly shall not droop more than 0.25 inch in 20 inches when tested in accordance with 4.6.6.

3.5.7 Vacuum: The hose assembly shall be capable of withstanding 22 inches of mercury vacuum at 160 °F (71 °C) for at least 10 min without evidence of collapse and/or flattening of more than the flattening percentage of Table 3 of the original unbent, and unpressurized diameter when tested in accordance with 4.6.7.

3.5.8 Tensile Strength: The hose assembly end fittings shall be capable of withstanding the Table 4 specified tensile pull without end fitting pull off or hose parting when tested in accordance with 4.6.8.

TABLE 4 - Minimum Tensile Load

| Hose Size Code | 04 | 06 | 08 | 10 | 12 | 16 |
|----------------|----|----|-----|-----|-----|-----|
| Load (lb) | 60 | 75 | 100 | 125 | 160 | 250 |

3.5.9 Repeated Torque: The hose assembly shall be capable of sealing and withstanding specified proof pressure requirements of 3.5.2 when tested in accordance with 4.6.9.

SAE AS4468 Revision B

- 3.5.10 Chlorine and Detergent Resistance: The hose assembly shall show no evidence of leakage or deterioration from exposure to chlorinated water (500 ppm of chlorine) and detergents when tested in accordance with 4.6.10.
- 3.5.11 Odor and Taste Test: The hose assembly shall not cause any objectionable odor or taste to water when tested in accordance with 4.6.11.
- 3.5.12 Burst Pressure: The hose assembly shall not rupture and shall show no evidence of leakage at any pressure up to the burst pressure specified in Table 2 and during the 5-min hold at minimum burst pressure when tested in accordance with 4.6.12.
- 3.5.13 Flammability: Flammability tests may be witnessed by the purchaser, FAA, or FAA designated Engineering Representative (DER) as applicable.
- 3.5.13.1 Self Extinguishing: Hose, when tested vertically per 4.6.13, shall meet the following self-extinguishing requirements:
- Average self-extinguishing time: 15 seconds max
 - Average burn length: 8 inches or less
 - Average extinguishing time for drippings: 5 seconds or less
- 3.5.14 Water Absorption: Water absorption of the hose inner tube shall not be greater than 0.1% when tested in accordance with 4.6.14.
- 3.5.15 Fungus Resistance: The hose assembly inner tube shall not show microscopic evidence of fungus growth that would affect performance of intended purpose when tested per 4.6.15.
- 3.5.16 Inner Tube Adhesion: There shall be no evidence of lifting or separation of the inner tube from the silicone outer lining when subjected to the compression loads of 4.6.16.

NOTE: Shearing or tearing of the silicone outer lining is permitted as a result of the compressive loading applied by the serrated tool.

SAE AS4468 Revision B

3.6 Identification of Hose Assembly:

Hose assemblies shall have permanent identification marking on a permanent stainless steel or plastic band, not more than 1.0 inch wide, or on the end fitting. The characters shall be a minimum of 0.064 inch high. The band shall be so designed as to remain tight on the hose to prevent relative movement and resultant chafing and be of sufficient strength to prevent removal by hand. After band installation, a 2.0 inch length of clear polyolefin, per AS1073, shall be heat shrunk to a tight fit over the band. Optional band material without the polyolefin is plastic (mylar, or equivalent). The identification marking shall show the following:

- a. "Suitable for Drinking Water"
- b. Manufacturer's name or trademark
- c. Complete manufacturer's CAGE number and part number
- d. Complete "AS" Standard number
- e. Operating pressure 125 psi
- f. Pressure test symbol PT
- g. Date of hose assembly manufacture in terms of month and year

Items (f) and (g) may be permanently marked on one end fitting socket (collar).

3.7 Workmanship:

The hose assembly shall be constructed and finished to produce a product free from all defects which would affect functioning in service. Particular attention shall be given to thoroughness of assembly, alignment of parts, protective finish, and removal of burrs and sharp edges.

3.7.1 Dimensions and Tolerances: All pertinent dimensions and tolerances, where interchangeability, operation, or performance of the hose assembly may be affected shall be as specified on the applicable standard or drawing.

3.7.2 Cleaning: All hose assemblies shall be clean for use in potable water systems. Cleaning methods may be in accordance with AS611 Class II, except drying temperature shall not exceed 250 °F, or equivalent.

4. QUALITY ASSURANCE PROVISIONS:

4.1 Suppliers Responsibility:

The supplier shall be responsible for performance of all quality assurance provisions and inspections specified herein. Accurate records of the testing shall be kept by the supplier and shall be available to the purchaser on request. The supplier's test data, subject to purchaser approval, shall be considered adequate for product qualification. The purchaser reserves the right to perform any of the inspections and tests set forth in this document to ensure conformance to this document.

SAE AS4468 Revision B

- 4.1.1 Rejection and Retest: Rejected hose or hose assemblies shall not be submitted for reinspection without furnishing full particulars concerning the previous rejection and measures taken to overcome the defects.
- 4.1.2 Defects on Items Already Accepted: If the investigation of the rejection indicates that the defect or defects causing the rejection may exist in hose assemblies previously supplied to the purchaser, the supplier shall advise the purchaser of this condition, the method for identifying these parts, and the recommended corrective action or disposition of the defective parts.

4.2 Purchaser's Responsibility:

The purchaser shall establish adequate inspection procedures to ensure that all requirements of this document are met. Emphasis shall be placed on the following aspects:

- a. Dimensional conformance
- b. Material, finish, and workmanship
- c. Marking
- d. Pressure test

4.3 Classification of Inspections:

The examining and testing of the hose assemblies are classified as follows:

- a. Qualification inspections
- b. Quality conformance inspections

4.4 Qualification Inspections:

The qualification inspections outlined herein are intended to qualify a manufacturer's hose construction and end fitting attachment method only. The configuration of the outlet ports shall be as described on the standard drawing. A number shall be assigned for each attachment method and hose construction used for qualification. The attachment method and hose shall be fully described in the test report by design standard drawings. All other end connections shall also be considered qualified, provided the hose and hose attachment method have not been altered.

- 4.4.1 Test Specimens: Seven hose assemblies of each hose size shall be used for qualifying performance of the manufacturer's product. For flareless end fitting configurations, the Table 5 standard "AS series" hose assemblies shall be used for qualifying hose assemblies to this document.

SAE AS4468 Revision B

TABLE 5 - Test Specimen Configurations

| Specimen | Basic Part Number | Hose Assembly Size Code and Specimen - Number 04 | Hose Assembly Size Code and Specimen - Number 06 | Hose Assembly Size Code and Specimen - Number 08 | Hose Assembly Size Code and Specimen - Number 10 | Hose Assembly Size Code and Specimen - Number 12 | Hose Assembly Size Code and Specimen - Number 16 |
|----------|-------------------|--|--|--|--|--|--|
| 1 | AS4470 | -04-0180 | -06-0180 | -08-0180 | -10-0180 | -12-0220 | -16-0290 |
| 2 | AS4471 | -04-0180 | -06-0180 | -08-0180 | -10-0180 | -12-0220 | -16-0290 |
| 3 | AS4469 | -04-0180 | -06-0180 | -08-0200 | -10-0200 | -12-0240 | -16-0240 |
| 4 | AS4469 | -04-0180 | -06-0180 | -08-0200 | -10-0200 | -12-0240 | -16-0240 |
| 5 | AS4469 | -04-0080 | -06-0080 | -08-0100 | -10-0100 | -12-0120 | -16-0120 |
| 6 | AS4469 | -04-0080 | -06-0080 | -08-0100 | -10-0100 | -12-0120 | -16-0120 |
| 7 | AS4474 | E0700-000 | G0700-000 | H0700-000 | J0700-000 | K0700-000 | M0700-000 |

4.4.2 Test Schedule and Sequence: The test specimens shall be subjected to qualification tests in the order indicated in Table 6.

TABLE 6 - Test Schedule and Sequence

| Test Title | Paragraph Number | Specimen Numbers |
|------------------------------------|------------------|------------------|------------------|------------------|------------------|------------------|------------------|------------------|
| | | /1/ 1 | /1/ 2 | /1/ 3 | /1/ 4 | /1/ 5 | /1/ 6 | /1/ 7 |
| 1. Examination of Product | 4.6.1 | X | X | X | X | X | X | X |
| 2. Proof Pressure Test | 4.6.2 | X | X | X | X | X | X | X |
| 3. Length and Diameter Change Test | 4.6.3 | X | X | | | | | |
| 4. Repeated Freeze Test | 4.6.4 | | | X | X | | | |
| 5. Bend Radius Test | 4.6.5 | X | X | | | | | |
| 6. Proof Pressure Test | 4.6.2 | X | X | X | X | | | |
| 7. Hose Droop Test | 4.6.6 | | | | | | | X |
| 8. Vacuum Test | 4.6.7 | X | X | | | | | |
| 9. Tensile Test | 4.6.8 | | | X | X | | | |
| 10. Repeated Torque Test | 4.6.9 | | | | | X | X | X |
| 11. Proof Pressure Test | 4.6.2 | X | X | | | X | X | X |
| 12. Chlorine and Detergent Test | 4.6.10 | X | X | | | | | |
| 13. Odor and Taste Test /3/ | 4.6.11 | | | X | X | | | |
| 14. Burst Test | 4.6.12 | X | X | | | X | X | X |
| 15. Flammability Test /2/ | 4.6.13 | | | | | | | |
| 16. Water Absorption Test /2/ | 4.6.14 | | | | | | | |
| 17. Fungus Test /2/ | 4.6.15 | | | | | | | |
| 18. Adhesion Test /2/ | 4.6.16 | | | | | | | |

/1/ See Table 5 for hose end fitting configuration and length.

/2/ Bulk hose or specimen cut from hose assembly, lengths as specified by applicable test procedure.

/3/ Test needed in one size only.

SAE AS4468 Revision B

4.5 Quality Conformance Inspections:

Quality conformance inspections shall consist of the following:

- a. Individual tests (100% inspection)
- b. Periodic control tests

4.5.1 Individual Tests (Functional Tests): Each production hose assembly shall be subjected to the following:

- a. Examination of product per 4.6.1.
- b. Proof pressure test per 4.6.2, except 30 seconds duration.

4.5.2 Periodic Control Tests: The following tests shall be performed on three hose assemblies per size selected at random from a production run when the supplier has manufactured an accumulated total of no more than 18,000 linear feet of the hose assemblies, all of one dash size, regardless of hose diameters, made to this document.

- a. Proof pressure test per 4.6.2 (all hose assemblies)
- b. Repeated freeze test per 4.6.4 (one hose assembly)
- c. Bend radius test per 4.6.5 (one hose assembly)
- d. Tensile test per 4.6.8 (one hose assembly)
- e. Adhesion test per 4.6.16 (one hose sample from each hose lot)

4.6 Test Methods:

4.6.1 Examination of Product: All test specimens, as shown in Table 6, shall be carefully examined to determine dimensional and material compliance with the applicable hose assembly standards or drawing.

4.6.2 Proof Pressure Test: All test specimens, as shown in Table 6, shall be subjected to a proof pressure test at room temperature with clean potable water or the option of air while immersed under water to a proof pressure of 250 psi. Pressure shall be maintained for 5 min. (See 3.5.2.)

4.6.3 Hose Length and Diameter Change Test: Test specimens 1 and 2, as shown in Table 6, shall be placed in a straight, unpressurized position. A standard 10 inch \pm .015 inch length shall be marked off on each hose and the actual gage length recorded. The hose diameter shall be measured at least in three places randomly selected along the 10 inch length and the measurements averaged. The hose assemblies shall then be pressurized to operating pressure and the diameter and gage length measurements again taken in the same location as the first measurement while pressurized. (See 3.5.3.)

SAE AS4468 Revision B

- 4.6.4 Repeated Freeze Test: Test specimens 3 and 4, as shown in Table 6, shall be filled with water. The hose assembly shall then be placed in a cold box stabilized at $-65\text{ }^{\circ}\text{F} \pm 5\text{ }^{\circ}\text{F}$ for a minimum period of 6 hours. The hose assembly shall be held horizontally and shall then be dropped 4 ft onto a concrete floor. The hose assembly shall then be allowed to reach room temperature at which point the water within the hose assembly shall be checked. Makeup water shall be added where necessary to compensate for hose expansion. The entire freeze test sequence shall be repeated 20 times. After completion of the freeze cycles, the hose assembly shall then be proof pressure tested per 4.6.2. (See 3.5.4.)
- 4.6.5 Bend Radius Test: Hose specimens 1 and 2, as shown in Table 6, shall be subjected to a bend radius test. The test shall be conducted at $-20\text{ }^{\circ}\text{F} \pm 5\text{ }^{\circ}\text{F}$ and $+160\text{ }^{\circ}\text{F} \pm 5\text{ }^{\circ}\text{F}$. After conditioning the hose for at least 4 hours at specified temperature, the hose shall be removed from the conditioning chamber and immediately bent approximately 180° around a mandrel having a diameter equal to two times the minimum bend radius given in Table 2. The hose shall then be straightened, rotated 180° , and bent in the opposite direction for approximately 180° around the mandrel. Each specimen shall then be proof pressure tested per 4.6.2. (See 3.5.5.)
- 4.6.6 Hose Droop Test: Hose specimen 7, as shown in Table 6, shall be completely filled with water and capped in an unpressurized condition. The hose shall be mounted horizontally and shall be supported at 20-inch intervals with loop type support clamps. Without any external axial loads being applied to the hose, the maximum hose droop between supports shall be measured as shown in Figure 2. (See 3.5.6.)

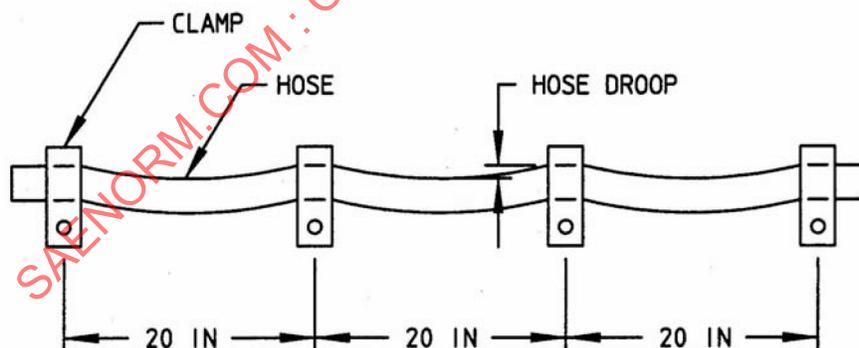


FIGURE 2 - Hose Droop

- 4.6.7 Vacuum Test: The hose assemblies shall be bent and maintained during test to the minimum bend radius specified in Table 2. Test specimens 1 and 2, as shown in Table 6, shall be conditioned at $160\text{ }^{\circ}\text{F} \pm 5\text{ }^{\circ}\text{F}$ ($71\text{ }^{\circ}\text{C} \pm 3\text{ }^{\circ}\text{C}$) for at least 10 min. A suitable vacuum pump shall be used to evacuate the hose to a negative pressure equivalent to 22 inches of mercury. Negative pressure shall be maintained for not less than 10 min. (See 3.5.7.)