

RATIONALE

AS4809C HAS BEEN REAFFIRMED TO COMPLY WITH THE SAE FIVE-YEAR REVIEW POLICY.

REV.  
C

AS4809

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user." SAE reviews each technical report at least every five years at which time it may be revised, reaffirmed, stabilized, or cancelled. SAE invites your written comments and suggestions.

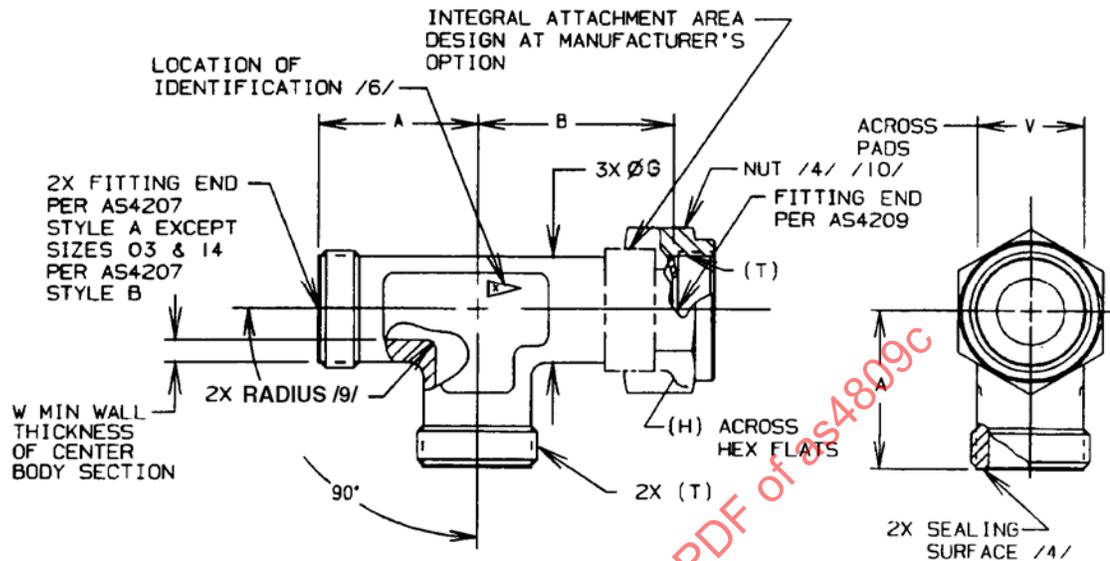



FIGURE 1 - FITTING ASSEMBLY, TEE

TABLE 1 - DIMENSIONS AND WEIGHTS

BASIC NO. AS4809 /16/ SIZE CODE	(NOMINAL TUBE SIZE)	T THREAD PER AS8879 CLASSES A AND B	A	B	G MIN	H	V	W	LB/EA MAX CRES	LB/EA MAX TI
03	.188	.3750-28 UNJS	.575	.781	.285	.500	.360- .377	.055	.0594	.0340
04	.250	.4375-24 UNJS	.617	.808	.329	.562	.360- .377	.060	.0689	.0394
05	.312	.5000-24 UNJS	.653	.850	.391	.625	.423- .440	.060	.0891	.0509
06	.375	.5625-20 UNJS	.704	.945	.454	.688	.485- .502	.060	.111	.0634
08	.500	.7188-20 UNJS	.824	1.045	.547	.875	.547- .565	.065	.161	.0922
10	.625	.8438-18 UNJS	.955	1.178	.673	1.000	.673- .681	.070	.232	.133
12	.750	1.0000-16 UNJ	1.062	1.316	.860	1.125	.860- .878	.095	.346	.198
14	.875	1.1250-16 UNJ	1.216	1.514	1.110	1.375	1.110-1.128	.105	.666	.380
16	1.000	1.2500-14 UNJS	1.246	1.529	1.110	1.500	1.110-1.128	.115	.636	.365
20	1.250	1.5781-14 UNJS	1.387	1.847	1.360	1.875	1.355-1.380	.110	.991	.566
24	1.500	1.8438-14 UNJS	1.688	2.171	1.610	2.125	1.605-1.630	.130	1.54	.879

SAE values your input. To provide feedback on this Technical Report, please visit <http://www.sae.org/technical/standards/AS4809C>

THIRD ANGLE PROJECTION



CUSTODIAN: G-3/G-3B

PROCUREMENT SPECIFICATION: /5/ AS85421, AS85720



**AEROSPACE STANDARD**

FITTING ASSEMBLY, TEE, BEAM SEAL, RETAINED NUT ON RUN

**AS4809**  
SHEET 1 OF 3

**REV. C**

NOTES:

/1/ MATERIAL:

a. CODE LETTER T

- (1) BODY: TYPE 6AL-4V TITANIUM ALLOY FORGING OR BAR PER AMS 4965.
- (2) NUT: TYPE 6AL-4V TITANIUM ALLOY BAR PER AMS 4965.

b. CODE LETTER P

- (1) BODY: TYPE 17-4PH CORROSION RESISTANT STEEL FORGING OR BAR PER AMS 5643.
- (2) NUT: TYPE 17-4PH CORROSION RESISTANT STEEL BAR PER AMS 5643.

c. CODE LETTER V

- (1) BODY: TYPE 15-5PH CORROSION RESISTANT STEEL FORGING OR BAR PER AMS 5659.
- (2) NUT: TYPE 15-5PH CORROSION RESISTANT STEEL BAR PER AMS 5659.

2. HEAT TREAT:

a. MATERIAL CODE LETTER T

- (1) BODY AND NUT: NONE.

b. MATERIAL CODE LETTERS P AND V

- (1) BODY AND NUT: HEAT TREAT TO CONDITION H 1075 PER AMS 2759/3.

3. FINISH:

a. MATERIAL CODE LETTER T

- (1) BODY: NONE.
- (2) NUT: NONE.

b. MATERIAL CODE LETTERS P AND V

- (1) BODY: PASSIVATE PER AMS 2700.
- (2) NUT: PASSIVATE PER AMS 2700.

/4/ DRY FILM LUBRICANT: APPLY DRY FILM LUBRICANT PER AS5272, TYPE I TO THE SEALING SURFACE. OVERSPRAY IN BORE IS NOT PERMITTED. APPLY DRY FILM LUBRICANT PER AS5272, TYPE I TO THE INSIDE OF THE NUT. MINOR OVERSPRAY IS PERMITTED ON THE NUT.

/5/ PROCUREMENT SPECIFICATION: AS85421 FOR OPERATING PRESSURES TO 4000 psi AND AS85720 FOR OPERATING PRESSURES TO 5000 psi, EXCEPT AS SPECIFIED ON THIS STANDARD. THIS PART SHALL BE QUALIFIED TO THE PROCUREMENT SPECIFICATION AS APPLICABLE IN A COMPLETE ASSEMBLY. USERS OF THIS STANDARD ARE ADVISED TO CONTROL SOURCE APPROVAL(S) BY STANDARD PAGE SUPPLEMENT SHEET OR SIMILAR MEANS.

	<b>AEROSPACE STANDARD</b>	<b>AS4809</b> SHEET 2 OF 3	<b>REV.</b> <b>C</b>
	FITTING ASSEMBLY, TEE, BEAM SEAL, RETAINED NUT ON RUN		