

RATIONALE

"INACTIVE IN PART" STATUS REPLACED BY "NOT RECOMMENDED IN PART." OPTIONAL MATERIALS ADDED TO NOTE 1. HEAT TREATMENT NOTE 2, REVISED. QML STATEMENT REVISED. INTENDED USE NOTE REVISED, TABLE 2 REMOVED. NOTE 10 REVISED TO REFLECT CURRENT SPECIFICATION CALLOUT. USE OF TITANIUM AND CADMIUM IN OXYGEN OR POTABLE WATER SYSTEM WARNING NOTE REMOVED. OLD NOTE 18 IS NOW NOTE 17. NEW NOTE 17 REVISED TO REFLECT CHANGE FROM "INACTIVE" TO "RECOMMENDED." GENERAL NON-TECHNICAL UPDATES INCORPORATED.

REV.
B

AS5193™

SAE Executive Standards Committee Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user." SAE reviews each technical report at least every five years at which time it may be revised, reaffirmed, stabilized, or cancelled. SAE invites your written comments and suggestions.


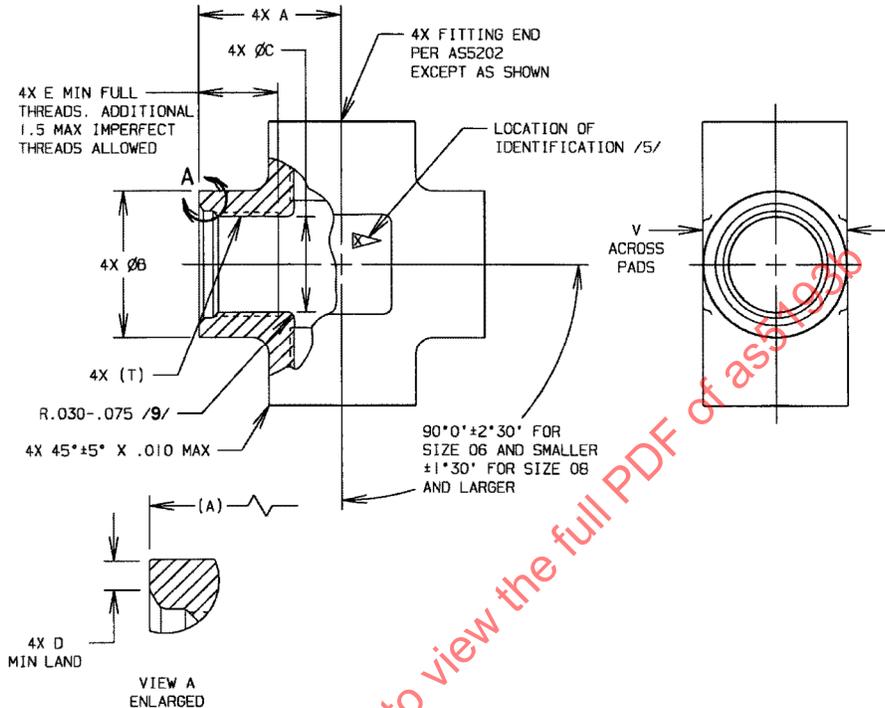


FIGURE 1 - FITTING, CROSS

NOT RECOMMENDED IN PART /17/

For more information on this standard, visit
<https://www.sae.org/standards/content/AS5193B/>

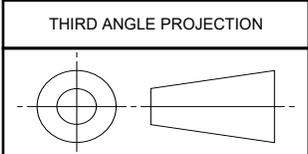

CUSTODIAN: G-3/G-3B

PROCUREMENT SPECIFICATION: AS4875 /4/



AEROSPACE STANDARD

FITTING, CROSS, INTERNAL
STRAIGHT THREAD PORT

AS5193™
SHEET 1 OF 4

REV.
B

TABLE 1 - DIMENSIONS A-V AND WEIGHTS

BASIC NO. AS5193 /15/ SIZE CODE	(NOMINAL TUBE SIZE)	T THREAD PER AS8879 CLASS 3B								LB/EA	LB/EA	LB/EA
			A	B	C	D	E	V	APPROX REF AL	APPROX REF STEEL	APPROX REF TI	
04	.250	.4375-20 UNJF	.787	.688	.397	.040	.483	.735-	.753	.0608	.175	.0963
05	.312	.5000-20 UNJF	.787	.750	.459	.040	.452	.735-	.753	.0611	.176	.0972
06	.375	.5625-18 UNJF	.849	.813	.516	.040	.475	.797-	.815	.0733	.211	.116
08	.500	.7500-16 UNJF	1.037	1.063	.697	.071	.569	1.047-	1.065	.141	.406	.224
10	.625	.8750-14 UNJF	1.193	1.188	.815	.071	.638	1.173-	1.191	.189	.544	.300
12	.750	1.0625-12 UNJ	1.396	1.438	.991	.077	.730	1.418-	1.443	.317	.909	.300
16	1.000	1.3125-12 UNJ	1.568	1.688	1.241	.077	.777	1.668-	1.693	.416	1.188	.658
20	1.250	1.6250-12 UNJ	1.771	2.000	1.553	.077	.824	1.980-	2.005	.549	1.575	.869

NOTES:

NOTICE

THIS DOCUMENT REFERENCES A PART WHICH CONTAINS CADMIUM AS A PLATING MATERIAL. CONSULT LOCAL OFFICIALS IF YOU HAVE QUESTIONS CONCERNING CADMIUM'S USE.

/1/ MATERIAL:

- a. DASH AS CODE LETTER - TYPE 4130 STEEL FORGING OR BAR PER AMS-S-6758 OR AMS6370, OR TYPE 4140 STEEL BAR PER AMS6349 OR AMS6382. /2/
- b. CODE LETTER D - TYPE 2014-T6 ALUMINUM ALLOY FORGING PER AMS-QQ-A-367 OR AMS4133 OR TYPE 2024-T6 ALUMINUM ALLOY BAR PER AMS-QQ-A-225/6, OR TYPE 2024-T851 ALUMINUM ALLOY BAR PER AMS-QQ-A-225/6 OR AMS4339. /17/
- c. CODE LETTER J - TYPE 304 CORROSION RESISTANT STEEL FORGING OR BAR PER AMS-QQ-S-763 OR AMS5639.
- d. CODE LETTER K - TYPE 316 CORROSION RESISTANT STEEL FORGING OR BAR PER AMS-QQ-S-763 OR AMS5648.
- e. CODE LETTER R - TYPE 321 CORROSION RESISTANT STEEL FORGING OR BAR PER AMS-QQ-S-763 OR AMS5645.
- f. CODE LETTER S - TYPE 347 CORROSION RESISTANT STEEL FORGING OR BAR PER AMS-QQ-S-763 OR AMS5646. /17/
- g. CODE LETTER T - TYPE 6AL-4V TITANIUM ALLOY FORGING OR BAR PER AMS4928.
- h. CODE LETTER W - TYPE 7075-T73 ALUMINUM ALLOY FORGING PER AMS-QQ-A-367 OR AMS4141; OR TYPE 7075-T73 ALUMINUM ALLOY BAR PER AMS-QQ-A-225/9; OR TYPE 7075-T7351 ALUMINUM ALLOY BAR PER AMS4124. /2/

/2/ HEAT TREATMENT:

- a. DASH AS MATERIAL CODE LETTER - REFER TO HARDNESS REQUIREMENT PER PROCUREMENT SPECIFICATION.
- b. MATERIAL CODE LETTER D AND W - REFER TO ELECTRICAL CONDUCTIVITY AND HARDNESS REQUIREMENT PROCUREMENT SPECIFICATION.
- c. OTHER MATERIAL CODE LETTERS - NONE.

	AEROSPACE STANDARD		AS5193™ SHEET 2 OF 4	REV. B
	FITTING, CROSS, INTERNAL STRAIGHT THREAD PORT			

3. FINISH:

- a. DASH AS MATERIAL CODE LETTER - CADMIUM PLATE PER AMS-QQ-P-416, TYPE II, CLASS 2, DYE BLACK AND COAT WITH A LIGHT FILM OF OIL PER PROCUREMENT SPECIFICATION.
- b. MATERIAL CODE LETTER D:
 - 1. ANODIZE PER AMS2472 OR MIL-A-8625, TYPE II, CLASS 2, DYE BLUE, DUPLEX SEAL PER PROCUREMENT SPECIFICATION.
 - 2. D CODE PARTS TO BE COATED WITH HIGH PURITY ALUMINUM ONLY WILL HAVE THE FINISH CODE LETTER "V" PLACED AFTER THE SIZE CODE IN THE PART NUMBER. THE FINISH WILL BE: COAT WITH HIGH PURITY ALUMINUM PER MIL-DTL-83488, CLASS 3, TYPE II, WITH MAXIMUM COATING THICKNESS OF .0005. GLASS BEAD PEEN PRESSURE SHALL BE 25 PSI MAXIMUM. /15/
- c. MATERIAL CODE LETTERS J, K, R, AND S - PASSIVATE PER AMS2700 TYPE 6 OR 7.
- d. MATERIAL CODE LETTER T - ANODIZE PER AMS2488, TYPE 2 OR FLUORIDE PHOSPHATE CONVERSION COAT PER AMS2486 WITH COLOR PER PROCUREMENT SPECIFICATION.
- e. MATERIAL CODE LETTER W:
 - 1. ANODIZE PER AMS2472 OR MIL-A-8625, TYPE II, CLASS 2, DYE BROWN, DUPLEX SEAL PER PROCUREMENT SPECIFICATION.
 - 2. W CODE PARTS TO BE COATED WITH HIGH PURITY ALUMINUM ONLY WILL HAVE THE FINISH CODE LETTER "V" PLACED AFTER THE SIZE CODE IN THE PART NUMBER. THE FINISH WILL BE: COAT WITH HIGH PURITY ALUMINUM PER MIL-DTL-83488, CLASS 3, TYPE II, WITH MAXIMUM COATING THICKNESS OF .0005. GLASS BEAD PEEN PRESSURE SHALL BE 25 PSI MAXIMUM. /15/

/4/ PROCUREMENT SPECIFICATION: AS4875 EXCEPT AS SPECIFIED ON THIS STANDARD. PRODUCT MANUFACTURED TO THIS STANDARD SHALL MEET THE REQUIREMENTS SPECIFIED HEREIN AND THE PROCUREMENT SPECIFICATION. ORIGINAL COMPONENT MANUFACTURERS (OCM) AND VALUE ADDED DISTRIBUTORS (VAD) SHALL BE LISTED IN THE NADCAP QUALIFIED MANUFACTURER LIST (QML) FOR THIS PRODUCT TYPE. THE QML IS AVAILABLE AT www.eAuditNet.com.

/5/ IDENTIFICATION AT LOCATION SHOWN: MARK PER AS478 CLASS C OR D, OR METHOD 7A3, 15A3, OR 15B.

- a. FOR SIZE 06 AND SMALLER: MANUFACTURER'S NAME, CAGE CODE OR TRADEMARK, LETTERS "AS," AND MATERIAL CODE LETTER.
- b. FOR SIZE 08 AND LARGER: MANUFACTURER'S NAME, CAGE CODE OR TRADEMARK, BASIC PART NUMBER, AND MATERIAL CODE LETTER.

6. INTENDED USE: THIS PART IS DESIGNED FOR USE IN SYSTEMS WITH MAXIMUM OPERATING PRESSURES AS SPECIFIED IN THE PROCUREMENT SPECIFICATION.

7. THIS STANDARD IS THE FUNCTIONAL EQUIVALENT OF AN937 AND IS INTENDED TO BE SUITABLE AS A REPLACEMENT STANDARD.

8. WHEN MACHINED FROM BAR OR OVERSIZED FORGING, THE CENTER BODY DIMENSIONS SHALL CONFORM TO AS1376, TABLE 6.

/9/ RADIUS APPLICABLE FOR TITANIUM ALLOY PARTS ONLY.

10. INTERPRETATION OF DRAWING PER AS4296.

11. SURFACE TEXTURE: SYMBOLS PER ASME Y14.36M; REQUIREMENTS PER ASME B46.1. UNLESS OTHERWISE SPECIFIED, MACHINED SURFACES TO BE 125 MICROINCHES Ra. FORGED SURFACES MAY BE 250 MICROINCHES Ra.

12. BREAK EDGES .003 TO .015, UNLESS OTHERWISE SPECIFIED.

13. DIMENSIONING AND TOLERANCING: ASME Y14.5M-1994.

	AEROSPACE STANDARD	AS5193™ SHEET 3 OF 4	REV. B
	FITTING, CROSS, INTERNAL STRAIGHT THREAD PORT		