

RATIONALE

THIS DOCUMENT IS A NEW DETAIL SHEET DESCRIBING THE REQUIREMENTS FOR A LIGHTWEIGHT, EXTRA FLEXIBLE ZERO HALOGEN CONVOLUTED TUBING PROCESSED USING PEEK MATERIAL.

NOTICE

THE REQUIREMENTS FOR ACQUIRING THE TUBING DESCRIBED HEREIN SHALL CONSIST OF THIS DOCUMENT AND THE LATEST ISSUE IN EFFECT OF SAE AS81914.

SAE AS81914/11


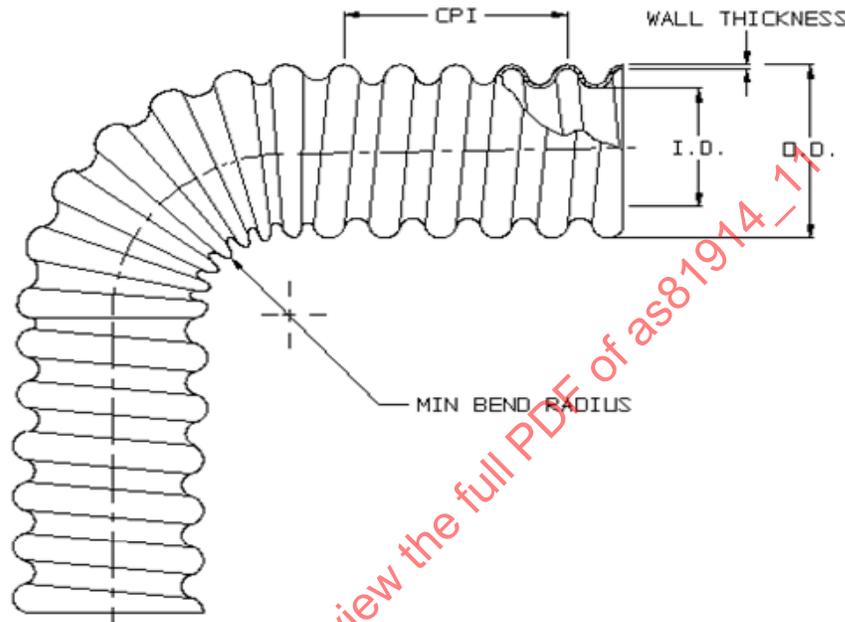


FIGURE 1 - DIMENSIONS AND CONFIGURATION

SAENORM.COM : Click to view the full PDF of as81914_11

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user." SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

SAE values your input. To provide feedback on this Technical Report, please visit <http://www.sae.org/technical/standards/AS81914/11>

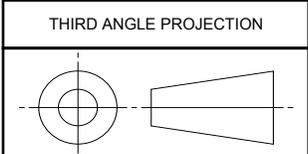

ISSUED 2011-01

CUSTODIAN: AE-8/AE-8C1

PROCUREMENT SPECIFICATION: AS81914

SAE Aerospace
An SAE International Group

AEROSPACE STANDARD

TUBING, PLASTIC, LIGHTWEIGHT, ZERO HALOGEN, EXTRA FLEXIBLE, CONVOLUTED, HELICAL, CLOSE CONVOLUTION, POLYETHERETHERKEYTONE (PEEK)

SAE AS81914/11
SHEET 1 OF 4

TABLE 1 – FIGURE 1 DIMENSIONS

DASH NUMBER	MAX INSIDE DIA. (I.D.)	MIN INSIDE DIA. (I.D.)	MAX OUTER DIA. (O.D.)	MAX WALL THICKNESS	CONVOLUTIONS PER INCH (CPI) ± 1	APPROX. WEIGHT LBS (KG) PER 100 FEET (30.5 M) REF.	MIN BEND RADIUS
01	.188 (4.78)	.181 (4.60)	.307 (7.80)	.010 (0.25)	8	0.6 (0.27)	.31 (7.9)
02	.281 (7.14)	.273 (6.93)	.405 (10.29)	.010 (0.25)	8	0.8 (0.36)	.44 (11.2)
03	.312 (7.92)	.300 (7.62)	.440 (11.18)	.010 (0.25)	8	1.4 (0.41)	.44 (11.2)
04	.375 (9.53)	.364 (9.25)	.500 (12.70)	.010 (0.25)	8	1.6 (0.50)	.50 (12.4)
05	.437 (11.10)	.427 (10.85)	.550 (13.97)	.010 (0.25)	8	1.8 (0.59)	.63 (16.0)
06	.500 (12.70)	.485 (12.32)	.630 (16.00)	.010 (0.25)	8	2.0 (0.59)	.75 (19.1)
07	.625 (15.88)	.608 (15.44)	.750 (19.05)	.010 (0.25)	8	2.4 (0.68)	.75 (19.1)
08	.750 (19.05)	.730 (18.54)	.890 (22.61)	.011 (0.28)	8	3.0 (0.95)	.94 (23.9)
09	.875 (22.23)	.855 (21.72)	1.060 (26.92)	.011 (0.28)	8	3.8 (1.27)	1.13 (28.7)
10	1.000 (25.40)	.980 (24.89)	1.195 (30.35)	.012 (0.30)	7	5.2 (1.59)	1.25 (31.8)
11	1.125 (28.58)	1.105 (28.07)	1.350 (34.29)	.012 (0.30)	7	6.4 (2.90)	1.31 (33.3)
12	1.250 (31.75)	1.220 (30.99)	1.500 (38.10)	.012 (0.30)	7	9.8 (4.45)	1.44 (36.6)
13	1.500 (38.10)	1.480 (37.59)	1.780 (45.21)	.014 (0.36)	7	11.5 (5.22)	1.75 (44.5)
14	1.750 (44.45)	1.730 (43.94)	2.020 (51.31)	.014 (0.36)	7	14.0 (6.35)	2.00 (50.8)
15	2.000 (50.80)	1.980 (50.29)	2.280 (57.91)	.015 (0.38)	7	16.0 (7.26)	2.25 (57.2)

NOTES:

- DIMENSIONS ARE IN INCHES.
- UNLESS OTHERWISE SPECIFIED TOLERANCES SHALL BE: .XX = ± .010 (0.25 MM), .XXX = ± .005 (0.13 MM).
- METRIC EQUIVALENTS ARE GIVEN FOR GENERAL INFORMATION ONLY AND ARE BASED ON 25.4 MM = 1 INCH.
- METRIC DIMENSIONS IN PARENTHESES ARE SHOWN IN MILLIMETERS.

REQUIREMENTS:

- DIMENSIONS AND CONFIGURATION: SEE FIGURE 1 AND TABLE 1.
- CONVOLUTION TYPE: HELICAL.
- LENGTHS SHALL BE SPECIFIED IN FEET BY THE PROCURING ACTIVITY AND DOES NOT FORM A PART OF THE IDENTIFYING PART NUMBER. MINIMUM ORDER LENGTH SHALL BE 3 FEET (0.914 M) AND THE TUBING ORDER LENGTH TOLERANCES SHALL BE AS SPECIFIED IN TABLE 2. TUBING SHALL BE PROCURED AS COILS.

 An SAE International Group	AEROSPACE STANDARD	SAE AS81914/11 SHEET 2 OF 4
	TUBING, PLASTIC, LIGHTWEIGHT, ZERO HALOGEN, EXTRA FLEXIBLE, CONVOLUTED, HELICAL, CLOSE CONVOLUTION, POLYETHERETHERKEYTONE (PEEK)	

TABLE 2 – ORDER LENGTH TOLERANCE

ORDER LENGTH RANGE	
LENGTH IN FEET (METERS)	TOLERANCE IN INCHES (MM)
3 – 12 (0.914 M – 3.66 M)	+ 2.0 / - 0.0 (+ 50.8 MM / - 0.0 MM)
13 – 50 (3.96 M – 15.24 M)	+ 4.0 / - 0.0 (+ 101.6 MM / - 0.0 MM)
51 AND UP (15.55 M AND UP)	+ 6.0 / - 0.0 (+ 152.4 MM / - 0.0 MM)

4. CONTINUOUS OPERATING TEMPERATURE: -55 °C (-67 °F) TO 250 °C (482 °F).
5. COLOR: UNLESS OTHERWISE SPECIFIED, THE SUPPLIED COLOR SHALL BE BLACK.
6. PHYSICAL PROPERTIES: GENERAL PHYSICAL REQUIREMENT VALUES ALONG WITH ASSOCIATED TEST CONDITIONS ARE LOCATED IN TABLE 3.
7. SHELF LIFE: THE STORAGE/SHELF LIFE SHALL BE 20 YEARS.

TABLE 3 – PHYSICAL PROPERTIES

PROPERTY	REQUIREMENT
CONSTRUCTION DETAILS	IN ACCORDANCE WITH TABLE 1
STRESS IN PSI @ 10% STRAIN	250 TO 900
SPECIFIC GRAVITY	1.32 MAX
CRUSH RESISTANCE, HORIZONTAL	10 LBS (4.54KG) MIN.
HEAT SHOCK	234/230°C (454/446°F) FOR 4 HOURS. 15% MAX LONGITUDINAL CHANGE. NO DRIPPING, FLOWING OR CRACKING
HEAT AGING	STRESS IN PSI @10% STRAIN, 80% OF INITIAL VALUE. 179/175 °C (354/347 °F) FOR 96 HOURS.
FLUID RESISTANCE	STRESS IN PSI @ 10% STRAIN 80% OF INITIAL VALUE
FLAMMABILITY	NON-FLAMMABLE 1/
FUNGUS RESISTANCE	NON-NUTRIENT 1/
HALOGEN	ZERO HALOGEN 1/
DIELECTRIC BREAKDOWN	12 000 VOLTS, NO BREAKDOWN

1/ PROPERTIES NOT TESTED FOR.