

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user." SAE reviews each technical report at least every five years at which time it may be revised, reaffirmed, stabilized, or cancelled. SAE invites your written comments and suggestions.

**REV. C**  
**AS9456™**

FEDERAL SUPPLY CLASS  
5306

**RATIONALE**


THIS DOCUMENT HAS BEEN DETERMINED TO CONTAIN BASIC AND STABLE TECHNOLOGY WHICH IS NOT DYNAMIC IN NATURE.

**STABILIZED NOTICE**

THIS DOCUMENT HAS BEEN DECLARED "STABILIZED" BY THE SAE E-25 GENERAL STANDARDS FOR AEROSPACE AND PROPULSION SYSTEMS COMMITTEE AND WILL NO LONGER BE SUBJECTED TO PERIODIC REVIEWS FOR CURRENCY. USERS ARE RESPONSIBLE FOR VERIFYING REFERENCES AND CONTINUED SUITABILITY OF TECHNICAL REQUIREMENTS. NEWER TECHNOLOGY MAY EXIST.

SAENORM.COM : Click to view the full PDF of as9456c

**SAE values your input. To provide feedback on this Technical Report, please visit <http://www.sae.org/technical/standards/AS9456C>**

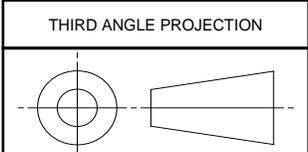

CUSTODIAN: E-25



**AEROSPACE STANDARD**  
BOLT, MACHINE - STEEL, DIFFUSED NICKEL-CADMIUM PLATED, HEXAGON HEAD, UNS K14675, 195 KSI MIN, .5000-20 UNJF-3A

**AS9456™**

**REV. C**

ISSUED 1998-08 REVISED 2003-11 REAFFIRMED 2007-06 STABILIZED 2015-10

THE INITIAL SAE PUBLICATION OF THIS DOCUMENT WAS TAKEN DIRECTLY FROM U.S. MILITARY STANDARD MS9456A, AMENDMENT 1. THIS SAE STANDARD RETAINS THE SAME PART NUMBERS ESTABLISHED BY THE ORIGINAL MILITARY DOCUMENT.

ANY REQUIREMENTS ASSOCIATED WITH QUALIFIED PRODUCTS LISTS (QPL) MAY CONTINUE TO BE MANDATORY FOR DOD CONTRACTS. REQUIREMENTS RELATING TO QPL'S HAVE NOT BEEN ADOPTED BY THE SAE FOR THIS STANDARD AND ARE NOT PART OF THIS SAE DOCUMENT.

WARNING

THIS DOCUMENT INCLUDES CADMIUM AS A PLATING MATERIAL. THE USE OF CADMIUM HAS BEEN RESTRICTED AND/OR BANNED FOR USE IN MANY COUNTRIES DUE TO ENVIRONMENTAL AND HEALTH CONCERNS. THE USER SHOULD CONSULT WITH LOCAL OFFICIALS ON THE ENVIRONMENTAL AND HEALTH REGULATIONS REGARDING ITS USE.

SAENORM.COM : Click to view the full PDF of as9456c

	<b>AEROSPACE STANDARD</b>	<b>AS9456™</b> SHEET 1 OF 4	<b>REV.</b> <b>C</b>
	BOLT, MACHINE - STEEL, DIFFUSED NICKEL- CADMIUM PLATED, HEXAGON HEAD, UNS K14675, 195 KSI MIN, .5000-20 UNJF-3A		

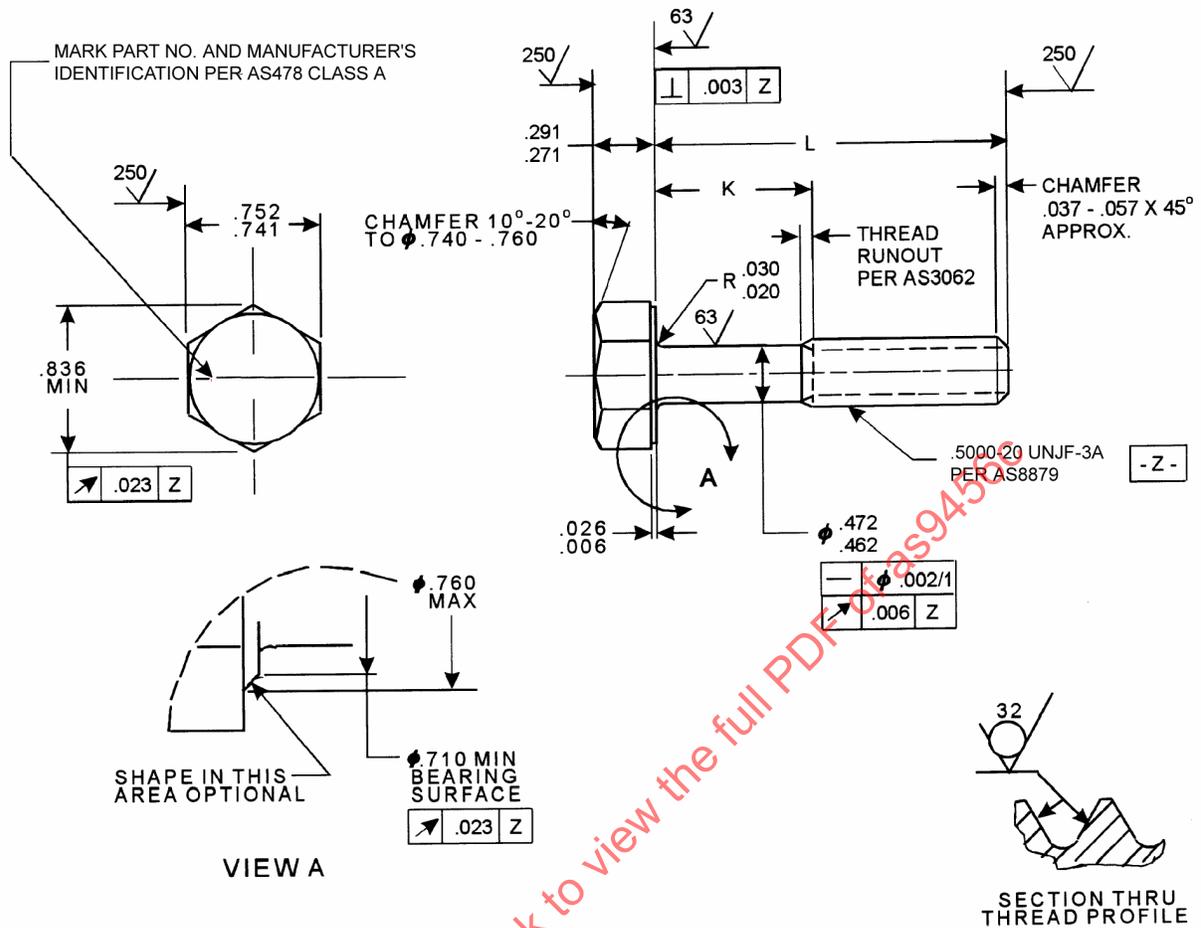


FIGURE 1 - BOLT

SAENORM.COM : Click to view the full PDF of AS9456

	<b>AEROSPACE STANDARD</b>	<b>AS9456™</b> SHEET 2 OF 4	<b>REV.</b> <b>C</b>
	BOLT, MACHINE - STEEL, DIFFUSED NICKEL-CADMIUM PLATED, HEXAGON HEAD, UNS K14675, 195 KSI MIN, .5000-20 UNJF-3A		

TABLE 1 - PART NUMBERS AND DIMENSIONS

PART NO.	L	K	APPROX. MASS LB/100	PART NO.	L	K	APPROX. MASS LB/100
MS9456-04	.802 - .822	.105 - .125	7.77	MS9456-31	3.240 - 3.260	1.940 - 2.000	19.55
MS9456-05	.865 - .885	.105 - .125	8.07	MS9456-32	3.365 - 3.385	2.065 - 2.125	20.16
MS9456-06	.928 - .948	.105 - .125	8.37	MS9456-33	3.490 - 3.510	2.190 - 2.250	20.76
MS9456-07	.990 - 1.010	.105 - .125	8.67	MS9456-34	3.615 - 3.635	2.315 - 2.375	21.36
MS9456-08	1.052 - 1.072	.105 - .125	8.98	MS9456-35	3.740 - 3.760	2.440 - 2.500	21.97
MS9456-09	1.115 - 1.135	.105 - .125	9.28	MS9456-36	3.865 - 3.885	2.565 - 2.625	22.57
MS9456-10	1.178 - 1.198	.105 - .125	9.58	MS9456-37	3.990 - 4.010	2.690 - 2.750	23.18
MS9456-11	1.240 - 1.260	.105 - .125	9.88	MS9456-38	4.115 - 4.135	2.815 - 2.875	23.78
MS9456-12	1.302 - 1.322	.105 - .125	10.19	MS9456-39	4.240 - 4.260	2.940 - 3.000	24.38
MS9456-13	1.365 - 1.385	.125 - .145	10.49	MS9456-40	4.365 - 4.385	3.065 - 3.125	24.99
MS9456-14	1.428 - 1.448	.128 - .188	10.79	MS9456-41	4.490 - 4.510	3.190 - 3.250	25.59
MS9456-15	1.490 - 1.510	.190 - .250	11.09	MS9456-42	4.615 - 4.635	3.315 - 3.375	26.20
MS9456-16	1.552 - 1.572	.252 - .312	11.39	MS9456-43	4.740 - 4.760	3.440 - 3.500	26.80
MS9456-17	1.615 - 1.635	.315 - .375	11.70	MS9456-44	4.865 - 4.885	3.565 - 3.625	27.41
MS9456-18	1.678 - 1.698	.378 - .438	12.00	MS9456-45	4.990 - 5.010	3.690 - 3.750	28.01
MS9456-19	1.740 - 1.760	.440 - .500	12.30	MS9456-46	5.115 - 5.135	3.815 - 3.875	28.61
MS9456-20	1.865 - 1.885	.565 - .625	12.90	MS9456-47	5.240 - 5.260	3.940 - 4.000	29.22
MS9456-21	1.990 - 2.010	.690 - .750	13.51	MS9456-48	5.365 - 5.385	4.065 - 4.125	29.82
MS9456-22	2.115 - 2.235	.815 - .875	14.11	MS9456-49	5.490 - 5.510	4.190 - 4.250	30.43
MS9456-23	2.240 - 2.260	.940 - 1.000	14.72	MS9456-50	5.615 - 5.635	4.315 - 4.375	31.03
MS9456-24	2.365 - 2.385	1.065 - 1.125	15.32	MS9456-51	5.740 - 5.760	4.440 - 4.500	31.64
MS9456-25	2.490 - 2.510	1.190 - 1.250	15.93	MS9456-52	5.865 - 5.885	4.565 - 4.625	32.24
MS9456-26	2.615 - 2.635	1.315 - 1.375	16.53	MS9456-53	5.990 - 6.010	4.690 - 4.750	32.84
MS9456-27	2.740 - 2.760	1.440 - 1.500	17.13				
MS9456-28	2.865 - 2.885	1.565 - 1.625	17.74				
MS9456-29	2.990 - 3.010	1.690 - 1.750	18.34				
MS9456-30	3.115 - 3.135	1.815 - 1.875	18.95				

NOTES:

- MATERIAL: LOW ALLOY STEEL AMS 6304 (UNS K14675).
- PROCUREMENT SPECIFICATION: AS7455.
- HARDNESS: 42-46 HRC.
- FINISH: DIFFUSED NICKEL-CADMIUM PLATE AMS 2416. DIMENSIONS ARE AFTER PLATING. CONTACT POINTS PERMISSIBLE. PD MAY BE REDUCED .0012 MAXIMUM BEFORE PLATING.
- MAGNETIC PARTICLE INSPECTION PER ASTM E 1444 BEFORE PLATING.
- INCOMPLETE THREADS NOT TO ENTER FILLET.
- SURFACE TEXTURE: SYMBOLS PER ASME Y14.36M. REQUIREMENTS PER ASME B46.1. UNLESS OTHERWISE SPECIFIED, SURFACES TO BE 125 MICROINCHES Ra.
- BREAK SHARP EDGES .003-.015, UNLESS OTHERWISE SPECIFIED.
- DIMENSIONING AND TOLERANCING PER ANSI Y14.5M-1982 (ASME PUBLICATION).

	<b>AEROSPACE STANDARD</b>	<b>AS9456™</b> SHEET 3 OF 4	<b>REV.</b> <b>C</b>
	BOLT, MACHINE - STEEL, DIFFUSED NICKEL-CADMIUM PLATED, HEXAGON HEAD, UNS K14675, 195 KSI MIN, .5000-20 UNJF-3A		