



SURFACE VEHICLE STANDARD

J1051

AUG2013

Issued 1974-01
Reaffirmed 2013-08

Superseding J1051 APR2008

Force-Deflection Measurements of Cushioned Components of Seats for Off-Road Work Machines

RATIONALE

J1051 has been reaffirmed to comply with the SAE five year review policy.

1. **Scope**—This SAE Standard provides a method to obtain consistent force-deflection data of finished (or unfinished, when specified) cushioned components of seats for off-road work machines as listed in SAE J1116. This data may be helpful in maintaining seat comfort characteristics and quality control. There is no intent to establish any acceptance criteria.

2. References

2.1 **Applicable Publications**—The following publication forms a part of this standard to the extent specified herein. The latest issue of SAE publications shall apply.

2.1.1 SAE PUBLICATIONS—Available from SAE, 400 Commonwealth Drive, Warrendale, PA 15096-0001.

SAE J1116—Categories of Off-Road Work Machines

SAE TSB 002—Preparation of SAE Technical Reports

SAE REPORT—Format Guidelines for the Electronic Capture of SAE Documents, June 1992

3. Technical Requirements

3.1 Test Apparatus

3.1.1 A 200 mm diameter, rigid, flat, or curved indenter (Figure 1 and Figure 2) or a 50 mm diameter, rigid, flat indenter (Figure 1). The indenter force shall be applied through a rigid joint or a swivel joint capable of accommodating the angle of the top surface of the test specimen.

3.1.2 A platform capable of positioning the top surface of the test specimen parallel to and centered with the rigid joint indenter and not to restrict the breathing or normal deformation of the specimen tested (Figure 3). The indenter with the swivel joint may be preferred for tapered or irregular shaped cushions or for a fixed platform (Figure 4).

3.1.3 An apparatus capable of applying forces and measuring the deflection of the indenter into the specimen.

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be revised, reaffirmed, stabilized, or cancelled. SAE invites your written comments and suggestions.

Copyright © 2013 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
Tel: +1 724-776-4970 (outside USA)
Fax: 724-776-0790
Email: CustomerService@sae.org
http://www.sae.org

SAE WEB ADDRESS:

SAE values your input. To provide feedback
on this Technical Report, please visit
http://www.sae.org/technical/standards/J1051_201308

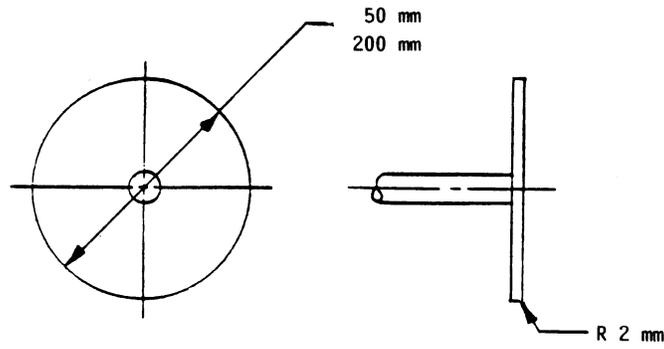


FIGURE 1—FLAT INDENTOR

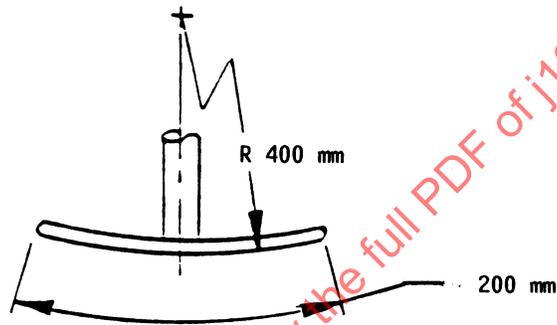


FIGURE 2—CURVED INDENTOR

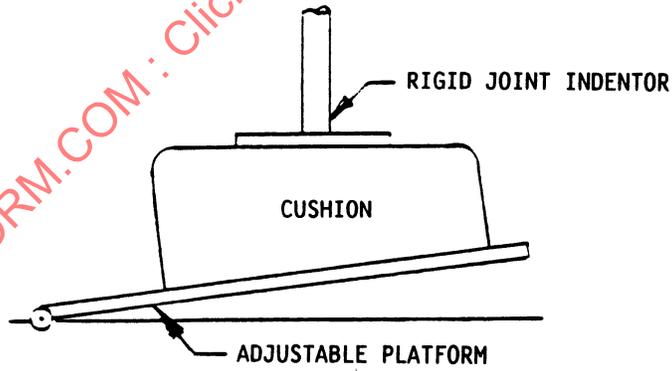


FIGURE 3—ADJUSTABLE PLATFORM

SAENORM.COM : Click to view the full PDF of j1051_201308

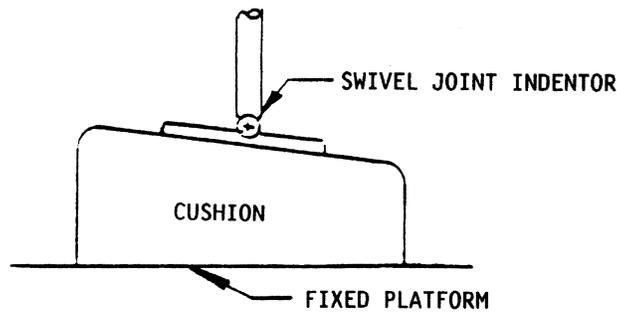


FIGURE 4—SWIVEL JOINT INDENTOR

3.2 Procedure

- 3.2.1 **TEST SPECIMEN**—The test specimen shall consist of a seat cushion, back cushion, or other components in an unused condition (with packaging or protective bag removed).
- 3.2.2 **TEST CONDITIONS**—The specimen shall be conditioned, undeflected, and undistorted at $22\text{ }^{\circ}\text{C} \pm 2.8\text{ }^{\circ}\text{C}$ and relative humidity of $50\% \pm 2\%$ for at least 12 h before being tested. The tests shall be performed 96 h or more after the manufacture of the raw materials used in the test specimen (foam, elastic components other than metal, etc.). In case of a question, refer to the applicable SAE or ASTM specification (if available) for the particular material.
- 3.2.3 **PERCENT DEFLECTION**—Percent Deflections are determined using the cushion material and cover without the supporting structure (base).
- 3.2.4 **TEST METHOD**
- 3.2.4.1 **Mount Specimen**—Mount the specimen with the top surface parallel to and centered with the indenter, unless otherwise specified by mutual agreement of the manufacturer and the customers. The 200 mm diameter curved or flat indenter shall be used on seat and back cushions unless otherwise specified. A light muslin of a quality comparable to a grade described as a weave of 48 threads per inch and density of 190 g/m^2 is allowed to prevent marking of the component. In the case of components with unusual shapes or contours, location for placement, and the size of the indenter is to be agreed upon by the manufacturer and customer and shall allow a minimum of 80% of the indenter area to be in contact when the initial zeroing force of 3.2.3.3 is applied. (Example: Smaller diameter or curved indenter for curved backrest—see Figure 2.)
- 3.2.4.2 **Preflex**—Preflex the test specimen three times by compressing and releasing the force at a rate of 100 mm/min. The specimen shall be compressed as follows:
- Seat Cushion: 1335 N
 - Back Cushion: 665 N
 - Other Components: Compress to 20% of original thickness
- Allow 10 min \pm 5 min for the specimen to stabilize after preflexing before continuing the test.
- 3.2.4.3 **Zero the Deflection Scale**—Apply a force of 45 N to the 200 mm diameter indenter or 10 N to the 50 mm diameter indenter and set the deflection scale to zero.