

SAE-J121

ADOPTION NOTICE

SAE-J121, "Decarburization in Hardened and Tempered Threaded Fasteners," was adopted on October 3, 1994 for use by the Department of Defense (DoD). Proposed changes by DoD activities must be submitted to the DoD Adopting Activity: Commander, Naval Sea Systems Command, SEA 03R42, 2531 Jefferson Davis Highway, Arlington, VA 22242-5160. DoD activities may obtain copies of this standard from the Standardization Document Order Desk, 700 Robbins Avenue, Building 4D, Philadelphia, PA 19111-5094. The private sector and other Government agencies may purchase copies from the Society of Automotive Engineers, Inc., 400 Commonwealth Drive, Warrendale, PA 15096.

Custodians:

Army - AR
 Navy - SH
 Air Force - 11

Adopting Activity

Navy - SH

SAENORM.COM : Click to view the full PDF of J121 - 199403

AREA THDS

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

SAE The Engineering Society
For Advancing Mobility
Land Sea Air and Space®
INTERNATIONAL

400 Commonwealth Drive, Warrendale, PA 15096-0001

SURFACE VEHICLE RECOMMENDED PRACTICE

Submitted for recognition as an American National Standard

SAE J121

REV.
AUG96

Issued 1969-09
Revised 1996-08

Superseding J121 MAY96

DECARBURIZATION IN HARDENED AND TEMPERED UNIFIED THREADED FASTENERS

1. Scope—This SAE Recommended Practice covers methods for measuring, classifying, and specifying decarburization in the threaded section of hardened and tempered steel bolts, screws, studs, and similar parts. It is not intended to cover products which are specifically carburized to achieve special properties.

2. References

2.1 Applicable Document—The following publication forms a part of this specification to the extent specified herein. The latest issue of SAE publications shall apply.

2.1.1 SAE PUBLICATION—Available from SAE, 400 Commonwealth Drive, Warrendale, PA 15096-0001.

SAE J419—Methods of Measuring Decarburization

2.2 Definitions—According to SAE J419, "decarburization" is the loss of carbon at the surface of commercial ferrous materials which have been heated to facilitate fabrication or heated to modify mechanical properties. SAE J419 defines also "complete decarburization," "partial decarburization," and "effective decarburization," as related to unhardened steels. This document extends these definitions, as follows, to cover more specifically hardened and tempered steel bolts, screws, studs, and similar products.

2.2.1 PARTIAL DECARBURIZATION—Decarburization with loss of carbon sufficient to cause a lighter shade of tempered martensite than that of the immediately adjacent base metal, when examined metallographically by the method outlined in 4.1, but insufficient carbon loss to show clearly defined ferrite grains. (The hardness traverse method, outlined in 4.2, is the referee method for determining that partial decarburization is not present at a point below that shown in Figure 1 for each classification.)


2.2.2 GROSS DECARBURIZATION—Decarburization with sufficient carbon loss to show only clearly-defined ferrite grains under metallographic examination by the method outlined in 4.1. This is sometimes called "Complete Decarburization."

2.2.3 CARBON RESTORATION—A process of restoring surface-carbon loss by heat treating in an atmosphere furnace of properly controlled carbon potential. (This process is permitted but not recommended for threaded fasteners unless furnace atmosphere is adequately controlled.)

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

SAE J121 Revised MAY96

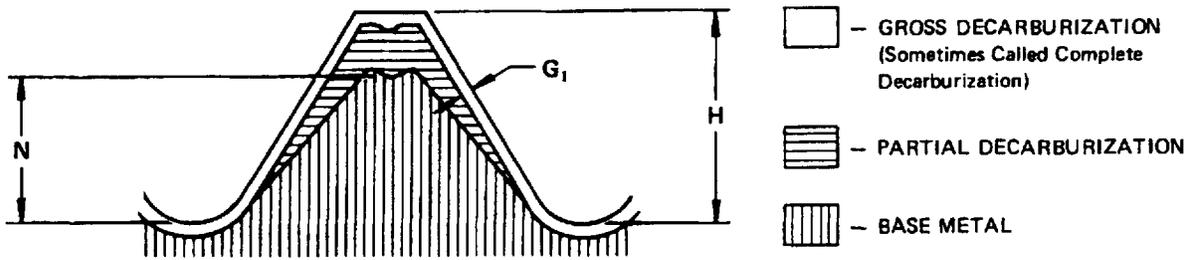

Limits for Unified Threads ¹ —in				
Threads Per in	Thread Height H ¹	Decarburization Class C (1/2 H) ²	Decarburization Class B (2/3 H) ²	G ³
		N	N	
		min	min	
28	0.02191	0.011	0.015	0.0006
24	0.02556	0.013	0.017	0.0006
20	0.03067	0.015	0.020	0.0006
18	0.03408	0.017	0.023	0.0006
16	0.03834	0.019	0.025	0.0006
14	0.04382	0.022	0.029	0.0006
13	0.04719	0.024	0.032	0.0006
12	0.05112	0.026	0.035	0.0006
11	0.05577	0.028	0.037	0.0006
10	0.06134	0.031	0.041	0.0006
9	0.06816	0.034	0.045	0.0006
8	0.07668	0.038	0.051	0.0006
7	0.08763	0.044	0.059	0.0006
6	0.10224	0.051	0.068	0.0006

All dimensions are inches.


1. H is height of external thread at its maximum boundary nonplated condition.
2. Decarburization Class C (1/2 H) and Class B (2/3 H) were formerly referred to as X and 4/3 X, respectively (where X equals one-half thread height).
3. G shall be measured perpendicular to the flank of the thread midway between crest and root. (The additional depth of gross decarburization shown at thread crest is due to "thread enfoliation" caused by thread rolling.)
4. See Section 3 for limits applicable to other threaded products.

FIGURE 1—DECARBURIZATION LIMITS FOR COMMONLY USED UNIFIED THREADS

SAE J121 Revised MAY96

2.2.4 CARBURIZATION—A darker shade of tempered martensite than that of the immediately adjacent base metal, when examined metallographically by the method outlined in 4.1, and harder by at least 30 points (Knoop or Vickers DPH) than the hardness at root diameter when checked by the method outlined in 4.2. (The limits established by this document exclude this condition.)

2.2.5 BASE-METAL HARDNESS—For purposes of this document, hardness at root diameter on a line bisecting the included angle of the thread (Position 1 in Figure 2) is considered "base-metal hardness."

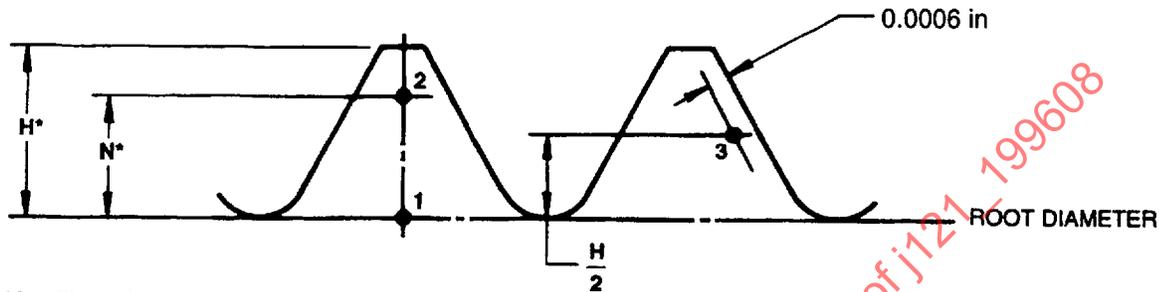

*See Figure 1

(R) FIGURE 2—POSITIONS FOR DETERMINING HARDNESS

3. **Classes of Decarburization**—This document establishes two classes of decarburization for inch-series threaded products. Each class is characterized by dimensional limits for decarburized zone, gross-decarburized zone, and/or base-carbon zone (as applied to longitudinal sections through the thread axis). Decarburization limits applicable to the more commonly used Unified Threads (in) are shown in Figure 1. Limits applicable to other threaded products are as follows:

- a. For Class C ($1/2 H$)— $N = 0.50 H$; $G = 0.0006$ in
- b. For Class B ($2/3 H$)— $N = 0.67 H$; $G = 0.0006$ in

NOTE—This document recognizes that the surface may vary in carbon content from the base-metal carbon content, and stipulates that this variation shall be either "partial decarburization" or "gross decarburization" or a "carbon-restored surface" to the extent allowed in Figure 1 for the different classes. "Carburization" is not permitted in the surface zone.

4. **Methods for Measuring Decarburization**—Two methods for measuring decarburization are provided. The microscopic method is intended primarily for routine inspection purposes. The hardness method is intended primarily for referee purposes. In the case of gross decarburization, however, only the microscopic method is applicable.

4.1 Microscopic Method¹

4.1.1 SPECIMENS—Use longitudinal sections taken through the thread axis of the bolt, screw, or stud, after all heat-treating operations have been performed on the product. If specimens are prepared from surface-coated fasteners, care should be used when interpreting the substrate-coating interface.

¹ Same as outlined in SAE J419, except "Specimen."