

SURFACE VEHICLE INFORMATION REPORT

SAE J413b

Issued 1932-01
Revised 1978-11

(R) MECHANICAL PROPERTIES OF HEAT TREATED WROUGHT STEELS

1. The charts in this report illustrate the principle that, regardless of composition, steels of the same cross sectional hardness produced by tempering after through hardening, will have approximately the same longitudinal¹ tensile strength at room temperature.

Chart 1 shows the relation between hardness and longitudinal tensile strength of 0.30 to 0.50% carbon steels in the fully hardened and tempered, as rolled, normalized, and annealed conditions. Chart 2 showing the relation between longitudinal tensile strength and yield strength, and Chart 3 illustrating longitudinal tensile strength versus reduction of area, are typical of steels in the quenched and tempered condition. Chart 3 shows the direct relationship between ductility and hardness and illustrates the fact that the reduction of area decreases as hardness increases, and that, for a given hardness, the reduction of area is generally higher for alloy steels than for plain carbon steels.

It is evident from these curves that steels of the same cross sectional hardness have about the same strength characteristics, so that any one of several different compositions would yield the same results. For some specific application then, the first thing to be determined is what composition is required to obtain proper hardening in the size section involved. This information is not contained in mechanical property charts, but can be determined from published data or by means of a hardenability test. Methods of making this hardenability test and interpretation of the test results are provided in SAE J406b.

Having selected a steel that will through harden in the size section under consideration, the engineer must decide from the service stresses imposed on the finished part what tensile properties are required in the part. These tensile properties may then be converted to hardness values from the charts given here; and from Chart 4 showing the effect of tempering temperature on

¹Longitudinal means parallel to rolling direction.

SAE Technical Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

1. (Continued):

hardness, the appropriate tempering temperature to obtain this hardness can be selected. In Chart 4 the curves are approximate values to be used as a guide. Carbon steels and lean alloy steels, when fully hardened, will fall slightly below the curves and strongly alloyed steels will fall slightly above the curves.





Chart 4 showing the effect of tempering temperature on hardness is a summary of information contained in a large number of mechanical property charts published by steel companies, alloy suppliers and users, and represents, as do the charts on tensile and yield strengths, and reduction of area, data on all SAE alloy and carbon steels with carbon contents of 0.30 to 0.50%.

Mechanical property values obtained from these few summary charts will be as accurate as the information formerly available in a large number of charts, each representing an individual type of steel. For more exact information it would be necessary to make tests on samples from individual heats of steel.

NOTE: Mechanical properties in this report are monotonic and do not represent cyclic test loading conditions. Cyclic loading and cyclic material properties are described in SAE J1099, Technical Report on Fatigue Properties.

SAENORM.COM : Click to view the full PDF of J413b-1978

The (R) is for the convenience of the user in locating areas where technical revisions have been made to the previous issue of the report. If the symbol is next to the report title, it indicates a complete revision of the report.

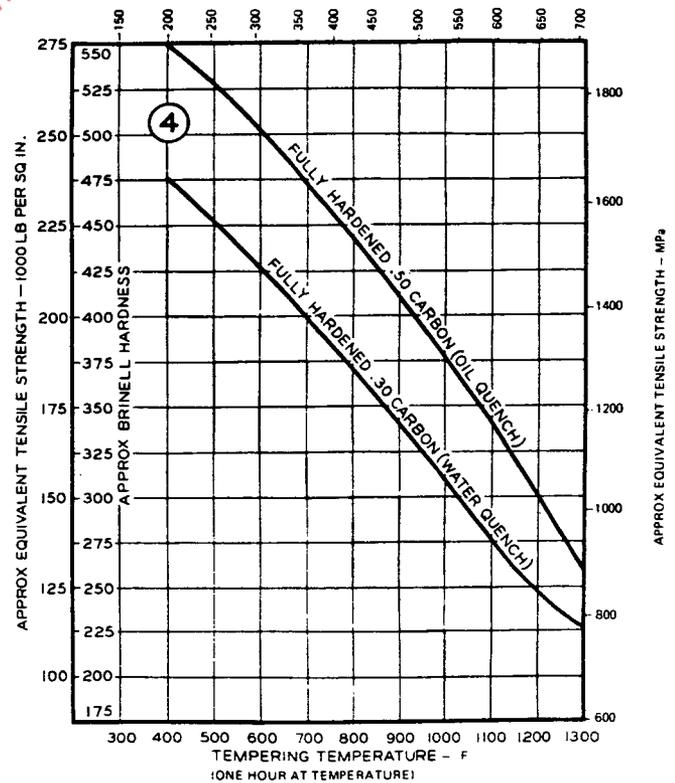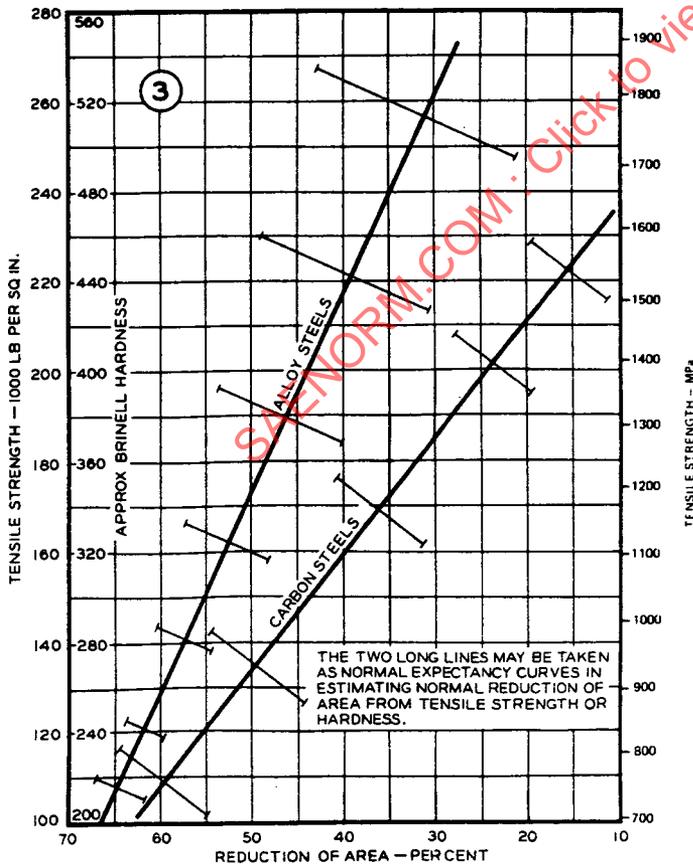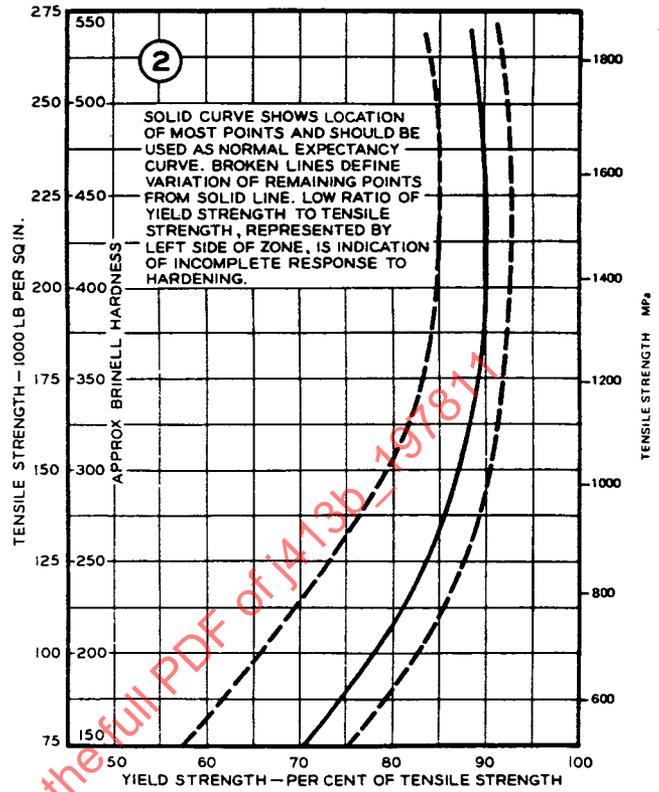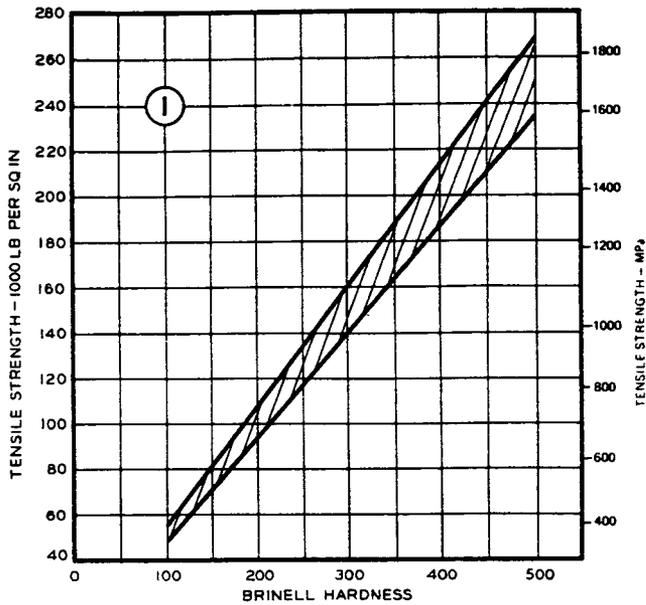

J413b

RATIONALE:

Not applicable.

RELATIONSHIP OF SAE STANDARD TO ISO STANDARD:

Not applicable.

REFERENCE SECTION:

SAE J406b, Methods of Determining Hardenability of Steels

SAE J1099, Technical Report on Fatigue Properties

APPLICATION:

The charts in this report illustrate the principle that, regardless of composition, steels of the same cross sectional hardness produced by tempering after through hardening, will have approximately the same longitudinal tensile strength at room temperature.

COMMITTEE COMPOSITION:

DEVELOPED BY THE SAE IRON AND STEEL TECHNICAL COMMITTEE

SAENORM.COM : Click to view the full PDF of J413b-197817